

AperTO - Archivio Istituzionale Open Access dell'Università di Torino

**Atomic and electronic structure of free niobium nanoclusters: Simulation of the M<sub>4,5</sub>-XANES spectrum of Nb<sub>13</sub><sup>+</sup>**

**This is the author's manuscript**

*Original Citation:*

*Availability:*

This version is available <http://hdl.handle.net/2318/1553920> since 2016-02-07T16:24:19Z

*Published version:*

DOI:10.1016/j.elspec.2014.07.005

*Terms of use:*

Open Access

Anyone can freely access the full text of works made available as "Open Access". Works made available under a Creative Commons license can be used according to the terms and conditions of said license. Use of all other works requires consent of the right holder (author or publisher) if not exempted from copyright protection by the applicable law.

(Article begins on next page)



## UNIVERSITÀ DEGLI STUDI DI TORINO

This Accepted Author Manuscript (AAM) is copyrighted and published by Elsevier. It is posted here by agreement between Elsevier and the University of Turin. Changes resulting from the publishing process - such as editing, corrections, structural formatting, and other quality control mechanisms - may not be reflected in this version of the text. The definitive version of the text was subsequently published in Atomic and electronic structure of free niobium nanoclusters: A.N. Kravtsova, K.A. Lomachenko, A.V. Soldatov, J. Meyer, G. Niedner-Schatteburg, S. Peredkov, W. Eberhardt, and M. Neeb, Simulation of the M4,5-XANES spectrum of Nb<sup>13+</sup>, J. Electron Spectrosc. Relat. Phenom., 195, 189-194 (2014), doi: 10.1016/j.elspec.2014.07.005.

You may download, copy and otherwise use the AAM for non-commercial purposes provided that your license is limited by the following restrictions:

- (1) You may use this AAM for non-commercial purposes only under the terms of the CC-BY-NC-ND license.
- (2) The integrity of the work and identification of the author, copyright owner, and publisher must be preserved in any copy.
- (3) You must attribute this AAM in the following format: Creative Commons BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/deed.en>), [10.1016/j.elspec.2014.07.005](https://doi.org/10.1016/j.elspec.2014.07.005)

# Atomic and electronic structure of free niobium nanoclusters: simulation of the $M_{4,5}$ -XANES spectrum of $Nb_{13}^+$

Antonina N. Kravtsova <sup>a,\*</sup>, Kirill A. Lomachenko <sup>a,b</sup>, Alexander V. Soldatov <sup>a,\*</sup>, Jennifer Meyer <sup>c</sup>, Gereon Niedner-Schatteburg <sup>c</sup>, Sergey Peredkov <sup>d,1</sup>, Wolfgang Eberhardt <sup>e</sup>,  
Matthias Neeb <sup>d,\*</sup>

<sup>a</sup> *Research Center for Nanoscale Structure of Matter, Southern Federal University, Sorge str. 5, 344090 Rostov-on-Don, Russia*

<sup>b</sup> *Department of Chemistry and NIS Centre of Excellence, University of Turin, Via P. Giuria 7, 10125 Turin, Italy*

<sup>c</sup> *Technische Universität Kaiserslautern, Fachbereich Chemie und Forschungszentrum OPTIMAS, Erwin-Schrödinger-Straße 52, 67663 Kaiserslautern, Germany*

<sup>d</sup> *Helmholtz-Zentrum Berlin für Materialien und Energie, Wilhelm-Conrad-Röntgen-Campus Adlershof, Elektronenspeicherring BESSY II, Albert-Einstein-Straße 15, Germany*

<sup>e</sup> *Technische Universität Berlin, IOAP, Straße des 17. Juni 135, 10623 Berlin, Germany*

## Abstract

The atomic and electronic structure of free niobium nanoclusters has been studied on the basis of X-ray absorption near-edge structure (XANES) spectroscopy and density functional theory.  $M_{4,5}$ -XANES spectra have been calculated for several structural models of the 13-atomic niobium cluster. The calculations have been done on the basis of both full multiple scattering theory within the muffin-tin approximation for a potential and full-potential finite difference method. The comparison of the experimental  $M_{4,5}$ -edge XANES spectrum (Peredkov et al, 2011) with the simulated X-ray absorption spectra of  $Nb_{13}^+$  hints to a highly-symmetric icosahedral structure of the cluster. An internuclear distance of  $2.2 \pm 0.1$  Å between neighboring “surface” atoms of the icosahedron and 2.09 Å between the central “bulk” atom and “surface” atoms, respectively, has been found upon comparison of the experimental and theoretical XANES spectra.

**Key words:** niobium nanoclusters, nanoscale atomic structure, XANES spectroscopy, DFT simulations.

\* Corresponding author. Tel.: +7 863 2875326 (A.N. Kravtsova, A.V. Soldatov) and +49-30-806213450 (M. Neeb).

E-mail addresses: [akravtsova@sfedu.ru](mailto:akravtsova@sfedu.ru) (A.N. Kravtsova), [soldatov@sfedu.ru](mailto:soldatov@sfedu.ru) (A.V. Soldatov), [matthias.neeb@helmholtz-berlin.de](mailto:matthias.neeb@helmholtz-berlin.de) (M. Neeb).

<sup>1</sup> Present address: Max-Planck-Institut fuer Chemische Energiekonversion, Stiftstr. 34-36, D-45470, Mülheim an der Ruhr, Germany

## 1. Introduction

Nanoclusters attract significant attention both from the fundamental point of view and from the standpoint of their possible applications in nanotechnologies. The properties of nanoclusters change significantly with size and atomic structure (Johnston, 2002; Eberhardt, 2002). Thus, a deep insight into the nature of nanoclusters is impossible without the data on their atomic structure. Such data can most reliably be obtained by studying free clusters, because deposition on any kind of substrate might cause major changes in clusters geometry and electronic structure.

Among the wide variety of different types of clusters, nanoclusters of  $4d$  transition metals are of particular interest because of their fundamental importance and potential applications as magnetic materials and nanocatalysts. Niobium nanoclusters are among the most extensively investigated transition-metal clusters due to the several features, such as the relatively large propensity for clusterisation and the existence of ferroelectric state related to superconductivity (Moro et al., 2004). Atomic and electronic structure of niobium nanoclusters has been previously studied by various experimental and theoretical methods. Niobium trimers  $\text{Nb}_3$  in argon matrices have been investigated based on an analysis of absorption (scattering depletion) and Raman spectra (Wang et al., 1996). Photoelectron spectra of mass-separated  $\text{Nb}_n^-$  clusters ( $n = 6-17$ ) have been discussed by Kietzmann et al. (1998), indicating a closed electronic shell of the neutral even-numbered clusters. Time-of-flight mass spectra of free niobium clusters  $\text{Nb}_n$  produced by laser vaporization have been measured and magic numbers were observed at  $n=7, 13, 15, 22$  (Sakurai, 1999). Theoretical methods of investigation have been applied to determine the most stable atomic geometries and electronic properties of niobium nanoclusters in the size range from 2 till 52 atoms (Fa et al., 2005; Fournier et al., 1998; Goodwin and Salahub, 1993; Grönbeck and Rosen, 1996; Grönbeck et al., 1998; Kumar and Kawazoe, 2002; Nayak et al., 1996; Ren et al., 2009). Atomic structure and magnetic moment of  $4d$  transition-metal clusters with 13 atoms (including  $\text{Nb}_{13}$  cluster) have been discussed (Chang and Chou, 2004; Kaiming et al., 1996; Sun et al., 2008, 2009).

An effective modern technique for the analysis of nanoscale atomic structure (as well as the density of unoccupied electronic states near the bottom of the conduction band) is the X-ray Absorption Near-Edge Structure (XANES) spectroscopy (Bianconi, 1998; Bunker, 2011). XANES spectroscopy could give full information on the local atomic structure around the absorbing atom (coordination numbers, bond lengths and bond angles) with high precision, even for materials without long-range order in the atomic arrangement, such as nanoclusters. The bond length distances can be determined using XANES spectroscopy with the accuracy up to 0.02 Å, bond angles – with the accuracy of few degrees (Smolentsev et al., 2007). At the same

time, the extraction of structural data from XANES spectra demands complicated theoretical analysis (Smolentsev and Soldatov, 2006, 2007). Recently, XANES spectroscopy has been successfully applied to investigate titanium and copper nanoclusters (Mazalova et al., 2007, 2009; Mazalova and Soldatov, 2008). In the present work, the theoretical analysis of the  $M_{4,5}$  XANES spectrum of free  $Nb_{13}^+$  has been performed and compared with the recently measured experimental spectrum (Peredkov et al., 2011a) in order to extract information on the geometry of the nanoclusters.

## 2. Experiment

The experimental setup used to measure  $M_{4,5}$ -XANES spectra of free mass-selected niobium clusters has been described in detail elsewhere (Peredkov et al., 2011a, 2011b). In short, X-ray absorption spectra of free  $Nb_{13}^+$  were measured at UE52-PGM beamline ( $\sim 10^{12}$  photons/s, 1<sup>st</sup> undulator harmonics) of the synchrotron source BESSY II (Helmholtz-Zentrum Berlin, Germany). A cluster beam has been produced by pulsed laser vaporization (532 nm, 20 Hz) and supersonic expansion using a synchronized pulsed He buffer gas. Clusters have been mass-selected by using a Penning-like ion trap and FT-ICR mass spectrometer (7 Tesla, Bruker). Figure 1 shows the ICR-mass spectrum of mass-isolated  $Nb_{13}^+$  clusters. Note the low degree of contamination after mass-selection and isolation. X-ray absorption spectra on  $Nb_{13}^+$  have been recorded near the  $M_{4,5}$ -absorption edge of niobium using linearly polarised X-ray undulator radiation. As absorption signal, the number of ionic fragments has been recorded inside the ion trap (Figure 2). The two smallest fragment ions ( $Nb_1^+$ ,  $Nb_2^+$ ) were the dominant ones and therefore they have been accumulated to represent the absorption spectrum of  $Nb_{13}^+$  at best signal-to-noise ratio. The accumulated absorption spectra are shown as top curves in Figure 4 and 6 (experimental spectrum). The fragmentation yield has been normalized to the photon flux of the beamline which was recorded by a GaAs-diode behind the monochromator exit slit. Therefore any absorption by the carbon contamination of the beamline optics should not falsify our Nb-absorption signal, even though the photon range of the niobium  $M$ -edge overlaps with the  $K$ -edge of carbon. The second order light intensity ( $>500$  eV) transmitted by the monochromator (plane grating) has been measured by us to be 2-3 % of the first order intensity. Absorption by carbon and oxygen contaminated  $Nb_{13}^+$ -clusters can be ruled out by the tiny degree of contamination (Figure 1) and the low degree of transmitted second order light. The ICR-cell has been quenched and refilled by new mother clusters after a few seconds of irradiation.

### 3. Computational details

Theoretical Nb  $M_{4,5}$ -XANES spectra for several structural models of 13-atomic niobium cluster have been calculated on the basis of two approaches.

Firstly, the self-consistent real-space full multiple-scattering (FMS) theory has been used. The calculations are based on the formalism of the relativistic Green's function in the real space. The muffin-tin approximation (Rehr and Albers, 2000) for the potential shape has been employed. This theory is implemented into the X-ray absorption spectra and electronic structure FEFF 8.4 code (Rehr and Ankudinov, 2005).

Secondly, the real-space full-potential finite difference method (FDM) realized in FDMNES2009 program code (Joly, 2001) has been applied. Its main advantage is the possibility to have a totally free potential shape, thus avoiding limitations associated with the classical muffin-tin approximation for a cluster potential.

Calculations of the Nb  $M_{4,5}$ -XANES spectra using both methods have been done within the Hedin-Lundquist model of the exchange-correlation potential taking into consideration a core hole effect.

Recently, FEFF code based on muffin-tin approximation has been applied to calculate the  $M_{4,5}$ -XANES spectrum of icosahedral Nb<sub>13</sub> in which the surface atoms have been considered as absorbing atom (Peredkov et al., 2011b). In the present study we use not only FEFF, but also FDMNES code, to exhibit the influence of non-muffin-tin effects. Such effects are particularly important to be considered in the simulations of nanoclusters due to the significant “surface” atoms contribution to the cluster’s electronic structure. Moreover, Nb  $M_{4,5}$ -edge spectra have independently been simulated for both the “surface” and central (“bulk”) atom of the icosahedron.

The atomic geometry of the structural models of Nb<sub>13</sub><sup>+</sup> has been optimized on the basis of the Kohn-Sham density functional theory using the ADF2009 program code (te Velde et al., 2001) within the generalized gradient approximation (GGA) using the OLYP (Handy and Cohen, 2001; Hoe et al., 2001) model for the exchange-correlation potential. This model was chosen among other tested models (PBE, OPBE, BLYP), as it results in better agreement between theoretical and experimental values of the dimer bond length. The experimental value of the Nb<sub>2</sub>-bond length is equal to  $d_{\text{Nb}} \sim 2.08 \text{ \AA}$  (Hales et al., 1990; James et al., 1993). Our calculation of the dimer bond length performed within the OLYP exchange-correlation model results in a value of  $d_{\text{Nb}} = 2.07 \text{ \AA}$ , while the calculation done within the OPBE model results in  $d_{\text{Nb}} = 2.03 \text{ \AA}$ . For cluster geometry optimization a core double zeta, valence triple zeta, polarized basis set (TZP) (van Lenthe and Baerends, 2003) of Slater-type orbitals has been used. The positive charge of Nb<sub>13</sub><sup>+</sup> cluster has been taken into account.

The FDM scheme has previously been successfully applied to compute X-ray absorption near-edge spectra of metal nanoclusters, for example, small titanium (Mazalova et al., 2007) and copper (Mazalova and Soldatov, 2008; Mazalova et al., 2009) nanoclusters. The DFT approach as realized in ADF code, on the other hand, has been successfully used to study the atomic geometries and electronic properties of free copper (Mazalova and Soldatov, 2008; Mazalova et al., 2009) and titanium (Kravtsova et al., 2011) nanoclusters.

#### 4. Results and discussion

At the first step the Nb  $M_{4,5}$ -edge XANES spectrum of bulk niobium was calculated to check the adequacy of the used theoretical approaches. The bulk niobium crystallizes in *bcc* structure with the lattice parameter  $a=3.30$  Å (Barns, 1968). A comparison of the theoretical Nb  $M_{4,5}$ -XANES spectrum of bulk niobium simulated on the basis of the full-potential finite difference method with the corresponding experimental EELS spectrum taken from Olszta et al. (2006) is presented in Figure 3. It can be seen that the calculated spectrum is in good agreement with the experimental one. Minor discrepancies between the experimental and theoretical spectra may be caused by the sample surface oxidation. An agreement between the theoretical and experimental spectra of bulk niobium supports the application of the finite difference method for the analysis of XANES of niobium nanoclusters.

Initially, the icosahedral model of the Nb<sub>13</sub> cluster structure was considered. The lattice parameter  $a=3.30$  Å of a *bcc* niobium crystal gives rise to an interatomic bulk distance of  $r=2.86$  Å ( $r=a/2 \cdot \sqrt{3}$ ) which was used as initial guess of the distance between the “surface” atoms ( $d_{\text{surf-surf}}$ ) of icosahedral Nb<sub>13</sub>. The distance between the central atom and the “surface” atoms ( $d_{\text{cent-surf}}$ ) of an icosahedron is generally related to  $d_{\text{cent-surf}} = 1/2\sqrt{(1+\phi^2)}d_{\text{surf-surf}}$  where  $\phi$  is the so-called Fibonacci number 1.618. Using the interatomic bulk distance as initial guess for the distance of the surface atoms of the icosahedron ( $d_{\text{surf-surf}}=2.86$  Å) the distance between the central and “surface” atoms is equal to 2.72 Å. Figure 4 compares the experimental  $M_{4,5}$ -edge X-ray absorption spectrum of Nb<sub>13</sub><sup>+</sup> ( $M_{4,5}$  edge) with the theoretical spectra calculated for the icosahedral structure of the 13-atomic cluster using the bulk atomic distance as initial guess for the “surface” atom distance. The displayed theoretical spectra are computed on the basis of both full-multiple scattering theory within the muffin-tin approximation for the potential shape (FEFF8.4 program) and full-potential finite difference method (FDMNES code). The spectra were simulated for the cases when both “surface” and central atoms were sequentially set as the absorbers. It can be seen from Figure 4 that fine structures of the experimental and theoretical

spectra contain features marked as *A* and *B*. However, maxima *B* of the theoretical spectra calculated on the basis of both FMS and FDM methods are shifted to the lower energy region as compared to maximum *B* of the experimental spectrum. The disagreement between the experimental and theoretical data (difference in the intensity of peak *A* and energy position of peak *B*) suggests for a refinement of the initially considered structural model of 13-atomic niobium cluster which is described in the following paragraph.

To further improve the agreement between theory and experiment the calculations of the Nb  $M_{4,5}$ -XANES spectra have been carried out for the icosahedral structural model of Nb<sub>13</sub> varying the interatomic distances (calculations have been done for  $d_{\text{surf-surf}}$  equal to 2.86 Å, 2.36 Å, 2.2 Å, 2.1 Å). A good agreement between experiment and theory is achieved when the internuclear distance between neighboring “surface” atoms is equal to  $d_{\text{surf-surf}} = 2.2$  Å. For this surface atom separation a distance from the center atom to the surface atoms of  $d_{\text{cent-surf}} = 2.09$  Å results (Figure 5a). This bond-length reduction agrees with the general tendency of decreasing interatomic distances with decreasing nanoparticles size (Riedler et al., 2001). We suppose that the significant bond length reduction in Nb<sub>13</sub> as compared to bulk niobium is not only due to coordination change but also due to change in chemical bonding from metallic (in macroscopic particles) to covalent one (in small clusters). Note that the interatomic distance of molecular Nb<sub>2</sub> is 2.08 Å (Hales et al., 1990; James et al., 1993), i.e. similar to the bond length between the central and surface atoms of the Nb<sub>13</sub><sup>+</sup>-icosahedron which results in the best agreement of the theoretical with the experimental XANES spectrum as shown in Figure 6.

Figure 6 shows theoretical XANES spectra simulated for the icosahedron of Nb<sub>13</sub><sup>+</sup> with distances  $d_{\text{surf-surf}} = 2.2$  Å and  $d_{\text{cent-surf}} = 2.09$  Å. The simulations have been done on the basis of the full multiple scattering theory within the muffin-tin approximation for the potential shape (FEFF8.4 code) and the full-potential finite difference method (FDMNES code). For both types of calculations the “surface” and center “bulk” atom have been individually chosen as photon absorber. It can be seen that FDMNES calculations of XANES spectra are in slightly better agreement with the experiment as compared with FEFF8.4 calculations, what can be explained by the presence of non-muffin-tin effects due to the surface contribution to the electronic structure of the cluster.

Finally, the optimization of the atomic geometry of the Nb<sub>13</sub><sup>+</sup> cluster was additionally performed based on the DFT implemented in the ADF code (te Velde et al., 2001). As described above the icosahedral model was used as starting structure for the optimization. Without symmetry restrictions during the optimization, an “amorphous” cluster is obtained. In other words, all atoms of the cluster become nonequivalent (see Figure 5b). Theoretical Nb  $M_{4,5}$ -XANES spectra of the amorphous cluster structure have been calculated based on the full-

potential finite difference method (FDMNES code) for all nonequivalent niobium positions of the obtained structure (every nonequivalent niobium atom was sequentially set up as an absorbing one). To get a final theoretical  $M_{4,5}$ -edge inner-shell absorption curve, XANES spectra for all nonequivalent positions were summed up. The theoretical  $M_{4,5}$ -edge XANES spectrum for the “amorphous” structure of  $\text{Nb}_{13}^+$  cluster is presented in Figure 6. It can be seen that the calculated spectrum of the “amorphous” cluster shows much less fine structure than those of the icosahedron (experimental features marked as *A* and *B* are not reproduced in the theoretical spectrum of the “amorphous” structure). The inequivalent atoms of the amorphous structure gives rise to slightly different absorption spectra which superimpose to a featureless total spectrum. Thus the insufficient agreement between experiment and theory indicates that the “amorphous” structure is less likely. In other words, the measured spectral fine structure favours a high symmetry of the 13-atomic niobium cluster which is formed under the chosen experimental conditions. The performed analysis allows for the conclusion that the icosahedron with the distance between the “surface” atoms of  $\sim 2.2 \text{ \AA}$  is the most preferable structure of the 13-atomic niobium cluster among the considered models.

The FDMNES code was also used to calculate a contour map of the potential of the 13-atomic icosahedral niobium cluster within one of the icosahedral symmetry planes containing the central atom and four “surface” atoms (the plane containing atoms marked as 1-2-3-4-5 in Figure 5a). The contour map of the potential of  $\text{Nb}_{13}$  is shown in Figure 7. One can see that the muffin-tin approximation (Rehr and Albers, 2000) is not valid for “surface” atoms of the  $\text{Nb}_{13}$  cluster. Within the muffin-tin approximation, the potential between atoms must be constant; thus, the potential along the line from the surface atoms to the outer region must be constant. From Figure 7 it can be seen that this is not the case of  $\text{Nb}_{13}$  cluster, as the potential is changing significantly. Thus, full-potential methods like FDMNES seems to be most appropriate to simulate XANES spectra of small niobium nanoclusters.

According to dipole selection rules, the electronic transition corresponding to the Nb  $M_{4,5}$ -XANES includes two  $\Delta l = \pm 1$  channels:  $3d \rightarrow 4f$  and  $3d \rightarrow 5p$ . In the present work  $M_{4,5}$ -XANES spectra for all considered structural models of niobium clusters have been calculated as a sum of two dipole allowed channels. The possibility of different transitions of  $3d$  electrons by photon absorption in niobium has been discussed earlier (Leapman et al., 1980). As an example, Figure 8 shows the calculations of two channels ( $d \rightarrow f$  and  $d \rightarrow p$ ) corresponding to the  $M_{4,5}$ -XANES of central niobium of icosahedral structure of 13-atomic niobium cluster with  $2.2 \text{ \AA}$  distance between the “surface” atoms. It can be seen that the  $d \rightarrow f$  transition contributes much more than the  $d \rightarrow p$  transition to the Nb  $M_{4,5}$ -XANES spectrum, which is similar to earlier results on bulk niobium (Leapman et al., 1980).

## 5. Conclusions

Theoretical analysis of the  $M_{4,5}$ -edge X-ray absorption spectra of  $\text{Nb}_{13}^+$  clusters has been performed and compared with experimental results. The Nb  $M_{4,5}$ -XANES spectra have been calculated on the basis of the full multiple scattering theory (FEFF8.4 code) and the full-potential finite difference method (FDMNES code) for several structural models of the cluster. XANES analysis has shown that high-symmetrical icosahedral structure of the 13-atomic niobium cluster is more preferable than the thermodynamically more stable “amorphous” one. The best agreement of the theoretical  $M_{4,5}$ -XANES with the experiment has been obtained for the icosahedral niobium clusters with the distances between the “surface” atoms of  $2.2\pm 0.1$  Å.

## Acknowledgements

This research has been supported by the German-Russian Interdisciplinary Science Center (G-RISC) and by the DFG funded Transregional Collaborative Research Center TRR 88 “3MET.de”. A.V.S. acknowledges the Mega-grant of the Russian Federation Government to support scientific research under the supervision of the leading scientist at Southern Federal University, No. 14.Y26.31.0001. Authors thank the referee for valuable comments finding consideration in the paper.

## References

- Barns, R.L., 1968. Niobium: lattice parameter and density. *J. Appl. Phys.* 39, 4044-4045.
- Bianconi, A., 1988. XANES spectroscopy, in: Prins, R., Koningsberger, D.C. (Eds.), *X-ray absorption: principles, applications and techniques of EXAFS, SEXAFS and XANES*. John Wiley and sons, New York, pp. 573–662.
- Bunker, G., 2011. *Introduction to XAFS: a practical guide to x-ray absorption fine structure spectroscopy*. Cambridge University Press.
- Chang, C.M., Chou, M.Y., 2004. Alternative low-symmetry structure for 13-atom metal clusters. *Phys. Rev. Lett.* 93, 133401.
- Eberhardt, W., 2002. Clusters as New Materials. *Surface Science* 500, 242-270.
- Fa, W, Luo, Ch., Dong, J., 2005. Structure-dependent ferroelectricity of niobium clusters ( $\text{Nb}_N$ ,  $N=2-52$ ). *Phys. Rev. B* 71, 245415.
- Fournier, R., Pang, T., Chen, Ch., 1998. Structural characterization of niobium-cluster anions from density-functional calculations. *Phys. Rev. A* 57, 3683-3691.
- Goodwin, L., Salahub, D.R., 1993. Density-functional study of niobium clusters. *Phys. Rev. A* 47, R774-R777.
- Grönbeck, H., Rosen, A., 1996. Investigation of niobium clusters: bare and CO-adsorption. *Phys. Rev. B* 54, 1549-1552.
- Grönbeck, H., Rosen, A., Andreoni, W., 1998. Structural, electronic, and vibrational properties of neutral and charged  $\text{Nb}_n$  ( $n=8, 9, 10$ ) clusters. *Phys. Rev. A* 58, 4630-4636.
- Hales, D.A., Lian, L., Armentrout, P.B., 1990. Collision-induced dissociation of  $\text{Nb}_n^+$  ( $n=2-11$ ): bond energies and dissociation pathways. *Int. J. Mass Spectrom. Ion Process.* 102, 269-301.
- Handy, N.C., Cohen, A.J., 2001. Left-right correlation energy. *Mol. Phys.* 99, 403-412.
- Hoe, W.-M., Cohen, A.J., Handy, N.C., 2001. Assessment of a new local exchange functional OPTX. *Chem. Phys. Lett.* 341, 319-328.
- James, A.M., Kowalczyk, P., Fournier, R., Simard, B., 1993. Electronic spectroscopy of the niobium dimer molecule: experimental and theoretical results. *J. Chem. Phys.* 99, 8504.
- Johnston, R.L., 2002. *Atomic and molecular clusters*. Taylor and Francis, London and New York.
- Joly, Y., 2001. X-ray absorption near-edge structure calculations beyond the muffin-tin approximation. *Phys. Rev. B* 63, 125120.
- Kaiming, D., Jinlong, Y., Chuanyun, X., Kelin, W., 1996. Magnetic properties of  $\text{M}_{13}$  clusters ( $\text{M}=\text{Y}, \text{Zr}, \text{Nb}, \text{Mo}, \text{and Tc}$ ). *Phys. Rev. B* 54, 11907-11910.

- Kietzmann, H., Morenzin, J., Bechthold, P.S., Ganteför, G., Eberhardt, W., 1998. Photoelectron spectra of  $Nb_n^-$  clusters: correlation between electronic structure and hydrogen chemisorptions. *J. Chem. Phys.* 109, 2275-2278.
- Kravtsova, A.N., Guda, A.A., Mazalova, V.L., Soldatov, A.V., Johnston, R.L., 2011. Electronic structure of titanium nanoclusters: a density functional theory analysis. *Nanostructures. Mathematical physics and modeling* 4, 15-22 (in Russian).
- Kumar, V., Kawazoe, Y., 2002. Atomic and electronic structures of niobium clusters. *Phys. Rev. B* 65, 125403.
- Leapman, R.D., Rez, P., Mayers, D.F., 1980. *K*, *L*, and *M* shell generalized oscillator strengths and ionization cross section for fast electron collisions. *J. Chem. Phys.* 72, 1232-1243.
- Mazalova, V., Kravtsova, A., Yalovega, G., Soldatov, A., Piseri, P., Coreno, M., Mazza, T., Lenardi, C., Bongiorno, G., Milani, P., 2007. Free small nanoclusters of titanium: XANES study. *Nucl. Instrum. Methods Phys. Res. A* 575, 165-167.
- Mazalova, V.L., Soldatov, A.V., 2008. Geometrical and electronic structure of small copper nanoclusters: XANES and DFT analysis. *J. Struct. Chem.* 49, Supplement, S107-S115.
- Mazalova, V.L., Soldatov, A.V., Adam, S., Yakovlev, A., Möller, T., Johnston, R.L., 2009. Small copper clusters in Ar shells: a study of local structure. *J. Phys. Chem. C* 113, 9086-9091.
- Moro, R., Yin, Sh., Xu, X., de Heer, W.A., 2004. Spin uncoupling in free Nb clusters: support for nascent superconductivity. *Phys. Rev. Lett.* 93, 086803.
- Nayak, S.K., Rao, B.K., Khanna, S.N., Jena, P., 1996. Structural isomerism of niobium clusters and its role on reactivity. *Chem. Phys. Lett.* 259, 588-592.
- Olszta, M.J., Wang, J., Dickey, E.C., 2006. Stoichiometry and valence measurements of niobium oxides using electron energy-loss spectroscopy. *J. Microsc.* 224, 233-241.
- Peredkov, S., Neeb, M., Eberhardt, W., Meyer, J., Tombers, M., Kampschulte, H., Niedner-Schatteburg, G., 2011a. Spin and orbital magnetic moments of free nanoparticles. *Phys. Rev. Lett.*, 107, 233401.
- Peredkov, S., Savci, A., Peters, S., Neeb, M., Eberhardt, W., Kampschulte, H., Meyer, J., Tombers, M., Hofferberth, B., Menges, F., Niedner-Schatteburg, G., 2011b. X-ray absorption spectroscopy of mass-selected transition metal clusters using a cyclotron ion trap: an experimental setup for measuring XMCD spectra of free clusters. *J. Electron Spectros. Relat. Phenomena* 184, 113-118.
- Rehr, J.J., Albers, R.C., 2000. Theoretical approaches to x-ray absorption fine structure. *Rev. Mod. Phys.* 72, 621 – 654.

- Rehr, J.J., Ankudinov, A.L., 2005. Progress in the theory and interpretation of XANES. *Coord. Chem. Rev.* 249, 131-140.
- Ren, F.-Zh., Wang, Y.-X., Zhang, G.-B., Wei, Sh.-K., Luo, Y.-H., 2009. An *ab initio* study of niobium ( $n=2-11$ ) clusters: structure, stability and magnetism. *Chin. Phys. B* 18, 1491-1497.
- Riedler, M., de Castro, A.R.B., Kolmakov, A., Löffken, J.O., Nowak, C., Soldatov, A.V., Wark, A., Yalovega, G., Möller, T., 2001. Photoabsorption of NaCl clusters at the Na K-edge: development of the bond length with the cluster size. *J. Chem. Phys.* 115, 1319-1323.
- Sakurai, M., Watanabe, K., Sumiyama, K., Suzuki, K., 1999. Magic numbers in transition metal (Fe, Ti, Zr, Nb, and Ta) clusters observed by time-of-flight mass spectrometry. *J. Chem. Phys.* 111, 235-238.
- Smolentsev, G., Soldatov, A., 2006. Quantitative local structure refinement from XANES: multidimensional interpolation approach. *J. Synchrotron Radiat.* 13, 19-29.
- Smolentsev, G., Soldatov, A.V., 2007. FitIt: new software to extract structural information on the basis of XANES fitting. *Comp. Matter. Science* 39, 569-574.
- Smolentsev, G., Soldatov, A.V., Feiters, M.C., 2007. Three-dimensional local structure refinement using a full-potential XANES analysis. *Phys. Rev. B* 75, 144106.
- Sun, Y., Fournier, R., Zhang, M., 2009. Structural and electronic properties of 13-atom 4d transition-metal clusters. *Phys. Rev. A* 79, 043202.
- Sun, Y., Zhang, M., Fournier, R., 2008. Periodic trends in the geometric structures of 13-atom metal clusters. *Phys. Rev. B* 77, 075435.
- te Velde, G., Bickelhaupt, F.M., Baerends, E.J., Fonseca Guerra, C., van Gisbergen, S.J.A., Snijders, J.G., Ziegler, T., 2001. Chemistry with ADF. *J. Comput. Chem.*, 22, 931-967.
- van Lenthe, E., Baerends, E.J., 2003. Optimized Slater-type basis sets for the elements 1-118. *J. Comp. Chem.* 24, 1142-1156.
- Wang, H., Craig, R., Haouari, H., Liu, Y., Lombardi, J.R., Lindsay, D.M., 1996. Spectroscopy of mass-selected niobium trimers in argon matrices. *J. Chem. Phys.* 105, 5355-5357.

## Figure legends

**Figure 1.** ICR-mass spectrum of parent  $\text{Nb}_{13}^+$  clusters after mass-isolation.

**Figure 2.** Mass-resolved ion yield absorption spectra of  $\text{Nb}_{13}^+$  recorded at the  $M_{4,5}$ -edge using soft X-ray undulator radiation (linear polarisation).

**Figure 3.** Comparison of the  $M_{4,5}$ -XANES spectrum of bulk niobium (bcc structure) calculated on the basis of the full-potential finite difference method (FDMNES code) with the corresponding experimental EELS spectrum from Olszta et al. (2006).


**Figure 4.** Experimental  $M_{4,5}$ -XANES spectrum of free  $\text{Nb}_{13}^+$  [Peredkov et al, 2011a] compared to the theoretical spectra (FDMNES and FEFF) calculated for an icosahedral structure with an atomic distance between surface atoms equal to that of the crystalline bulk (2.86 Å).

**Figure 5.** (a) Schematic representation of the icosahedral structure of the  $\text{Nb}_{13}$  cluster used for calculation of the  $M_{4,5}$ -XANES spectra shown in Figure 6. Labels 1-2-3-4-5 mark atoms laying in the plane used for calculations of a contour map of the potential of the niobium cluster (see Figure 7). (b) Scheme of the “amorphous” structure obtained by atomic geometry optimization based on density functional theory implemented in the ADF code (see text).


**Figure 6.** Experimental  $M_{4,5}$ -edge XANES spectrum of free  $\text{Nb}_{13}^+$  [Peredkov et al, 2011a] with the corresponding theoretical spectra (FDMNES, FEFF) calculated for the icosahedral structure having a distance between the “surface” atoms of 2.2 Å. Note that the simulated FDMNES spectrum of the amorphous structure shows definitely less fine structure than the spectra of the icosahedrons.

**Figure 7.** Contour map of the potential of the 13-atomic icosahedral niobium cluster along the plane containing the central atom and four “surface” atoms. Darker areas correspond to weaker potential.


**Figure 8.** Calculated  $3d \rightarrow 4f$  and  $3d \rightarrow 5p$  electronic transitions corresponding to the  $M_{4,5}$ -XANES of central niobium atom of icosahedral structure of 13-atomic niobium cluster (distance between the “surface” atoms is 2.2 Å). The total  $M_{4,5}$ -XANES spectrum calculated with the consideration of both Nb  $3d \rightarrow 4f$  and Nb  $3d \rightarrow 5p$  channels are also presented.

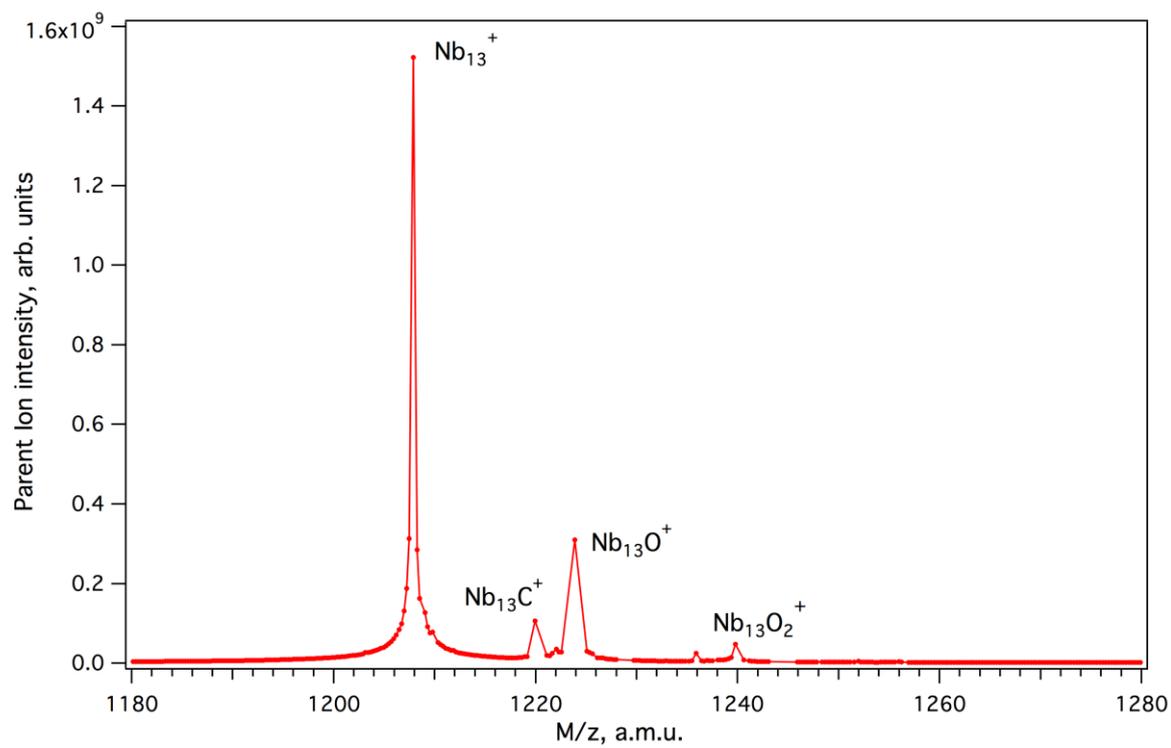


**Figure 1.** ICR-mass spectrum of parent Nb<sub>13</sub><sup>+</sup> clusters after mass-isolation.

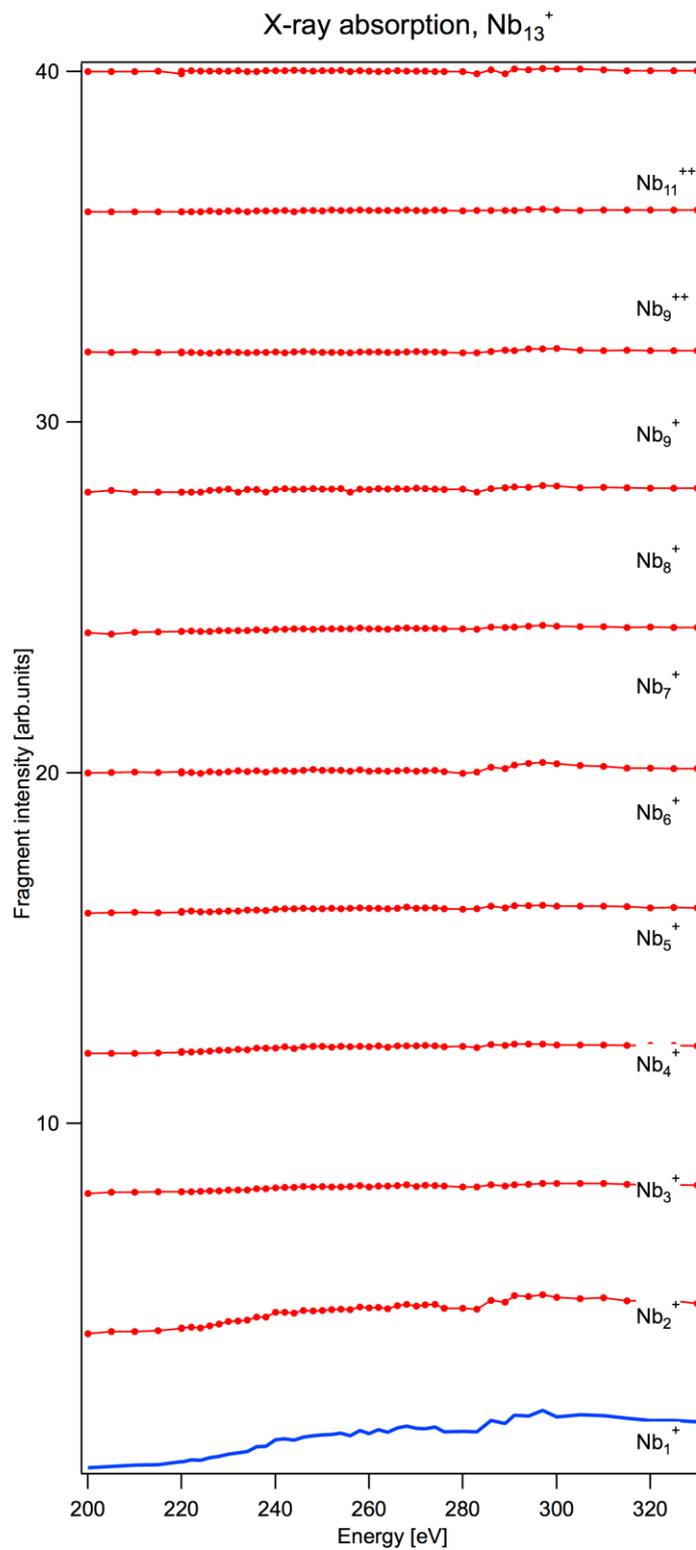


**Figure 2.** Mass-resolved ion yield absorption spectra of  $\text{Nb}_{13}^+$  recorded at the  $M_{4,5}$ -edge using soft X-ray undulator radiation (linear polarisation).

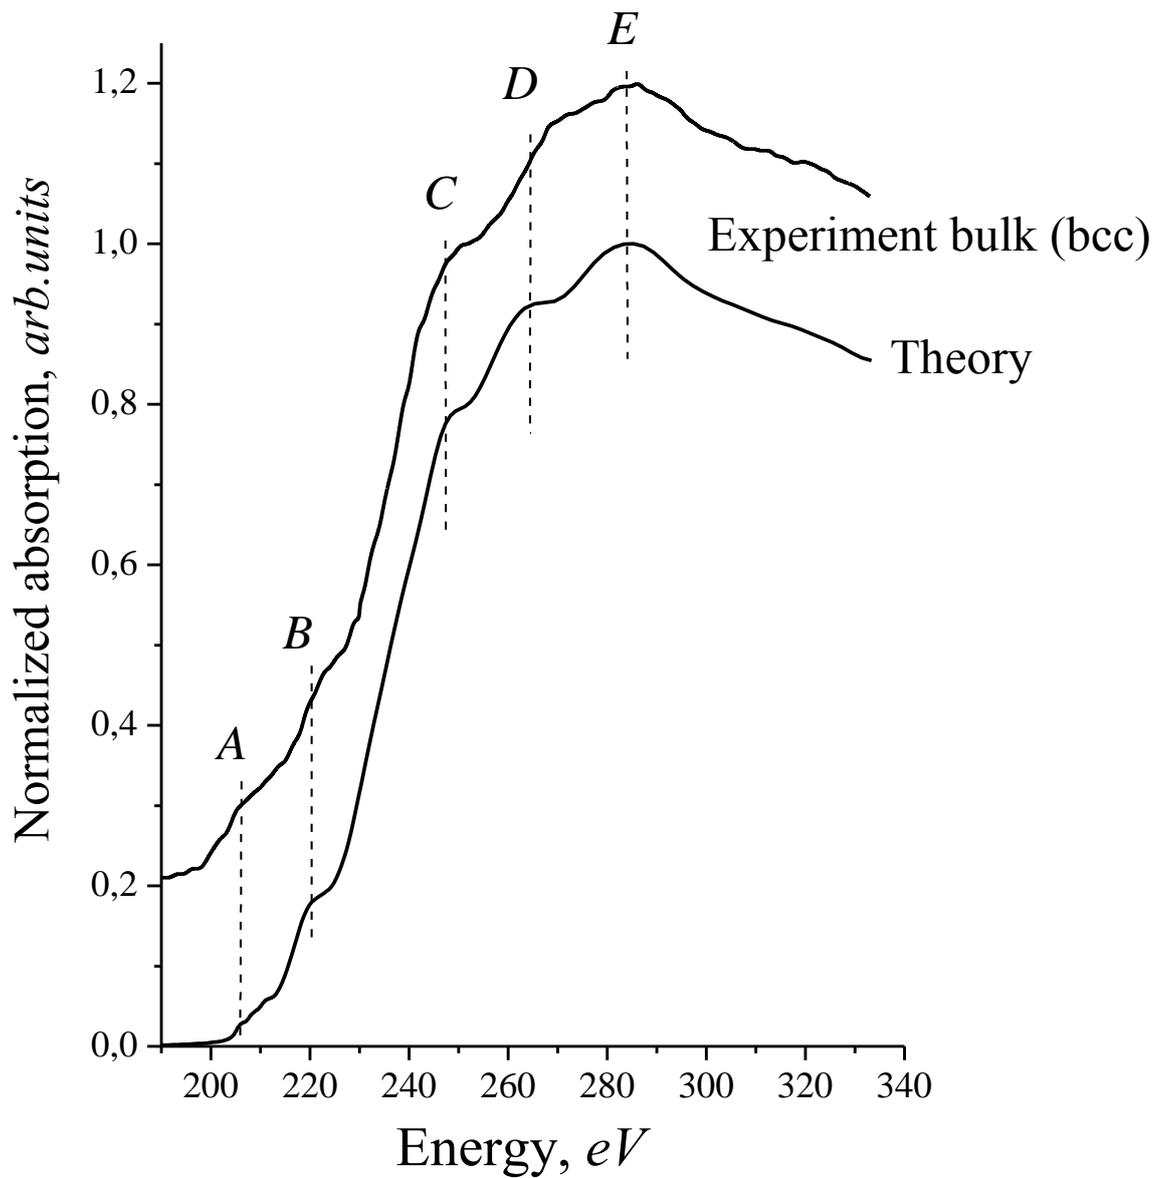


**Figure 3.** Comparison of the  $M_{4,5}$ -XANES spectrum of bulk niobium (bcc structure) calculated on the basis of the full-potential finite difference method (FDMNES code) with the corresponding experimental EELS spectrum from Olszta et al. (2006).

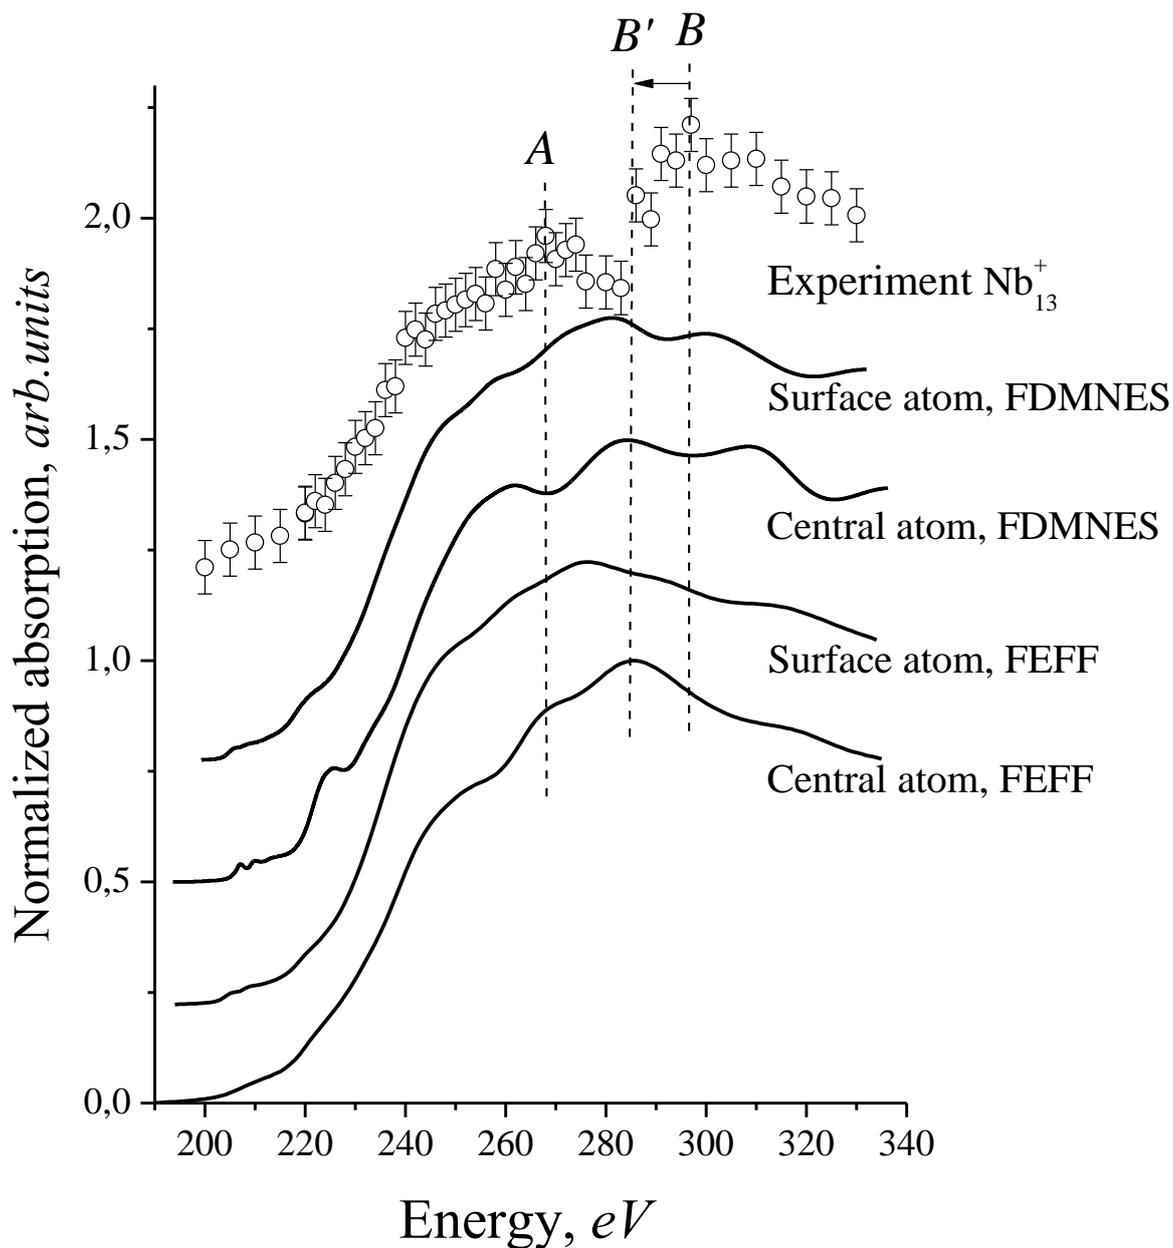


**Figure 4.** Experimental  $M_{4,5}$ -XANES spectrum of free  $\text{Nb}_{13}^+$  [Peredkov et al, 2011a] compared to the theoretical spectra (FDMNES and FEFF) calculated for the icosahedral model with an atomic distance between surface atoms equal to that of the crystalline bulk (2.86 Å).

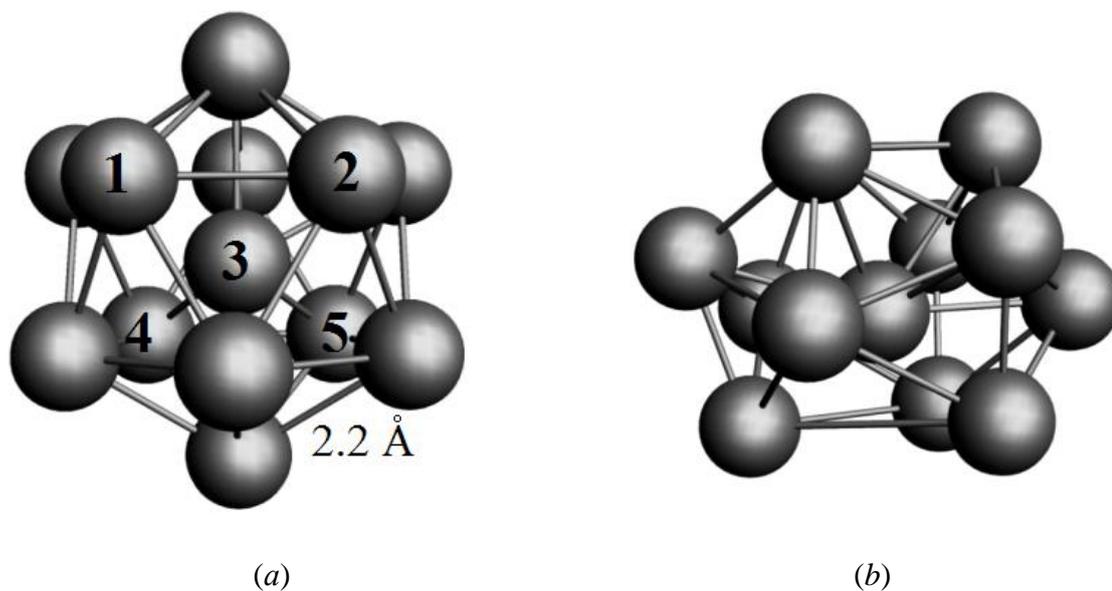


**Figure 5.** (a) Schematic representation of the icosahedral structure of the  $\text{Nb}_{13}$  cluster used for calculation of the  $M_{4,5}$ -XANES spectra shown in Figure 6. Labels 1-2-3-4-5 mark atoms laying in the plane used for calculations of a contour map of the potential of the niobium cluster (see Figure 7). (b) Scheme of the “amorphous” structure obtained by atomic geometry optimization based on density functional theory implemented in the ADF code (see text).

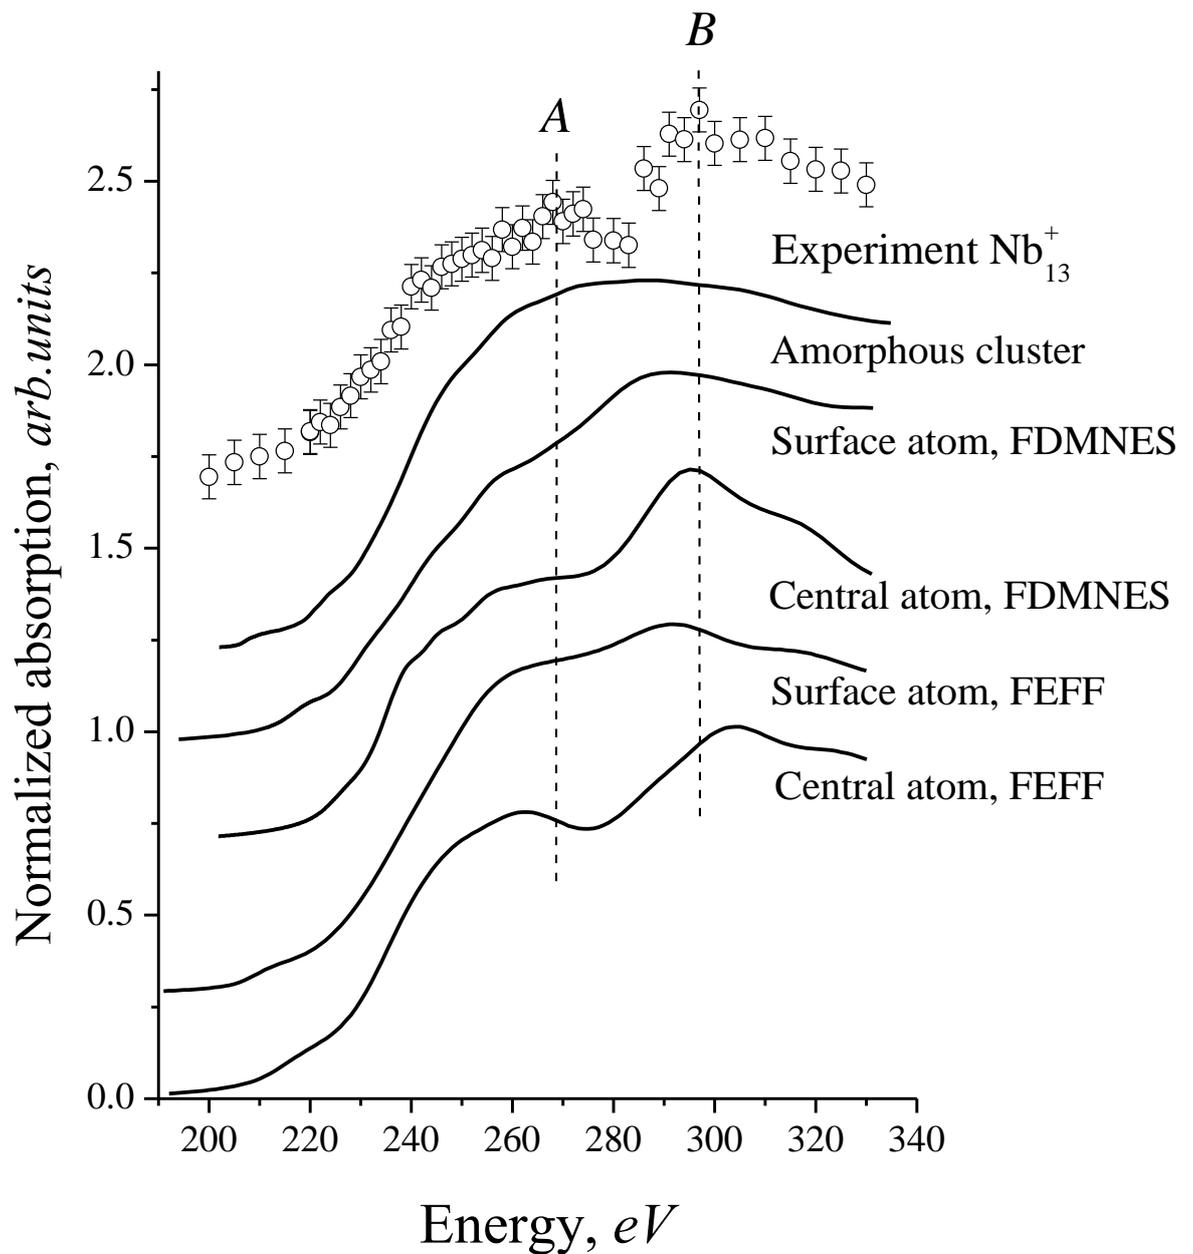

**Figure 6.** Experimental  $M_{4,5}$ -edge XANES spectrum of free  $\text{Nb}_{13}^+$  [Peredkov et al, 2011a] with the corresponding theoretical spectra (FDMNES, FEFF) calculated for the icosahedral structure having a distance between the “surface” atoms of 2.2 Å. Note that the simulated FDMNES spectrum of the amorphous structure shows definitely less fine structure than the spectra of the icosahedrons.

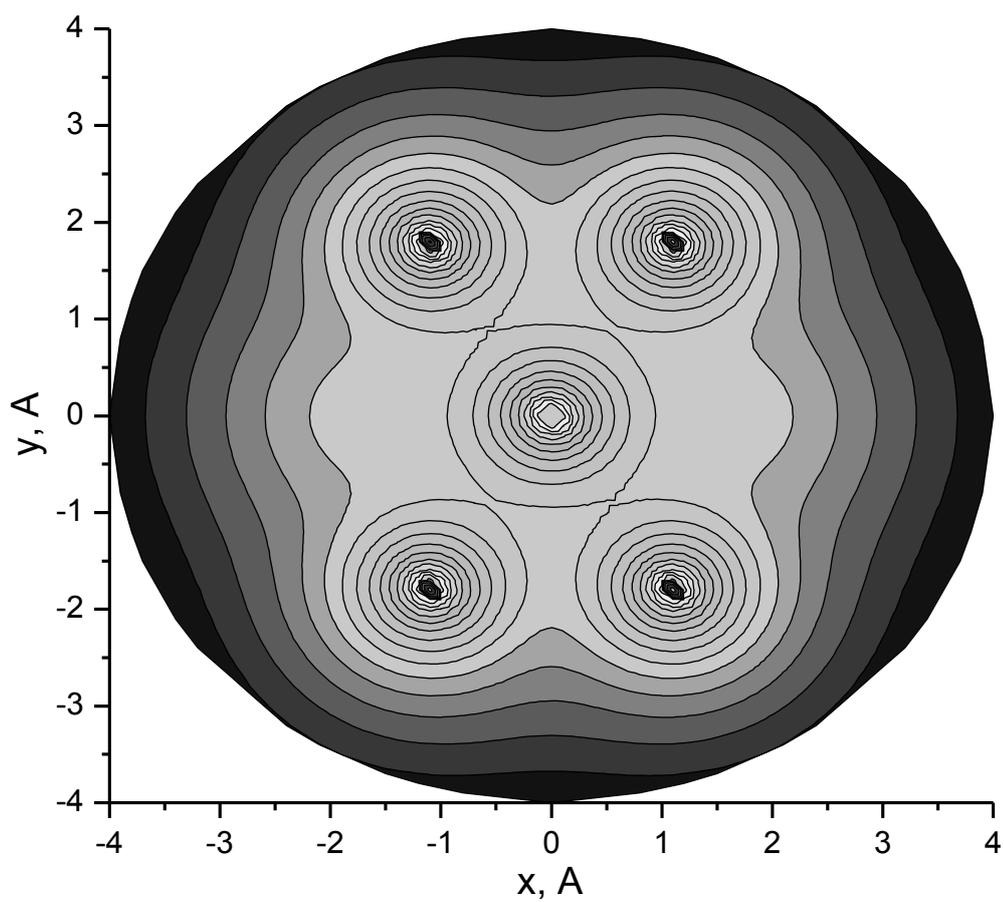

**Figure 7.** Contour map of the potential of the 13-atomic icosahedral niobium cluster along the plane containing the central atom and four “surface” atoms. Darker areas correspond to weaker potential.

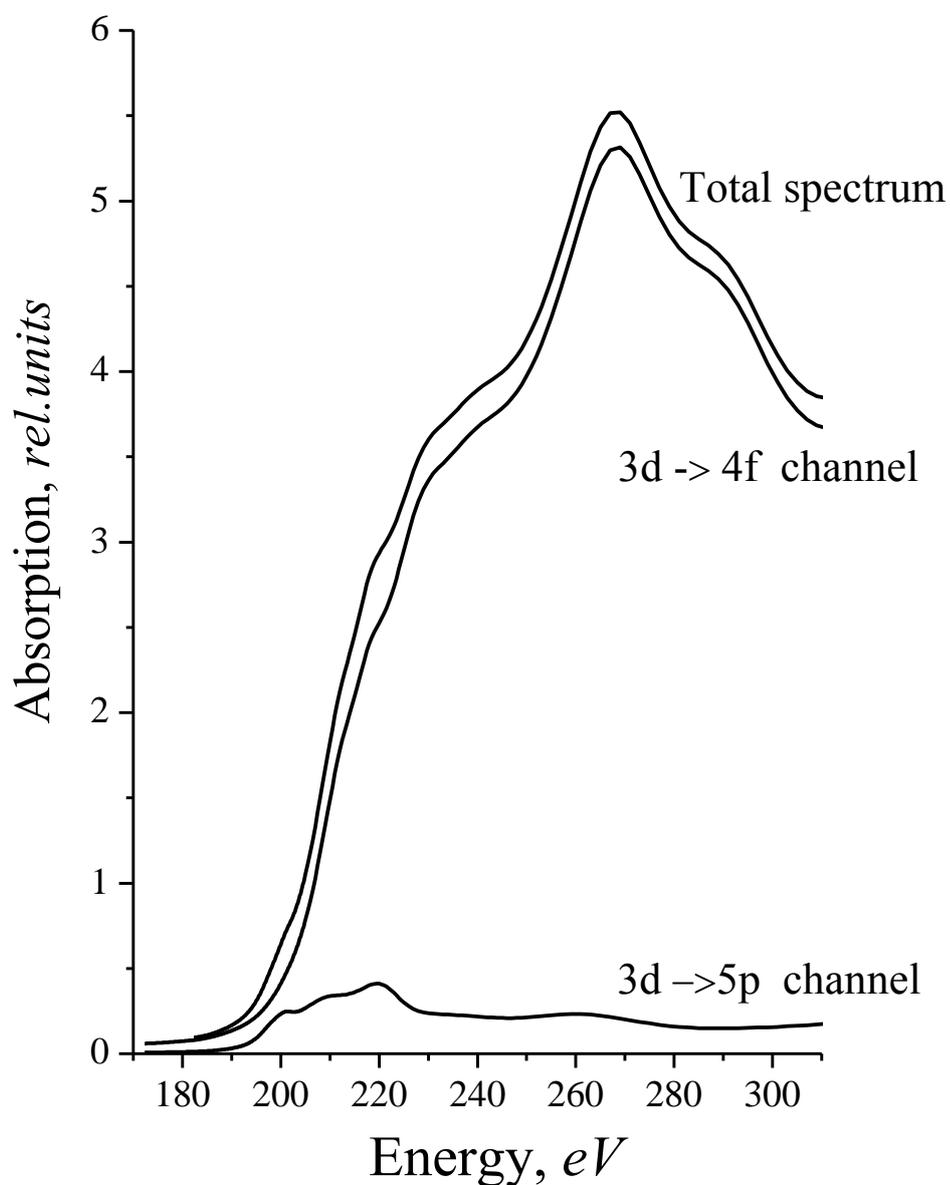

**Figure 8.** Calculated  $3d \rightarrow 4f$  and  $3d \rightarrow 5p$  electronic transitions corresponding to the  $M_{4,5}$ -XANES of central niobium atom of icosahedral structure of 13-atomic niobium cluster (distance between the “surface” atoms is 2.2 Å). The total  $M_{4,5}$ -XANES spectrum calculated with the consideration of both Nb  $3d \rightarrow 4f$  and Nb  $3d \rightarrow 5p$  channels are also presented.