

AperTO - Archivio Istituzionale Open Access dell'Università di Torino

Preparation of activated carbon from Xinjiang region coal by microwave activation and its application in naphthalene, phenanthrene, and pyrene adsorption

This is the author's manuscript

Original Citation:

Availability:

This version is available <http://hdl.handle.net/2318/1576955> since 2016-06-30T22:29:46Z

Published version:

DOI:10.1016/j.jtice.2015.02.031

Terms of use:

Open Access

Anyone can freely access the full text of works made available as "Open Access". Works made available under a Creative Commons license can be used according to the terms and conditions of said license. Use of all other works requires consent of the right holder (author or publisher) if not exempted from copyright protection by the applicable law.

(Article begins on next page)

This Accepted Author Manuscript (AAM) is copyrighted and published by Elsevier. It is posted here by agreement between Elsevier and the University of Turin. Changes resulting from the publishing process - such as editing, corrections, structural formatting, and other quality control mechanisms - may not be reflected in this version of the text. The definitive version of the text was subsequently published in JOURNAL OF THE TAIWAN INSTITUTE OF CHEMICAL ENGINEERS, 53, 2015, 10.1016/j.jtice.2015.02.031.

You may download, copy and otherwise use the AAM for non-commercial purposes provided that your license is limited by the following restrictions:

- (1) You may use this AAM for non-commercial purposes only under the terms of the CC-BY-NC-ND license.
- (2) The integrity of the work and identification of the author, copyright owner, and publisher must be preserved in any copy.
- (3) You must attribute this AAM in the following format: Creative Commons BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/deed.en>), 10.1016/j.jtice.2015.02.031

The publisher's version is available at:

<http://linkinghub.elsevier.com/retrieve/pii/S1876107015000851>

When citing, please refer to the published version.

Link to this full text:

<http://hdl.handle.net/2318/1576955>

1 **Preparation of activated carbon from Xinjiang region coal by microwave**
2 **activation and its application in naphthalene, phenanthrene, and pyrene**
3 **adsorption**

4 Xuemin Xiao¹, Dandan Liu¹, Yujun Yan¹, Zhilin Wu², Zhansheng Wu^{1,*}, Giancarlo Cravotto²

5 1. School of Chemistry and Chemical Engineering, Shihezi University, Shihezi 832003, China

6 2. Dipartimento di Scienza e Tecnologia del Farmaco, University of Turin, Torino 10125, Italy

7 Corresponding author: Zhansheng Wu, Shihezi University, Shihezi 832003, China.

8 Tel: 86993-2055015, Fax: 86993-2057270. E-mail address: wuzhans@126.com

23 **Abstract:**

24 Coal-based activated carbons (CAC) were prepared from coal in Xinjiang China by
25 microwave-assisted activation. The effects of preparation conditions on adsorption capabilities of
26 CAC for methylene blue (MB) and iodine were investigated. The microwave activation was carried
27 out with coal alkali ratio (CAR) of 1:3 for 12 min at 700 W of power, the adsorption capacities of the
28 prepared CAC achieved the maximal values of 312 and 1048.19 mg/g for MB and iodine. The
29 increasing of CAR, activation time, and microwave power reduced the surface functional groups and
30 improved the pH_{PZC} of CAC. The BET surface area and total pore volume of CAC prepared were
31 identified as 1770.49 m^2/g and 0.99 cm^3/g , respectively. Hence, the work demonstrates that the use
32 of microwave heating for preparing CAC is more rapid, cheaper and efficient. The adsorption
33 behaviors of typical polycyclic aromatic hydrocarbons (PAHs) in ethanol aqueous solution on CAC
34 were also explored. Equilibrium data were favorably described by the Langmuir and Freundlich
35 isotherms, and adsorption kinetics was fitted to the pseudo-second-order model well. The
36 equilibrium adsorption amounts were 117.17 mg/g for pyrene, 111.39 mg/g for phenanthrene, and
37 78.18 mg/g for naphthalene. Thus, CAC prepared by microwave activation could have a very
38 effective application in removal of these PAHs.

39 **Key words:** Coal-based activated carbon; Microwave activation; PAHs; Adsorption

40

41

42

43

44

45 **1. Introduction**

46 Activated carbons (AC) are porous material with extremely high surface areas; they have been
47 widely used in a variety of industrial applications such as separation/purification of liquids and gases,
48 removal of toxic substances, catalysts and catalyst support, super capacitors, electrodes and gas
49 storage [1]. AC is usually prepared from different sources of raw materials utilizing different
50 processing methods. Major raw materials for the preparation of AC are coal, petroleum, peat, wood
51 and agricultural wastes. Among which, coal is the most commonly used precursor for AC production
52 due to the advantage of its low cost of production and abundant resources as well as specific
53 beneficial properties [2]. Furthermore, coal-based activated carbon (CAC) is greater demand since it
54 has greater density, corrosion endurance, hardness and more durable than other AC [3]. Coal is an
55 abundant resource with geological reserves exceeding 2.19 million tons. China accounts for 40% of
56 the total reserves. Xinjiang Province in Northwest China has become a large-scale coal production
57 base. The high quality of coals is characterized as low ash yields, low S contents, and low mineral
58 contents [4]. Providing abundant and high quality raw materials is thus important for the
59 development of high value-added coal chemical products. For this reason, coal is selected as a stable
60 alternative for the preparation of AC in Xinjiang.

61 Generally, two methods are used for the preparation of ACs via physical and chemical activation.
62 During physical activation, the raw material is carbonized first at high temperature and then it is
63 activated by CO₂ or steam under pressure to increase porosity and surface area of ACs. In chemical
64 activation both carbonization and activation takes place simultaneously, in which raw material is first
65 impregnated with activating chemical and then carbonized at desired temperature that varies
66 according to activating chemical used [5]. Conventional heating method is usually transferred from

67 surface into the interior of the material by thermal conduction using the tubular furnace at relatively
68 high temperature and long time; as a result, the process of heating was slow, high energy
69 consumption and non-uniform with the surfaces [6]. In recent years, microwave irradiation has been
70 widely investigated due to the tremendous thermal gradient from the interior of the char particle to
71 its cool surface allows the microwave-induced reaction to proceed more quickly and effectively at a
72 lower bulk temperature [7]. Moreover, microwave radiation supply energy directly to carbon
73 skeleton at molecular level. Thus, microwave heating provides additional advantages such as energy
74 savings and shortening the processing time, possibility of selective heating, precise control of
75 temperature, small equipment size and reduced waste comparing with traditional heating techniques
76 [8, 9, 10, 11, 12, 13].

77 In microwave irradiation chemical activation, the raw material is first impregnated by activating
78 agents such as H_3PO_4 , KOH or ZnCl_2 , followed by thermal activation to create the pore structure.
79 The microwave induced chemical activation usually has higher carbon yield and better developed
80 pore structure than the physical activation [14, 15, 16, 17]. Liu *et al.* [9] develop a microwave
81 induced activation process for the preparation of high surface area bamboo-based AC. The optimal
82 activation conditions were determined as: microwave power 350 W, radiation time 20 min and
83 phosphoric acid/carbon ratio 1:1, under which a surface area of $1432 \text{ m}^2/\text{g}$ could be reached. Li *et al.*
84 [7] prepared relatively well developed porosity AC from tobacco stems by chemical activation with
85 K_2CO_3 using microwave radiation. The optimum conditions were as follow: microwave power 700
86 W, microwave radiation time 30 min, $\text{K}_2\text{CO}_3/\text{C}$ ratio 1.5:1. Wang *et al.* [10] has been successfully
87 used to prepare AC from wood via microwave-induced ZnCl_2 activation. However, relatively few
88 studies have focused on the preparation of CAC from anthracite by microwave activation. Revealing

89 the correlation between the microwave process conditions of preparing CAC and its adsorption
90 performance is also necessary.

91 Polycyclic aromatic hydrocarbons (PAHs) are a class of compounds that have more than two
92 aromatic rings in their molecules. PAHs can transport long distance in air and water, and some PAHs
93 are capable of interacting with DNA to promote mutagenic and carcinogenic responses [18, 19].
94 Because of their stability and difficult degradation by microorganisms, it is difficult to remove PAHs
95 using only biological treatment processes. Additionally, PAHs are not efficiently removed by
96 conventional physicochemical methods such as coagulation, flocculation, sedimentation, filtration,
97 or ozonation. AC is the most commonly used porous media for the removal of PAHs from solution
98 [20-22]. Yuan *et al.* [23] reported that porous carbons were prepared from petroleum coke by KOH
99 chemical activation and used as adsorbents for effective adsorbing naphthalene, fluorene,
100 phenanthrene, pyrene and fluoranthene from aqueous solutions, at an initial concentration of
101 3250–6250 ng/mL, over 90% of PAHs are removed from the solution within 30 min. Kong *et al.* [20]
102 reported that the performance of sesame stalk-based AC by potassium hydroxide in the efficient
103 removal of phenanthrene from an aqueous solution, at a carbon concentration of 10 mg/32mL and a
104 carbonization temperature of 700 °C, the removal efficiency of phenanthrene approached 100%,
105 which was comparable to that by the commercial carbon. Cabal *et al.* [21] studied the preparation of
106 AC from bean pods waste by chemical activation was investigated as adsorbents for the adsorption
107 of naphthalene from water solutions at low concentration. Moreover, a number of studies have
108 shown that AC prepared from different materials has significant differences in the adsorption of
109 PAHs. The adsorption behavior of different PAHs on AC has some differences [24, 25, 26]. These
110 three typical PAHs (naphthalene, phenanthrene, pyrene) were selected owing to their common

111 presence in the environment and their troublesome properties. These are taken as representatives of
112 two-, three- and four-ringed PAHs. It can be seen that these substances have low solubility in water,
113 which tends to be even lower when the number of aromatic rings is increased. Therefore, exploring
114 CAC prepared using microwave activation for the adsorption features of typical PAHs in 30%
115 ethanol aqueous solution is considerably interesting and informative.

116 The main purpose of the present study is to use rich anthracite from Xinjiang as raw material to
117 develop a microwave-induced activation process for the preparation of CAC with high surface area
118 and high adsorption performance to PAHs. The effects of activator types, coal alkali ratio (CAR),
119 activation time, and microwave power on the adsorption capabilities of CAC for MB and iodine
120 were investigated. CAC was characterized by using the Boehm method, point of zero charge,
121 nitrogen adsorption isotherm, and scanning electron microscopy (SEM). The adsorption features,
122 isotherm, and kinetics of typical PAHs such as naphthalene, phenanthrene, and pyrene were also
123 explored. The results were used to evaluate the potential application of CAC prepared by
124 microwave-induced activation for the removal of PAHs.

125 **2. Materials and methods**

126 **2.1. Materials**

127 This raw anthracite coal was purchased from TBEA, Changji, Xinjiang Uygur Autonomous
128 Region, China. The coal was passed through a 100 mesh sieve, washed with distilled water to
129 remove carbon and fines, and dried in an air oven at 110 °C for 4 h. The resultant coal powder was
130 used to prepare the CAC. The selected physio-chemical properties of naphthalene, phenanthrene and
131 pyrene are shown in **Table 1**. Naphthalene, phenanthrene and pyrene (>98%; Aladdin, Shanghai,
132 China) were used to prepare the stock solutions by dissolving an appropriate amount in 30% ethanol

133 aqueous solution.

134 **Table 1 should be positioned here.**

135 **2.2. Preparation of CAC**

136 CAC was prepared within a microwave oven (MM823LA6-NS, Midea) at a frequency of 2.45
137 GHz. The oven was equipped with a power controller (100, 300, 500, 700, and 900 W) and a time
138 controller (4, 8, 12, 16, and 20 min). The mixture of 10 g with various ratios (1:1, 1:2, 1:3, 1:4, and
139 1:5) of the dried coal powder to activator (KOH, ZnCl₂ and H₃PO₄) was placed in a quartzose tube
140 of a microwave reactor to activate under vacuum atmosphere at the given power and time. The
141 resultant products were washed with 10% hydrochloric acid and then with distilled water until the
142 filtrate reached neutral. The remaining solid was dried in an oven at 110 °C for 4 h and stored in
143 sealed glass bottles for the adsorption experiments.

144 The amount of MB adsorption is often regarded as a measure of its performance for high
145 molar-mass species and was determined according to GB/T12496.10-1999 (Detection standard of
146 activated carbon in China) [20]. On the other hand, the adsorption performance of activated carbons
147 for low-molar mass species is generally indicated by the iodine number, which was determined at
148 303 K based on the Standard Detection Method (ASTM Designation: D4607-86) [20].

149 **2.3. Characterization methods**

150 The textural properties of the CAC were evaluated by measuring nitrogen adsorption isotherm at
151 77 K with ASAP 2020C surface area and porosity analyzer (Micromeritics Instrument Corp., USA).
152 The S_{BET} was calculated using the BET equation. The total pore volume (V_t) was calculated by
153 converting the adsorption amount at P/P₀ = 0.95 to a volume of liquid adsorbate. The micropore area
154 (A_m) and volume (V_m) were obtained using the t-plot method. The external volume (V_e) was the

155 deduction of V_m from V_t and the external area (A_a) was the deduction of A_m from S_{BET} . The surface
156 morphology of the CAC was examined using scanning electron microscopy (SEM) (JSM-6490LV,
157 Japan Electron Optics Laboratory Ltd. Corp., Japan) at accelerating voltages of 15 kV. Before
158 observation, the samples were coated with gold in E-1010 Ion sputter. X-ray diffraction (XRD) was
159 carried out on a Rigaku D/MAX-YA diffractometer with Ni-filtered Cu Ka radiation as the X-ray
160 source.

161 The “Boehm titration” is a commonly used technique to determine the acidic oxygen surface
162 functional groups on carbon samples whereby bases of various strengths (NaHCO_3 , Na_2CO_3 , NaOH)
163 neutralize different acidic oxygen surface functionalities [19]. The weakest base, NaHCO_3 ,
164 neutralizes only the strongest acidic carbon surface functionalities (CSFs) which are carboxylic
165 groups, while Na_2CO_3 neutralizes carboxylic and lactonic groups. The strongest base typically used,
166 NaOH , neutralizes carboxylic, lactonic and phenolic groups. The number of each type of CSF can be
167 determined by difference between the uptake of each reaction base [19]. A mixture of 1.5 g CAC and
168 25.00 mL of one of the three 0.05 M reaction bases, NaHCO_3 , Na_2CO_3 and NaOH was filtered and
169 wash with distilled water adequately after stirring for 24 h, then all the filtrate collected was added
170 0.05 M HCl to completely neutralize and end with methyl red indicator.

171 The point of zero charge (pH_{PZC}) is defined as the pH of the mixtures at which surface charge
172 density on the adsorbent is zero. The pH_{PZC} values were determined by a mass titration method
173 proposed by Franz [14]. Activated carbon (0.1 g) was added to 20 mL NaCl solutions, and then the
174 initial pH had been adjusted with NaOH or HCl . The flasks were sealed and placed on a shaker for
175 24 h. The pH_{PZC} occurred when there was no change in the pH after contact with the carbon.

176 **2.4. Adsorption experiments of PAHs**

177 2.4.1. Adsorption performance analysis

178 Naphthalene, phenanthrene and pyrene were initially solved into ethanol aqueous solution (30
179 vol%) to prepare the 300 mg/L stock solutions, respectively. The concentrations of various adsorbate
180 solutions were measured after adsorption by a UV-vis spectrophotometer (UV-752N, Shanghai
181 Metash Instruments Co., Ltd, China). The concentration of naphthalene, phenanthrene and pyrene
182 were calculated based on the following calibration equations, respectively: (1) at 218 nm, (2) at 249
183 nm, (3) at 237 nm. $C = 1.7319A_{218} - 0.2309$ (1), and R^2 was equal to 0.9995. $C = 3.4483A_{249} +$
184 0.0103 (2), and R^2 was equal to 0.9998. $C = 3.4483A_{237} - 0.0469$ (3), and R^2 was equal to 0.9998.

185 For each adsorption kinetics experiment, 40 mL of 300 mg/L adsorbate solution was placed in a
186 100 mL conical flask with a cover. The solution was shaken at 25 °C and 60 rpm. After preheating
187 for 5 min, 100 mg of CAC prepared was added to the solution. Then, the samples were taken
188 periodically and filtrated immediately by suction. The supernatant solution was analyzed for the
189 remaining concentration of adsorbate by a UV-vis spectrophotometer.

190 For each adsorption isotherm experiment, approximately 40 mL of different adsorbate solution of
191 various concentrations was placed in a 100 mL conical flask with cover. To establish the thermal
192 equilibrium before adsorption, the solution was shaken at 25 °C and a stirring rate of 60 rpm. After
193 preheating for 5 min, 150 mg of CAC prepared was added to the solution. Then, the samples were
194 taken after 50 min and filtrated immediately by suction. The supernatant solution was analyzed for
195 the remaining concentration of adsorbate by a UV-vis spectrophotometer. The amount of adsorbate
196 (Q_e) was calculated as follow:

197
$$Q_e = \frac{(C_0 - C_e)V}{m} \quad (1)$$

198 where C_0 (mg/L) and C_e (mg/L) are liquid-phase concentrations of adsorbate at initial and

199 equilibrium, respectively. V (mL) represents the volume of the solution and m (g) stands for the mass
200 of CAC used.

201 2.4.2. Adsorption isotherm

202 The Langmuir adsorption Eq. (2), predicts the existence of monolayer coverage of the adsorbate
203 at the outer surface of the adsorbent [9].

$$204 \quad \frac{C_e}{Q_e} = \frac{1}{q_m K_L} + \frac{C_e}{q_m} \quad (2)$$

205 where C_e and Q_e are as defined in Eq. (1), q_m is adsorption maximum (mg/g); K_L is sorption
206 equilibrium constant (L/mg).

207 The Freundlich isotherm [9] is an empirical equation employed to describe heterogeneous
208 systems, and is expressed by the following Eq. (3):

$$209 \quad \log Q_e = \frac{1}{n} \log C_e + \log K_F \quad (3)$$

210 where K_F is a constant which represents a measure of the adsorption capacity of the adsorbent for
211 specific solute, and n is a measure of intensity of adsorption.

212 2.4.3. Adsorption kinetics

213 Kinetic models are used to examine the rate of the adsorption process and potential rate
214 controlling step, i.e., particle diffusion or chemical reaction. The capability of pseudo-first-order,
215 pseudo-second-order and intraparticle diffusion, were examined in this study.

216 The pseudo-first-order kinetic rate equation is expressed as [15]:

$$217 \quad \frac{1}{Q_t} = \frac{1}{Q_e} + \frac{k_1}{Q_e t} \quad (4)$$

218 where k_1 is the rate constant of pseudo-first-order sorption (min), which can be determined from the
219 slope of the linearized pseudo-first-order rate equation.

220 The pseudo-second-order kinetic rate equation is expressed as [15]:

$$221 \quad \frac{t}{Q_t} = \frac{1}{k_2 Q_e^2} + \frac{t}{Q_e} \quad (5)$$

222 where k_2 is the second-order rate constant (g/mg/min) can be determined from the intercept of the
223 linearized pseudo-second-order rate equation.

224 In the intraparticle diffusion model, the relationship between the adsorption capacity at time t ,
225 Q_t and $t^{1/2}$ could be written as [27]:

$$226 \quad Q_t = K_p t^{1/2} + C \quad (6)$$

227 where K_p is the intraparticle diffusion constant (mg/g/min^{1/2}) and C is the intercept of the line, which
228 is proportional to the boundary layer thickness.

229 **3. Results and discussion**




230 **3.1 Preparation of CAC**

231 3.1.1. Effects of activator

232 MB molecule has been estimated that the minimum pore size it can enter is 1.3 nm [28] and can
233 be used to indicate the capacity of a carbon for sorption of medium-sized molecules. The iodine
234 molecule provides information about the surface area that is contributed by pores larger than 1 nm
235 [29], and the iodine number provides a good indication of the capacity of a carbon for sorption of
236 small molecules [30]. The average pore width of KOH-activated CAC was approximately 2.8 nm in
237 **Table 2**, which was a sufficiently large pore width to allow MB and iodine molecules to pass through
238 for a large amount of adsorption.

239 According to the preliminary experiment, the ratio for ZnCl₂ or H₃PO₄ was also 1:3, whose is
240 optimum conditions are the same as KOH. The influences of activator types on the adsorption
241 amounts of MB and iodine on CAC prepared at a coal activator ratio of 1:3, activation time of 12

242 min, and microwave power of 700 W are shown in Fig. 1. In the chemical activation, the adsorption
243 property of CAC prepared with various activating agents showed a significant difference. The
244 adsorption amounts of MB and iodine on CAC prepared with KOH reached the maximum. Alkaline
245 hydroxide activation involves the redox reduction and carbon oxidation to generate porosity. During
246 the reactions, the evolution of CO, CO₂ and H₂ constituents, and additional reactions [11] between
247 the active intermediates with the carbon surface are possible (Eqs. (1) - (3)).




251 The produced alkaline is intercalated to the carbon matrix responsible for both stabilization and
252 widening of the spaces between the carbon atomic layers. Thus, KOH activated samples exhibited
253 the best adsorption capacity. Metallic potassium formed during the redox reaction can be intercalated
254 into the carbon walls independently of the structural order responsible for separation and degradation
255 of graphitic layers thus develop the microporosity and mesoporosity. The resulting CAC by the
256 activation agents of ZnCl₂ and H₃PO₄ had very low adsorption amounts of MB and iodine
257 (particularly the adsorption amounts of MB), which may be due to the activation of ZnCl₂ and
258 H₃PO₄ producing a lower specific surface area and smaller pore size on CAC, which is showed in
259 Table 2. The activation agents of ZnCl₂ and H₃PO₄ could be widely used to prepare AC from
260 lignocellulosic products [31]. So KOH was selected as appropriate activator in this investigation.

261 **Table 2 should be positioned here.**

262 **Fig. 1 should be positioned here.**

263 3.1.2. Effects of coal to KOH ratio (CAR)

264 **Table 3** presents the influences of the CAR on the adsorption amounts of MB and iodine on CAC
265 prepared at microwave power of 700 W for 8 min. The activation reaction was strengthened and a
266 large number of pores were formed with the rising ratio, enhancing the CAC adsorption capacity.
267 When CAR reached 1:3, the carbons on the active sites could be reacted completely, and the
268 adsorption capacity reached the maximum [7]. When CAR was larger than 1:3, the pores were
269 widened. Besides, excessive KOH molecules might decompose following the reactions:



272 Therefore, the catalytic oxidation entailed the widening of mesoporous structures and carbon
273 burn off, so the adsorption capacity of AC was decreased.

274 Surface functional groups such as phenolic group (-OH), lactonic group (-COOCO-), and
275 carboxylic group (-COOH) were determined by Boehm titration. The results of these surface
276 functional groups for CAC with various CARs are shown in **Table 3**. The CAR apparently had a
277 destructive influence on the functional groups of CAC. With increased CAR, the amount of lactonic
278 groups, phenolic and carboxylic groups decreased, and phenolic and carboxylic groups are fairly low.
279 A possible explanation for this could be that the alkali activator affected the number of surface acidic
280 functional groups. The results of pH_{PZC} titrations for CAC under various CARs can also be seen in
281 **Table 3**. pH_{PZC} increased with increased CAR. Previous research has indicated that the existence of
282 surface functional groups, such as carboxyl, carbonyl, and phenol, constitutes the source of surface
283 acidity [9, 12, 32] and the opposite is observed for alkali treatment. Considering the results of the
284 adsorption capacity of CAC, CAR was set at 1:3 for this study.

285 3.1.3. Effects of activation time

286 **Table 3** demonstrates the effects of activation time on the adsorption amounts of MB and iodine
287 on CAC prepared with CAR of 1:3 at microwave power of 700 W. The MB adsorption amounts of
288 CAC increased from approximately 234 to 312 mg/g with increased activation time from 4 to 12 min,
289 and then decreased to 238.5 mg/g for 20 min activation. Similarly, the iodine number of the CAC
290 increased gradually from approximately 962.12 to 1048.19 mg/g with increased time from 4 to 12
291 min, and then slightly decreased to 1045.87 mg/g for 20 min activation. However, when the
292 activation time reached a certain value, the carbon pores were burnt off by microwave heating,
293 thereby lowering the CAC adsorption capacity. A similar tendency was observed in the preparation
294 of AC from rice husk [17].

295 The results of the surface functional content and pH_{PZC} titrations for CAC under various
296 activation times can be seen in **Table 3**. With increased activation time from 4 to 20 min, the number
297 of surface functional groups decreased. pH_{PZC} generally showed the opposite trend. The
298 phenomenon implied that increasing activation time promoted an acceleration of energy, leading to a
299 destruct of surface functional groups and developed the rudimentary of the pore structure [11].
300 Considering the results of the CAC adsorption capacity, the activation time was set at 12 min in this
301 study.

302 3.1.4. Effects of microwave power

303 The effects of microwave power on the adsorption amounts of MB and iodine of CAC prepared
304 by KOH activator with CAR of 1:3 for 12 min, as shown in **Table 3**. The adsorption amounts of MB
305 rose from 54 to 312 mg/g with increased power from 100 to 700 W and then decreased. The
306 adsorption amounts of iodine increased from 769.02 to 1048.19 mg/g with increased power from 100
307 to 700 W and then decreased. More carbon molecules were activated along with the higher

308 microwave power participate in the activation reaction, and lead to the development of pore structure
309 adequately. However, the exceeded of a certain power may lead to excessive destruction of pore
310 structure [11].

311 The results of the surface functional content and pH_{PZC} titrations for CAC under various
312 microwave powers can be seen in Table 3. With increased microwave power from 100 to 900 W, the
313 number of lactonic groups decreased. The surface functional content and pH_{PZC} had the opposite
314 trend. Menéndez *et al.* [12] pointed out that microwave treatment reduced the functional group,
315 especially those of acidic in nature, and increased the pH_{PZC} of the carbon. In this study, CAC
316 produced directly by microwave heating agreed with the reported findings [12]. The optimum
317 microwave power in this experiment was thus 700 W.

318 **Table 3 should be positioned here.**

319 **3.2. Characterization of CAC**

320 3.2.1. Porous structure analysis

321 The N_2 adsorption isotherms of the CAC at 77 K are presented in Fig. 2. The adsorption
322 isotherms demonstrated a sharp rise at low P/P_0 range, and a gradual increase was seen at relatively
323 high P/P_0 range. According to the classification of IUPAC [33], all adsorption isotherms were of type
324 I, indicating that the CACs were mainly microporous. The N_2 adsorption isotherms on activated
325 carbons from Zonguldak region coals using chemical activation also conformed to type I isotherm by
326 Kopac and Toprak [3]. Moreover, the saturated adsorption amounts of N_2 increased after microwave
327 activation, implying an increase in the pore volume.

328 The textural properties obtained from the N_2 adsorption isotherms are summarized in Table 2.
329 CAC-4 had a well-developed porosity with a surface area of $1770.49 \text{ m}^2/\text{g}$, which was primarily

330 microporous under optimal conditions. Liu *et al.* [9] reported that bamboo-based AC using
331 microwave radiation has a maximum surface area of 1409 m²/g. Yagmur *et al.* [13] reported that the
332 maximum BET surface area was 1157 m²/g for the AC from waste tea treated with chemical
333 activation with microwave energy. Compared with previous works, CAC obtained a higher specific
334 surface area. This observation suggested that coal could also form a considerable porous structure
335 through microwave-assisted chemical activation. The specific surface area obtained by the BET
336 equation (S_{BET}), micropore area (A_{m}), external surface area (A_{e}), micropore volume (V_{m}), and total
337 pore volume (V_{t}) of CAC-2 were larger than those of CAC-1, whereas the average pore width of
338 CAC-2 was smaller than CAC-1. This result indicated that the increasing potassium hydroxide
339 amount enhanced the pore development and created new pores of coal, resulting in further increased
340 specific surface area and decreased average pore width. CAC-2, CAC-3, and CAC-4 were obtained
341 using different activation times. With increased activation time from 4 min to 12 min, the S_{BET} , A_{e} ,
342 and V_{t} gradually increased. The A_{m} and V_{m} of CAC-2 and CAC-4 had no significant differences, and
343 they were larger than those of CAC-3 but not significantly. The phenomenon implied that the
344 increase in activation time promotes an acceleration of energy, which in turn increases the reaction
345 rates, thus developed the rudimentary of the pore structure [11]. The six surface physical parameter
346 values of CAC-5 prepared at 100 W of microwave power were small, indicating no strong reaction
347 occurred between the coal and activation agent at low microwave power.

348 **Fig. 2 should be positioned here.**

349 Enhancing microwave power from 100 to 700 W drastically improved textural properties,
350 possibly ascribed to the combined effect of internal and volumetric heating responsible for the
351 expansion of carbon structure [11]. Also, considerable changes in the surface properties were

352 achieved within a short time, which should be attributed to the distinct mechanism of microwave
353 heating. As listed in **Table 4**, the samples obtained by microwave heating have higher BET surface
354 area. It can be seen advantage of microwave heating is that the treatment time as well as the
355 consumption of gases used in the treatment can be considerably reduced, which resulted in a
356 reduction in the energy consumption, compared with conventional surface heating. In addition,
357 microwave heating technique has overall shown better effect in terms of porous structure, relatively
358 greater surface area than conventional heating method [3]. Hence, the work reported here clearly
359 demonstrates that the use of microwave heating for preparation CAC is more rapid, cheaper and
360 efficient than the use of a conventional furnace.

361 **Table 4 should be positioned here.**

362 3.2.2. Surface morphology analysis

363 SEM images of the coal and CAC prepared under optimum conditions (CAC-4) are shown in **Fig.**
364 **3**. The surface of raw material (**Fig. 3(A)**) was fairly smooth without any pores except for some
365 occasional cracks. After activation, it shows the obtained CAC has an irregular surface with pores
366 and craters. From **Table 2**, it was also known that the pores are micro- and mesopores. As shown in
367 **Fig. 3(B)**, the external surface of the CAC-4 demonstrated a well pronounced pore structure,
368 indicating constitution of new matrix during the activation stage.

369 **Fig. 3 should be positioned here.**

370 3.2.3. Crystal structure

371 X-ray diffraction technique is a powerful tool to analyze crystalline nature of materials. **Fig. 4**
372 shows the XRD profiles of coal and CAC-4. The coal shows an intense diffraction peaks at 26° . The
373 CAC-4 prepared from coal via microwave-induced KOH activation shows an intense diffraction

374 peaks at around 29° and several not obvious diffraction peaks at around 44° , corresponding to the
375 (002) and (100) diffraction of disordered stacking of micrographites, respectively [14].

376 **Fig. 4 should be positioned here.**

377 **3.3. Adsorption isotherm of selected PAHs on CAC-4**

378 **Table 5** lists the parameters of the Langmuir and Freundlich adsorption isotherm models of
379 naphthalene, phenanthrene, and pyrene in ethanol aqueous solution onto CAC-4 at 25°C , along with
380 their regression coefficients (R^2), the adsorption capacity and sorption equilibrium constants (q_m and
381 K_L), and intensity parameters (K_F and n). R^2 reflected the goodness of fit of each of the models to the
382 data. For the Langmuir isotherm, the R^2 values were >0.9934 . The regression coefficients R^2 of the
383 Freundlich isotherm were >0.9809 . Both Langmuir and Freundlich isotherm models efficiently
384 predicted the adsorption of the three PAHs on CAC-4 with high correlation coefficients. This
385 observation indicated that the sorption of naphthalene, phenanthrene, and pyrene onto CAC-4 may
386 be confined to a monolayer adsorption and heterogeneous sorption. Similarly, adsorption isotherm of
387 PAHs from vegetable oil on AC also fitted well by both isotherm models [26]. While Yuan *et al.* [22]
388 reported that the equilibrium adsorption isotherms of PAHs from water on petroleum coke-derived
389 porous carbon fitted the Freundlich equation well, and Kong *et al.* [20] reported that the
390 phenanthrene removal from aqueous solution on sesame stalk-based carbon fit the Freundlich
391 equation well.

392 With carbon, the sorption process results from molecular interactions between the carbon surface
393 and the adsorbate, such as van der Waals attractions, electrostatic forces, and weak intermolecular
394 association [34]. The properties of the adsorbate greatly influence the sorption process. Since PAHs
395 are nonpolar compounds, sorption is governed mainly by hydrophobic interactions [24]. The values

396 of K_L , K_F , and q_m followed the trend of pyrene > phenanthrene > naphthalene, which confirmed that
397 hydrophobic interactions follow the same trend. Kong *et al.* [20] reported that the hydrophobic
398 interactions were the key factor for phenanthrene removal from aqueous solution by the sesame
399 stalk-based carbon. Moreover, the values of n were all greater than 1 and did not significantly change,
400 showing that the prepared CAC favorably adsorbed the three PAHs [22].

401 **Table 5 should be positioned here.**

402 **3.4. Adsorption kinetics of selected PAHs on CAC-4**

403 **Fig. 5** shows the plots of the adsorption amounts of naphthalene, phenanthrene, and pyrene at
404 different time intervals. The adsorption process consisted of two distinguished periods. In the first
405 stage, the three PAHs were rapidly adsorbed onto easily accessible hydrophobic sites in the CAC-4
406 matrix within 5 min. In a well-stirred, solid–liquid system, the first stage of diffusive transport of
407 PAHs molecules from the bulk solution to the exterior surface of porous CAC particles, as well as
408 the intraparticle diffusion of the PAHs through the interior pores of CAC, were assumed to be rapid.
409 In the second stage, adsorption was probably limited by the slow migration of adsorbates to less
410 accessible sites associated with micropores within the CAC-4 matrix, which could take a long time.
411 Valderrama *et al.* [25] reported similarly that the adsorption process of PAHs onto granular AC also
412 was the two-stage. The adsorption amount increased with increased contact time. The maximum
413 adsorption was observed at 20 min, beyond which almost no further increase in the adsorption
414 amount was observed.

415 The experimental data for the naphthalene, phenanthrene, and pyrene adsorption onto CAC-4
416 were fitted by three kinetic models, the values of k_1 , k_2 , k_p , and Q_e , and the correlation coefficients
417 are listed in **Table 6**. The experimental kinetic data followed the pseudo-second-order kinetic curves

418 for the three PAHs, which can be demonstrated by higher R^2 (>0.9999) and closer Q_e values to the
419 experimental ones, q_{exp} . The adsorption progress of the PAHs on the CAC surface were presumably
420 caused by the chemical interaction [14]. Cabal *et al.* [21] found the experimental data of adsorption
421 kinetics of aqueous naphthalene on the AC were fitted to the pseudo-second kinetic model with a
422 high correlation coefficient. While a literature showed that sorption systems of naphthalene and
423 pyrene on AC followed a pseudo-first-order reaction model, although the pseudo-second-order
424 reaction model provides an acceptable description of the sorption process [25]. The equilibrium
425 adsorption amounts at 20 min were 117.17 mg/g for pyrene, 111.39 mg/g for phenanthrene, and
426 78.18 mg/g for naphthalene, respectively, decreased as follows: pyrene > phenanthrene >
427 naphthalene. Compared with the carbonaceous materials such as the phenanthrene adsorption
428 amount at 24 h from aqueous solution of sesame stalk- based AC was 73.74 mg/g [20], the
429 naphthalene adsorption amount at 60 min from aqueous solution of reed straw- based AC was 107.00
430 mg/g [35], and the pyrene adsorption amount at 24 h from aqueous solution of rice husk- based AC
431 was 104.50 mg/g [36], the PAHs adsorption performance of prepared carbon in this work was higher
432 and faster. In addition, coal as a precursor is relatively cheaper. Thus, these results indicate that CAC
433 prepared with microwave activation had excellent capability to remove PAHs from aqueous solution.

434 The agreement between the equilibrium adsorption values determined (q_{exp}) and the adsorption
435 maximum (q_m) obtained from the Langmuir isotherm was clear and sufficient. The observed trend in
436 adsorption amounts was generally consistent with the trend in the amount of aromatic rings and
437 molecular weight shown in Table 2. The adsorption amounts were higher for larger molecular PAHs
438 such as pyrene, which suggested that the PAHs were able to form a π - π complex between the
439 π -electrons of benzene rings and active sites on the AC surface [18]. Therefore, the π - π dispersive

440 interactions between the aromatic ring in PAHs and the graphene layers on CAC were the key
441 parameters that determined the adsorptive affinity of those molecules with a polycyclic aromatic
442 skeleton structure [19]. This phenomenon can explain why molecules with more aromatic rings
443 showed a significantly higher adsorptive affinity than aromatics with fewer rings. The electron
444 donor–acceptor mechanism could involve lactonic groups that predominated on the basic carbon
445 surface. Lactonic groups acted as electron donors. The aromatic rings in the adsorbate accepted
446 electrons [21], consistent with the number of lactonic groups and pH_{PZC} CAC-4 prepared at 0.35
447 mmol/g and 8.35, respectively.

448 **Fig. 5 should be positioned here.**

449 **Table 6 should be positioned here.**

450 **4. Conclusions**

- 451 1. The optimum conditions for CAC preparation were identified to be KOH activator, CAR of 1:3,
452 activation time of 12 min, and microwave power of 700 W. Under the optimum conditions
453 adsorption amounts of MB and iodine on CAC was 312 and 1048.19 mg/g, respectively.
- 454 2. The CAR, activation time, and microwave power destructed surface functional groups and
455 raised the pH_{PZC} of CAC. The BET surface area and pore volume of the optimal CAC were
456 evaluated as 1770.49 m²/g and 0.99 cm³/g, which was primarily microporous. The SEM image
457 of the optimal CAC showed that the external surface of CAC had a well-pronounced and almost
458 uniform pore structure. Hence, the work clearly demonstrates that the use of microwave heating
459 for preparing CAC is more rapid, cheaper and efficient.
- 460 3. The adsorption equilibrium of naphthalene, phenanthrene, and pyrene on CAC-4 was
461 satisfactorily represented by both the Langmuir and Freundlich isotherm models with high

462 correlation coefficients. The prepared CAC favorably adsorbed naphthalene, phenanthrene, and
463 pyrene. The experimental kinetic data followed the pseudo-second-order kinetic curves for
464 naphthalene, phenanthrene, and pyrene, presuming that the adsorption progress is affected by
465 chemical interactions. The equilibrium adsorption amounts were 117.17 mg/g for pyrene, 111.39
466 mg/g for phenanthrene, and 78.18 mg/g for naphthalene. Overall, CAC from Xinjiang region
467 coal prepared by microwave activation could be effectively applied in liquid-phase adsorption
468 involving PAHs.

469 **Acknowledgements**

470 This work was supported financially by funding from the National Natural Science Foundation
471 of China (51262025) and International scientific and technological cooperation project of Xinjiang
472 Bingtuan (2013BC002).

473 **References**

- 474 [1] Ahmadpour A, Do DD. The preparation of active carbons from coal by chemical and physical
475 activation. *Carbon* 1996; 34: 471-474.
- 476 [2] Duan XX, Srinivasakannan C, Qu WW, Wang X, Peng JH, Zhang LB. Regeneration of
477 microwave assisted spent activated carbon: Process optimization, adsorption isotherms and
478 kinetics, *Chem Eng Process* 2012; 53: 53-62.
- 479 [3] Kopac T, Toprak A. Preparation of activated carbons from Zonguldak region coals by physical
480 and chemical activations for hydrogen sorption. *Int J Hydrogen Energ* 2007; 32: 5005-5014.
- 481 [4] Li J, Zhuang XG, Querol X, Font O, Moreno N, Zhou JB, Lei GM. High quality of jurassic coals
482 in the southern and eastern junggar coalelds, Xinjiang, NW China: geochemical and
483 mineralogical characteristics, *Int J Coal Geol.* 2012; 99: 1-15.
- 484 [5] Hayashi J, Kazehaya A, Muroyama K, Watkinson AP. Preparation of activated carbon from
485 lignin by chemical activation. *Carbon* 2008; 38: 1873-1878.
- 486 [6] Li W, Peng JH, Zhang LB, Yang KB, Xia HY, Zhang SM, Guo SH. Preparation of activated
487 carbon from coconut shell chars in pilot-scale microwave heating equipment at 60 KW. *Waste*

- 488 Manage 2009; 29: 756-760.
- 489 [7] Li W, Zhang LB, Peng JH, Li N, Zhu XY. Preparation of high surface area activated carbons
490 from tobacco stems with K_2CO_3 activation using microwave radiation. *Ind Crop Prod* 2008; 27:
491 341-347.
- 492 [8] Jone DA, Lelyveld TP, Mavrofidis SD, Kingman SW, Miles NJ. Microwave heating applications
493 in environmental engineering-a review. *Resour Conserv Recy* 2002; 34: 75-90.
- 494 [9] Liu QS, Zheng T, Wang P, Guo L. Preparation and characterization of activated carbon from
495 bamboo by microwave-induced phosphoric acid activation. *Ind Crop Prod* 2010; 31: 233-238.
- 496 [10] Wang TH, Tan SX, Liang CH. Preparation and characterization of activated carbon from wood
497 via microwave-induced $ZnCl_2$ activation, *Carbon* 2009; 47: 1867-1885.
- 498 [11] Foo KY, Hameed BH. Coconut husk derived activated carbon via microwave induced activation:
499 Effects of activation agents, preparation parameters and adsorption performance. *Chem En J*
500 2012; 184: 57-65.
- 501 [12] Menéndez JA, Menéndez EM, Iglesias MJ, García A, Pis JJ. Modification of the surface
502 chemistry of active carbons by means of microwave-induced treatments. *Carbon* 1999; 37:
503 1115-1121.
- 504 [13] Yagmur E, Ozmak M, Aktas Z. A novel method for production of activated carbon from waste
505 tea by chemical activation with microwave energy. *Fuel* 2008; 87: 3278-3285.
- 506 [14] Huang LH, Sun YY, Wang WL, Yue QY, Yang T. Comparative study on characterization of
507 activated carbons prepared by microwave and conventional heating methods and application in
508 removal of oxytetracycline (OTC). *Chem En J* 2011; 171: 1446-1453.
- 509 [15] Zhong ZY, Yang Q, Li XM, Luo K, Liu Y, Zeng GM. Preparation of peanut hull-based
510 activated carbon by microwave-induced phosphoric acid activation and its application in
511 Remazol Brilliant Blue R adsorption. *Ind Crop Prod* 2012; 37: 178-185.
- 512 [16] Puziy AM, Poddubnaya OI, Martinez-Alonso A, Suarez-Garcia F, Tascon JMD. Surface
513 chemistry of phosphorus-containing carbons of lignocellulosic origin. *Carbon* 2005; 43:
514 2857-2868.
- 515 [17] Kennedy LJ, Vijaya JJ, Sekaran G. Effect of two-stage process on the preparation and
516 characterization of porous carbon composite from rice husk by phosphoric acid activation. *Ind.*
517 *Eng. Chem. Res* 2004; 43: 1832-1838.

- 518 [18] Dowaidar AM, El-Shahawi MS, Ashour I. Adsorption of polycyclic aromatic hydrocarbons
519 onto activated carbon from non-aqueous media: 1. The influence of the organic solvent polarity.
520 Sep. Sci. Technol 2007; 42: 3609-3622.
- 521 [19] Bu J, Loh G, Gwie CG, Dewiyanti S, Tasrif M, Borgna A. Desulfurization of diesel fuels by
522 selective adsorption on activated carbons: Competitive adsorption of polycyclic aromatic sulfur
523 heterocycles and polycyclic aromatic hydrocarbons. Chem En J. 2011; 166: 207-217.
- 524 [20] Kong HL, He J, Wu HF, Wu H, Gao YZ. Phenanthrene Removal from Aqueous Solution on
525 Sesame Stalk-based Carbon. Clean-Soil Air Water 2012; 40: 752-759.
- 526 [21] Cabal B, Budinova T, Ania CO, Tsyntsarski B, Parra JB, Petrova B. Adsorption of naphthalene
527 from aqueous solution on activated carbons obtained from bean pods. J Hazard Mater 2009; 161:
528 1150-1156.
- 529 [22] Xiao XM, Tian F, Yan YJ, Wu ZS. Adsorption behavior of pyrene onto coal-based activated
530 carbon prepared by microwave activation. Journal of Shihezi University 2014; 32:485-490.
- 531 [23] Yuan MJ, Tong ST, Zhao SQ, Jia CQ. Adsorption of polycyclic aromatic hydrocarbons from
532 water using petroleum coke-derived porous carbon. J Hazard Mater 2010; 181: 1115-1120.
- 533 [24] Boving TB, Zhang W. Removal of aqueous-phase polynuclear aromatic hydrocarbons using
534 aspen wood fibers. Chemosphere 2004; 54: 831-839.
- 535 [25] Valderrama C, Cortina JL, Farran A, Gamisans X, Lao C. Kinetics of sorption of polyaromatic
536 hydrocarbons onto granular activated carbon and Macronet hyper-cross-linked polymers
537 (MN200). J Colloid Interf Sci 2007; 310: 35-46.
- 538 [26] Gong ZQ, Alef K, Wilke BM, Li PJ. Activated carbon adsorption of PAHs from vegetable oil
539 used in soil remediation. J Hazard Mater 2007; 143: 372-378.
- 540 [27] Weber WJ, Morris JC. Determination of alkylbenzenesulfonates by ultraviolet
541 spectrophotometry. Anal Chem 1962; 34: 1844-1845.
- 542 [28] Barton SS. The adsorption of methylene blue by active carbon. Carbon 1987; 25: 343-350.
- 543 [29] Baccar R, Bouzid J, Feki M, Montiel A. Preparation of carbon from Tunisian olive-waste cakes
544 and its application for adsorption of heavy metal ions. J Hazard Mater 2009; 162: 1522-1529.
- 545 [30] Dalai AK, Zaman J, Hall E, Tollefson SEL. Preparation of carbon from Canadian coals using a
546 fixed-bed reactor and a spouted bedkiln system. Fuel 1996; 75: 227-237.
- 547 [31] Puziy AM, Poddubnaya OI, Martinez-Alonso A, Suarez-Garcia F, Tascon JMD. Surface

548 chemistry of phosphorus-containing carbons of lignocellulosic origin. Carbon 2005; 43:
549 857-2868.

550 [32] Lu XC, Jiang JC, Sun K, Xie XP, Hu YM. Surface modification characterization and adsorptive
551 properties of a coconut activated carbon. Appl Surf Sci 2012; 258: 8247- 8252.

552 [33] Gregg SJ, Sing KSW. Adsorption, Surface and Porosity, Academic Press, London, 1982.

553 [34] Cooney DO. Adsorption designer for wastewater treatment, Lewis Publishers, London,
554 England, UK, 1999.

555 [35] Gu L, Guo HQ, Zhou P, Zhu NW, Zhang DF, Yuan HP, Lou ZY. Enhanced adsorptive removal
556 of naphthalene intermediates from aqueous solution by introducing reed straw into sewage
557 sludge-based activated carbon. Environ Sci Pollut Res 2014; 21: 2043- 2053.

558 [36] Yakout SM, Daifullah AAM and El-Reefy SA. Adsorption of Naphthalene, Phenanthrene and
559 Pyrene from Aqueous Solution Using Low-Cost Activated Carbon Derived from Agricultural
560 Wastes. Adsorpt Sci Technol 2013; 31: 293- 302.

561 [37] Foo KY, Hameed BH. Utilization of rice husks as a feedstock for preparation of activated
562 carbon by microwave induced KOH and K₂CO₃ activation. Bioresource Technology 2011; 102:
563 9814- 9817.

564 [38] Deng H, Li GX, Yang HB, Tang JP, Tang JY. Preparation of activated carbons from cotton stalk
565 by microwave assisted KOH and K₂CO₃ activation. Chem En J 2010; 163: 373- 381.

566

567

568

569

570

571

572

573

574

575 **Figure captions:**

576 **Fig. 1** Adsorption amounts of MB and iodine by CAC with various activator types (preparation
577 conditions: activation time = 12 min; microwave power = 700 W; CAR= 1:3).

578 **Fig. 2** Nitrogen adsorption isotherm for the prepared CACs (CAC-1: activation time = 8 min;
579 microwave power = 700 W; CAR= 1:1, CAC-2: activation time = 8 min; microwave power = 700 W;
580 CAR= 1:3, CAC-3: activation time = 4 min; microwave power = 700 W; CAR= 1:3, CAC-4:
581 activation time = 12 min; microwave power = 700 W; CAR= 1:3, CAC-5: activation time = 12 min;
582 microwave power = 100 W; CAR= 1:3).

583 **Fig. 3** SEM micrographs of the selected samples at 5000× magnification: (A) coal, (B) CAC-4
584 (preparation conditions: activation time = 12 min; microwave power = 700 W; CAR= 1:3).


585 **Fig. 4** XRD profiles of coal and CAC-4 (preparation conditions: activation time = 12 min;
586 microwave power = 700 W; CAR= 1:3).

587 **Fig. 5** Adsorption amounts of naphthalene, phenanthrene and pyrene in ethanol aqueous solution on
588 CAC-4 (preparation conditions: activation time = 12 min; microwave power = 700 W; CAR= 1:3) at
589 various times and at 25 °C.

590

591

592

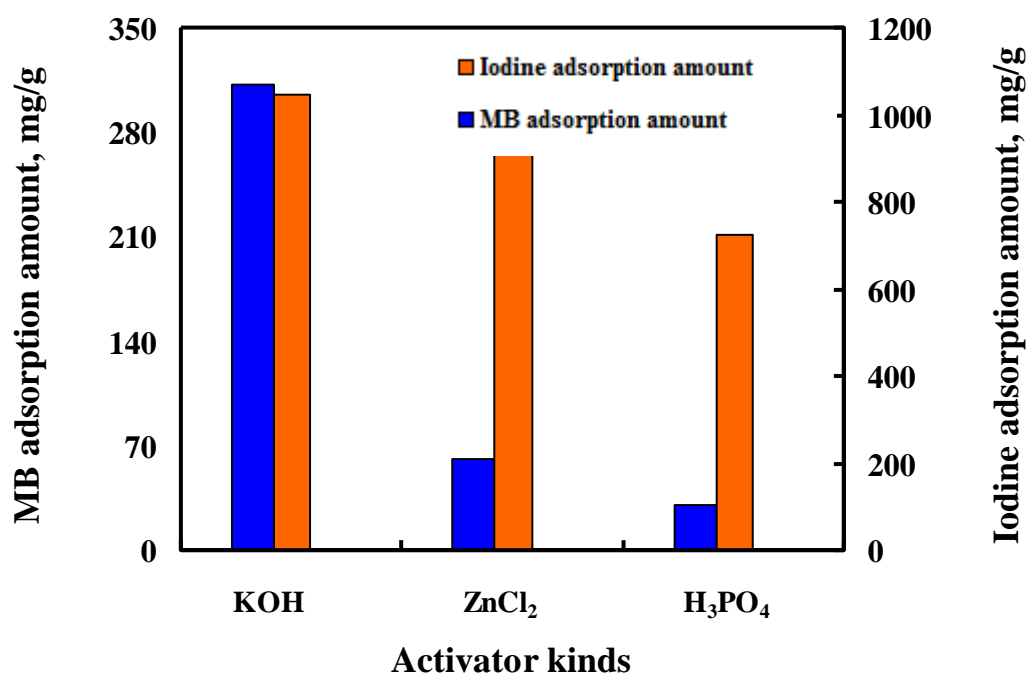

593

594 **Fig. 1** Adsorption amounts of MB and iodine by CAC with various activator types (preparation

595 conditions: activation time = 12 min; microwave power = 700 W; CAR= 1:3).

596

597

598


599

600

601

602

603

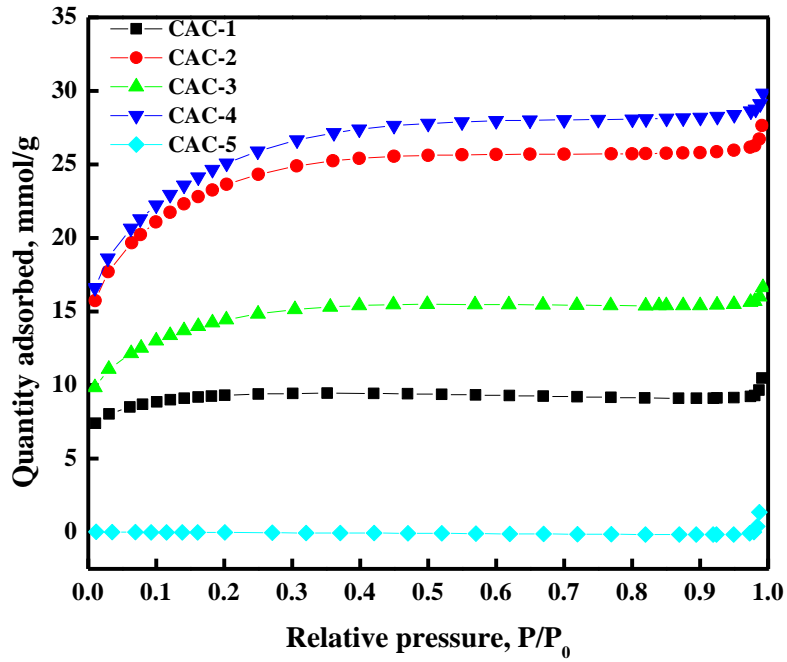


604

605 **Fig. 2** Nitrogen adsorption isotherm for the prepared CACs (CAC-1: activation time = 8 min;
 606 microwave power = 700 W; CAR= 1:1, CAC-2: activation time = 8 min; microwave power = 700 W;
 607 CAR= 1:3, CAC-3: activation time = 4 min; microwave power = 700 W; CAR= 1:3, CAC-4:
 608 activation time = 12 min; microwave power = 700 W; CAR= 1:3, CAC-5: activation time = 12 min;
 609 microwave power = 100 W; CAR= 1:3).


610

611

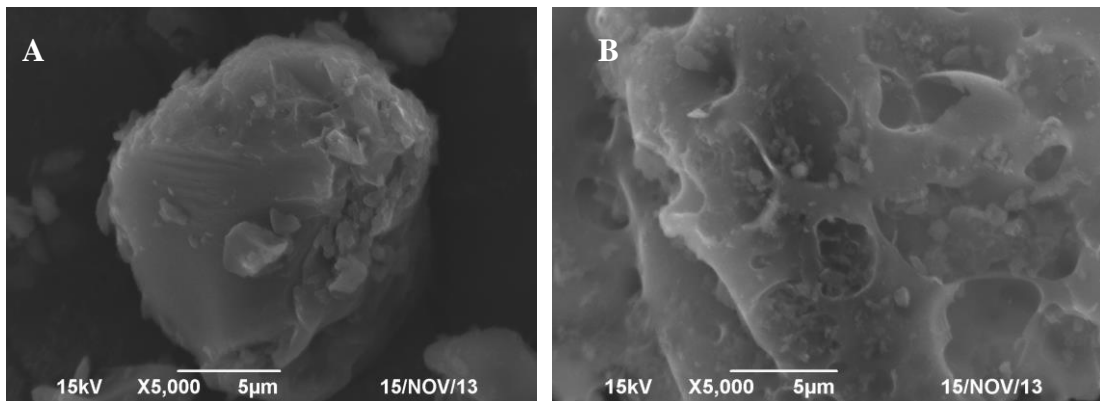

612

613 **Fig. 3** SEM micrographs of the selected samples at 5000× magnification: (A) coal, (B) CAC-4
 614 (preparation conditions: activation time = 12 min; microwave power = 700 W; CAR= 1:3).

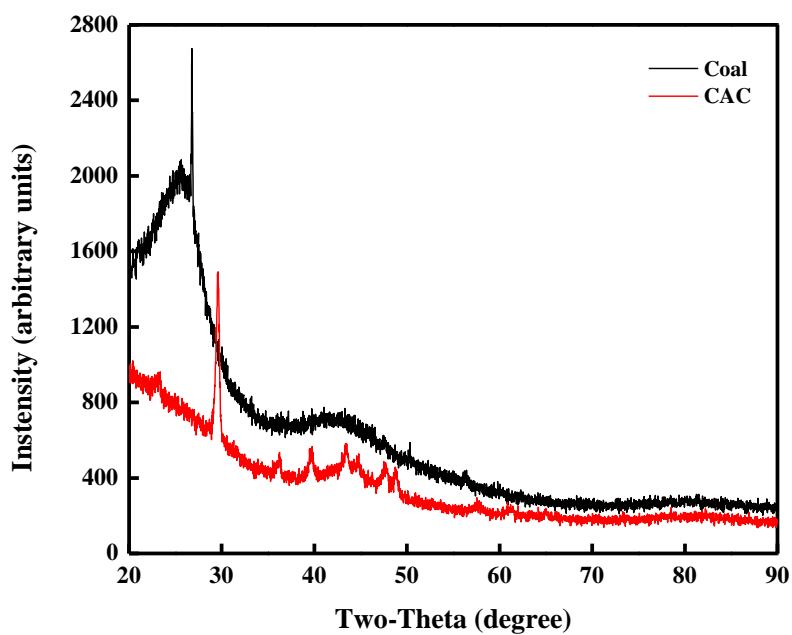


615

616 **Fig. 4** XRD profiles of coal and CAC-4 (preparation conditions: activation time = 12 min;

617 microwave power = 700 W; CAR= 1:3).

618

619

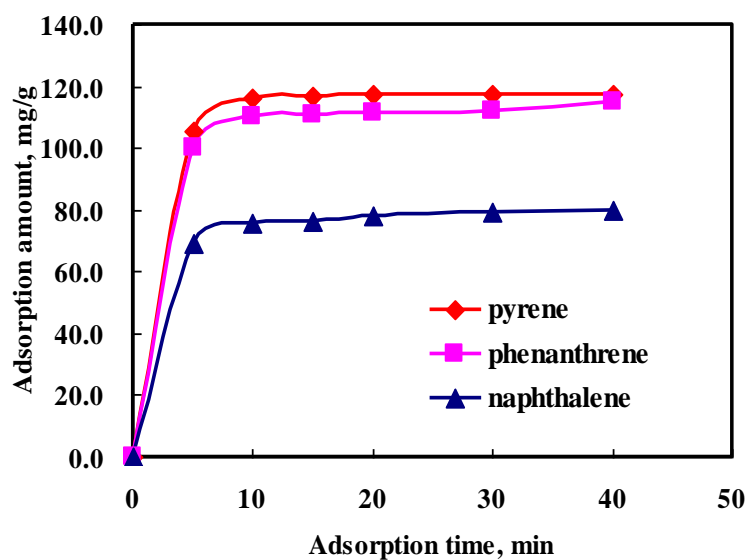

620




621 **Fig. 5** Adsorption amounts of naphthalene, phenanthrene and pyrene in ethanol aqueous solution on

622 CAC-4 (preparation conditions: activation time = 12 min; microwave power = 700 W; CAR= 1:3) at

623 various times and at 25 °C.

624

625 **Table 1** Selected properties of PAHs used [22]

PAHs	Structure	Formula	Molecular weight (g/mol)	Molecular dimension (nm×nm×nm)	Molar volume (cm ³ /mol)	Water solubility (ng/g)	logKow
Naphthalene		C ₁₀ H ₈	128.17	0.91×0.73×0.38	148	30800	3.30
Phenanthrene		C ₁₄ H ₁₀	178.22	1.17×0.80×0.34	199	1283	4.57
Pyrene		C ₁₆ H ₁₀	202.25	0.92	214	135	5.18

626

627

628

629

630

631

632

633 **Table 2** Activation conditions and surface characteristics of the prepared CACs.

Sample	Activation conditions			S _{BET}	A _m	A _e	V _m	V _t	V _m /V _t	Average pore width
	Microwave time min	Microwave power W	Coal activator ratio	m ² /g	M ² /g	M ² /g	cm ³ /g	cm ³ /g	%	nm
CAC-1	8	700	1:1	623.84	417.31	206.53	0.23	0.32	71.88	3.25
CAC-2	8	700	1:3	1651.50	543.09	1108.40	0.33	0.91	36.26	2.86
CAC-3	4	700	1:3	1007.27	379.35	627.92	0.22	0.54	40.74	2.86
CAC-4	12	700	1:3	1770.49	508.87	1261.62	0.61	0.99	61.62	2.82
CAC-5	12	100	1:3	0.21	0.00	0.00	0.00	0.00	0.00	0.00
CAC-6	12	700	1:3	934.54	425.64	534.22	0.37	0.49	75.51	1.95
CAC-7	12	700	1:3	843.56	384.34	423.55	0.31	0.42	73.81	1.88

634 S_{BET}: specific surface area obtained by BET equation, A_m, A_e: micropore area, external surface area,635 V_m, V_t: micropore volume, total pore volume.

636 Activator: The CAC-1, CAC-2, CAC-3, CAC-4, CAC-4 and CAC-5 with KOH; the CAC-6 with

637 ZnCl₂; the CAC-7 with H₃PO₄.

638

639

640

641

642

643

644 **Table 3** Adsorption performance and surface properties of CAC prepared with various CAR,
 645 activation time and microwave power.

Treatments		MB adsorption amount (mg/g)	Iodine adsorption amount (mg/g)	Lactonic group (mmol/g)	Carboxylic groups (mmol/g)	Phenolic groups (mmol/g)	pH _{PZC}
CAR	1:1	77.7	999.38	0.5667	0.0333	0.0812	8.10
	1:2	268.5	1034.24	0.4933	0.0167	0.0530	8.20
	1:3	291.0	1038.90	0.4700	0.0063	0.0233	8.30
	1:4	270.0	1034.23	0.3500	0.0056	0.0100	8.35
	1:5	256.5	1017.95	0.2333	0.0028	0.0067	8.30
Activation time (min)	4	234.0	962.12	0.5267	0.0900	0.0267	8.10
	8	282.0	1033.54	0.4700	0.0733	0.0190	8.30
	12	312.0	1048.19	0.3500	0.0700	0.0058	8.35
	16	238.5	1045.87	0.2267	0.0333	0.0047	8.32
	20	241.5	1045.87	0.1833	0.0083	0.0033	8.31
Microwave power (W)	100	54.0	769.02	0.5733	0.0933	0.0562	7.50
	300	180.0	1003.99	0.4567	0.0267	0.0333	7.60
	500	210.0	1031.91	0.4133	0.0133	0.0193	7.90
	700	312.0	1048.19	0.3500	0.0093	0.0097	8.35
	900	219.0	1043.54	0.3333	0.0045	0.0033	8.30

646

647

648

649

650

651

652

653

654

655

656 **Table 4** Comparison of different kinds of ACs.

Sample	Carbon source	Heating methods	S _{BET} (m ² /g)	V _{total} (cm ³ /g)	Data sources
Commercial AC	Pitch	Convention	1403.00	0.583	[19]
Commercial AC	Wood	Convention	1100.00	1.061	[19]
Lotus stalk based - AC	Lotus stalk	Convention	1220.00	1.191	[14]
Jatropha hull based - AC	Jatropha hull	Convention	748.00	0.580	[2]
CAC	Coal	Convention	830.5m ² /g	0.250	[3]
Rice husk based - AC	Rice husk	Microwave	752.00	0.640	[37]
Cotton stalk based - AC	Cotton stalk	Microwave	729.33.00	0.380	[38]
CAC	Coal	Microwave	1770.49	0.990	This work

657

658

659

660

661

662

663

664

665

666

667

668

669

670

671

672

673

674

675

676

677

678

679 **Table 5** Isotherm constants for the adsorption of naphthalene, phenanthrene, and pyrene in ethanol
 680 aqueous solution onto CAC-4 at 25 °C.

PAHs	Langmuir			Freundlich		
	K_L (L/mg)	q_m (mg/g)	R^2	K_F (L/mg)	n	R^2
Naphthalene	0.03	89.29	0.9934	5.50	1.71	0.9921
Phenanthrene	0.28	116.28	0.9990	24.62	1.60	0.9848
Pyrene	0.90	117.65	0.9991	52.16	1.61	0.9809

681
682
683
684
685
686
687
688
689
690
691

692 **Table 6** Kinetics constants for the adsorption of naphthalene, phenanthrene, and pyrene in ethanol
 693 aqueous solution onto CAC-4.

PAHs	q_{exp} (mg/g)	Pseudo-first-order kinetic			Pseudo-second-order kinetic			Intraparticle diffusion	
		model			model			model	
		k_1 (min ⁻¹)	Q_e (mg/g)	R^2	k_2 (g/mg min)	Q_e (mg/g)	R^2	k_p (mg/g/ min ^{1/2})	R^2
Naphthalene	78.18	0.61	80.65	0.9615	0.02	81.30	0.9999	1.84	0.9125
Phenanthrene	111.39	0.25	112.36	0.9970	0.04	112.36	1.0000	0.76	0.9124
Pyrene	117.17	0.13	117.65	0.9644	0.06	117.65	1.0000	0.61	0.9049

694
695