

AperTO - Archivio Istituzionale Open Access dell'Università di Torino

## Nanoporous FePd alloy as multifunctional ferromagnetic SERS-active substrate

**This is a pre print version of the following article:**

*Original Citation:*

*Availability:*

This version is available <http://hdl.handle.net/2318/1797887> since 2021-08-24T17:08:27Z

*Published version:*

DOI:10.1016/j.apsusc.2020.148759

*Terms of use:*

Open Access

Anyone can freely access the full text of works made available as "Open Access". Works made available under a Creative Commons license can be used according to the terms and conditions of said license. Use of all other works requires consent of the right holder (author or publisher) if not exempted from copyright protection by the applicable law.

(Article begins on next page)





## UNIVERSITÀ DEGLI STUDI DI TORINO

This Accepted Author Manuscript (AAM) is copyrighted and published by Elsevier. It is posted here by agreement between Elsevier and the University of Turin. Changes resulting from the publishing process - such as editing, corrections, structural formatting, and other quality control mechanisms - may not be reflected in this version of the text. The definitive version of the text was subsequently published in

**Matteo Cialone, Federica Celegato, Federico Scaglione, Gabriele Barrera, Deepti Raj, Marco Coisson, Paola Tiberto, Paola Rizzi**  
**“Nanoporous FePd alloy as multifunctional ferromagnetic SERS-active substrate” Applied Surface Science 543 (2021) 148759,**  
**<https://doi.org/10.1016/j.apsusc.2020.148759>**

You may download, copy and otherwise use the AAM for non-commercial purposes provided that your license is limited by the following restrictions:

- (1) You may use this AAM for non-commercial purposes only under the terms of the CC-BY-NC-ND license.
- (2) The integrity of the work and identification of the author, copyright owner, and publisher must be preserved in any copy.
- (3) You must attribute this AAM in the following format: Creative Commons BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/deed.en>),



# Nanoporous FePd alloy as multifunctional ferromagnetic SERS-active substrate

Matteo Cialone<sup>a,b</sup>, Federica Celegato<sup>b</sup>, Federico Scaglione<sup>a</sup>, Gabriele Barrera<sup>b</sup>,  
Deepti Raj<sup>a</sup>, Marco Coïsson<sup>b</sup>, Paola Tiberto<sup>b</sup>, Paola Rizzi<sup>a,\*</sup>

<sup>a</sup>*Department of Chemistry and NIS, University of Turin, Torino, Italy*

<sup>b</sup>*Division for metrology of Innovative Materials and Life Science, Italian National Institute of Metrological Research, Torino, Italy*

---

## Abstract

Nanoporous materials represent a unique class of materials, given to their unforeseen magnetic, mechanical, optical and catalytic properties arising from their network of pores and ligaments. *Here a polycrystalline thin film of FePd is considered as a starting system, in which the porosity is induced via dealloying. This process determines the removal of iron from the alloy and the diffusion of palladium on the surface, which in turn influences the evolution of the material's composition, magnetic properties and optical properties. In addition, from the magnetic point of view, the material acquires a more isotropic behaviour while the magnetic moment decreases due to the removal of iron. In the same way, there is an improvement of the surface enhanced Raman scattering as the dealloying proceeds, due to the formation of clusters of palladium on the surface. This mixture of optical and magnetic properties, combined with its high corrosion resistance and biocompatibility, gives the system a strong multifunctional connotation, paving the way for new applications, ranging from magnetic trapping to detection of low concentration of molecules.* In particular, palladium-rich nanoporous thin films have been produced by dealloying a polycrystalline Fe<sub>75</sub>Pd<sub>25</sub> (at. %) alloy in hydrochloric acid. The depletion of the iron and the surface diffusion of the palladium determines not only an evolution of the

---

\*Paola Rizzi

Email address: [paola.rizzi@unito.it](mailto:paola.rizzi@unito.it) (Paola Rizzi)



morphology and stoichiometry of the alloy but moreover a change in the optical and magnetic properties of the system. Concerning the magnetic properties, as the dealloying process proceeds, the system acquires a more isotropic behavior. In a like manner, the surface enhancement of the Raman scattering, that has been proven using bipyridine as a probe molecule, increases with the dealloying time. This enhancement, alongside with the high corrosion resistance and biocompatibility of the FePd alloys, makes them ideals for being employed as surface enhanced Raman spectroscopy substrates in bio-medical applications. Therefore, this mixture of optical and ferromagnetic properties gives these systems a strong multifunctional connotation, which can pave the way for new applications.

*Keywords:* Nanoporous alloys, nanoporous thin films, chemical dealloying, SERS effect

---

## 1. Introduction

Nanoporous materials have been attracting more and more attention lately because of their exceptional properties and a wide variety of potential applications. Surely, nanoporous (NPs) materials own their fame thanks to the high surface-to-volume ratio that distinguishes them from their continuous counterpart. This favourable surface-to-volume ratio makes them suitable for different applications such as fuel cells [1], capacitors [2], batteries [3], catalysis [4, 5], and more in general sensing [6, 7]. In this work, single-phase polycrystalline Fe<sub>75</sub>Pd<sub>25</sub> (at.%) alloy has been considered as starting material to produce nanoporous thin films via chemical dealloying. The initial stoichiometry, abundant in iron, guarantees to be far away from the parting limiting, making possible the dealloying process. Dealloying is based on the selective removal of the less noble atoms from the alloy and the surface diffusion of the remaining more noble atoms, which eventually led to an interconnected network of pores and ligaments [8]. Most of the work on dealloying has been done on a bi-component, single-phase, solid solution alloys, among which the most common are the Cu-Au [9], Au-



Ag [10, 11], Cu-Mn [12], and more, in general, the  $\text{Al}_x\text{M}_{100-x}$  alloys, where  $\text{M}=(\text{Au}, \text{Pd}, \text{Pt}, \text{Ag} \text{ and } \text{Cu})$  [13]. In this perspective several binary systems have been considered for the production of porous palladium, such as AlPd [13], PdCu [14, 15], NiPd [16], PdCo [17, 18], as well ternary systems such as the FeAlPd [19] and AlPdNi [20]. However, in all the cases listed above, the main aim was to produce a single element (e.g. palladium) porous material. In this work the approach is different, as the goal is to produce a two-component porous material which allows to widen the spectrum of possible applications. In fact, the novelty of the system presented in this work is precisely the possibility of obtaining a multifunctional system, a material that is ferromagnetic and at the same time has a surface-enhanced Raman scattering effect (SERS). Indeed, mainly precious metals such as gold and silver [21, 22] have been used in SERS-active substrates due to the presence of resonance of surface plasmons. As a result, the use of other materials for the synthesis of SERS-active substrates has been limited, even if also other metals, such as platinum and palladium, have been shown to be suitable for the synthesis of SERS-active substrates [23, 24]. In the case of porous metals, the presence of ligaments with dimensions in the nanometer scale, provides the necessary spatial confinement for the generation of surface plasmons, making nanoporous materials particularly suitable to be used as SERS-active substrates [25], which is one of the most promising methods for the detection of the small concentration of organic molecules and nanoparticles [26, 27].

In addition, their particular morphology has made porous materials popular in the field of magnetism, where it has been shown that their exceptional surface extension dramatically increases the magnetoelectric effect mediated by liquid electrolyte [28]. Moreover, these types of nanoporous magnetic materials can be used as magnetic traps [29] and separation of organic molecules [30] or even bio-catalysis [31]. Subsequently, the trapped molecules be detected by exploiting the detection ability due to it SERS effect. Last but not least, the composition of this alloy makes this material biocompatible [32] and the presence of a passivation layer of palladium renders this material particularly



resistant to oxidation and therefore suitable for use in harsh environments.

## 2. Experimental

50 The deposition of thin film of  $\text{Fe}_{75}\text{Pd}_{25}$  (at.%) was performed via dual source sputtering ( $P_{base} = 1.0 \cdot 10^{-7}$  mbar) in an argon atmosphere ( $P_{dep} = 1.0 \cdot 10^{-2}$  mbar). Two different targets of elemental iron (purity 99.99%) and elemental palladium (purity 99.98%) were used in a confocal configuration, with the iron target driven at radio frequency and the palladium target driven with a continuous current. The thickness of the as prepared films, measured via atomic force microscopy (AFM), is of  $(100 \pm 2)$  nm. The FePd films were deposited on a gold-coated silicon oxide substrate and subsequently chemically dealloyed in a 2 molar aqueous solution of hydrochloric acid, without applying any external potential. In this regime, since the pH of the electrolyte is almost zero, accord-  
60 ing to the Pourbaix diagrams at room temperature [33], the iron gets corroded, while being in the immunity region for the palladium, avoiding the formation of palladium hydrides. All the dealloying experiments were carried out at room temperature and without stirring the solution. Samples were dealloyed for selected times, ranging from 15 up to 120 minutes. To interrupt the action of  
65 the etching solution, the samples were rinsed repeatedly with de-ionised water. The evolution of the morphology and of the stoichiometry was studied via scanning electron microscopy (SEM) equipped with a energy dispersive x-ray spectrometer (EDS) and with atomic force microscopy (AFM). Analysis of the SEM images was performed using the ImageJ software [34]. The crystal  
70 structure of the films, for selected dealloying times, has been investigated via grazing incidence x-ray diffraction (GIXRD) using the  $\text{Cu-K}_\alpha$  radiation. The magnetic properties were investigated at room temperature using a vibrating sample magnetometer (VSM) capable to provide a maximum field of 20 kOe and equipped with a rotating head, used to investigate the magnetic anisotropy  
75 of the samples. The dealloyed samples were studied as well as a substrate for Surface Enhanced Raman Scattering (SERS). SERS measurements were per-



formed with a Renishaw inVia Raman Microscope, equipped with a 514 nm wavelength laser line. The optimised experimental conditions were defined as an acquisition time of 40 s, 100% power at the surface and a 20x magnification  
80 objective. Before experiment, samples were deeply cleaned in de-ionised water to remove traces of acids from pores and then dried at air. As a probe molecule, 4-4 bipyridine (bipy) in ethanol solution with concentrations ranging from  $10^{-6}$  to  $10^{-14}$  M. The samples were incubated for one hour into the solution with the desired concentration of bipy, then dried at air, and subsequently measured.  
85 All the solutions were prepared from reagents grade chemicals and de-ionised water.

### 3. Results and discussion

#### 3.1. Morphology and crystal structure

The evolution of the morphology of samples dealloyed for different times can  
90 be observed from scanning electron microscope and atomic force microscope images (Fig. 1 (a)-(e)). Looking at Fig. 1 (a), small cracks on the surface of the as-prepared film can be recognised, most probably generated by the residual stresses determined during the deposition of the film [35]. However, the surface is smooth, with a roughness of  $(1.4 \pm 0.2)$  nm (calculated according to [36, 37]).  
95 Moreover, on the surface of the as-prepared film, beside cracks, it is evident the presence of bumps that can be related to the presence of columnar crystalline grains, usually formed during sputtering deposition [35]. This interpretation can be confirmed from AFM image (see Fig. 1 (d)) where individual grains can be associated to the bumps on the surface of the sample. From GIXRD of the  
100 as-prepared sample (Fig. 2) it can be seen that the (110) reflection of the  $\alpha$ -(Fe,Pd) has an anomalous shape due to the presence of a non homogeneous Pd content in the  $\alpha$ -(Fe,Pd) supersaturated solid solution that enable the formation of a convolution of diffraction peaks at slightly different angles, each one related to a solid solution with a slightly different composition, i.e. slightly different  
105 lattice parameters. Therefore, an asymmetric reflection characterised by high



full width at half maximum (FWHM) and a broad and rounded tip is obtained. From this evidence, areas characterised by different reduction voltages can be inferred due to the not uniform distribution of Fe and Pd in the crystalline grains of the  $\alpha$ -(Fe,Pd) supersaturated solid solution. Areas with higher Pd content can
   
 be expected to be more noble with respect to regions with a reduced amount
   
 of Pd. Therefore, electrolyte is expected to act preferably on the less noble
   
 areas, starting the dealloying process where Fe content is higher. Moreover, at
   
 the beginning of the process, the electrolyte can penetrate into cracks present
   
 on the surface, therefore, Fe atoms will be firstly removed from the side of the
   
 cracks. From Fig. S1 (a) and (b), showing the surface of the film dealloyed for 15
   
 minutes, the cracks appears slightly enlarged and the bumps, previously related
   
 to columnar crystalline grains, have voids surrounding them, hence, it can be
   
 observed that at the beginning, the dealloying process, is acting in cracks and at
   
 the grain boundaries. As can be seen from Fig. 2, the (110) reflection of the  $\alpha$ -
   
 (Fe,Pd) belonging to the film after 15 minutes of dealloying has a different profile
   
 with respect to the as-prepared film, that is, the peak becomes symmetric, the
   
 tip is sharp and the FWHM is reduced. This can be related to the dealloying of
   
 the less noble areas in the sample, with the dissolution of Fe and the consequent
   
 surface diffusion of Pd adatoms. As voids are created where grains boundaries
   
 are present, it can be inferred that grain boundaries are less noble then the core
   
 of the grains, i.e. they have an higher Fe content. Therefore, one can assume
   
 that during sputtering, an increase in Fe content is produced from the core
   
 of the columnar crystals to the grain boundaries with a composition gradient.
   
 Therefore, when dealloying starts, Fe is removed preferentially from the side of
   
 the grains while the core, characterised by an uniform more noble composition,
   
 remains unaltered due to its higher electrochemical stability. This hypothesis
   
 is validated by the large decrease in Fe content after 15 minutes of dealloying
   
 down to 62% at.% as shown in Fig. 4. Furthermore, the roughness of the
   
 surface of the sample increases, reaching a value of  $(1.6 \pm 0.2)$  nm, due to the
   
 dealloying acting preferentially on the grain boundaries. After 30 minutes of
   
 dealloying (see Fig. S2 (a) and (b),  $t = 30$  minutes), the process is proceeding



by increasing the deepness of the voids around the grains as it can be observed from the AFM image in which the grain morphology is similar to the one of the film dealloyed for 15 minutes (see Fig. S1), while the roughness is increased up ( $3.0 \pm 0.3$ ) nm as reported in Fig. 3. After 60 minutes, the iron content decreases further, reaching an atomic content of 60 % and the grain boundaries of the crystalline grains are well evident. At this stage, the dealloying is not only proceeding between cracks and in the grain boundaries, but begins to act also on the surface of the grains and ligaments start to be formed. This can be evidenced both from SEM and AFM images, and from a further increase in roughness up to ( $3.4 \pm 0.3$ ) nm. According to the model proposed by Erlebacher *et al.*[38], at this stage, palladium adatoms are diffusing on the surface, forming clusters that start to coalesce, giving rise to hill-shaped features on the surface. Simultaneously, the dissolution of the iron is proceeding, removing more atoms from the surface of the film.

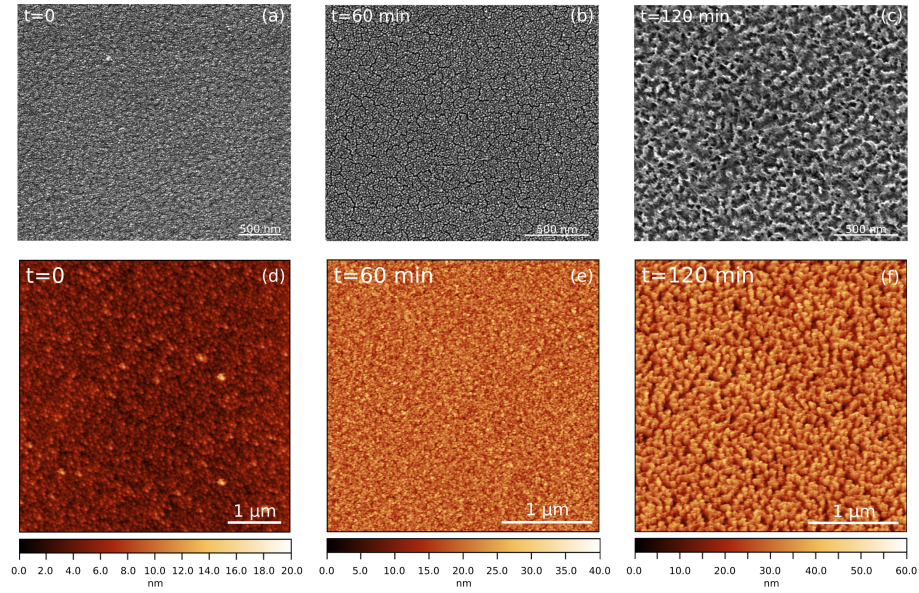


Figure 1: SEM images of the surface of the film: (a) as prepared, (b) dealloyed for 60 minutes, (c) dealloyed for 120 minutes. AFM images of the surface of the film: (d) as prepared, (e) dealloyed for 60 minutes, (f) dealloyed for 120 minutes.



Increasing the dealloying time up to 90 (see Fig. S3 (a) and (b),  $t=90$  minutes) and 120 minutes (see Fig. 1 (c) and (f)), a strong evolution of the surface morphology can be observed. This is due to the evolution of the dealloying process with the formation of an array of pores and ligaments which dimensions, well evident from SEM images (Fig. S3 (a) and (b),  $t=90$  minutes), are increasing with the dealloying time (from 90 up to 120 minutes). At this stage (film dealloyed for 120 min), the surface roughness reaches its maximum, with a value of  $(6.6 \pm 0.4)$  nm. However, in this phase, there is only a slight decrease in the average composition, with a decrease in Fe content that reaches a value of about 52%. As can be seen from the diffraction patterns of Fig. 2, for the film dealloyed for 120 minutes, besides the  $\alpha$ -(Fe,Pd) solid solution, an additional face-centred cubic (FCC) phase is recognisable, belonging to a palladium rich phase. Comparing the angular position of the (200) reflection of a pure palladium phase ( $2\theta=46.956^\circ$ ) with the angular position of (200) reflection measured for the dealloyed film ( $2\theta=47.204^\circ$ ), it can be seen that it has a smaller lattice parameter, accounting for the presence of some Fe dissolved by the Pd phase, which form a solid solution  $\gamma$ -(Fe,Pd). Moreover, the peak belonging to the  $\gamma$ -(Fe,Pd) phase presents a high FWHM which indicates for the formation of nanocrystalline grains. According to the observed trend of the alloy stoichiometry, reported in Fig. 4, it can be seen that after 90 minutes of dealloying the composition remains almost unaltered. Therefore, it can be inferred the formation of a Pd rich passivation layer on the surface of the material, that preserve the FePd solid solution still presents underneath from a further dealloying. The formation of the passivating layer could be related to the coalescence of the Pd clusters formed on the surface during the dealloying process. The formation of a passivation layer on the surface of a nanoporous sample was previously observed in literature for a Cu-Rh system in which an oxide passive layer was detected [39]. Liu *et al.* observed that the oxide passive layer was mainly constituted by the noble Rh element and stated that similar behaviour can be detected in alloys containing passive noble metals (such as Pt and Pd). On this basis, the formation of a Pd rich passivation layer is confirmed in Fe-Pd system. In



the Fe-Pd system, a change in structure is observed from BCC  $\alpha$ -(Fe,Pd) solid solution to FCC Pd rich phase. That is related to a process of nucleation and growth of a new phase [40] that is not observed when the starting alloy and the resulting nanoporous metal have the same crystal structure and similar lattice constants (i.e for example in well-known Au-Ag or Au-Cu systems [10]). In the latter case, ligament formation can be explained by the surface diffusion of the more noble element on a rigid lattice that is followed by the adatoms in their diffusion, so that the original crystalline orientation of the grains is retained in the final ligament network. Still, the dealloying mechanism is much less understood for systems where a change of both crystalline structure and lattice constant is observed during dealloying. When a change in structure is acting, the more noble adatoms (Pd in this case) can nucleate clusters randomly oriented on the surface that can grow up to the impingement forming very fine nanocrystals. For Pd the surface mass transfer diffusion coefficient in vacuum is  $1.1 \cdot 10^{-20} \text{ cm}^2 \cdot \text{s}^{-1}$  and much higher is expected at the alloy/electrolyte interfaces with an increase of four orders of magnitude [13]. Therefore, a high rate of diffusion is acting during dealloying, which enables the formation of a Pd passivation layer on the ligaments surface. According to the observed trend of the alloy stoichiometry (see Fig. 4), it can be seen that the composition remains almost unaltered after 90 minutes of dealloying. Therefore, it can be expected that the passivation layer is already formed at that stage and it was growing in time. However, in the GIXRD patterns of Fig. 2, the presence of the palladium layer is recognisable only in the film dealloyed for 120 minutes. Most probably the thickness of the Pd passivation layer in the film dealloyed for 90 minutes was too thin to be detected by GIXRD.

After the film is dealloyed for 120 minutes (see Fig. 1 (c) and (f),  $t=120$  minutes), on the surface is recognizable a network of thin ligaments which dimension are in the range  $(20 \pm 5) \text{ nm}$ . Accordingly, the surface roughness increases reaching a value of  $(6.6 \pm 0.4) \text{ nm}$ , however, this value represents an underestimation because the radius of the AFM tip (which nominal value provided by the manufacturer is of 35 nm [41]) exceeds the dimension of the



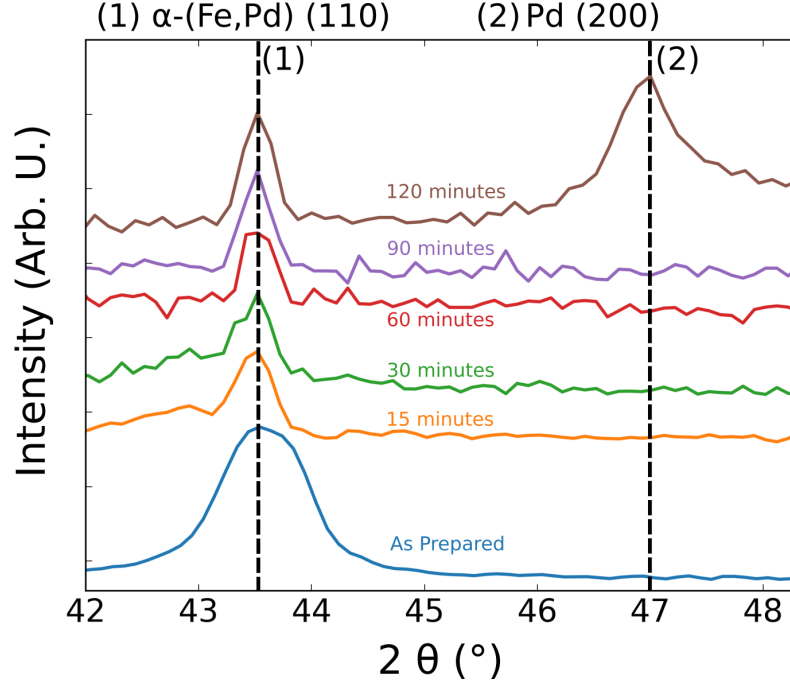


Figure 2: GIXRD pattern for the dealloyed films at selected times for the angular range between 40 and 47 degree.

ligaments, hence the images are dominated by the convolution of ligaments profile and tip shape. After 120 minutes the content of iron in the alloy reaches  
 215 its minimum, with the final stoichiometry being of  $\text{Fe}_{52}\text{Pd}_{48}$  (at. %). Nevertheless, this value represents an average between the Pd-rich passivation layer and the underlying part of the film, which will contain a lower amount of iron as compared to the one reported.

### 3.2. Magnetic characterisation

220 The evolution of the magnetic properties of the dealloyed films has been investigated via vibrating sample magnetometer, recording hysteresis loop at room temperature both for the in-plane and for the out-of-plane direction, as shown in Fig. 5 panels (a)-(d). The hysteresis loop for the as-prepared sample, for the in-plane direction, shows a typical soft magnetic behaviour, with a single



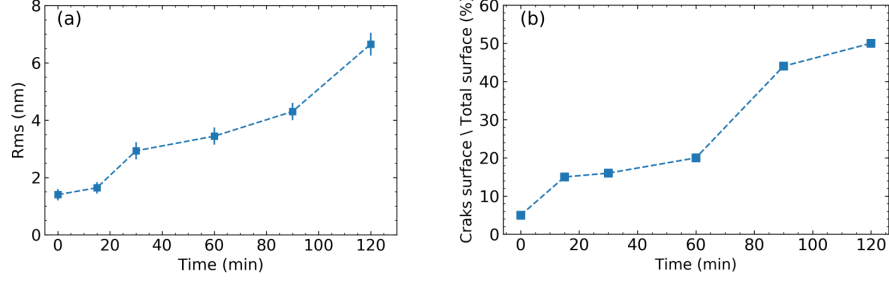


Figure 3: Evolution (a) of the surface roughness as a function of the dealloying time and (b) of the ratio between cracks and materials surfaces as a function of the dealloying time.

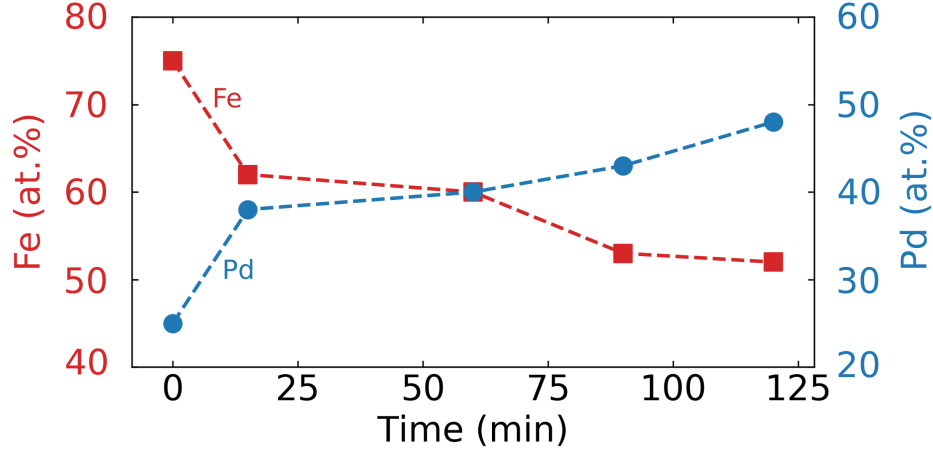


Figure 4: Evolution of the stoichiometry of the alloy as a function of the dealloying time

irreversible jump of the magnetisation, low coercive field ( $H_c \simeq 65$  Oe) and a high susceptibility at coercive field ( $\chi_c^{in} = 3.08 \cdot 10^{-5}$  emu·Oe<sup>-1</sup>, where the apex *in* indicates the in-plane direction). Conversely, along the out-of-plane direction, the reversal of the magnetisation occurs mainly through reversible mechanism, requiring a field as high as 12 kOe to reach saturation, as well the susceptibility at coercive field is almost two orders of magnitude lower of the one for the in-plane direction ( $\chi_C^{out} = 2.15 \cdot 10^{-7}$  emu·Oe<sup>-1</sup>, where the apex *out* indicates for the out of plane direction). Hence, for the as-prepared film, the easy axis



of magnetisation lies on the film plane, whereas the direction perpendicular to the film plane represents a hard axis for the magnetisation. The dealloying process causes an evolution of magnetic properties, such as magnetic moment, anisotropy and coercive field, as can be seen in Fig. 6 (a) and (b). From the data reported in the graph of Fig. 6 (a), it can be seen that the value of the magnetic moment of the films decreases as the dealloying time increases; after 60 minutes of dealloying, the magnetic moment of the films drops to almost 80 % of its initial value.

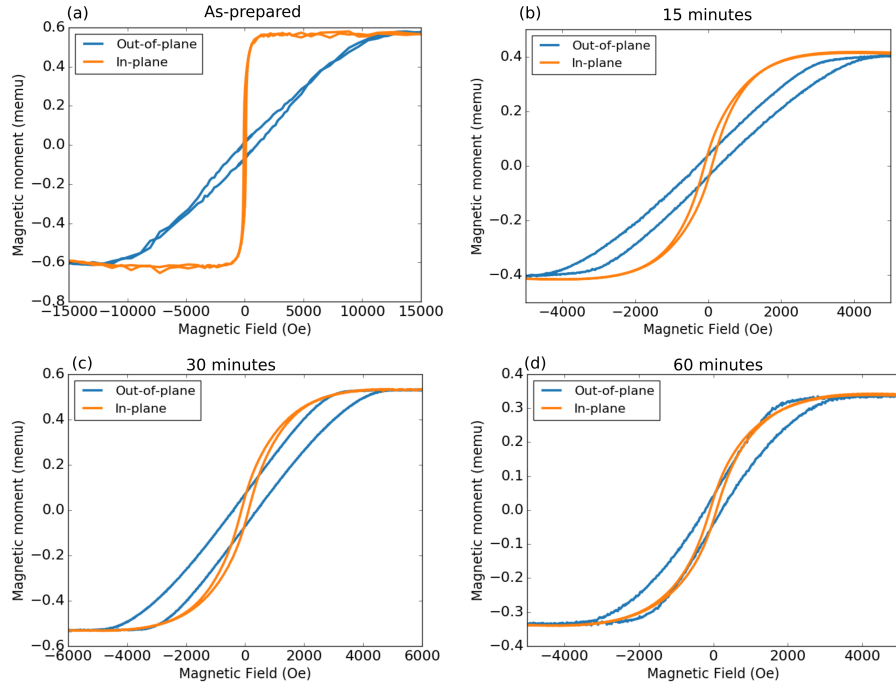


Figure 5: Comparison between the in-plane and out-of-plane hysteresis loops for the (a) as-prepared film, (b) film dealloyed for 15 minutes, (c) film dealloyed for 30 minutes, (d) film dealloyed for 60 minutes.

The main mechanism that determines such loss is intrinsic in the dealloying process, which selectively removes the less noble atoms from the alloys, that in this particular case are the iron atoms, which give the ferromagnetic behaviours to the alloy. However, only the depletion of the iron atoms (see Fig. 4) does not



245 justify for the 60 % loss of magnetic moment after only 15 minutes of dealloying.  
 Indeed, it has to be taken into account that part of the film gets lost during  
 the process. Considering the ratio between the area of the trenches and the  
 area of the film, it is possible to estimate the percentage of material loss during  
 the process, as shown in Fig. 3 (b). With this approach, the material losses  
 250 are underestimated, since it takes into account only the surface and not the  
 volume of the films. Looking at Fig. 6 (a) it can be noticed that the decrease  
 of magnetic moment at shorter times is more pronounced as compared to the  
 one at longer times. This behaviour can be described considering that the onset  
 of the dealloying process are the grains boundaries, which, as discussed before,  
 255 are rich in Fe. Hence, a great part of the Fe gets lost in the first moments of  
 the process. Another fact that is evident from the GIXRD pattern of Fig. 2,  
 is the formation of a palladium-rich phase, which eventually passivates the film  
 surface preventing further dealloying. The formation of the  $\gamma$ -(Fe,Pd) phase  
 determines a decrease of the magnetic moment carried by the Fe atoms [42].  
 260 The combination of the depletion of the iron atoms, the loss of material and the  
 formation of the  $\gamma$ -(Fe,Pd) phase, causes the reduction of the magnetic moment  
 of the film during the dealloying process. As well the value of the coercive field  
 is influenced by the dealloying process. From the graph reported in Fig. 6  
 (a), it can be seen that it reaches a maximum value of  $H_c \approx 120$  Oe for the  
 265 film dealloyed for 30 minutes, afterwards, its value decreases by increasing the  
 dealloying time. This trend is determined by the process of grain refinement that  
 took place as a consequence of the dealloying process [43]. Indeed, as pointed  
 out in the previous discussion, the preferential sites for the dealloying process  
 are the grain boundaries. Therefore, the grain dimension decreases during the  
 270 dealloying, determining, from the magnetic point of view, an hardening of the  
 material. However, this effect of magnetic hardening does not have a monotonic  
 trend, indeed, the coercive field drops when dealloying the films for more than  
 30 minutes. The transition from a continuous to a nanoporous system, strongly  
 influence the magnetic anisotropy of the system. Indeed, looking the loops along  
 275 the out-of-plane direction reported in Fig. 5 (a) - (d), it can be seen how the



sample, which in its as-prepared state is strongly anisotropic, acquire a more isotropic behaviour after dealloying. In Fig. 5, a more detailed comparison

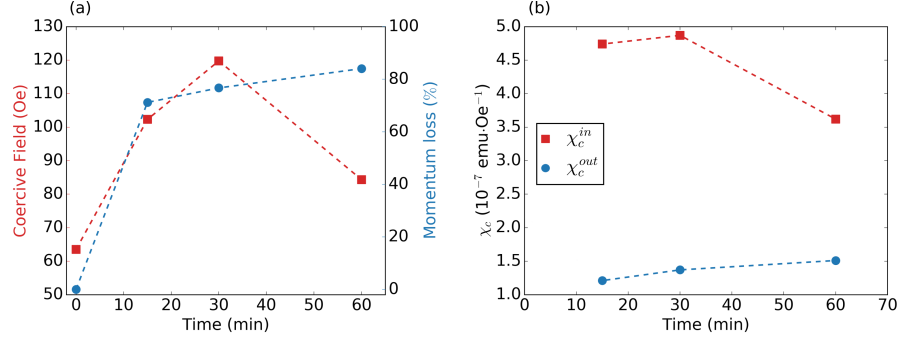


Figure 6: Evolution of: (a) the coercive field (in red) and percent loss of magnetic moment (in red) for the in-plane direction for dealloyed films, (b) the value of the susceptibility at coercive field for the in-plane (in red) and out-of-plane (in blue) for dealloyed films.

between the in-plane and out-of-plane hysteresis loop of the films dealloyed at different times is reported. In this regard, another parameter that has been investigated is the evolution of the susceptibility at coercive field which is shown both for the in-plane ( $\chi_c^{in}$ ) and for the out-of-plane ( $\chi_c^{out}$ ) direction, which is reported in Fig.6 (b). As can be seen, by the trend of the  $\chi_c^{out}$ , its value increases as increasing the dealloying time, meaning that the system is becoming more and more isotropic. Conversely, the value for the susceptibility at coercive field for the in-plane direction decreases with time. Nevertheless, the two values get closer to each other, underlying once more that the system is acquiring a more isotropic behaviour, since the two values, for a fully isotropic system coincide. The films dealloyed at 90 and 120 minutes were not taken into account because of the reduced intensity of the magnetic moment, which makes the signal of the probe and of the substrate prevails on the ferromagnetic signal of the films.

### 3.3. Surface enhanced Raman scattering

Meso- and nanoporous meta-materials have shown the potentiality to be used as SERS-active substrates [26]. In particular, to the best of our knowledge,



there are no studies analysing Pd-rich nanoporous materials as SERS-active sub-  
 295 strates, even if the palladium should present harmonic oscillation of conduction  
 electron on the surface, which will locally enhance the magnitude of the electric  
 field, with the consequence to enhance the Raman scattering of several orders of  
 magnitude. Here, we analysed the presence and evolution of SERS enhancement

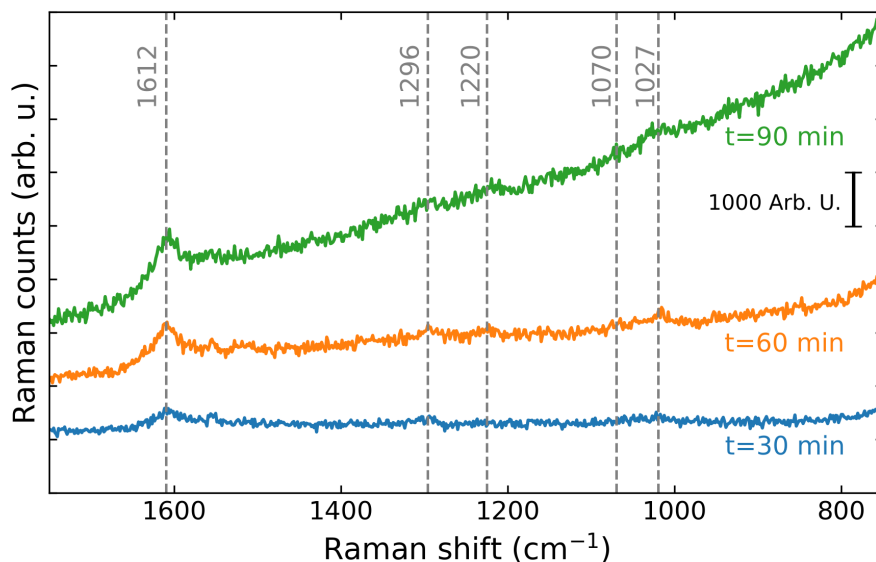


Figure 7: Comparison of the SERS response for sample dealloyed in 2M HCl for (a) 30 minutes, (b) 60 minutes and (c) 90 minutes, incubated for 1 hour in a  $10^{-6}$ M ethanol solution of bipyridine.

for the films dealloyed at different times. Indeed, as seen so far, the superficial  
 300 structure of the films evolves as a function of the dealloying time, going from a  
 smooth surface to a rough surface with the presence of ligaments and pores. As  
 probe molecule, we use a standard bipyridine in ethanol solution with different  
 concentration. Firstly, the effect of different dealloying time on the SERS effect  
 has been investigated for the detection of a fixed concentration of bipyridine of  
 305  $10^{-6}$  M and the acquired spectra are reported in Fig. 7. The only visible peak,  
 that may be ascribed to the bipyridine is the one at  $1613\text{ cm}^{-1}$ . Looking at the  
 spectrum of Fig.7 (b), for the sample dealloyed for 60 minutes, the intensity of



the peak at  $1613\text{ cm}^{-1}$  increases. Moreover, other peaks (as indicated in the graph) are appearing in the spectrum. The same consideration can be done  
 310 on the spectrum (c) of Fig. 7, relative to the sample dealloyed for 90 minutes. Increasing the dealloying time, a broad, monotonic feature appears as a baseline at lower energies. Interestingly, the morphology of the samples surface becomes coarser and coarser when dealloying proceeds (Figs. 1 (a) -1 (c)). At the be-  
 315 ginning, pores diameter is still below the wavelength of visible light, meaning that the last sees the sample as an effective homogeneous medium, whereas scattering can occur for heavy dealloyed samples, being the pores several tens nanometer wide. The increased Raleigh scattering from the excitation laser is then the origin for baseline here observed. The situation recalls that of nano- and meso-porous Si [44] as opposed to macro-porous Si [45].

320 Being the spectrum of the sample dealloyed for 60 minutes the most resolved, and the one which presents the higher intensity of the peak at  $1613\text{ cm}^{-1}$ , we proceed to analyse the effect of different concentration of the bipyridine molecule on the sample dealloyed for 60 minutes. The acquired spectra are shown in Fig. 8. Decreasing the bipyridine concentration of 6 order of magnitude, a noticeable  
 325 SERS enhancement is still visible. However, the spectrum becomes almost flat for a concentration of  $10^{-14}\text{ M}$ . Hence, these kind of substrates are suitable to detect bipyridine in concentrations as low as  $10^{-12}\text{ M}$ .

### 3.4. Conclusions

Pd-rich nanoporous thin films were fabricated via chemical dealloying from  
 330 single phase polycrystalline  $\text{Fe}_{75}\text{Pd}_{25}$  (at. %) continuous thin films produced via confocal sputtering. The master alloy in its as-prepared state is a polycrystalline supersaturated solid solution of  $\alpha\text{-(Fe,Pd)}$  with a body-centered cubic structure. The dealloying was carried out immersing the films in a 2 molar aqueous solution of HCl at room temperature for different times. The stoi-  
 335 chiometry of the alloy's decays exponentially in time, showing an asymptotic behavior for times longer than 90 minutes, where a stoichiometry of  $\text{Fe}_{52}\text{Pd}_{48}$  is reached. The removal of the less noble element generates adatoms of palladium



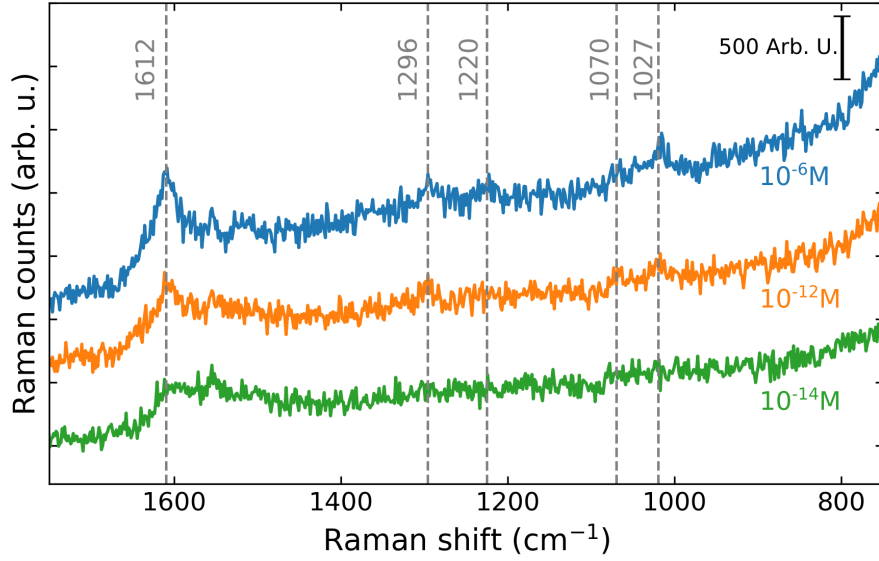


Figure 8: Comparison of the SERS response for sample dealloyed for 1 hour, incubated in different concentration of bipyridine.

on the film surface, which diffuses towards each-others to form clusters which eventually coalesce forming a passivation layer which hinders the dealloying process. The morphology of the films evolves as a function of the dealloying time. In its as-prepared state, the films show the presence of fractures on the surface, ascribable to the presence of residual stresses. Those trenches, which coincide as well with grain boundaries, represent a preferential on-set for the dealloying process. The evolution in time of the magnetic properties of the film has been investigated at room temperature for the in-plane and out-of-plane direction of the magnetic field. The film, in its as-prepared state is characterized by a soft magnetic behavior and a strong anisotropy, with the easy axes of magnetization lying on the film plane. During dealloying, iron atoms are removed from the alloy, hence the magnetic moment of the film decreases during the dealloying. Contemporary, the crystalline grains, undergo a refinement process that influences the coercive field which increases at short dealloying times and then



decreases again for longer dealloying times. Evolving from a continuous towards a nanostructured system, as well the magnetic anisotropy gets influenced by the dealloying process, which confers to the film a more isotropic behavior. Finally, films dealloyed at different times were investigated as surface-enhanced Raman spectroscopy substrates, using bipyridine as a probe molecule. The as-prepared film does not show any SERS effect, while dealloyed films show an enhancement in the Raman signal related to the bipyridine. The higher enhancement has been found for the sample dealloyed for 60 minutes. Most probably, in this case, the dimension of the palladium clusters formed on the surface determines the proper spatial confinement which generates surface plasmons which in turn determine the enhancement of the Raman signal.

## References

## References

- [1] L. H. Qian, A. Inoue, M. W. Chen, Large surface enhanced Raman scattering enhancements from fracture surfaces of nanoporous gold, *Applied Physics Letters* 92 (9) (2008) 1–4. doi:10.1063/1.2890164.
- [2] M. W. Verbrugge, P. Liu, Microstructural Analysis and Mathematical Modeling of Electric Double-Layer Supercapacitors, *Journal of The Electrochemical Society* 152 (5) (2005) D79. doi:10.1149/1.1878052.  
URL <http://jes.ecsdl.org/cgi/doi/10.1149/1.1878052>
- [3] J. Liu, X. W. Liu, Two-dimensional nanoarchitectures for lithium storage, *Advanced Materials* 24 (30) (2012) 4097–4111. doi:10.1002/adma.201104993.
- [4] F. Scaglione, Y. Xue, F. Celegato, P. Rizzi, L. Battezzati, Amorphous molybdenum sulphide @ nanoporous gold as catalyst for hydrogen evolution reaction in acidic environment, *Journal of Materials Science* 53 (17) (2018) 12388–12398. doi:10.1007/s10853-018-2490-2.  
URL <https://doi.org/10.1007/s10853-018-2490-2>



- 380 [5] E. M. Paschalidou, F. Scaglione, A. Gebert, S. Oswald, P. Rizzi, L. Battezzati, Partially and fully de-alloyed glassy ribbons based on Au: Application in methanol electro-oxidation studies, *Journal of Alloys and Compounds* 667 (2016) 302–309. doi:10.1016/J.JALLCOM.2016.01.181.  
URL <https://www.sciencedirect.com/science/article/pii/S0925838816301839>  
385
- [6] F. Scaglione, E. Alladio, A. Damin, F. Turci, C. Baggiani, C. Giovannoli, S. Bordiga, L. Battezzati, P. Rizzi, Functionalized nanoporous gold as a new biosensor platform for ultra-low quantitative detection of human serum albumin, *Sensors and Actuators B: Chemical* 288 (2019) 460–468.  
390 doi:10.1016/J.SNB.2019.03.005.  
URL <https://www.sciencedirect.com/science/article/pii/S0925400519303521>
- [7] Y. Xue, S. Wang, P. Shi, Y. Huang, F. Scaglione, P. Rizzi, L. Battezzati, P. Denis, H.-J. Fecht, Nanoporous gold chemically de-alloyed from Au-based amorphous thin film for electrochemical nonenzymatic H<sub>2</sub>O<sub>2</sub> sensing, *Chemical Physics Letters* 723 (2019) 22–27.  
395 doi:10.1016/J.CPLETT.2019.03.024.  
URL <https://www.sciencedirect.com/science/article/pii/S0009261419302027?via=ihub>
- 400 [8] J. Erlebacher, R. Seshadri, Hard Materials with Tunable Porosity, *MRS Bulletin* 34 (08) (2009) 561–568. doi:10.1557/mrs2009.155.  
URL [http://www.journals.cambridge.org/abstract/\\_/S0883769400003390](http://www.journals.cambridge.org/abstract/_/S0883769400003390)
- [9] R. Morrish, K. Dorame, A. Muscat, Formation of nanoporous Au by dealloying AuCu thin films in HNO<sub>3</sub>, *Scripta Materialia* 64 (9) (2011) 856–859. doi:10.1016/J.SCRIPTAMAT.2011.01.021.  
405 URL <https://www.sciencedirect.com/science/article/pii/S1359646211000224/#}b0035>



- [10] J. Erlebacher, M. J. Aziz, A. Karma, N. Dimitrov, K. Sieradzki, Evolution  
 410 of nanoporosity in dealloying, *Nature* 410 (6827) (2001) 450–453. [arXiv:0103615](#), [doi:10.1038/35068529](#).
- [11] X. Lu, E. Bischoff, R. Spolenak, T. Balk, Investigation of dealloying in  
 AuAg thin films by quantitative electron probe microanalysis, *Scripta Ma-*  
*terialia* 56 (7) (2007) 557–560. [doi:10.1016/J.SCRIPTAMAT.2006.12.022](#).  
 415 URL [https://www.sciencedirect.com/science/article/pii/](https://www.sciencedirect.com/science/article/pii/S1359646207000085)  
[S1359646207000085](https://www.sciencedirect.com/science/article/pii/S1359646207000085)
- [12] J. Hayes, A. Hodge, J. Biener, A. Hamza, K. Sieradzki, Monolithic  
 nanoporous copper by dealloying mncu, *Journal of Materials Research*  
 21 (10) (2006) 2611–2616. [doi:10.1557/jmr.2006.0322](#).
- 420 [13] Z. Zhang, Y. Wang, Z. Qi, W. Zhang, J. Qin, J. Frenzel, Generalized fab-  
 rication of nanoporous metals (Au, Pd, Pt, Ag, and Cu) through chemical  
 dealloying, *Journal of Physical Chemistry C* 113 (29) (2009) 12629–12636.  
[doi:10.1021/jp811445a](#).
- [14] S. Shan, J. Markmann, J. Weissmüller, Actuation by hydrogen electrosorp-  
 425 tion in hierarchical nanoporous palladium, *Philosophical Magazine* 97 (19)  
 (2017) 1571–1587. [arXiv:https://doi.org/10.1080/14786435.2017.1311428](#),  
[doi:10.1080/14786435.2017.1311428](#).  
 URL <https://doi.org/10.1080/14786435.2017.1311428>
- [15] S. Shan, J. Markmann, J. Weissmüller, Synthesis of uniform bulk  
 430 nanoporous palladium with tunable structure, *Electrochimica Acta* 285  
 (2018) 60 – 69. [doi:https://doi.org/10.1016/j.electacta.2018.07.081](#).  
 URL [http://www.sciencedirect.com/science/article/pii/](http://www.sciencedirect.com/science/article/pii/S0013468618315822)  
[S0013468618315822](http://www.sciencedirect.com/science/article/pii/S0013468618315822)
- 435 [16] L. Chen, H. Guo, T. Fujita, A. Hirata, W. Zhang, A. Inoue, M. Chen,  
 Nanoporous pdni bimetallic catalyst with enhanced electrocatalytic per-  
 formances for electro-oxidation and oxygen reduction reactions, *Advanced*



Functional Materials 21 (22) (2011) 4364–4370. doi:10.1002/adfm.201101227.

- 440 [17] M. Hakamada, M. Mabuchi, Fabrication of nanoporous palladium by dealloying and its thermal coarsening, Journal of Alloys and Compounds 479 (1) (2009) 326 – 329. doi:<https://doi.org/10.1016/j.jallcom.2008.12.078>.

URL <http://www.sciencedirect.com/science/article/pii/S0925838808022433>

- [18] M. Goessler, M. Albu, G. Klinser, E.-M. Steyskal, H. Krenn, R. Würschum, Magneto-ionic switching of superparamagnetism, Small 15 (46) (2019) 1904523. arXiv:<https://onlinelibrary.wiley.com/doi/pdf/10.1002/smll.201904523>, doi:10.1002/smll.201904523.

450 URL <https://onlinelibrary.wiley.com/doi/abs/10.1002/smll.201904523>

- [19] J. Wang, Z. Wang, D. Zhao, C. Xu, Facile fabrication of nanoporous pdfe alloy for nonenzymatic electrochemical sensing of hydrogen peroxide and glucose, Analytica Chimica Acta 832 (2014) 34 – 43. doi:<https://doi.org/10.1016/j.aca.2014.04.062>.

455 URL <http://www.sciencedirect.com/science/article/pii/S0003267014005388>

- [20] Z. Qi, H. Geng, X. Wang, C. Zhao, H. Ji, C. Zhang, J. Xu, Z. Zhang, Novel nanocrystalline pdni alloy catalyst for methanol and ethanol electro-oxidation in alkaline media, Journal of Power Sources 196 (14) (2011) 5823 – 5828. doi:<https://doi.org/10.1016/j.jpowsour.2011.02.083>.

460 URL <http://www.sciencedirect.com/science/article/pii/S0378775311005118>

- [21] J. F. Li, Y. F. Huang, Y. Ding, Z. L. Yang, S. B. Li, X. S. Zhou, F. R. Fan, W. Zhang, Z. Y. Zhou, D. Y. Wu, B. Ren, Z. L. Wang, Z. Q. Tian, Shell-isolated nanoparticle-enhanced Raman spectroscopy, Nature 464 (7287)

465



(2010) 392–395. doi:10.1038/nature08907.

URL <http://dx.doi.org/10.1038/nature08907>

470 [22] R. G. Freeman, K. C. Grabar, K. J. Allison, R. M. Bright, J. A. Davis,  
A. P. Guthrie, M. B. Hommer, M. A. Jackson, P. C. Smith, D. G. Wal-  
ter, M. J. Natan, Self-assembled metal colloid monolayers: An approach to  
sers substrates, *Science* 267 (5204) (1995) 1629–1632. arXiv:[https://](https://science.sciencemag.org/content/267/5204/1629.full.pdf)  
[science.sciencemag.org/content/267/5204/1629.full.pdf](https://science.sciencemag.org/content/267/5204/1629.full.pdf), doi:10.  
1126/science.267.5204.1629.

475 URL <https://science.sciencemag.org/content/267/5204/1629>

[23] Z.-Q. Tian, B. Ren, J.-F. Li, Z.-L. Yang, Expanding generality of surface-  
enhanced raman spectroscopy with borrowing sers activity strategy, *Chem.*  
*Commun.* (2007) 3514–3534doi:10.1039/B616986D.

URL <http://dx.doi.org/10.1039/B616986D>

480 [24] L.-M. Chen, Y.-N. Liu, Palladium crystals of various morphologies for  
sers enhancement, *CrystEngComm* 13 (2011) 6481–6487. doi:10.1039/  
C1CE05557G.

URL <http://dx.doi.org/10.1039/C1CE05557G>

485 [25] Y. Xue, F. Scaglione, E. M. Paschalidou, P. Rizzi, L. Battezzati, Excellent  
surface enhanced raman scattering obtained with nanoporous gold fabri-  
cated by chemical de-alloying, *Chemical Physics Letters* 665 (2016) 6 – 9.  
doi:<https://doi.org/10.1016/j.cplett.2016.10.046>.

URL [http://www.sciencedirect.com/science/article/pii/](http://www.sciencedirect.com/science/article/pii/S0009261416308247)  
S0009261416308247

490 [26] X. Zhang, Y. Zheng, X. Liu, L. Wei, J. Dai, D. Lei, D. MacFarlane, Hi-  
erarchical porous plasmonic metamaterials for reproducible ultrasensitive  
surface-enhanced raman spectroscopy, *Advanced Materials* 27 (6) (2015)  
1090–1096. doi:10.1002/adma.201404107.

495 [27] Y. Xue, F. Scaglione, P. Rizzi, L. Battezzati, High performance SERS  
on nanoporous gold substrates synthesized by chemical de-alloying a



Au-based metallic glass, *Applied Surface Science* 426 (2017) 1113–1120.  
doi:10.1016/J.APSUSC.2017.07.302.

URL <https://www.sciencedirect.com/science/article/pii/S0169433217323127>

- 500 [28] A. Quintana, J. Zhang, E. Isarain-Chávez, E. Menéndez, R. Cuadrado,  
R. Robles, M. D. Baró, M. Guerrero, S. Pané, B. J. Nelson, C. M. Müller,  
P. Ordejón, J. Nogués, E. Pellicer, J. Sort, Voltage-Induced Coercivity Re-  
duction in Nanoporous Alloy Films: A Boost toward Energy-Efficient Mag-  
netic Actuation, *Advanced Functional Materials* 27 (32) (2017) 1701904.  
505 doi:10.1002/adfm.201701904.

URL <http://doi.wiley.com/10.1002/adfm.201701904>

- [29] T. Sen, A. Sebastianelli, I. J. Bruce, Mesoporous silicamagnetite nanocom-  
posite: fabrication and applications in magnetic bioseparations, *Journal*  
of the American Chemical Society 128 (22) (2006) 7130–7131. doi:  
510 doi.org/10.1021/ja061393q.

URL <https://doi.org/10.1021/ja061393q>

- [30] E. Y. Misochko, A. V. Akimov, A. A. Masitov, D. V. Korchagin,  
I. K. Yakushchenko, S. V. Chapyshev, High-spin organic molecules with  
dominant spin-orbit contribution and unprecedentedly large magnetic  
515 anisotropy, *The Journal of Chemical Physics* 137 (6) (2012) 064308. doi:  
10.1063/1.4742342.

URL <https://doi.org/10.1063/1.4742342>

- [31] T. Sen, I. J. Bruce, T. Mercer, Fabrication of novel hierarchically ordered  
porous magnetic nanocomposites for bio-catalysis, *Chem. Commun.* 46  
520 (2010) 6807–6809. doi:10.1039/C0CC01747G.

URL <http://dx.doi.org/10.1039/C0CC01747G>

- [32] Y. Ma, M. Zink, S. G. Mayr, Biocompatibility of single crystalline fe70pd30  
ferromagnetic shape memory films, *Applied Physics Letters* 96 (21) (2010)  
213703. arXiv:<https://doi.org/10.1063/1.3435260>, doi:10.1063/1.



- 525 3435260.  
URL <https://doi.org/10.1063/1.3435260>
- [33] M. Pourbaix, Atlas d'Equilibres Electrochimiques, Gauthier-Villars, 1963.
- [34] C. A. Schneider, W. S. Rasband, K. W. Eliceiri, Nih image to imagej: 25  
years of image analysis, *Nature methods* 9 (2012) 671–675. doi:10.1038/  
530 nmeth.2089.  
URL <https://doi.org/10.1038/nmeth.2089>
- [35] J. A. Thornton, Influence of substrate temperature and deposition rate  
on structure of thick sputtered Cu coatings, *Journal of Vacuum Science  
and Technology* 12 (4) (1975) 830–835. arXiv:arXiv:1011.1669v3, doi:  
535 10.1116/1.568682.  
URL <http://avs.scitation.org/doi/10.1116/1.568682>
- [36] P. K. D. Necas, Gwyddion: an open-source software for SPM data analysis,  
*Central European Journal of Physics* 10 (6753) (2012) 118–188. doi:10.  
2478/s11534-011-0096-2.  
540 URL <http://www.nature.com/articles/44065>
- [37] P. Klapetek, Quantitative Data Processing in Scanning Probe Microscopy,  
William Andrew, 2012.
- [38] J. Erlebacher, M. J. Aziz, A. Karma, N. Dimitrov, K. Sieradzki, Evolution  
of nanoporosity in dealloying, *Nature* 410 (6827) (2001) 450–453. arXiv:  
545 0103615, doi:10.1038/35068529.
- [39] F. Liu, H.-J. Jin, Extrinsic Parting Limit for Dealloying of Cu-Rh, *Journal  
of The Electrochemical Society* 165 (16) (2018) C999–C1006. doi:10.  
1149/2.0631816jes.
- [40] E. Paschalidou, F. Celegato, F. Scaglione, P. Rizzi, L. Battezzati,  
550 A. Gebert, S. Oswald, U. Wolff, L. Mihaylov, T. Spassov, The mechanism  
of generating nanoporous Au by de-alloying amorphous alloys, *Acta*



Materialia 119 (2016) 177–183. doi:10.1016/J.ACTAMAT.2016.08.025.  
URL <https://www.sciencedirect.com/science/article/pii/S1359645416306036>

- 555 [41] Bruker, Afm probes mesp-hr10 (July 2019).  
URL <https://www.brukerafmprobes.com/p-3413-mesp-hr10.aspx>
- [42] K. Adachi, D. Bonnenberg, J. J. M. Franse, R. Gersdorf, K. A. Hempel, K. Kanematsu, S. Misawa, M. Shiga, M. B. Stearns, H. P. J. Wijn, Numerical Data and Functional Relationships in Science and Technology, Springer, 1986.  
560
- [43] E. Arzt, Size effects in materials due to microstructural and dimensional constraints: a comparative review, Acta Materialia 46 (16) (1998) 5611–5626. doi:10.1016/S1359-6454(98)00231-6.  
URL <https://www.sciencedirect.com/science/article/pii/S1359645498002316>  
565
- [44] G. G. Amato, G. Benedetto, L. Boarino, G. Léron del, M. Rossi, R. Spagnolo, Semiconductors and Electronic Materials, SPIE, Bellingham, 2000, Ch. Photothermal and photoacoustic characterization of porous silicon structures.
- 570 [45] G. Amato, Optical and morphological properties of light-emitting porous silicon prepared by chemical dissolution of silicon wafers, Japanese Journal of Applied Physics 34 (Part 1, No. 4A) (1995) 1716–1722. doi:10.1143/jjap.34.1716.  
URL <https://doi.org/10.1143%2Fjjap.34.1716>