

The Role of Metallic and Acid Sites of Ru-Nb-Si Catalysts in the Transformation of Levulinic Acid to γ -Valerolactone

Serena Esposito¹, Brigida Silvestri², Carmelina Rossano³, Valeria Vermile^{3,4}, Claudio Imparato², Maela Manzoli⁵, Barbara Bonelli¹, Vincenzo Russo³, Eric M. Gaigneaux⁴, Antonio Aronne^{2,*}, Martino Di Serio^{3,*}

* Corresponding authors email: antonio.aronne@unina.it; diserio@unina.it

¹Department of Applied Science and Technology and INSTM Unit, Politecnico di Torino, Corso Duca degli Abruzzi 24, IT-10129 Turin, Italy

²Department of Chemical, Materials and Production Engineering, University of Naples Federico II, Piazzale Tecchio 80, IT-80125 Naples, Italy

³Department of Chemical Sciences, University of Naples Federico II, Via Cinthia, IT-80126 Naples, Italy

⁴Université Catholique de Louvain, Institute of Condensed Matter and Nanosciences (IMCN), Place Louis Pasteur 1. L04.01.09, BE-1348 Louvain-la-Neuve, Belgium.

⁵Department of Drug Science and Technology and NIS- Interdepartmental Centre, University of Turin, Via Pietro Giuria 9, 10125 Turin, Italy

Abstract:

The transformation of γ -valerolactone (GVL) into levulinic acid (LA) requires the use of bifunctional catalysts allowing the hydrogenation and lactonization steps to occur. The aim of this study is to clarify the role played by both redox (Ru) and acid (Nb) sites of the ruthenium-niobium-silicon mixed oxides catalysts, synthesized by sol-gel route, when this reaction is performed in mild conditions. The catalytic performances of the materials are related to an in-depth morphologic and structural characterization, demonstrating that the interaction between the two metals and their relative amount and dispersion are crucial in determining their activity. The results confirm the hydrogenation-dehydration consecutive reaction network and evidence the possibility to selectively produce either GVL or the intermediate γ -hydroxypentanoic acid by an accurate choice of the catalyst composition.

Keywords: γ -valerolactone; sol-gel synthesis, bifunctional catalyst, kinetics, morphological characterization

1. Introduction

The enormous potential of the biomass conversion into value added products is a key point to ease the pressure on the global crisis about fossil resources and to reduce the environmental pollution.

Biomass, through the photosynthesis process, absorbs water, sunlight and the available atmospheric CO₂, which is then released during the combustion process realizing what is called “closed carbon cycle”, with net zero emissions that do not contribute to the global warming [1,2]. Furthermore, biomass and biomass derived compounds are relatively cheap, and they are ethically accepted by the society because their production does not compete with food crop production. The research community based on this motivation is looking for the development of new and economically viable routes to sustainable chemical products.

In this context, many studies have highlighted the lignocellulosic biomass as feedstock to obtain levulinic acid (LA), that was identified by the United States Department of Energy as key target molecule for the production of renewable fuels, fuel additives, green solvents, polymers, value-added fine chemicals, flavoring agents and resins [3–6].

Thus, LA offers one of the largest families of derivatives of potential industrial interest because it possesses both keto and carboxylic acid groups and with this special molecular structure a series of chemical reactions such as esterification, hydrogenation, halogenation, and oxidation can occur. To highlight the value of LA, the most promising reaction is the hydrogenation to γ -valerolactone (GVL), a platform molecule that has gained considerable attention in the last decade.

GVL is a heterocyclic five carbon ester (C₅H₈O₂) with one methyl group in γ -position, has a sweet, herbaceous odor that makes it perfect for application in perfumes and food additives [7,8]. For its attractive physicochemical properties, GVL can be used as a solvent for various processes, for the synthesis of biomass derived chemicals; a precursor for even higher value-added chemicals (like 1,4-pentanediol, 2-methyltetrahydrofuran) and in the fuel sector [9–11].

Although GVL also possesses a stereogenic carbon center, the major applications in the fuel sector or as solvent does not require a specific enantiomeric form and GVL is usually synthesized and used in the racemic form.

According to the literature, the production of GVL from LA hydrogenation over a catalyst is the most efficient and economic method reported to date [12]. Both homogeneous and heterogeneous catalysts have been studied over the past decades for this reaction. Typically, precious metals such as iridium (Ir) [13], palladium (Pd) [14], platinum (Pt) [15] and ruthenium (Ru) [16,17] are the most often used catalysts. In particular, Ru-based catalysts are by now classified as benchmark catalysts for this reaction, since high GVL yield can be reached (> 97%) under relatively mild condition [18].

The most accredited reaction pathway at low temperature is the hydrogenation of LA to γ -hydroxypentanoic acid (HPA) followed by the intramolecular lactonization to GVL [19,20].

A recent mechanistic study performed by isotopic labeling experiments has confirmed the above hypotheses establishing that the hydrogenation goes mainly via HPA and subsequent lactonization when the reaction occurs in mild conditions using Ru/C as catalyst [21].

It has been hypothesized that the two reactions are catalyzed by two different sites: the metallic sites for hydrogenation reaction and the acid sites for the lactonization reaction. Although Ru/C is the commonly used catalyst for such reaction, being characterized by the presence of both metallic and acid sites, [22] it suffers from slow but irreversible deactivation, probably due to the sintering of the ruthenium particles and the formation of carbonaceous deposits on the catalyst surface.

Lately we have synthesized a bifunctional catalyst, obtained by a proper reduction of a gel-derived $(\text{RuO}_2)_{0.038}(\text{Nb}_2\text{O}_5)_{0.024}(\text{SiO}_2)_{0.938}$ nanomaterial, showing a much higher stability than Ru/C catalysts for this reaction and characterized by a high and uniform dispersion of Ru nanoparticles in the acid matrix [20]. In particular, the mentioned catalyst showed an activity of 370 times higher than Ru/C, considered nowadays a benchmark catalyst for γ -valerolactone synthesis activity [20].

In a recent review Yu et al. [23] examined the effects of the acid characteristic of the support in which the metallic phase is dispersed on the performance of bifunctional catalysts for the heterogeneous transformation LA to GVL. They conclude that the acidity of the support plays a key role in this transformation affecting both the metal dispersion and the stability of the catalyst in mild reaction conditions [23].

In this paper the effect of the chemical composition of different Ru-Nb-Si gel-derived nanostructured materials on the catalytic performance in the LA hydrogenation reaction was explored with special attention to the acid surface characteristics of the matrix in which the Ru nanoparticles are dispersed. Keeping the RuO_2 amount at 3.8 mol% the Nb_2O_5 content was changed from 0 to 6.9 mol% in the RuO_2 - Nb_2O_5 - SiO_2 (Ru-Nb-Si) mixed-oxide system with the aim to clarify the role played by the two components (the metallic phase and the acid matrix) in determining the reaction pathway and then the GVL yields. In this context, the possibility to study the interaction between Ru and Nb is of pivotal importance. Therefore, Field Emission Scanning Electron Microscopy (FESEM) combined with Energy Dispersive Spectroscopy (EDS) mapping were employed to get information at nanometric level on the location of the Ru and Nb metals within the silica matrix, depending on the composition of the catalysts. This advanced tridimensional characterization allowed therefore to monitor the morphology and to make correlations with the composition close to the surface of the materials upon activation. It should be noted that modulating the composition of the support and then its acid characteristics, either HPA or GVL were isolated as the only product of the reaction.

2. Materials and methods

2.1 Sol-gel synthesis

The following reagents by Sigma–Aldrich were used: tetraethoxysilane (TEOS, Si(OC₂H₅)₄ 99%), niobium(V) chloride, (NbCl₅ 99%), ruthenium(III) chloride-3-hydrate (RuCl₃·3H₂O 99.98%), anhydrous ethanol (EtOH). Mixed-oxide materials, whose nominal molar composition is reported in Table 1, were prepared by a one-pot sol-gel route with slight modification of our previous procedure [20].

More in detail, an alcoholic solution of NbCl₅ with a molar ratio NbCl₅/EtOH = 1:6 was prepared in a dry box at room temperature. The solution was stirred for 60 minutes to allow the formation of partially substituted Nb(OEt)_{5-x}(Cl)_x species and the removal of produced HCl. To an alcoholic solution of TEOS (with molar ratio TEOS/EtOH = 1:4) a proper amount of RuCl₃·3H₂O was added and the latter solution was mixed with the former. The resulting clear reddish mixture was hydrolysed at room temperature by using deionized water (with final molar ratio TEOS/H₂O = 1:4). Transparent dark-red gels were obtained within few days, depending on the Nb content; the gelled systems were kept aging for 3 days and then fully dried in air at 110 °C in an electric oven. The amorphous dried gels (xerogels) were annealed for 2 h at 500 °C in air (Table 1).

Table 1. Composition and textural properties of studied samples.

Sample	Molar Composition	N ₂	NH ₃ -TPD ^a	Nb/Ru ^c	D _{Ru} ^g	
		physisorption ^a	Acid sites ^d	Ox ^a	Red ^f	
		S _{BET} ^b	(mmol/g)			
		(m ² g ⁻¹)				
4Ru0Nb	RuO _{2(0.038)} ·SiO _{2(0.962)}	523*	>0.01	-	-	12
4Ru2.5Nb	RuO _{2(0.038)} ·Nb ₂ O _{5(0.024)} ·SiO _{2(0.938)}	398	0.08	0.6	1.6	5
4Ru5Nb	RuO _{2(0.038)} ·Nb ₂ O _{5(0.047)} ·SiO _{2(0.915)}	472	2.39	1.1	3.6	5
4Ru7.5Nb	RuO _{2(0.038)} ·Nb ₂ O _{5(0.069)} ·SiO _{2(0.893)}	412	2.00	1.9	11.0	4

^a annealed sample at 500°C for 2 h

^b specific surface area calculated by BET method.

^d amount of NH₃ chemisorbed per gram of sample.

^c Nb/Ru mass ratio of Nb and Ru average amounts from EDS maps of different regions of the sample.

^f reduced sample in H₂ (1 bar, 0.1 ml/min) at 300°C for 3 h.

^g ruthenium dispersion obtained by CO chemisorption.

*[38]

The catalysts used in the reaction were obtained from these materials by a reduction treatment under a 0.1 L min⁻¹ H₂ flow, 1 bar, 300 °C for 3 h and finally cooled at room temperature (r.t.) under H₂ flow.

2.2 Structural, morphological, and surface acidity characterization

X-ray diffraction patterns were recorded with a Bruker D8 X-ray diffractometer, operating in the reflection mode with Cu-K α radiation ($\lambda = 1.5418 \text{ \AA}$, 40 kV, 30 mA). The data were collected in the 5 - 80° range ($2\theta_B$) with steps of 0.015°, time per step of 0.15 s.

FTIR (Fourier Transform Infrared) spectra were collected in the ATR (Attenuated Total Reflection) mode using a Bruker Equinox 55 spectrometer equipped with a Platinum ATR cell, in which diamond (refractive index = 2.41) is used as ATR crystal. The spectra were recorded with 100 scans between 4000 and 500 cm⁻¹ with a resolution of 4 cm⁻¹.

DR UV-vis (Diffuse Reflectance UV-Visible) spectra were recorded in the range of 200 – 800 nm on a Shimadzu UV-3600 Plus spectrophotometer. A Spectralon® Diffuse Reflectance Standard was used to measure the background spectra. The measured intensity was expressed as the value of the Kubelka–Munk function $F(R)$.

N₂ adsorption/desorption isotherms at -196 °C were obtained with a Quantachrome Autosorb 1 instrument on samples previously outgassed at 300 °C under vacuum for 3 h to remove water and other atmospheric contaminants. The BET (Brunauer-Emmett-Teller) method was used to calculate the samples specific surface area, S_{BET} .

FTIR spectroscopy measurements of NH₃ adsorption were carried out at room temperature (r.t.). FTIR spectra of self-supporting wafers were collected on an Equinox 55 (Bruker) spectrophotometer equipped with MCT (Mercury – Cadmium- Telluride) cryodetector. The powders were pressed into thin self-supporting wafers (optical density of about 20 mg cm⁻²) and treated under high vacuum (residual pressure <10⁻³ mbar) at 300 °C in a standard vacuum frame, to remove water and other atmospheric contaminants. Afterwards, increasing pressures of NH_{3(g)} were dosed on the outgassed samples (equilibrium pressure range: 0 – 15 mbar) and then, the samples were outgassed for 1 h at r.t. and at 300 °C, to check adsorption reversibility.

NH₃-TPD (Temperature Programmed Desorption) measurements were carried out using a CATLAB-PCS (Hiden Analytical), a quartz microreactor coupled to a Mass Spectrometer. About 0.1 g fresh sample was preheated in argon flow (50 mL min⁻¹) at 300 °C for 60 min (ramp 10 °C min⁻¹). Adsorption of NH₃ (5 vol. % in helium; flow rate 30 mL min⁻¹) was done at 70 °C. The TPD measurement, under an argon flow of 30 mL min⁻¹, was conducted by heating the sample from 70 to 600 °C at a 10°C min⁻¹ rate.

FESEM (Field Emission Scanning Electron) measurements were performed using a Tescan S9000G FESEM 3010 microscope (30 kV) equipped with a high brightness Schottky emitter and fitted with Energy Dispersive X-ray Spectroscopy (EDS) analysis by an Ultim Max Silicon Drift Detector (SDD, Oxford). For analyses, the samples, in the form of powders, were deposited on a stub coated with a conducting adhesive and inserted in the chamber by a fully motorized procedure. In order to determine the Nb/Ru ratios listed in Table 1 for 4Ru2.5Nb, 4Ru5Nb and 4Ru7.5Nb, EDS mapping were carried out on each sample either annealed for 2 h at 500 °C in air or reduced for 3 h at 300 °C for 3 h under H₂ flow. The EDS analyses were performed on different regions of each sample by adopting the same instrumental beam parameters to keep constant the interaction volume. In this way, the average amounts (weight %) of Nb and Ru were obtained and then the Nb/Ru ratios were calculated.

Carbon monoxide chemisorption was performed in a Micromeritics Pulse Chemisorb 2705 equipment. The catalyst (0.15 g), placed in a U-shaped sample tube, was heated at a rate of 10 °C min⁻¹, under a pure flow of H₂, to perform a reduction pretreatment at 300 °C for 3 hours. The sample was cooled down to 35 °C. The CO chemisorption was performed sending pulses of 0.037 mL of CO in helium, to the sample and recording the corresponding peak value of the non adsorbed CO. This process was repeated until saturation, namely when no more CO was adsorbed when an additional pulse is given. The total amount of CO adsorbed is found by summing the amount adsorbed at each pulse.

2.3 Catalytic tests

The catalytic experiments were conducted following our previous studies in the field [Minieri, L.; Esposito, S.; Russo, V.; Bonelli, B.; Serio, D.; Silvestri, B.; Vergara, A.; Aronne, A. A Sol – Gel Ruthenium – Niobium – Silicon Mixed-Oxide Bifunctional Catalyst for the Hydrogenation of Levulinic Acid in the Aqueous Phase. 2017, ChemCatChem 1476–1486.]. The experimental procedure is here briefly described: 4.0 g of LA, 200 g of water and 0.5 g of pre-reduced catalyst were loaded to the reactor. The system was heated at 70 °C at a constant stirring rate of 300 rpm, then hydrogen was fed at a constant pressure. Samples were withdrawal along the experimental time to measure the products distribution via GC analysis, using ethylene glycol as an external standard (100 µL in 2 mL of reaction sample). The sample (1µL) was injected in a PerkinElmer Clarus 580 GC, working with a 30 m x 0.32 mm x 0.26 µm Supelco SLB-IL60 column, with a FID detector, a PSSI injector working at 300 °C, carrier (He) pressure of 14 psi and working in on-column mode. The temperature ramp was set as follows: 100 °C heating to 300 °C with a rate of 10 °C min⁻¹; the temperature was kept at the final value for 25 min. The retention times were the

following: ethylene glycol: 4.7 min; γ -valerolactone: 6.2 min; γ -hydroxypentanoic acid: 7.11 min; levulinic acid: 10.4 min.

The reliability of GC-FID analysis was checked by comparing the results with the ones obtained via $^1\text{H-NMR}$: GVL and HPA selectivity values show an error below 6% (see Supplementary Material). The catalyst pre-treatment was performed in a fixed bed reactor working at $0.1 \text{ L min}^{-1} \text{ H}_2$ flow, 1 bar and $300 \text{ }^\circ\text{C}$ for 3 h.

3. Results and discussion

3.1 Structural, textural, and electronic properties

All dried gels are amorphous (data not shown) while the XRD profiles of the annealed samples (2 h at $500 \text{ }^\circ\text{C}$) are shown in Fig. 1. The peaks of Ru(IV) oxide, RuO_2 , (JCPDS Card No. 40-1290) can be noticed in all profiles [20,24] together with a broad halo centred at approximately $2\theta = 24^\circ$, typical of amorphous silica [25–27]. This indicates that the annealing causes the precipitation in the amorphous matrix of small RuO_2 crystals. On the other hand, the lack of typical peaks of Nb_2O_5 crystalline aggregates corroborates the hypothesis of a very high dispersion of niobium in the siloxane matrix.

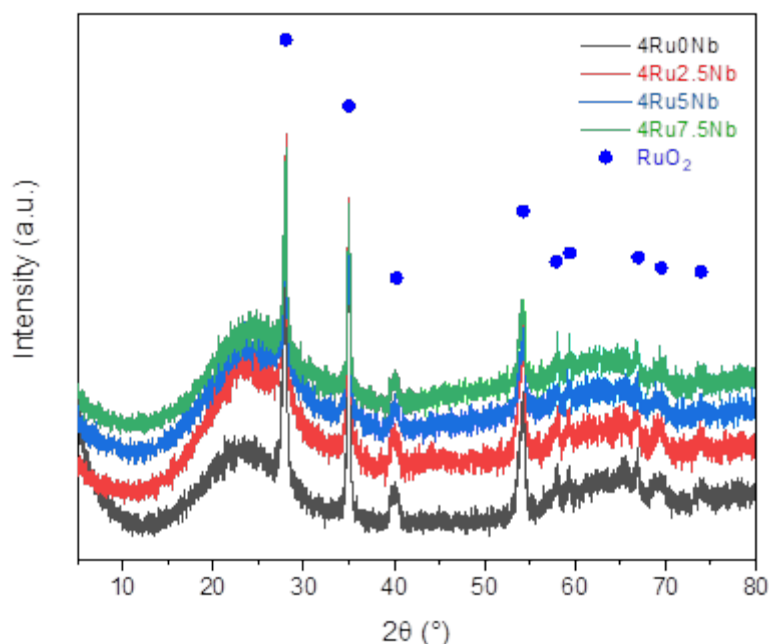


Fig. 1. XRD patterns of gel-derived materials annealed at $500 \text{ }^\circ\text{C}$ for 2 h. The pattern of the corresponding 4Ru0Nb sample is also reported as a reference.

Actually, the highest lines for the monoclinic ($\text{H-Nb}_2\text{O}_5$, JCPDS card 32–711) and the orthorhombic ($\text{T-Nb}_2\text{O}_5$, JCPDS card 27–1312) polymorphs occur in the 20° – 25° 2θ range where only the peak of

the amorphous halo is seen (Figure 1). On the other hand, due to the more complex structure of H-phase, containing 3×5 and 3×4 ReO_3 type blocks superstructures, than the T-phase one, formed by corner- and edge- sharing distorted octahedra and pentagonal bipyramids, it was expected that at this temperature the initial crystallization of T- Nb_2O_5 could eventually to occur at least for the samples at high Nb content, but the bottom-up procedure adopted to synthesize the materials allow to obtain a dispersion of niobium into the siloxane matrix at molecular level, as demonstrated by the structural characterization later on reported. [Aronne et al. *J Sol-Gel Sci Technol* (2007) 43:193–204].

The FTIR-ATR spectra of the annealed samples are displayed in Fig. S1. In the range 2850-3650 cm^{-1} , the FTIR-ATR spectra of all the samples exhibit a broad absorption band due to the O-H stretching mode of H-bonded hydroxy groups, due to the adsorption of water vapour after exposure to the atmosphere, as the spectra were taken at ambient conditions. Accordingly, at lower wavenumbers (Figure S1), the bending mode of adsorbed molecular water ($\delta_{\text{O-H}}$) [30, 31] is observed at 1630 cm^{-1} . All the samples show the typical vibration modes of siloxanes (Si-O-Si) groups in the silica network at 1055 and 1200 cm^{-1} and at 795 cm^{-1} assigned to the asymmetric ($\nu_{\text{Si-O}}$) [28] and symmetric ($\nu_{\text{Si-O-Si}}$) [29] stretching mode of Si-O-Si groups. The spectrum of the 4Ru0Nb sample shows a band at 970 cm^{-1} , due to the stretching mode of Si-O-Ru groups, forming by insertion of Ru in the silica matrix (*Applied Catalysis A: General* 182 (1999) 257-265). Interestingly, the addition of Nb (samples 4Ru2.5Nb, 4Ru5Nb and 4Ru7.5Nb) brings about the appearance of a (more intense) absorption at much lower wavenumbers, i.e. 950 cm^{-1} , due to the progressive formation of Si-O-Nb bonds due to the insertion of Nb within the silica matrix [29], in agreement with the XRD findings.

The DR UV-vis spectra (Fig. S2) of the annealed samples containing niobium are dominated by the band due to the charge-transfer transition (from O^{2-} to Nb^{5+}) centred at about 245 nm. It can be assigned to distorted NbO_6 octahedra, which are associated with Brønsted acid sites.

As the niobium content increases, the peaks position shift to slightly higher wavelengths and the absorption bands become a little wider indicating the presence of a broad distribution of isolated NbO_6 octahedra (less or more distorted), in agreement with FESEM findings. [32]. The lack of absorption bands above 300 nm suggests that the occurrence of niobia-like domains can be excluded since Nb_2O_5 strongly absorbs below 400 nm (*Catalysts*, 2019, **9**, 344).

The specific surface areas were obtained by the elaboration of the N_2 adsorption isotherm using the BET method and reported in Table 1. The shape of the adsorption–desorption isotherms (not reported) appears of type Ib according to the IUPAC classification, indicating the possible presence

of wide micropores; differently from a microporous material the plateau starts at $P/P^0 > 0.2$ values, suggesting the presence of a certain mesoporosity. According to the results, among the samples with the same content of ruthenium, the 4Ru0Nb catalyst displays the highest specific surface area ($523 \text{ m}^2\text{g}^{-1}$) while a decrease can be observed in the samples containing niobium.

3.2 Surface acidity properties

To assess the nature of acid sites on the surface of the synthesized materials a spectroscopic IR investigation was performed using NH_3 as probe molecule, because it can interact with both Brønsted acidic sites (by forming NH_4^+ ions) and Lewis acidic sites (by forming acidic–basic adducts) [33]. Its small size allows quantitatively probing of almost all acid sites in micro-, meso-, and macro-porous oxides [34]. The protonated species (NH_4^+ ions) and the coordinatively bonded NH_3 in Lewis adducts have different N-H vibrations. In particular, the deformation vibrations (bending modes) at ca. 1450 and 1610-1630 cm^{-1} provide reliable indicators for the presence of protonated and coordinatively bonded NH_3 , respectively.

Figure 2 reports difference spectra (after subtraction of the spectra of the bare samples, i.e., outgassed at 300 °C) concerning NH_3 adsorption (equilibrium pressure ca. 5.0 mbar) at r.t. on the annealed samples previously outgassed at 300 °C.

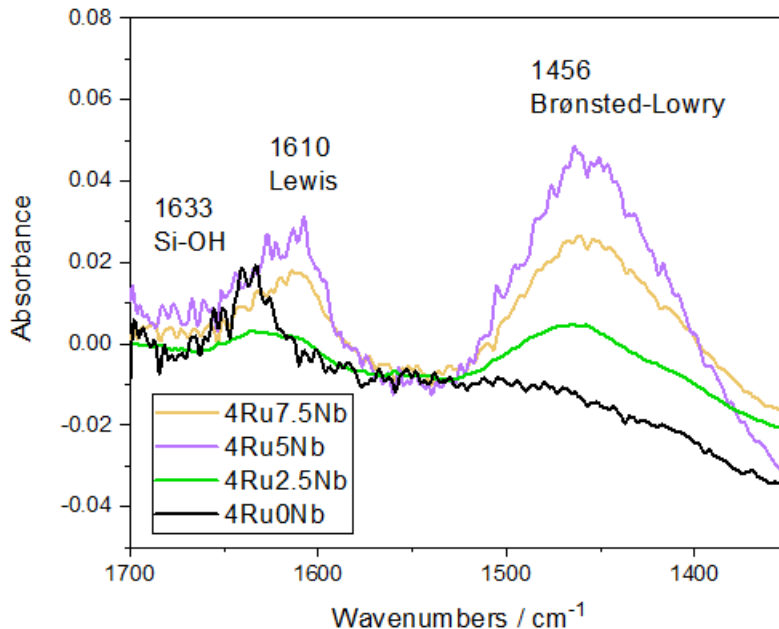


Fig. 2. Difference FTIR spectra concerning the room temperature adsorption of NH_3 (equilibrium partial pressure ca 5.0 mbar) on the samples previously outgassed at 300 °C. Spectra have been normalized to sample unit weight, in order to allow comparison.

To allow comparison, the spectra in Fig. 2 were normalized to sample unit weight, in such a way that the bands intensity of different samples can be compared.

The analysis of the spectra displayed in Fig. 2 reveals that, in the absence of Nb a single band is observed at 1633 cm^{-1} (4Ru0Nb sample), readily ascribed to NH_3 molecules interacting with surface Si-OH species via H-bond [35,36], such OH groups being weakly acidic and, thus, unable to transfer a proton to NH_3 , but able to H-bond the molecule at r.t.. Addition of Nb brings about the appearance of other two bands at ca. 1610 and $1456\text{-}1465\text{ cm}^{-1}$. The former is assigned to the bending mode of NH_3 molecules adsorbed on coordinatively unsaturated Lewis (L) sites (e.g. Nb^{5+} ions) [37], the latter to the bending mode of NH_4^+ species, formed upon interaction between NH_3 and (Nb-related) acidic -OH groups acting as Brønsted sites (B). Such bands were not removed by prolonged evacuation at r.t., but by outgassing the samples at $300\text{ }^\circ\text{C}$ (spectra not shown). Since the spectra have been normalized to sample unit weight, a comparison of the relative intensity of the bands is allowed, showing that both intensities follow this trend: $4\text{Ru}2.5\text{Nb} < 4\text{Ru}7.5\text{Nb} < 4\text{Ru}5\text{Nb}$. This trend also agrees with the total desorbed amounts of NH_3 measured by TPD later reported. Both L and B bands are less intense with 4Ru2.5Nb, showing that at low Nb loading the surface acidic sites are less abundant; moreover, the band due to the bending mode of the NH_4^+ species is seen at 1465 cm^{-1} , i.e., at lower wavenumbers than with the other two samples (4Ru5Nb and 4Ru7.5Nb), giving rise to a bending mode at 1456 cm^{-1} . The position of the bending mode is related to the strength of the interaction of NH_3 with surface OH groups, i.e., to their acidic strength [37] showing that the 4Ru2.5Nb has weaker B sites. Considering the spectra in Fig. 2, the 4Ru5Nb catalysts seems to be the one containing more acidic sites, whereas at higher Nb loadings (4Ru7.5Nb) some Nb-related phenomena occur, which bring about an overall decrease of acidity.

The surface acidic properties of the synthesized materials were also analysed by NH_3 temperature-programmed desorption (TPD) experiments. The obtained values of the total amount of NH_3 desorbed are reported in Table 1. As can be seen, the trend of these values well agrees with the above IR analysis. As matter of fact, the acidity of 4Rb0Nb is very low, then we observe an increase of acidity with the increase of Nb content until a nominal concentration of 4.7%. The acidity then decreases for a further increase in Nb amount.

The trend of the surface acidity displayed by the studied samples can be explained considering that the intensity of NH_3 bands is due to the increased number of available acidic sites to which ammonia molecules have access. The fact that the bands intensity and, hence, the number of accessible acidic sites, increases by reaching a maximum, then decreases, is a rather common phenomenon, due to the dispersion of adsorbing sites, which typically reaches a maximum and

decreases at higher loading. On the other hand, the decrease of the acidity with the Nb increase was also observed in the Nb-P-Si system (A. Gervasini et al. / *Molecular Catalysis* 458 (2018) 280–286). It was explained as due to the structural evolution occurring with the increase of Nb content producing a higher the crosslinking degree of Nb-O-Si and a consequent decrease of the fraction of isolated NbO₄ tetrahedra, which give a strong Lewis acidity, in agreement with UV–vis DRS findings.

NH₃ TPD and FTIR spectroscopy studies point out that the composition, i.e. the Nb/Ru ratio, strongly influences the surface acidity of the catalysts, which suggest that a synergic interaction between Ru and Nb is established within the silica matrix.

3.3 Morphology and elemental distribution of both annealed and reduced materials

The morphology and element distribution of both annealed (500 °C in air for 2 h) and reduced (300 °C under H₂ flow for 3 h) materials were investigated by FESEM. The aim was to obtain information on the dispersion of Ru and Nb as well as on their respective arrangements within the materials to disclose the interaction between the two elements. Upon reduction at 300 °C the 4Ru0Nb catalyst contains large metallic Ru flower-like agglomerates, as shown in panel a of Fig. S3. Such peculiar Ru morphology was previously observed on the same sample annealed in air, before reduction (see Supporting Information, Figs. S4 and S5) [38], confirming that the Ru flower-like morphology is not induced by the reduction treatment. Moreover, EDS analyses carried out on different points of the reduced sample (panel b of Fig. S3) clearly put in evidence the presence of Ru also in regions of the catalyst where the flower-like Ru species are not observed, therefore indicating that Ru species are homogeneously dispersed within the silica matrix, in agreement with the results of EDS mapping carried out on the annealed sample (panel c of Fig. S5) [20,26].

FESEM representative images of the 4Ru2.5Nb catalyst (reduced sample) are shown in panels a and b of Fig. 3, revealing similar Ru flower-like morphology also in the presence of Nb. EDS maps of Si, O, Ru and Nb showed homogeneous distribution of the different elements at nanometric scale within the 4Ru2.5Nb catalyst, panel c of Fig. 3 (additional experimental findings on both annealed and reduced materials are reported in Figs. S6-S8 of the Supporting Information).

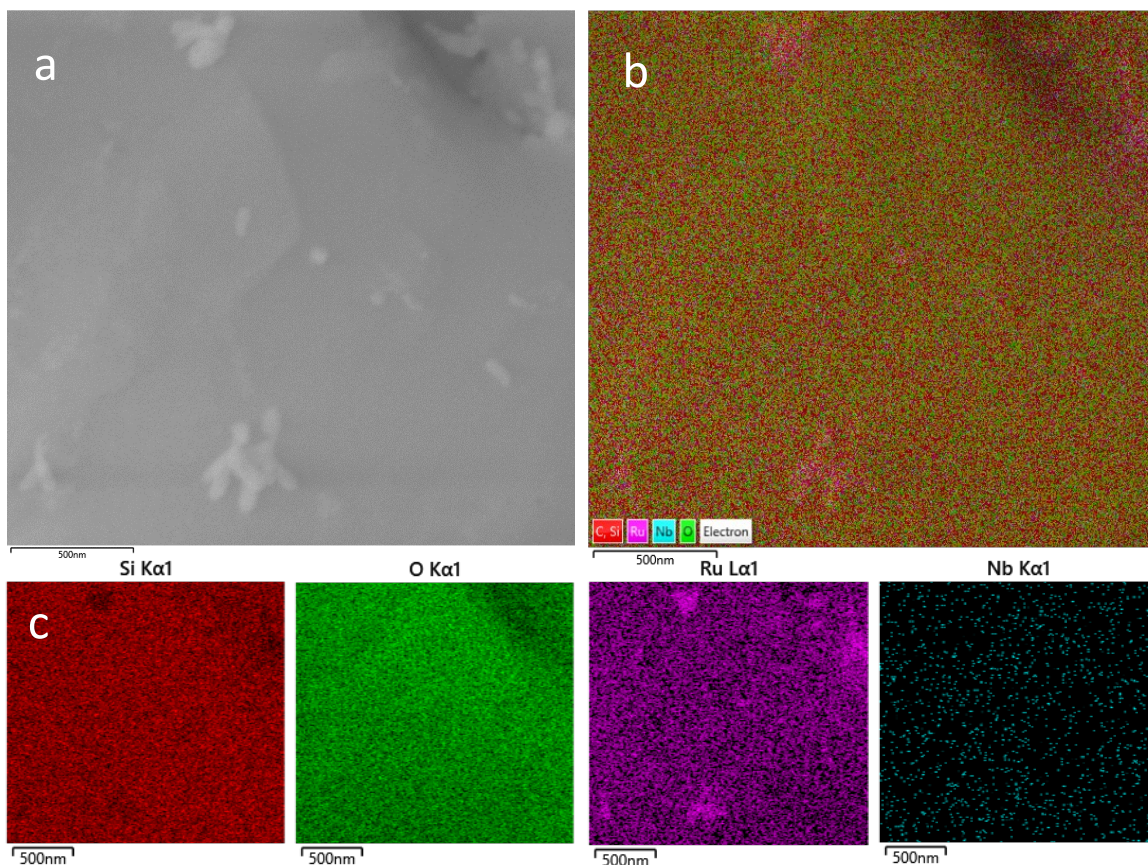


Fig. 3. FESEM image (a) and EDS layered image (b) of the 4Ru_{2.5}Nb catalyst. EDS maps of the region shown in a) for Si, O, Ru and Nb (c). Image collected at 25 kV with the standard SE detector. Instrumental magnification: 34000x.

These findings were corroborated by measurements carried out at higher magnification (Fig. 4), that highlighted the Nb dispersion at atomic level, whereas Ru is in the form of very small nanoparticles with size similar to that observed previously for 4Ru₀Nb [20, 26]. These features put in evidence a close contact between the highly dispersed Nb and Ru species.

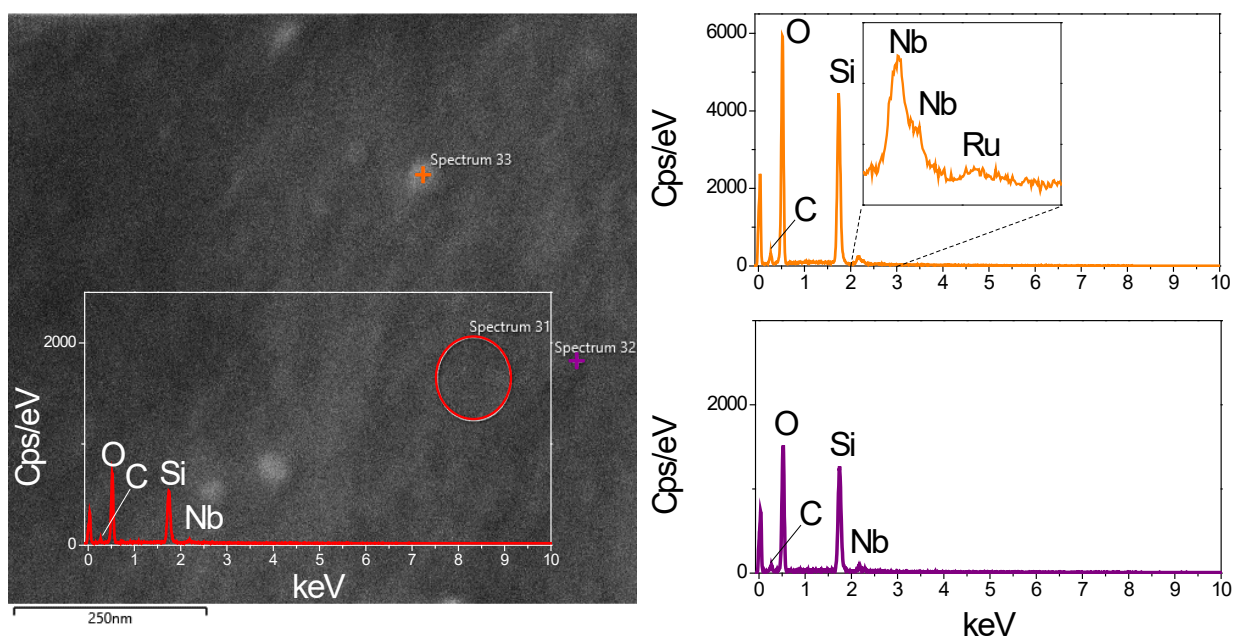


Fig. 4. FESEM representative image of 4Ru2.5Nb catalyst and EDS spectra of selected points/regions. Image collected at 25 kV with the standard SE detector. Instrumental magnification: 261000x.

Morphology and element distribution were checked also in the case of both annealed and reduced 4Ru5Nb and 4Ru7.5Nb samples. Similar features were observed, as shown in Figs. 5 and 6, confirming that also in these cases, Ru is located in regions where the flower-like morphology is not present and that Nb is homogeneously dispersed within the materials, independently of the Ru amount in the catalysts. (Further experimental evidence is reported in Figs. S9-S13 of the Supporting Information.)

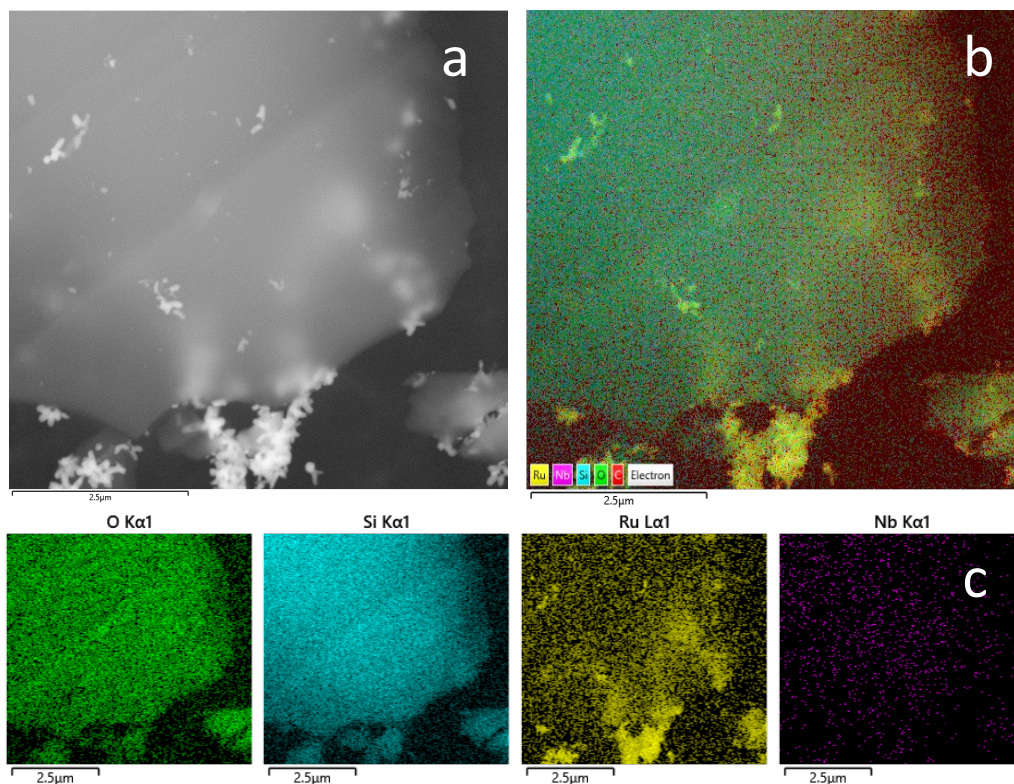


Fig. 5. FESEM image of the 4Ru5Nb catalyst (a), EDS layered image (b) with the corresponding EDS maps O, Si, Ru and Nb (c). Image collected at 25 kV with the standard SE detector. Instrumental magnification: 30000x.

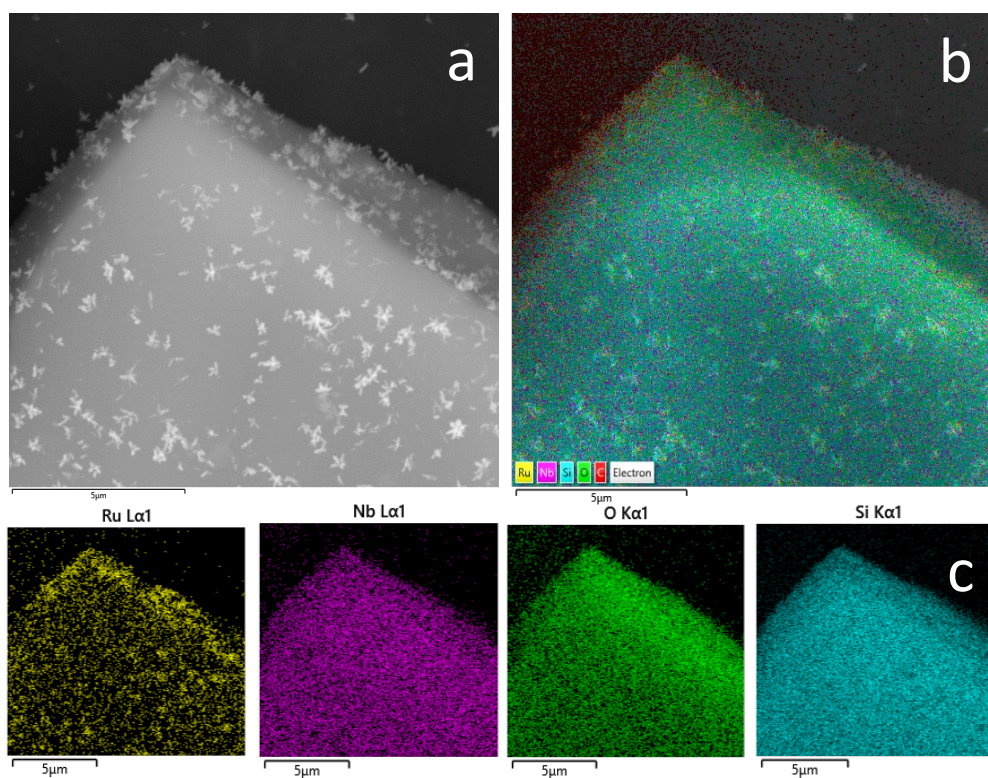


Fig. 6. FESEM image of the 4Ru7.5Nb catalyst (a), EDS layered image (b) with the corresponding EDS maps of Ru, Nb, O, and Si (c). Image collected at 25 kV with the standard SE detector. Instrumental magnification: 15000x.

In Table 1 the Nb/Ru ratios calculated based on EDS maps (obtained as wt % of the different elements) are summarised for all ternary materials containing Nb. The ratios have been determined for both annealed and reduced catalysts. As already reported, the ratios have been determined from the average amounts (weight %) of Nb and Ru detected by EDS in different regions of both annealed and reduced catalysts.

Overall, the Nb/Ru increases with increasing the Nb loading and it is shown that, among the annealed samples, 4Ru2.5Nb has the lowest Nb/Ru ratio, meaning that in this case the lowest amount of Nb is located at the surface and/or close to the surface of the material.

Upon reduction at 300 °C, an increased Nb/Ru ratio was observed for all the catalysts, which could be an indication that Nb migrates toward the surface of the catalyst under reducing conditions, possibly affecting the distribution of the highly dispersed Ru phase [39]. Moreover, such enhancement was minimum for 4Ru2.5Nb and it was particularly evident for 4Ru7.5Nb. These features corroborated that the Nb species are highly and homogeneously dispersed on the 4Ru2.5Nb material either after oxidation at 500 °C or after reduction at 300 °C, in agreement with XRD and FTIR-ATR results.

In addition, the ruthenium dispersion in the reduced materials was also estimated by CO chemisorption and the results are summarized in Table 1. As established in our previous study [Esposito et al. ACS Catal. ACS Catal. 2019, 9, 3426–3436], in the case of Ru catalysts synthesized by sol–gel this technique is a hardly applicable method because it is difficult to exactly determine how many of the Ru atoms are incorporated into the three-dimensional network of the matrix covalent skeleton. Nevertheless, the Ru dispersion estimated for the 4Ru0Nb catalyst (about 12%) well agrees with the previously reported one [Esposito et al. ACS Catal. ACS Catal. 2019, 9, 3426–3436]. The Nb addition gives an apparent lower dispersion (about 5 %) that is the same independently from the Nb content. This result is related to the strong mutual interaction occurring between the Ru and Nb in agreement with the above characterization, that shows a similar elemental distribution among the studied catalysts [39,40].


In conclusion, the observed interaction between Nb and Ru is depending on the composition and affects both metal availability and acidity of the bifunctional Ru-Nb-Si catalysts.

3.4 Catalyst screening for LA hydrogenation to GVL

The Ru-Nb-Si catalysts were tested in the hydrogenation of LA to GVL, under mild conditions and in aqueous environment. In Fig. 7, the intermediate γ -hydroxypentanoic acid (HPA) and product (GVL) final concentrations (after 2 h) for each catalyst are displayed.

Using the 4Ru0Nb catalyst at the end of the reaction LA is completely converted into HPA and only traces of GVL were observed.

Fig. 7. Conversion (x) of LA and selectivity (s) to GVL and HPA obtained for each catalyst at 2h reaction (70 °C, P_{H₂}= 20 bar, 200g water, 4.0 g LA, 0.5 g catalyst).

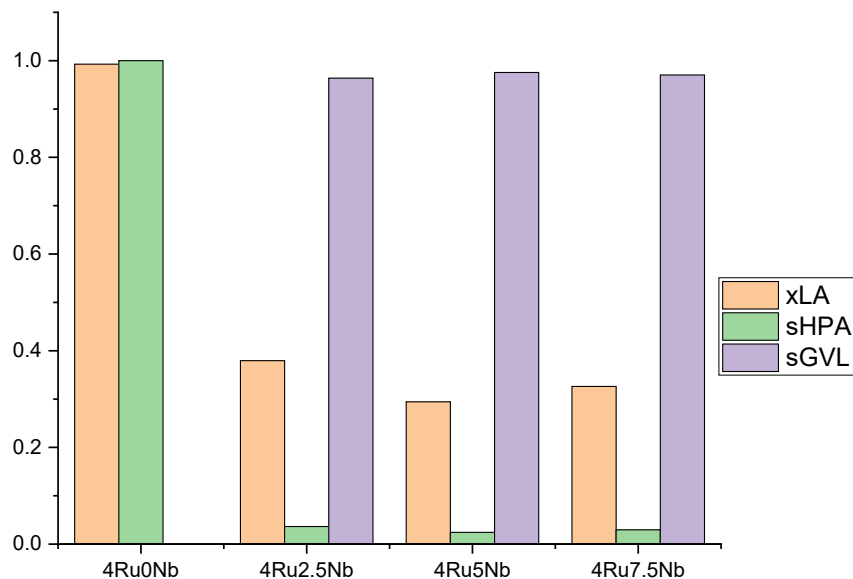

In the case of catalysts containing niobium the lactonization reaction of HPA to GVL was favoured with almost complete selectivity to GVL whereas different final LA conversion values were obtained with the increase of niobium content indicating that the yield to GVL is strongly influenced by the acid characteristics of the matrix.

The turnover frequency (TOF) per mole of ruthenium was calculated as the LA consumption rate referred to the number of moles of ruthenium, as shown in the following equation:


$$TOF_{Ru} = \frac{1}{n_{Ru}} \frac{dn_{LA}}{dt} \quad (1)$$

and the results obtained are shown in Table 2, where the TOF_{Ru} normalized with respect to the estimated dispersion values (TOF_{Ru}/D_{Ru}) are also displayed.

Table 2. TOF_{Ru}, TOF_{Ru}/D_{Ru} values and kinetic constants calculated on the experimental data.

Catalyst	TOF _{Ru} [s ⁻¹]	TOF _{Ru} /D _{Ru} [s ⁻¹]	k ₁ [h ⁻¹]	k ₂ [h ⁻¹]
4Ru0Nb	(5.85±0.02)·10 ⁻²	(4.9±0.2)·10 ⁻³	2.20±0.04	0.010±0.005
4Ru2.5Nb	(1.24±0.02)·10 ⁻²	(2.5±0.2)·10 ⁻³	0.26±0.02	8.8±0.1
4Ru5Nb	(0.98±0.01)·10 ⁻²	(2.0±0.2)·10 ⁻³	0.25±0.02	29.4±0.1
4Ru7.5Nb	(0.95±0.01)·10 ⁻²	(2.4±0.2)·10 ⁻³	0.25±0.02	29.9±0.2

The TOF_{Ru} values calculated on the LA reveal the influence of catalyst composition on LA conversion. However, to investigate quantitatively the influence of morphology on both LA conversion and selectivity to GVL or HPA, deeper kinetic analysis of the data was performed. The kinetic data collected using the different Ru-Nb-Si catalysts were elaborated using a pseudo-homogeneous kinetic model, which considers that the reaction is in series, the reagent LA produces the intermediate HPA in the first step, and HPA is converted into the product GVL in the second

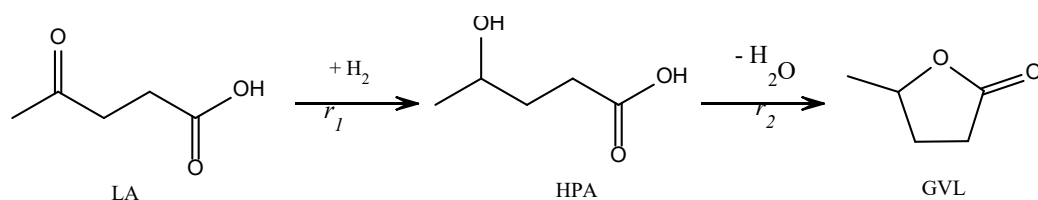

step:

The rate of LA disappearance, r_1 , is given by the equation:

$$r_1 = k_1 C_{LA} \quad (2)$$

The rate of disappearance of the intermediate HPA, r_2 , is given by the equation:

$$r_2 = k_2 C_{HPA} \quad (3)$$

It is assumed that the kinetics are of the first order both in the first and in the second reaction step since the experiments were conducted in excess of hydrogen and both kinetic constants have physical dimensions equal to [h⁻¹]. The mass balance equations are as follows:

$$\frac{dC_{LA}}{dt} = -k_1 C_{LA} \quad (4)$$


$$\frac{dC_{HPA}}{dt} = +k_1C_{LA} - k_2C_{HPA} \quad (5)$$

$$\frac{dC_{GVL}}{dt} = +k_2C_{HPA} \quad (6)$$

The two kinetic constants of the reactions, k_1 and k_2 , were estimated and their values are displayed in Table 2.

In Fig. 8, as an example, the comparison between experimental data and the concentration profiles obtained by the model is displayed for 4Ru2.5Nb.

Fig. 8. Experimental data and calculated concentration profile for 4Ru2.5Nb as catalyst. (70 °C, $P_{H_2} = 20$ bar, 200 g water, 4.0 g LA, 0.5 g catalyst).

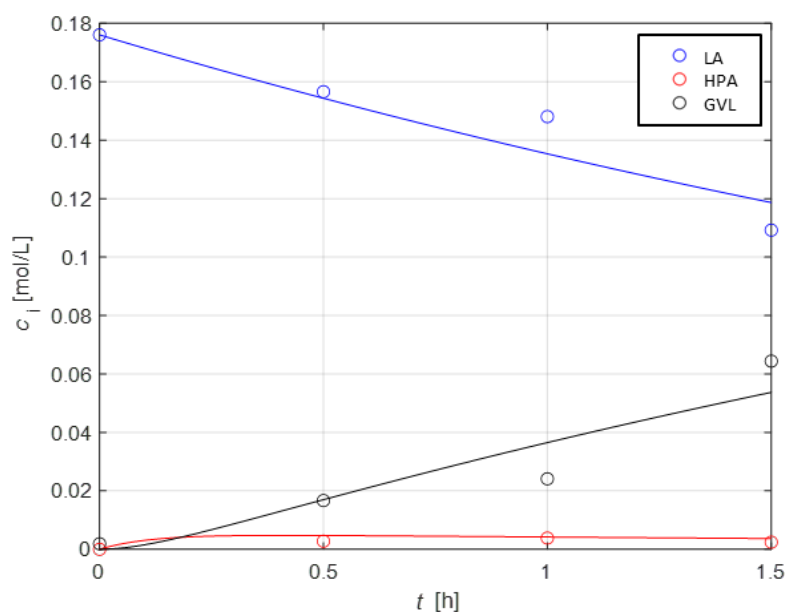

The values of k_1 calculated well agree with both TOF_{Ru} and TOF_{Ru}/D_{Ru} values (Table 2) confirming that the hydrogenation is mainly controlled by extent of interaction between Ru and Nb. The hydrogenation activity is maximum for the Nb-free catalyst (4Ru0Nb) and becomes lower with the increase of niobium. As revealed, even the trend of TOF_{Ru}/D_{Ru} values follows that of TOF_{Ru} ones, showing the pivotal role in the Ru availability and thus in the hydrogenation activity is played by the synergistic interaction between the Ru and Nb. An opposite trend is seen for the lactonization kinetic constant k_2 that is mainly favoured by the increasing niobium content and so by the increasing of the acidity of the surface.

It must be pointed out the observed 100% selectivity of 4Ru0Nb catalyst to HPA with the complete conversion of LA. At our knowledge this is the first case where such results have been reported.

The silica support for ruthenium in the LA hydrogenation is not extensively used because ruthenium catalysts on silica prepared by impregnation are subject to irreversible deactivation for the sintering phenomena [41]. However, in addition to the acidity of the support, selectivity can also be inflected by reaction conditions. For example, Kuwahara et al. [42], working at 70°C (as in this work) with a ruthenium catalyst supported by impregnation on silica, achieved a selectivity of 4% at HPA for a conversion of 88% LA [42]. However, one must consider that in addition to the possible difference in acidity of the support, they used about 15 times higher concentration of LA and about 2.5 times higher concentration of catalyst. This certainly increases the acidity of the reaction environment.

Based on the above results, we explored the possibility to perform the whole transformation of LA to GVL by means of two separate and consecutive steps. In the former the LA hydrogenation to HPA takes place using the 4Ru0Nb catalyst and in the successive step the HPA dehydration to GVL occurs using a catalyst with suitable distribution of acid sites. For the latter step we used the 2.5Nb₂O₅·97.5SiO₂ catalyst whose catalytic performance was described in a previous paper [25].

A preliminary test was performed adopting the same reaction conditions described in section 2.3 for the first step, obtaining a liquid solution rich of HPA. This solution, in the consecutive step, was put in contact with the 2.5Nb₂O₅·97.5SiO₂ catalyst, obtaining very encouraging results: after 2h of reaction, HPA was fully converted in GVL, leading to no side product.

4. Conclusions

Bifunctional ruthenium-niobium-silicon mixed oxides-based catalysts, with different contents of ruthenium and niobium, were studied for levulinic acid hydrogenation to γ -valerolactone. The results of catalytic tests in a fed-batch reactor under H₂ flow were coupled with a comprehensive characterization, in order to establish structure-activity relationships. The pre-reduced Ru-containing catalysts demonstrated to be effective in the hydrogenation of LA to HPA, whereas for the successive lactonization reaction the presence of niobium is necessary as it is responsible of the increased acidity of the catalyst. The sol-gel synthetic procedure allowed to obtain materials with high dispersion of both niobium and ruthenium and intimate interaction between them. Upon the reduction treatment, a competitive migration between the two metals takes place, leading to a variation in the surface exposure of Ru and Nb species. This phenomenon is strongly connected with the different Nb/Ru ratios of the catalysts and therefore affects in different extent the ruthenium availability, ultimately ruling the hydrogenation activity.

Furthermore, for the first time a catalyst has been found to obtain 100% selectivity to HPA at complete conversion of LA.

Acknowledgements

Benedetta De Liso (Università di Napoli Federico II, DSC) is cordially acknowledged for their experimental support in conducting the catalytic test and in the catalysts synthesis. François Devred (UCLouvain) is acknowledged for his support in the characterization carried out in Louvain-la-Neuve. Nicola Blangetti (Politecnico di Torino) is acknowledged for IR measurements concerning NH_3 adsorption at r.t..

References

- [1] S.A. Razzak, M.M. Hossain, R.A. Lucky, A.S. Bassi, H. de Lasa, Integrated CO₂ capture, wastewater treatment and biofuel production by microalgae culturing—A review, *Renew. Sustain. Energy Rev.* 27 (2013) 622–653. <https://econpapers.repec.org/RePEc:eee:rensus:v:27:y:2013:i:c:p:622-653>.
- [2] T. Ansell, S. Cayzer, Limits to growth redux: A system dynamics model for assessing energy and climate change constraints to global growth, *Energy Policy*. 120 (2018) 514–525. <https://doi.org/10.1016/j.enpol.2018.05.053>.
- [3] T. Werpy, G. Petersen, Top Value Added Chemicals from Biomass Volume I, Us Nrel. (2004) Medium: ED; Size: 76 pp. pages. <https://doi.org/10.2172/15008859>.
- [4] Z. Xue, D. Yu, X. Zhao, T. Mu, Upgrading of levulinic acid into diverse N-containing functional chemicals, *Green Chem.* 21 (2019) 5449–5468. <https://doi.org/10.1039/C9GC02415H>.
- [5] F.D. Pileidis, M.M. Titirici, Levulinic Acid Biorefineries: New Challenges for Efficient Utilization of Biomass, *ChemSusChem.* 9 (2016) 562–582. <https://doi.org/10.1002/cssc.201501405>.
- [6] J.J. Bozell, L. Moens, D.C. Elliott, Y. Wang, G.G. Neuenschwander, S.W. Fitzpatrick, R.J. Bilski, J.L. Jarnefeld, Production of levulinic acid and use as a platform chemical for derived products, *Resour. Conserv. Recycl.* 28 (2000) 227–239. [https://doi.org/https://doi.org/10.1016/S0921-3449\(99\)00047-6](https://doi.org/https://doi.org/10.1016/S0921-3449(99)00047-6).
- [7] M. Liu, S. Li, G. Fan, L. Yang, F. Li, Hierarchical Flower-like Bimetallic NiCu catalysts for Catalytic Transfer Hydrogenation of Ethyl Levulinate into γ -Valerolactone, *Ind. Eng. Chem. Res.* 58 (2019) 10317–10327. <https://doi.org/10.1021/acs.iecr.9b01774>.
- [8] K. Yan, Y. Yang, J. Chai, Y. Lu, Catalytic reactions of gamma-valerolactone: A platform to fuels and value-added chemicals, *Appl. Catal. B Environ.* 179 (2015) 292–304. <https://doi.org/https://doi.org/10.1016/j.apcatb.2015.04.030>.
- [9] D.M. Alonso, J.M.R. Gallo, M.A. Mellmer, S.G. Wettstein, J.A. Dumesic, Direct conversion of cellulose to levulinic acid and gamma-valerolactone using solid acid catalysts, *Catal. Sci. Technol.* 3 (2013) 927–931. <https://doi.org/10.1039/c2cy20689g>.
- [10] M.G. Al-Shaal, A. Dzierbinski, R. Palkovits, Solvent-free γ -valerolactone hydrogenation to 2-methyltetrahydrofuran catalysed by Ru/C: a reaction network analysis, *Green Chem.* 16 (2014) 1358–1364. <https://doi.org/10.1039/C3GC41803K>.
- [11] H. Wang, B. Yang, Q. Zhang, W. Zhu, Catalytic routes for the conversion of lignocellulosic biomass to aviation fuel range hydrocarbons, *Renew. Sustain. Energy Rev.* (2019) 109612. <https://doi.org/10.1016/j.rser.2019.109612>.
- [12] I. Orłowski, M. Douthwaite, S. Iqbal, J.S. Hayward, T.E. Davies, J.K. Bartley, P.J. Miedziak, J. Hirayama, D.J. Morgan, D.J. Willock, G.J. Hutchings, The hydrogenation of levulinic acid to γ -valerolactone over Cu–ZrO₂ catalysts prepared by a pH-gradient methodology, *J. Energy Chem.* 36 (2019) 15–24. <https://doi.org/https://doi.org/10.1016/j.jechem.2019.01.015>.
- [13] J. Wang, Y. Wang, X. Tong, Y. Wang, G. Jin, X. Guo, Highly active Ir/SiC catalyst for aqueous hydrogenation of levulinic acid to γ -valerolactone, *Catal. Commun.* 139 (2020) 105971. <https://doi.org/https://doi.org/10.1016/j.catcom.2020.105971>.
- [14] A.S. Amarasekara, M.A. Hasan, Pd/C catalyzed conversion of levulinic acid to γ -

- valerolactone using alcohol as a hydrogen donor under microwave conditions, *Catal. Commun.* 60 (2015) 5–7. <https://doi.org/10.1016/j.catcom.2014.11.009>.
- [15] R.Y. Parapat, F.A. Yudatama, M.R. Musadi, M. Schwarze, R. Schomäcker, Antioxidant as Structure Directing Agent in Nanocatalyst Preparation. Case Study: Catalytic Activity of Supported Pt Nanocatalyst in Levulinic Acid Hydrogenation, *Ind. Eng. Chem. Res.* 58 (2019) 2460–2470. <https://doi.org/10.1021/acs.iecr.8b03555>.
- [16] P.P. Upare, J.-M. Lee, D.W. Hwang, S.B. Halligudi, Y.K. Hwang, J.-S. Chang, Selective hydrogenation of levulinic acid to γ -valerolactone over carbon-supported noble metal catalysts, *J. Ind. Eng. Chem.* 17 (2011) 287–292. <https://doi.org/10.1016/j.jiec.2011.02.025>.
- [17] A. Seretis, P. Diamantopoulou, I. Thanou, P. Tzevelekidis, C. Fakas, P. Lilas, G. Papadogianakis, Recent Advances in Ruthenium-Catalyzed Hydrogenation Reactions of Renewable Biomass-Derived Levulinic Acid in Aqueous Media, *Front. Chem.* 8 (2020) 221. <https://doi.org/10.3389/fchem.2020.00221>.
- [18] L.E. Manzer, Catalytic synthesis of α -methylene- γ -valerolactone: a biomass-derived acrylic monomer, *Appl. Catal. A, Gen.* 272 (2004) 249–256. <https://doi.org/10.1016/j.apcata.2004.05.048>.
- [19] A.M.R. Galletti, C. Antonetti, V. De Luise, M. Martinelli, A sustainable process for the production of γ -valerolactone by hydrogenation of biomass-derived levulinic acid, *Green Chem.* 14 (2012) 688–694. <https://doi.org/10.1039/c2gc15872h>.
- [20] L. Minieri, S. Esposito, V. Russo, B. Bonelli, D. Serio, B. Silvestri, A. Vergara, A. Aronne, A Sol – Gel Ruthenium – Niobium – Silicon Mixed-Oxide Bifunctional Catalyst for the Hydrogenation of Levulinic Acid in the Aqueous Phase, *ChemCatChem* 9 (2017) 1476–1486. <https://doi.org/10.1002/cctc.201601547>.
- [21] Q. Yuan, H.H. van de Bovenkamp, Z. Zhang, A.S. Piskun, S. Sami, R.W.A. Havenith, H.J. Heeres, P.J. Deuss, Mechanistic Investigations into the Catalytic Levulinic Acid Hydrogenation, Insight in H/D Exchange Pathways, and a Synthetic Route to d 8 - γ -Valerolactone, *ACS Catal.* 11 (2021) 10467–10477. <https://doi.org/10.1021/acscatal.1c02662>.
- [22] M. Jędrzejczyk, E. Soszka, J. Goscińska, M. Kozanecki, J. Grams, A.M. Ruppert, The Influence of Carbon Nature on the Catalytic Performance of Ru/C in Levulinic Acid Hydrogenation with Internal Hydrogen Source, *Molecules* 25 (2020). <https://doi.org/10.3390/molecules25225362>.
- [23] Z. Yu, X. Lu, H. Bai, J. Xiong, W. Feng, N. Ji, Effects of Solid Acid Supports on the Bifunctional Catalysis of Levulinic Acid to γ -Valerolactone: Catalytic Activity and Stability, (2020) 1182–1201. <https://doi.org/10.1002/asia.202000006>.
- [24] F. Murena, S. Esposito, F.A. Deorsola, C. Galletti, M. V Prati, CO₂ abatement and CH₄ recovery at vehicle exhausts: Comparison and characterization of Ru powder and pellet catalysts, *Int. J. Hydrogen Energy.* 45 (2020) 8640–8648. <https://doi.org/10.1016/j.ijhydene.2020.01.120>.
- [25] R. Turco, A. Aronne, P. Carniti, A. Gervasini, L. Minieri, P. Pernice, R. Tesser, R. Vitiello, M. Di Serio, Influence of preparation methods and structure of niobium oxide-based catalysts in the epoxidation reaction, *Catal. Today.* 254 (2015) 99–103. <https://doi.org/10.1016/j.cattod.2014.11.033>.

- [26] P. Velmurugan, J. Shim, K.-J. Lee, M. Cho, S.-S. Lim, S.-K. Seo, K.-M. Cho, K.-S. Bang, B.-T. Oh, Extraction, characterization, and catalytic potential of amorphous silica from corn cobs by sol-gel method, *J. Ind. Eng. Chem.* 29 (2015) 298–303. <https://doi.org/https://doi.org/10.1016/j.jiec.2015.04.009>.
- [27] I. Rossetti, B. Bonelli, G. Ramis, E. Bahadori, R. Nasi, A. Aronne, S. Esposito, New Insights into the Role of the Synthesis Procedure on the Performance of Co-Based Catalysts for Ethanol Steam Reforming, *Top. Catal.* 61 (2018) 1734–1745. <https://doi.org/10.1007/s11244-018-0969-3>.
- [28] S. Esposito, A. Setaro, P. Maddalena, A. Aronne, P. Pernice, M. Laracca, Synthesis of cobalt doped silica thin film for low temperature optical gas sensor, *J. Sol-Gel Sci. Technol.* 60 (2011) 388–394. <https://doi.org/10.1007/s10971-011-2483-y>.
- [29] A. Aronne, E. Marenga, V. Califano, E. Fanelli, P. Pernice, M. Trifuoggi, A. Vergara, Sol-gel synthesis and structural characterization of niobium-silicon mixed-oxide nanocomposites, *J. Sol-Gel Sci. Technol.* 43 (2007) 193–204. <https://doi.org/10.1007/s10971-007-1563-5>.
- [30] A. Aronne, M. Turco, G. Bagnasco, P. Pernice, M. Di Serio, N.J. Clayden, E. Marenga, E. Fanelli, Synthesis of High Surface Area Phosphosilicate Glasses by a Modified Sol-Gel Method, *Chem. Mater.* 17 (2005) 2081–2090. <https://doi.org/10.1021/cm047768t>.
- [31] M. Cerruti, G. Magnacca, V. Bolis, C. Morterra, Characterization of sol-gel bioglasses with the use of simple model systems: a surface-chemistry approach, *J. Mater. Chem.* 13 (2003) 1279–1286. <https://doi.org/10.1039/B300961K>.
- [32] A. Aronne, M. Turco, G. Bagnasco, G. Ramis, E. Santacesaria, M. Di Serio, E. Marenga, M. Bevilacqua, C. Cammarano, E. Fanelli, Gel derived niobium-silicon mixed oxides: Characterization and catalytic activity for cyclooctene epoxidation, *Appl. Catal. A Gen.* 347 (2008) 179–185. <https://doi.org/10.1016/j.apcata.2008.06.011>.
- [33] B. Bonelli, I. Bottero, N. Ballarini, S. Passeri, F. Cavani, E. Garrone, IR spectroscopic and catalytic characterization of the acidity of imogolite-based systems, *J. Catal.* 264 (2009) 15–30. <https://doi.org/https://doi.org/10.1016/j.jcat.2009.03.003>.
- [34] A. Zecchina, S. Bordiga, G. Spoto, D. Scarano, G. Petrini, G. Leofanti, M. Padovan, C.O. Areàn, Low-temperature Fourier-transform infrared investigation of the interaction of CO with nanosized ZSM5 and silicalite, *J. Chem. Soc. {,} Faraday Trans.* 88 (1992) 2959–2969. <https://doi.org/10.1039/FT9928802959>.
- [35] B. Bonelli, M. Cozzolino, R. Tesser, M. Di Serio, M. Piumetti, E. Garrone, E. Santacesaria, Study of the surface acidity of TiO₂/SiO₂ catalysts by means of FTIR measurements of CO and NH₃ adsorption, *J. Catal.* 246 (2007) 293–300. <https://doi.org/https://doi.org/10.1016/j.jcat.2006.12.015>.
- [36] A. Katovic, G. Giordano, B. Bonelli, B. Onida, E. Garrone, P. Lentz, J.B. Nagy, Preparation and characterization of mesoporous molecular sieves containing Al, Fe or Zn, *Microporous Mesoporous Mater.* 44–45 (2001) 275–281. [https://doi.org/https://doi.org/10.1016/S1387-1811\(01\)00193-7](https://doi.org/https://doi.org/10.1016/S1387-1811(01)00193-7).
- [37] B. Bonelli, B. Onida, J.D. Chen, A. Galarneau, F. Di Renzo, F. Fajula, E. Garrone, Spectroscopic characterisation of the strength and stability of the acidic sites of Al-rich microporous micelle-templated silicates, *Microporous Mesoporous Mater.* 67 (2004) 95–106. <https://doi.org/https://doi.org/10.1016/j.micromeso.2003.10.007>.
- [38] S. Esposito, B. Silvestri, V. Russo, B. Bonelli, M. Manzoli, F.A. Deorsola, A. Vergara, A.

Aronne, M. Di Serio, Self-Activating Catalyst for Glucose Hydrogenation in the Aqueous Phase under Mild Conditions, *ACS Catal.* 9 (2019) 3426–3436. <https://doi.org/10.1021/acscatal.8b04710>.

- [39] M.E. Grigorev, S.P. Mikhailov, A. V Bykov, I.Y. Tiamina, L.Z. Nikoshvili, M.G. Sulman, A.L. Vasiliev, A.I. Sidorov, T. V dos Santos, M.R. Meneghetti, S.M.P. Meneghetti, L.M. Bronstein, V.G. Matveeva, Surface interactions with the metal oxide surface control Ru nanoparticle formation and catalytic performance, *Colloids Surfaces A Physicochem. Eng. Asp.* 610 (2021) 125722. <https://doi.org/https://doi.org/10.1016/j.colsurfa.2020.125722>.
- [40] W. Jiang, J.-P. Cao, X.-Y. Zhao, T. Xie, C. Zhu, J.-X. Xie, L. Zhao, M. Zhao, Y.-P. Zhao, J.-L. Zhang, Highly selective aromatic ring hydrogenation of lignin-derived compounds over macroporous Ru/Nb₂O₅ with the lost acidity at room temperature, *Fuel.* 282 (2020) 118869. <https://doi.org/https://doi.org/10.1016/j.fuel.2020.118869>.
- [41] O.A. Abdelrahman, H.Y. Luo, A. Heyden, Y. Román-Leshkov, J.Q. Bond, Toward rational design of stable, supported metal catalysts for aqueous-phase processing: Insights from the hydrogenation of levulinic acid, *J. Catal.* 329 (2015) 10–21. <https://doi.org/https://doi.org/10.1016/j.jcat.2015.04.026>.
- [42] Y. Kuwahara, Y. Magatani, H. Yamashita, Ru nanoparticles confined in Zr-containing spherical mesoporous silica containers for hydrogenation of levulinic acid and its esters into γ -valerolactone at ambient conditions, *Catal. Today.* 258 (2015) 262–269. <https://doi.org/https://doi.org/10.1016/j.cattod.2015.01.015>.