

AperTO - Archivio Istituzionale Open Access dell'Università di Torino

**Study of pre-treatments of fly ashes aimed to the reuse as construction materials: chemical and mineralogical characterization**

**This is the author's manuscript**

*Original Citation:*

*Availability:*

This version is available <http://hdl.handle.net/2318/1933823> since 2023-09-21T08:55:03Z

*Terms of use:*

Open Access

Anyone can freely access the full text of works made available as "Open Access". Works made available under a Creative Commons license can be used according to the terms and conditions of said license. Use of all other works requires consent of the right holder (author or publisher) if not exempted from copyright protection by the applicable law.

(Article begins on next page)



Università degli  
Studi di Torino



Università degli  
Studi di Ferrara



Università degli  
Studi di Modena e  
Reggio Emilia

# Study of pre-treatments of fly ashes aimed to the mineralogical reuse as construction materials: chemical and characterization

ENRICO DESTEFANIS<sup>1</sup>, CATERINA CAVIGLIA<sup>1</sup>, DAVIDE BERNASCONI<sup>1</sup>, COSTANZA BONADIMAN<sup>2</sup>, GIORGIA CONFALONIERI<sup>3</sup>, LINDA PASTERO<sup>1</sup>, RENZO TASSINARI<sup>2</sup> AND ALESSANDRO PAVESE<sup>1</sup>

<sup>1</sup>UNIVERSITÀ DEGLI STUDI DI TORINO, DIPARTIMENTO DI SCIENZE DELLA TERRA, TORINO, ITALY ([ENRICO.DESTEFANIS@UNITO.IT](mailto:ENRICO.DESTEFANIS@UNITO.IT))

<sup>2</sup>UNIVERSITÀ DEGLI STUDI DI FERRARA, DIPARTIMENTO DI FISICA E SCIENZE DELLA TERRA, FERRARA, ITALY

<sup>3</sup>UNIVERSITÀ DEGLI STUDI DI MODENA E REGGIO EMILIA, DIPARTIMENTO DI CHIMICA E SCIENZE GEOLOGICHE, MODENA, ITALY





Università degli  
Studi di Torino



Università degli  
Studi di Ferrara



Università degli  
Studi di Modena e  
Reggio Emilia

## INTRODUCTION

The **management of waste** and its **sustainable reuse** is one of the most important concern in our society in recent years, together with the increasing need to find primary materials without resorting to new extraction of resources. In this context, the thermovalorization of municipal solid waste (MSW) is currently the method that is spreading and replacing landfill disposal; the thermal treatment allows to reduce the volumes significantly, producing energy and returning **bottom ashes (BA)** and **fly ashes (FA)** in the measure of 20% and 5% of the total waste respectively. The MSW incineration BA are classified as non-hazardous waste and can be reused as a raw material after some physical-chemical treatments [4]. [The **FA**, on the contrary, **are classified as hazardous waste** and according to current legislation, they are usually subjected to vitrification treatments and stored in dedicated landfills; the hazard is due to the high content of soluble salts (chlorides and sulphates) and heavy metals (mainly Zn and Pb). Therefore, for their possible reuse as construction materials [3], [4], [6], [8]. (e.g. ceramic, cement, concrete aggregates) or base roads [5], a **preliminary stabilization step is required** which often **requires the use of significant quantities of energy**.

In the present work, **low energy cost methods are considered to reduce the dangerousness of FA** and consequently make them more easily treatable for their reintegration into the production cycles.

Among the methods, **washing of FA with water is examined**, to find the lowest L/S ratio in the reduction of salts and heavy metals, analysing the dissolution kinetics and the mineralogical content of fly ash before and after each washing treatment.

For a better definition of the kinetics, the FA are previously submitted to particle size separation to understand in which fractions the most dangerous substances are concentrated. Washing treatments can be useful **to remove or reduce soluble salts**, in particular chlorides, by using a different *liquid/solid* (L/S) ratio, in order to obtain a more suitable material for the solidification / stabilization treatments carried out by geopolymerization or in cement. The **eluates of washing** are also taken into consideration to evaluate the **recovery of elemental species of interest and the purification of the liquid phase with biochar**.





Università degli Studi di Torino



Università degli Studi di Ferrara



Università degli Studi di Modena e Reggio Emilia

## MATERIAL AND METHODS

Sample FA51

Preliminary Characterization

Presence of **Organic Compounds**  
**Particle Size Analysis**  
**Mineralogical Analysis**  
Reactivity

Characterization of the release in dissolution

Leaching test: kinetics and effects  
**L/S ratios**

Characterization of Treated **Material**

**Mineralogical Analysis**  
**Chemical Analysis**

Test on Treated **Material**

Reactivity  
Treatments of residual washing water





Università degli Studi di Torino



Università degli Studi di Ferrara




Università degli Studi di Modena e Reggio Emilia

## MATERIAL AND METHODS

TGA + FTIR analysis research of secondary organic compounds generated by not optimal combustion processes.



The presence of such compounds (e.g. dioxins and furans) would make the treatment very difficult.

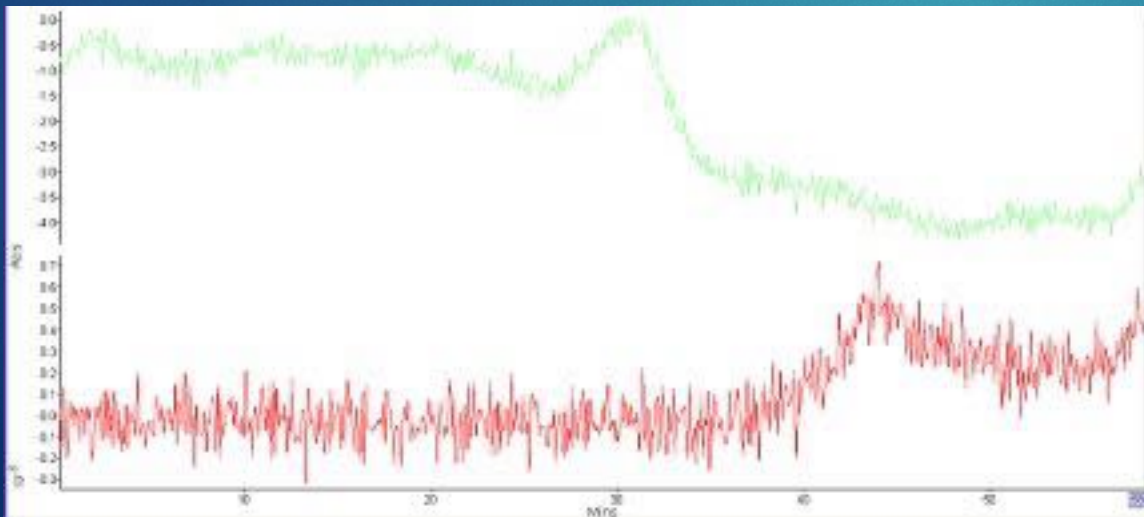

Analysis parameters: heating in an inert atmosphere from 35 to 900 °C; this temperature was maintained for 15 minutes in an oxidizing atmosphere (N<sub>2</sub>/O<sub>2</sub> ratio 3: 1).






## MATERIALS AND METHODS

### Particle Size Analysis

The FA51 sample was subjected to granulometric analysis for its dimensional characterization, the purpose of the approach was to evaluate any relationship between composition and size. Four sieves were used to define the average size of the FA. More than 50% by weight of the analysed sample falls in the class between 0.025 and 0.053 mm.

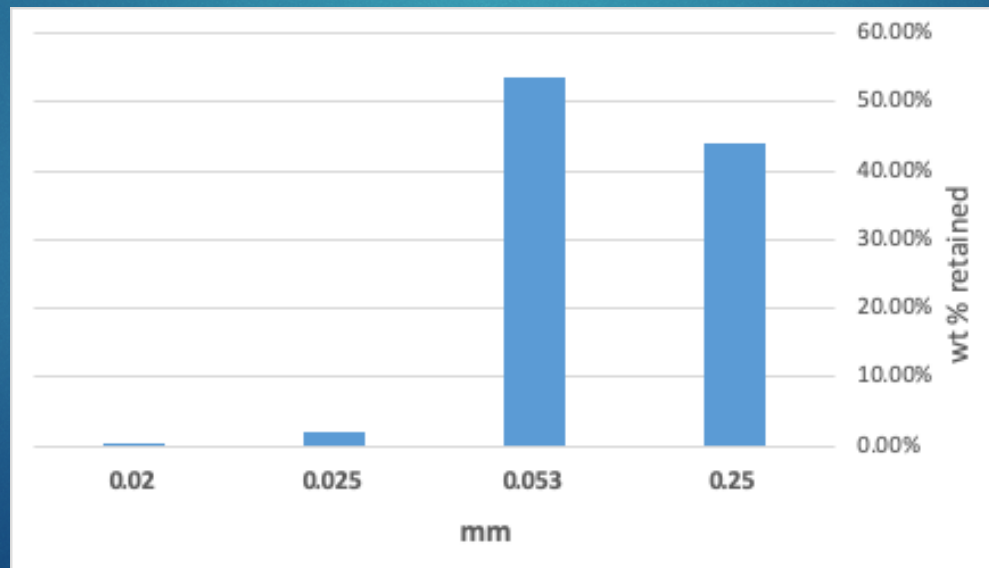

Università degli Studi di Torino



Università degli Studi di Ferrara



Università degli Studi di Modena e Reggio Emilia





## MATERIALS AND METHODS



Università degli Studi di Torino




Università degli Studi di Ferrara



Università degli Studi di Modena e Reggio Emilia

### Mineralogical Analysis

The sample was analyzed in XRD analysis using a Rigaku Miniflex system to define the main mineralogical phases that make up the particle size fractions.

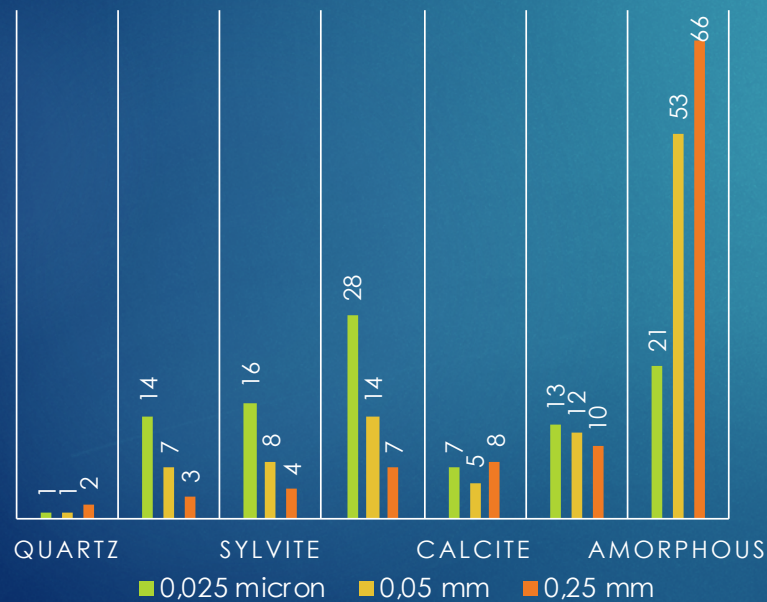

FA are mainly made up of phases with an alk-chloride and Ca-alk-sulfate chemistry; subordinately from  $\text{CaCO}_3$  and quartz. In particular in fig. the mineralogical phases are reported in detail and it is observed that in the finer fractions, the mineralogical phases defined at the expense of the amorphous fraction increase; among these in particular Halite and Sylvite for chlorides and Syngenite for sulphates. Less notably, an increase in Calcite and Anhydrite is observed. Quartz is slightly more abundant in the fraction  $> 0.25 \text{ mm}$ .





## MATERIAL TREATMENTS

### Water Washing

The water washing was tested at different L/S ratios in order to define the value corresponding to the maximum efficiency. Experiments were carried out with values of the L/S ratios between 2 and 50 to evaluate the kinetics of the dissolution reaction. FA samples were dissolved in ultrapure water.

The indicator parameters taken into consideration were the electrolytic conductivity of the solution and the weight loss detected on the residual FA sample.

The table shows the quantities of FA used for the washing tests.

V(H <sub>2</sub> O)/m(FA)	L/S
100 ml/2 g	50
100 ml/10 g	10
100 ml/20 g	5
100 ml/25 g	4
100 ml/50 g	2



Università degli Studi di Torino



Università degli Studi di Ferrara




Università degli Studi di Modena e Reggio Emilia





Leaching tests: reaction kinetics as a function of electrolytic conductivity and weight loss

2 **Increasing L/R ratio** 50

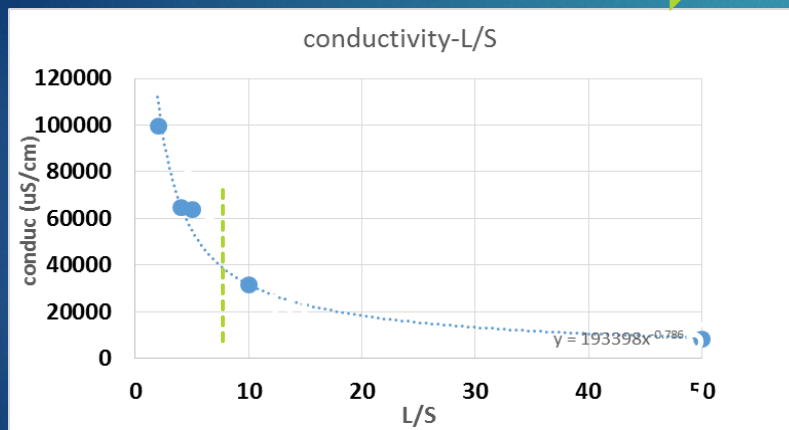

The conductivity values of the solutions range from 100 mS for lower L/S to 8.5 mS for higher L/S.

2 **Increasing L/R ratio** 50




The (%) weight loss values measured on the solid residues range from 12% for lower L/S to 30 for higher L/S.




The most suitable L/S range for the dissolution of the FA is therefore between 5 and 10. With L / S > 10, the use of water is too high compared to the amount of dissolution detected.

Fly ashes leaching chemical composition: results of the leaching test at different dilution ratios

2 Increasing L/R ratio 50

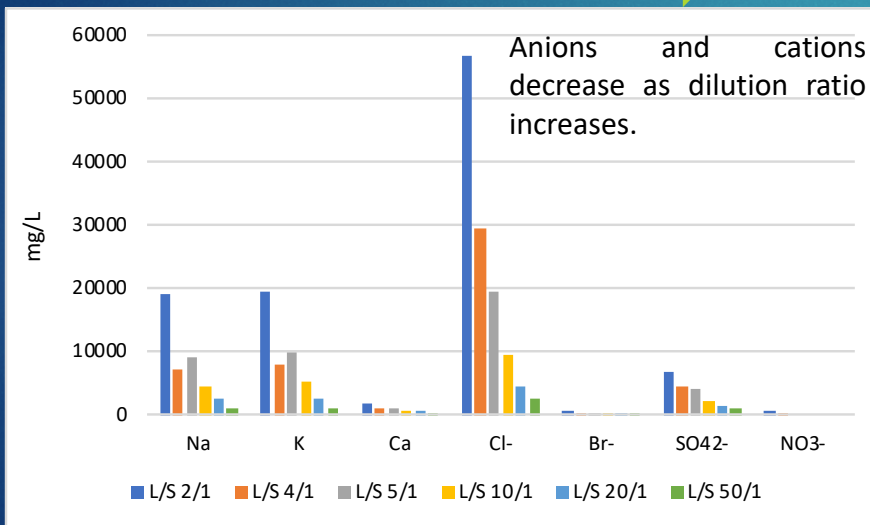

2 Increasing L/R ratio 50

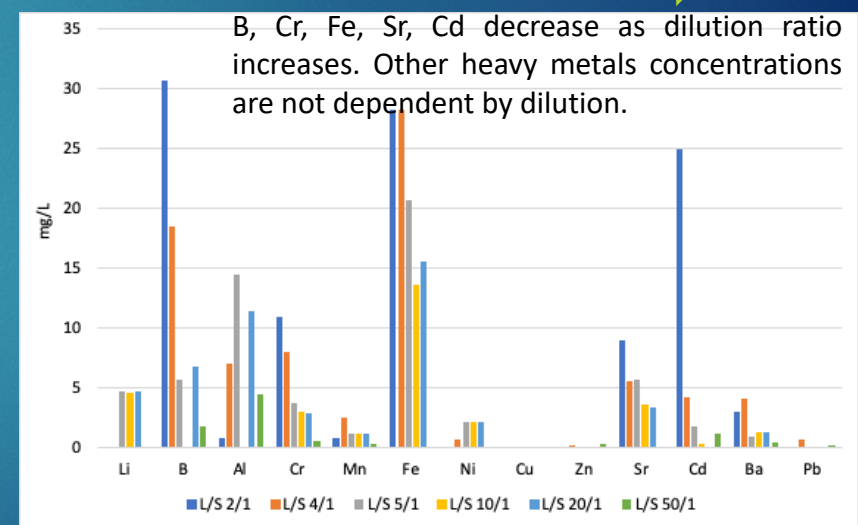

The most suitable L/S range for the decrease of chlorides and sulfates is between 5 and 10. With L / S > 10, the use of water is too high compared to the amount of dissolution detected.



## MATERIAL TREATMENTS



Università degli Studi di Torino



Università degli Studi di Ferrara



Università degli Studi di Modena e Reggio Emilia

XRD results after leaching test: analysis of residual phases at different L/S

Untreated fly ashes	L/S=2	L/S=4	L/S 5	L/S=10	L/S=20	L/S 50
<b>Amorphous</b>	Amorphous	Amorphous	Amorphous	Amorphous	Amorphous	Amorphous
<b>Halite</b>	Halite					
<b>Anidrite</b>	Anidrite	Anidrite	Anidrite	Anidrite	Anidrite	Anidrite
<b>Syngenite</b>	Syngenite	Syngenite	n.d.	n.d.	n.d.	n.d.
<b>Sylvite</b>	Sylvite	n.d.	n.d.	n.d.	n.d.	n.d.
<b>Calcite</b>	Calcite	Calcite	Calcite	Calcite	Calcite	Calcite
<b>Quartz</b>	Quartz	Quartz	Quartz	Quartz	Quartz	Quartz

KCl and NaCl are not detected by XRD in the residual solid with a ratio > of L/S 4.

The amorphous decreases from L/S 2 to 20 Syngenite





## MATERIAL TREATMENTS



Università degli Studi di Torino



Università degli Studi di Ferrara



Università degli Studi di Modena e Reggio Emilia


Washing Treatment: (L/S 10 = 5 mg fly ash/50 mL deionized water), 15 minutes

In this test fly ashes are washed in 5 steps. After the first step water has been reuse for the next washing step without any addition of volume. Total time: 15 min.

step	conductivity	total filtered volume (from 50 ml)
1	36200	45,2
2	34600	43,9
3	35000	43,4
4	35000	42,4
5	35000	41,1

L/S 10 at the step 1; L/S 8 at the step 5: no water volume added. Final volume of residual water: 41 ml.

The treatment system allows the water to recirculate. The electrolytic conductivity of the residual water is measured at the end of each wash and is brought back into the tank in contact with the FA with a peristaltic pump for a new wash. The treatment ends when there are no increases in EC value.

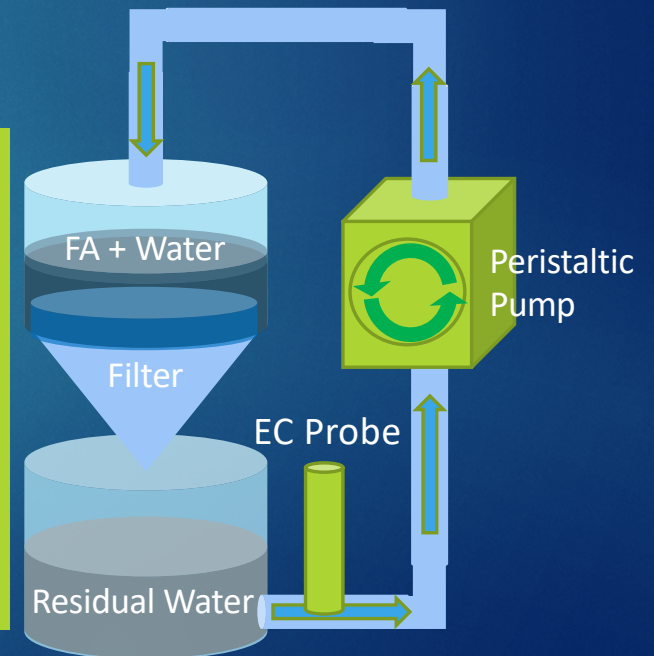




## TEST ON TREATED MATERIAL

Residual water purification: addition of BIOCHAR

Vegetal biochar was mixed to fly ashes leachates in a ratio 4:1 mixed into the solution for 24 h and then filtered. The reduction is very effective on Cd. A 20-30% reduction of chlorides and sulphates occurs, too.

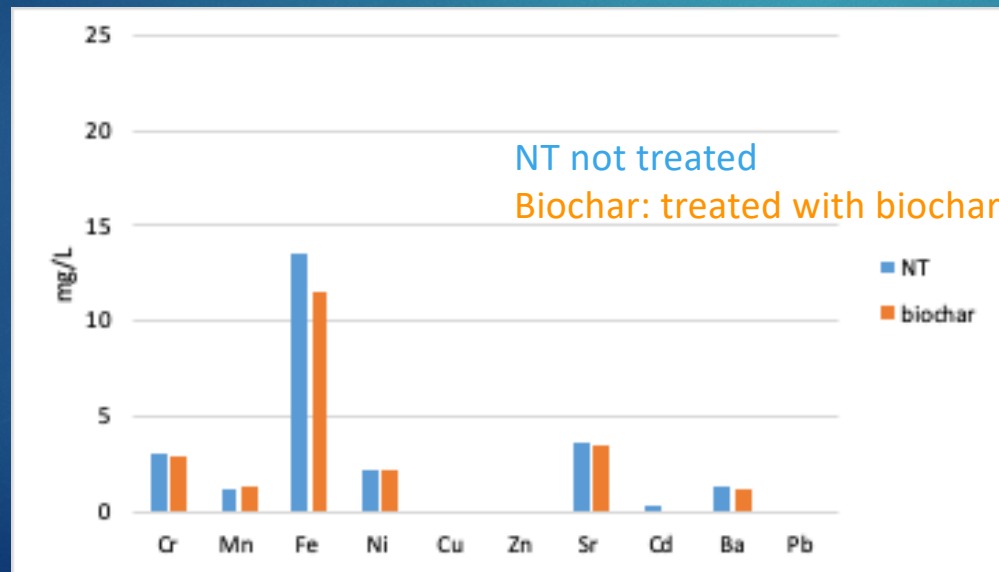

This study is still in progress, using different ratios of liquid/ biochar



Università degli Studi di Torino



Università degli Studi di Ferrara



Università degli Studi di Modena e Reggio Emilia






## TEST ON TREATED MATERIAL

Heavy metals and anions concentrations after washing treatment + leaching test L/S 10


Fly ashes were submitted to leaching test after the washing treatment

Before treatment: blue

After washing: orange

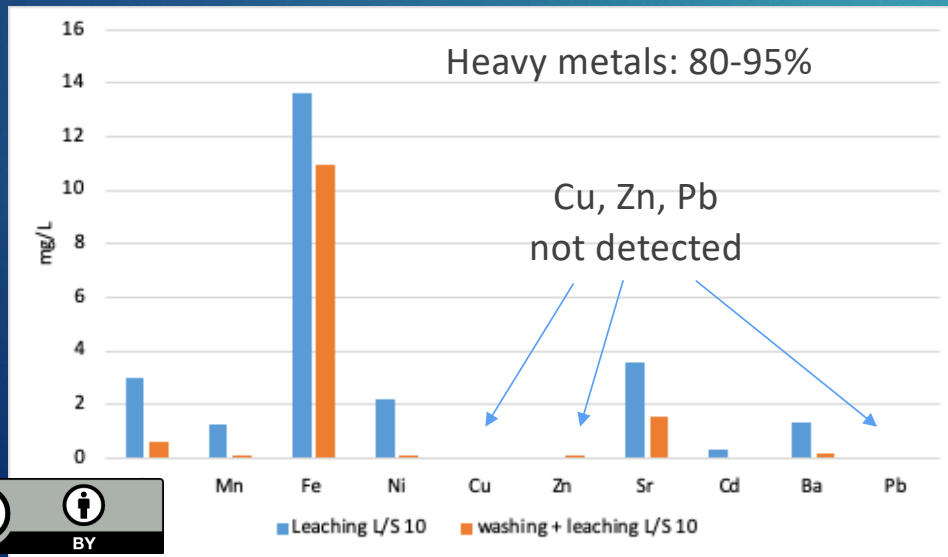

XRD tests after the washing test + leaching test are not available because of the stop caused by the COVID19...

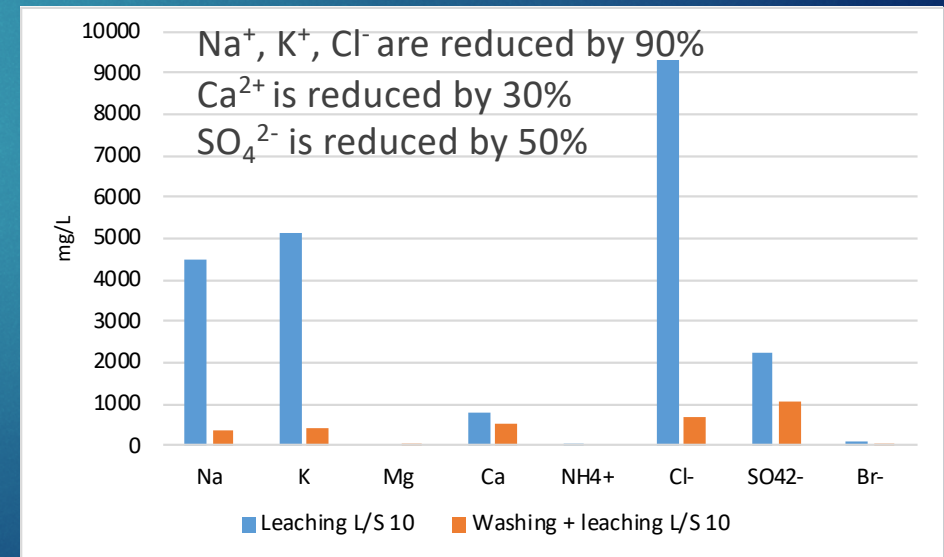

Università degli Studi di Torino



Università degli Studi di Ferrara



Università degli Studi di Modena e Reggio Emilia





## TEST ON TREATED MATERIAL

treatment products on FA material

Treatment products on FA material

SOLID RESIDUE  
80 % (wt) after  
washing



STABILIZATION

GEOPOLYMERIZATION

CEMENTS

LIQUID RESIDUE



High concentrations of chlorides and sulphates; biochar added to the solution **can reduce** heavy metals as **Cd** by 100%  
**Less effective on Cr and Ni reduction.** Cu, Pb, Zn not detected.



Università degli Studi di Torino



Università degli Studi di Ferrara



Università degli Studi di Modena e Reggio Emilia





Università degli Studi di Torino



Università degli Studi di Ferrara



Università degli Studi di Modena e Reggio Emilia

## Solid Residue: applications

The solid residue of fly ashes after a washing treatment shows a lower content of anions and cations (chlorides, sulphates,  $\text{Na}^+$ ,  $\text{K}^+$ ,  $\text{Ca}^{2+}$ , and some heavy metals). The presence of soluble salts (e.g. chloride and sulphates) is especially important for the reuse of fly ash as construction aggregates because it could have a negative impact by decreasing the mechanical properties of concrete and causing corrosion [1], [2], [3].

After the treatment fly ashes residues can be applied for:

- Cements [5], [6]
- Geopolymerization [7]
- Civil engineering applications, as roads, embankment...
- Brick and construction materials [8]





## Results and discussion

Washing treatments can be useful to remove most of the soluble salts and main heavy metals from fly ashes:

- The residual solid after leaching has a wt % from 15% to 20% depending to the leaching ratio of water/ solid
- After a leaching test with a ratio of  $L/S=4$  NaCl and KCl are not detected by X-Ray diffraction in the solid residues. Soluble salts and heavy metals significantly decrease.
- The washing treatment with  $L/S 10$  is required to reduce leaching concentrations up to 95% for chlorides and 50% for sulphates. Cr, Ni, Cd significantly decrease.
- Waste water can be treated by the mixing or filtration with biochar (the study is in progress) which reduces heavy metals like Cr, Cd, and Mn.
- The residual solid can be reused for civil engineering applications and construction materials.





## References

- [1] Evangelina Atanes, Blanca Cuesta-García, Antonio Nieto-Márquez, Francisco Fernández-Martínez. A mixed separation-immobilization method for soluble salts removal and stabilization of heavy metals in municipal solid waste incineration fly ash, *Journal of Environmental Management*, Volume 240, (2019), Pages 359-367.
- [2] Xiongfei Chen, Yafan Bi, Hongbo Zhang, Jia Wang, Chlorides Removal and Control through Water-washing Process on MSWI Fly Ash, *Procedia Environmental Sciences*, Volume 31, (2016), Pages 560-566
- [3] Xiaomin Dou, Fei Ren, Minh Quan Nguyen, Ashiq Ahamed, Ke Yin, Wei Ping Chan, Victor Wei-Chung Chang. Review of MSWI bottom ash utilization from perspectives of collective characterization, treatment and existing application, *Renewable and Sustainable Energy Reviews*, Volume 79, (2017), Pages 24-38.
- [4] Ferraro, A., Farina, I., Race, M. *et al.* Pre-treatments of MSWI fly-ashes: a comprehensive review to determine optimal conditions for their reuse and/or environmentally sustainable disposal. (2019), *Rev Environ Sci Biotechnol* 18, 453–471.
- [5] K.L Lin, K.S Wang, B.Y Tzeng, C.Y Lin. The reuse of municipal solid waste incinerator fly ash slag as a cement substitute, *Resources, Conservation and Recycling*, Volume 39, Issue 4, (2003), Pages 315-324.
- [6] Singh D., Kumar T., James B.E., Hanifa M. (2019) Utilization of MSWI Ash for Geotechnical Applications: A Review. In: Agnihotri A., Reddy K., Bansal A. (eds) *Environmental Geotechnology. Lecture Notes in Civil Engineering*, vol 31. Springer, Singapore
- [7] Yuancheng Li, Xiaobo Min, Yong Ke, Degang Liu, Chongjian Tang. Preparation of red mud-based geopolymer materials from MSWI fly ash and red mud by mechanical activation, *Waste Management*, Volume 83, (2019), Pages 202-208.
- [8] Xu, P.; Zhao, Q.; Qiu, W.; Xue, Y.; Li, N. Microstructure and Strength of Alkali-Activated Bricks Containing Municipal Solid Waste Incineration (MSWI) Fly Ash Developed as Construction Materials. *Sustainability* (2019), 11, 1283



Università degli  
Studi di Torino



Università degli  
Studi di Ferrara



Università degli  
Studi di Modena e  
Reggio Emilia

