

AperTO - Archivio Istituzionale Open Access dell'Università di Torino

Thermal analysis of the interaction of inorganic pigments with p(nBA/MMA) acrylic emulsion before and after UV ageing

This is the author's manuscript

Original Citation:

Availability:

This version is available <http://hdl.handle.net/2318/141618> since 2016-01-09T17:34:13Z

Published version:

DOI:10.1007/s10973-012-2869-2

Terms of use:

Open Access

Anyone can freely access the full text of works made available as "Open Access". Works made available under a Creative Commons license can be used according to the terms and conditions of said license. Use of all other works requires consent of the right holder (author or publisher) if not exempted from copyright protection by the applicable law.

(Article begins on next page)

Journal of Thermal Analysis and Calorimetry

Thermal analysis of the interaction of inorganic pigments with p(nBA/MMA) acrylic emulsion before and after UV ageing

--Manuscript Draft--

| | |
|--|---|
| Manuscript Number: | JTAC-D-12-00521R2 |
| Full Title: | Thermal analysis of the interaction of inorganic pigments with p(nBA/MMA) acrylic emulsion before and after UV ageing |
| Article Type: | Original Research |
| Corresponding Author: | Valentina Pintus AUSTRIA |
| Corresponding Author Secondary Information: | |
| Corresponding Author's Institution: | |
| Corresponding Author's Secondary Institution: | |
| First Author: | Valentina Pintus |
| First Author Secondary Information: | |
| Order of Authors: | Valentina Pintus Rebecca Ploeger Oscar Chiantore Shuya Wei Manfred Schreiner |
| Order of Authors Secondary Information: | |
| Abstract: | Differential scanning calorimetry (DSC) and thermogravimetry (TG) analyses were used to investigate the influence of inorganic pigments on the photo-oxidative stability of an acrylic emulsion binding medium. For this purpose, three different types of inorganic pigments such as ultramarine blue, cadmium red, and hydrated chromium oxide green were selected and mixed with an acrylic emulsion binding medium of poly(n-butyl acrylate/methyl methacrylate), p(nBA/MMA). These laboratory mixed paints were analysed before and after UV exposure for different periods of time. Additionally, three acrylic commercial paints such as ultramarine blue, cadmium red, and chromium oxide green from Liquitex® and Rembrandt® companies were also analysed. The results obtained with both thermal techniques suggested that ultramarine blue has the strongest influence on the photo-oxidative stability of the binding medium. A higher increase of the glass transition temperature T _g was observed by DSC analysis on the UV aged binder mixed with ultramarine blue. This result was confirmed by the TG investigations that showed a gradual decrease of the initial temperature of degradation as well as a strongest decrease of the final mass percent of the organic compounds. Similar results were measured from the Liquitex® and Rembrandt® blue paints. |
| Response to Reviewers: | General comments: The minor remarks by the referee 2 are very much appreciated and they helped us to improve much more the quality of this paper. We have carefully considered all three minor comments and have tried to reply in a precise way. We have especially homogenized the figures and tables according to the requirements of the Journal. Referee 2: 1- Introduction. After lines 19-20 pag.3, use the forms "TG" or "DSC" instead of using |

entire names.

Accepted. We have used the TG and DSC forms instead the entire names.

2- Experimental: page 5, lines 5-6: please specify that 31 and 83 are related to UV ageing and add a note related to the choice of these time periods.

Accepted. We have specified that 31 and 83 days correspond to the UV ageing and additionally we have explained the reason of the choice of these ageing periods adding the reference number 39 [ASTM International D2565 – 99 (Reapproved 2008) Standard Practice for Xenon-Arc Exposure of Plastics Intended for Outdoor Applications], which is related to that explanation.

3- page 9, line 55: there is a comma before the full stop to be erased.

Accepted. The comma has been erased.

4- Technical notes: Please use only black fonts in the text; the publisher will prepare the page-proof as it is.

Accepted. We have provided all text using only black fonts.

5- The exotherm and/or endotherm directions should be marked in figures demonstrating calorimetric results.

Accepted. The exotherm direction in the Fig 1 has been marked.

6- Please homogenize the titles of axes in all figures and table headings according to the standards of the Journal. (Example: Temperature/°C; Temperature/K; Mass/%; Heat flow/mW; Heat capacity/J g⁻¹K⁻¹ Time/min; Theta/degree; Wavenumber/cm⁻¹ etc.).

Accepted. We have homogenized the title of axes in all figures and table headings according to the standards of the journal.

7- Please use additional symbols for the designation in the figures. Please take it into consideration that the printed version of the Journal is black and white.

Accepted. We have provided the figure 1 as well as 3, 4, and 5 in black and white form using different symbols.

Supplementary Material

[Click here to download Supplementary Material: Cover letter submission of revised manuscript Pintus et al.doc](#)

Revision notes on the reviews of the manuscript

Pintus V, Ploeger R, Chiantore O, Wei S, Schreiner M: Thermal analysis of the interaction of inorganic pigments with p(*n*BA/MMA) acrylic emulsion before and after UV ageing

General comments: The minor remarks by the referee 2 are very much appreciated and they helped us to improve much more the quality of this paper.

We have carefully considered all three minor comments and have tried to reply in a precise way. We have especially homogenized the figures and tables according to the requirements of the Journal.

Referee 2:

1- Introduction. After lines 19-20 pag.3, use the forms "TG" or "DSC" instead of using entire names.

Accepted. We have used the TG and DSC forms instead the entire names.

2- Experimental: page 5, lines 5-6: please specify that 31 and 83 are related to UV ageing and add a note related to the choice of these time periods.

Accepted. We have specified that 31 and 83 days correspond to the UV ageing and additionally we have explained the reason of the choice of these ageing periods adding the reference number 39 [ASTM International D2565 – 99 (Reapproved 2008) Standard Practice for Xenon-Arc Exposure of Plastics Intended for Outdoor Applications], which is related to that explanation.

3- page 9, line 55: there is a coma before the full stop to be erased.

Accepted. The coma has been erased.

4- Technical notes: Please use only black fonts in the text; the publisher will prepare the page-proof as it is.

Accepted. We have provided all text using only black fonts.

5- The exotherm and/or endotherm directions should be marked in figures demonstrating calorimetric results.

Accepted. The exotherm direction in the Fig 1 has been marked.

6- Please homogenize the titles of axes in all figures and table headings according to the standards of the Journal. (Example: Temperature/°C; Temperature/K; Mass/%; Heat flow/mW; Heat capacity/J g-1K-1 Time/min; Theta/degree; Wavenumber/cm-1 etc.).

Accepted. We have homogenized the title of axes in all figures and table headings according to the standards of the journal.

7- Please use additional symbols for the designation in the figures. Please take it into consideration that the printed version of the Journal is black and white.

Accepted. We have provided the figure 1 as well as 3, 4, and 5 in black and white form using different symbols.

Thermal analysis of the interaction of inorganic pigments with p(*n*BA/MMA) acrylic emulsion before and after UV ageing

Valentina Pintus^{1,2}, Rebecca Ploeger³, Oscar Chiantore⁴, Shuya Wei¹, Manfred Schreiner^{1,2}

1. Institute of Science and Technology in Art, Academy of Fine Arts,
Schillerplatz 3, A-1010 Vienna, Austria

2. Institute of Chemical Technologies and Analytics, Analytical Chemistry Division, Vienna
University of Technology,

Getreidemarkt 9/161, A-1060 Vienna, Austria

3. National Gallery of Art, Washington DC USA

4. Department of Chemistry and Nanostructured Interfaces and Surfaces-Centre of Excellence,
University of Torino,

Via Pietro Giuria 7, 10125 Torino, Italy

v.pintus@akbild.ac.at

Tel.: +43 1 58816 8680, Fax: +43 1 58816 8699

Formatted: English (U.K.)

Field Code Changed

Formatted: Font color: Auto

Abstract

Differential scanning calorimetry (DSC) and thermogravimetry (TG) analyses were used to investigate the influence of inorganic pigments on the photo-oxidative stability of an acrylic emulsion binding medium. For this purpose, three different types of inorganic pigments such as ultramarine blue, cadmium red, and hydrated chromium oxide green were selected and mixed with an acrylic emulsion binding medium of poly(*n*-butyl acrylate/methyl methacrylate), p(*n*BA/MMA). These laboratory mixed paints were analysed before and after UV exposure for different periods of time. Additionally, three acrylic commercial paints such as ultramarine blue, cadmium red, and chromium oxide green from Liquitex[®] and Rembrandt[®] companies were also analysed. The results obtained with both thermal techniques suggested that ultramarine blue has the strongest influence on the photo-oxidative stability of the binding medium. A higher increase of the glass transition temperature T_g was observed by DSC analysis on the UV aged binder mixed with ultramarine blue. This result was confirmed by the TG investigations that showed a gradual decrease of the initial temperature of degradation as well as a strongest decrease of the final weightmass percent of the organic compounds. Similar results were measured from the Liquitex[®] and Rembrandt[®] blue paints.

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Keywords

Acrylic emulsion; inorganic pigments; ultramarine blue; UV ageing; DSC; TG;

1. Introduction

The composition of acrylic emulsion paints are particularly complex and their exact chemical compositions are kept a corporate secret by the paint manufacturers. In general, they are mainly a mixture of an acrylic emulsion as a binder, a pigment, and an extender (or filler). Through time the chemical and physical properties of the acrylic paint formulations have been improved using several chemically different additives. Depending on their type, additives are able to modify the colour, to improve the performance, to give resistance to heat degradation, and also to increase resistance to light degradation [1]. Particularly the pigments can influence the chemical stability of the acrylic binding media and they themselves can also be considered as additives. ~~The main commercially available white pigments are titanium dioxide (TiO₂), zinc oxide (ZnO), zinc sulphide (ZnS), and lithopone (a mixture of ZnS and BaSO₄). TiO₂ due to its whiteness and brightness because of its high refractive index and its relatively low and uniform absorption of visible light, is the most commonly used white pigment [2, 3] and it is also the main studied pigment [4, 5]. Spathis et al. [4] studied the photo-degradation of a series of Paraloid B72 films containing titanium dioxide (TiO₂) pigments. For this purpose, two crystallographic different kinds of TiO₂, anatase and anatase/rutile mixtures, were used in different concentration. The results obtained by Fourier transform infrared spectroscopy (FTIR), gel permeation chromatography, and solubility measurements demonstrated that the presence of anatase pigment significantly improved the photo stability of Paraloid B72 films [4]. In contrast, it has also been reported that anatase can form radicals and may degrade the polymers due to its high reactivity to ultraviolet (UV) radiation [6].~~

Among the coloured inorganic pigments, ultramarine blue, cadmium red and chromium oxide green are widely used in the acrylic emulsion paints. In particular, ultramarine blue pigment has a long history stretching back to ancient Egypt where the blue mineral lazurite was ground into a powder [72]. Ultramarine blue pigment is a sodium aluminium sulfosilicate with a generally accepted empirical formula (Na₆Al₆Si₆O₂₄S₄) [83]. The S₃⁻, S₂⁻ radical anions and S₄ or S₃Cl are placed inside a sodalite framework (also known as the “β-cage”) with the generic formula (Al₃Si₃O₁₂)³⁻ and they are responsible for the colours of the ultramarine pigment [94]. Inside the cage the Na⁺ cations balance the

Formatted: English (U.K.)

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

1
2
3
4
5
6
7
8
9 negative charges [405]. The S_3^- radical anions are mainly responsible for the blue colour
10 of the pigment. ~~It was demonstrated by using Raman spectroscopy that a higher amount~~
11 ~~of S_3^- chromophore with small amount of S_2^- – responsible for the yellow colour [11] –~~
12 ~~was present in the blue ultramarine than in the violet ultramarine, which contained an~~
13 ~~higher amount of the red chromophores (S_4 or S_3Cl) [12]. Furthermore, Del Federico et~~
14 al. [426] investigated the fading of the blue ultramarine pigments in simulated fresco
15 environments, which corresponded mainly to the decrease of the major S_3^-
16 chromophores. Generally, ultramarine blue has a good lightfastness and heat stability
17 (>350 °C) [83], but a low resistance to acids resulting in the conversion of the free
18 chromophores into H_2S and possibly elemental sulfur [426]. The ultramarine pigment
19 exhibited a low UV absorption and small protective effect on the UV stability of
20 unstabilized polypropylene [437]. However, the absorption alone is not the only
21 contributing influence on the UV stabilisation because the chemical and physical
22 properties of the pigment may also control the stabilisation of a polymer [448].
23 Additionally, a comparably low photo-oxidative stability of ultramarine blue commercial
24 acrylic paints was shown by colour measurements, Py-GC/MS and FTIR-ATR analyses
25 [459].

26
27
28
29
30
31
32 Compared to ultramarine blue, cadmium red is regarded as one of the most stable
33 pigments with a good hiding power, moderate tinting strength and good thermal stability
34 [4610]; however, it can oxidize to cadmium sulphate when exposed to light in presence
35 of moisture, leading to a consequent loss in colour intensity [72]. Generally, cadmium
36 red is considered a good stabilizer [4711] and it is especially more stable to bleaching
37 when exposed to UV light and air than cadmium yellow, which can oxidise into insoluble
38 colourless sulphates [4812] mainly due to the added zinc [4610]. Cadmium red is based
39 on cadmium sulfide and sulfoselenide (CdS , $xCdSe$) and is a product of a reaction
40 between cadmium and sulphur resulting with a hexagonal wurtzite lattice crystallization
41 form. The addition of the selenium in the intercrystalline lattice contributes to the
42 darkening of the red colour, up to a maximum useful cadmium selenide content of 50
43 mole percent [4812, 4913]. Although cadmium red acrylic paints are widely formulated
44 by the artist paint companies, its use is prohibited in many countries because of the
45 toxicity of the soluble cadmium [72].

46
47
48
49
50
51
52 Chromium oxide green pigment – also known as chromium sesquioxide – is
53 characterized by chromium(III) oxide, (Cr_2O_3), with an eskolaite mineral form and with a
54 dark olive-green shade. It is listed by the *Colour Index* (1971) as CI 77288/Pigment
55
56
57
58
59
60
61
62
63
64
65

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

1
2
3
4
5
6
7
8
9 Green 17 (PG17). It is often confused with chrome green and fast green pigments, which
10 are a blend of chromium yellow and iron blue or phthalocyanine pigments [4812];
11 mixtures can provide a colour range from light yellow green when the percentage of iron
12 blue is very low, to a dark green colour by increasing the percentage of iron blue [2014].
13 Additionally, there is a hydrated form - hydrated chromium sesquioxide ($\text{Cr}_2\text{O}(\text{OH}_4)$) -
14 listed as *Colour Index* CI 77289/Pigment Green 18 (PG18) and also called Viridian (from
15 Latin *Viridis*: green). The chromic oxides pigments are thermally stable and insoluble in
16 water [4812] and they are considered to provide good UV stabilization for polyolefins
17 [2415]. Unlike chromium oxide green, the thermal stability of Viridian pigment is low
18 because it starts to lose its water content at 95°C [72].

19 All of these three inorganic pigments have a critical influence on the photo-stability of an
20 acrylic emulsion binding medium when exposed to UV light. Consequently, UV light has
21 an important effect on the photo-oxidative stability of modern and contemporary works of
22 art based on acrylic emulsions, especially those exposed in outdoor conditions,
23 compared to those kept in indoor conditions such as museums or private collections. In
24 particular, the UV-B light (315 to 280 nm, middle UV) may cause discoloration, cracks,
25 and other damages on acrylic materials placed in external environments [2216]. Several
26 UV ageing studies have been carried out on the co-emulsion of poly(*n*-butyl
27 acrylate/methyl methacrylate), p(*n*BA/MMA), in order to investigate the long-term effects
28 on the physical and optical properties, especially considering wavelengths between 400
29 and 315 nm (UV-A, near UV), which are normally present in indoor conditions, [2317-
30 2519]. Since the late 1980s, most artists acrylic emulsion paints are based on a
31 p(*n*BA/MMA) emulsion binding medium, which ~~shows a superior hydrophobicity in~~
32 ~~comparison with poly(ethyl acrylate/methyl methacrylate), p(EA/MMA). They have~~ been
33 adopted and used by many paint companies [2620]. ~~It has been demonstrated that~~
34 ~~wavelengths in the UV region can cause chemical reactions in the polymer structure~~
35 ~~such as chain-breaking and cross-linking with the decomposition of the synthetic~~
36 ~~material [17]. It has been demonstrated that wavelengths in the UV region can cause~~
37 ~~chemical reactions in the polymer structure such as chain-breaking and cross-linking~~
38 ~~with the decomposition of the synthetic material [23].~~ Scaroni et al. [25] demonstrated
39 ~~by colour measurements that p(*n*BA/MMA) and p(EA/MMA) co-polymers have a high~~
40 ~~resistance to yellowing. Additionally, a decreased solubility of all p(*n*BA/MMA) copolymer~~
41 ~~paint samples in comparison with p(EA/MMA) copolymer paints was determined.~~
42 ~~Chiantore et al. [27] used a Xenon light source filtered for $\lambda < 295$ nm to investigate acrylic~~

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9
10 ~~polymers characterized by long ester groups, such as *n*-butyl groups, and observed a~~
11 ~~fast and extensive cross-linking in combination with some fragmentation, due to the~~
12 ~~favorable oxidation on the tertiary carbon of the butyl group. In addition, some attention~~
13 ~~has been paid to the competition between chain scission reactions and cross-linking~~
14 ~~reactions during the photo-oxidative degradation, which is mainly controlled by the glass~~
15 ~~transition temperature T_g of the polymer. Polymer chains above their T_g s (surface glass~~
16 ~~temperature transition) would preferentially undergo cross-linking [28]. Additionally, the~~
17 ~~development of cross-linking in two commercial acrylic dispersions — BA/MMA and~~
18 ~~EA/MMA formulations — after accelerated photo-ageing was directly related to the~~
19 ~~progressive reduction of ultimate tensile strengths, although the moderate increase of~~
20 ~~the T_g values studied by differential scanning calorimetry (DSC) remains in an~~
21 ~~acceptable range of use [29].~~

Formatted: English (U.K.)

22
23
24
25
26 DSC and ~~thermal gravimetry (TG)~~ analyses have been widely used in the field of art [21-
27 ~~24]~~ and ~~analysis~~ represent two valuable techniques for the study of the thermal
28 properties of acrylic emulsion materials. The determination of the glass transition
29 temperature (T_g) by differential scanning calorimetry (DSC) is a useful method to define
30 the state of an acrylic material at room temperature. Below the T_g the material is usually
31 in a glassy and hard state and above the T_g is normally in a soft and rubbery state. Thus
32 a change of the T_g , possibly due to the addition of a pigment or to the UV ageing, can
33 indicate whether the material becomes more brittle and fragile (increase of the T_g) or
34 more tacky and soft (decrease of the T_g). Additionally, DSC has been applied for the
35 investigation of paint media in order to analyze the influences of the pigment and of the
36 binding medium based on the shape of the thermal analysis curve [25].

Formatted: English (U.K.)

37
38
39
40
41 The thermogravimetry (TG) analyses carried out under an inert atmosphere and non-
42 isothermal mode have commonly been applied to understand the thermal degradation
43 behaviour and the challenging composition of different modern synthetic materials used
44 in the field of modern and contemporary art [18, 19, 26-29]. The organic component of
45 acrylic paints, mainly based on the acrylic binding medium, usually decomposes in a
46 range of temperature between 300 and 500 °C [30], where also several additives might
47 thermally react. In contrast, the inorganic part, consisting of inorganic pigments and/or
48 different fillers is quite stable at high temperature, although some decomposition
49 reactions may occur depending on their type and origin. Furthermore, ~~the thermoal~~
50 gravimetry ~~ie~~ (TG) technique was also used to determine the amount of different organic
51 components in several pigmented artists' acrylic emulsions under different ageing

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4
5
6
7
8
9 conditions [3026]. DSC has been applied for the investigation of paint media in order to
10 analyze the influences of the pigment and of the binding medium based on the shape of
11 the thermal analysis curve [31].
12

13
14 ▲
15 So far, pigmented and un-pigmented modern acrylic materials have been characterized
16 and identified [159, 2216, 3026, 3231-3837], but detailed data on the influence of
17 inorganic pigments on the stability of acrylic emulsion paint films are still lacking. As UV
18 ageing studies of unpigmented synthetic binding media does not accurately reflect the
19 UV ageing of synthetic paints because of all other components present that can also
20 contribute significantly to their degradation under UV, the exact context of the
21 degradation still remained unclear in many cases. Therefore, more studies concerning
22 the influence of inorganic pigments on acrylic emulsions are desirable. Especially, the
23 influence of UV-B light on the stability/degradation of materials in works of art in outdoor
24 environments has been rarely investigated. Pintus et al. [2216] studied the influence of
25 UV-B light on pure acrylic emulsions as well as their mixture with different inorganic
26 pigments showing material alterations and the formation of new products, which were
27 recorded by FTIR-ATR. Generally, these changes were more pronounced when the
28 acrylic binding media were mixed with pigments. Moreover, similar results were
29 observed for different acrylic commercial paints [159]. Dimers, trimers and sesquimers
30 were already detected at lower temperatures (<300°C) by Py-GC/MS double-shot
31 technique, which demonstrated the important UV impact on the thermal stability of the
32 acrylic paints [159, 2216].
33

34
35 Based on these previous studies [159, 2216], the influence of three different inorganic
36 pigments, ultramarine blue, cadmium red, and hydrated chromium oxide green, on the
37 stability of a co-p(nBA/MMA) acrylic emulsion when exposed to the UV light, was
38 investigated by differential scanning calorimetry (DSC) and thermogravimetry (TG)
39 analyses on the prepared samples before and after UV exposure. Both thermal
40 techniques are fundamental for studying the thermal stability and behavior/behaviour of a
41 polymeric material. In particular, a change of the glass transition temperature in an
42 acrylic emulsion film is considered as an indicator of photo-oxidative degradation [2938].
43 Additionally, the above mentioned colours of two different commercial companies
44 (Liquitex® and Rembrandt®), which were previously characterized by Py-GC/MS as a co-
45 p(nBA/MMA) acrylic emulsions binding medium [159], were selected for a comparison
46 with the self-made samples. Unfortunately, it was not possible to find the hydrated
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

- Formatted: Font color: Auto, English (U.K.)
- Formatted: Font color: Auto
- Formatted: English (U.K.)
- Formatted: Font color: Auto, English (U.K.)
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: Font color: Auto, English (U.K.)
- Formatted: Font color: Auto
- Formatted: Font color: Auto, English (U.K.)
- Formatted: Font color: Auto
- Formatted: Font color: Auto, English (U.K.)
- Formatted: Font color: Auto
- Formatted: Font color: Auto, English (U.K.)
- Formatted: Font color: Auto
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: Font color: Auto
- Formatted: Font color: Auto
- Formatted: Font color: Auto
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: Font color: Auto, English (U.K.)
- Formatted: Font color: Auto
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: Font color: Auto, English (U.K.)
- Formatted: Font color: Auto
- Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9 chromium oxide green paints based on a co-p(*n*BA/MMA) acrylic binder. The objective of
10 this study is to investigate the influence of three widely used inorganic pigments on the
11 photo-oxidative stability of a well-known p(*n*BA/MMA) acrylic emulsion.
12
13

14 2. Experimental

15
16 To evaluate the influence of three inorganic pigments on the photo-oxidative stability of a
17 p(*n*BA/MMA) acrylic emulsion binding medium, each specimen (Table 1) was analyzed
18 by differential scanning calorimetry (DSC) and thermogravimetry (TG) analyses before
19 and after UV exposure, respectively 31 and 83 days of UV ageing. According to the
20 ASTM 2565 – 99 standard [39], the exposure time of the specimens under UV light was
21 established from a long-term evaluation and control of the material. This evaluation was
22 periodically carried out under an optical microscope – to observe any change in the
23 morphology of the surface – and by Fourier transform attenuated total reflection (FTIR-
24 ATR) analysis. 31 and 83 days of UV ageing were then chosen, because of noticeable
25 changes.
26
27

Formatted: Font color: Auto

28
29 Due to the need of a relatively high amount of sample material for DSC and TG
30 analyses, it was not possible to investigate the pure acrylic binding medium Plextol®
31 D498 after 31 and 83 days of UV ageing. By lightly scraping the paint film from the glass
32 slide with the help of a scalpel, a higher brittleness and a decreased plasticity were
33 observed, which could be considered as an effect of the photo-oxidative ageing.
34
35
36
37

38 2.1 Sample preparation

39
40 Approximately 60 mg of a pure acrylic binding medium (Plextol® D498) was cast
41 separately on glass plates, which produced a dried film with a thickness in a range of 10-
42 20 µm. Additionally, different mock-ups of pure Plextol® D498 mixed with inorganic
43 pigments such as ultramarine blue, cadmium red, and hydrated chrome oxide green in a
44 mixing ratio of about 3:1 were cast on glass plates. The dried film thickness of these
45 paint samples was approximately in the range of 30-40 µm. The acrylic emulsions
46 binding medium and the inorganic pigments were products of KREMER (Kremer
47 Pigmente GmbH & Co. KG, Germany). Moreover, approximately 200 mg of three acrylic
48 paint colours (ultramarine blue, cadmium red, and chromium oxide green) from 2
49 companies (Liquitex® and Rembrandt®) were also cast on glass plates, producing a dried
50 film with an average thickness of 130 µm. In total, 12 identical specimens for the pure
51 acrylic binding medium, three for each pigment mixed with an acrylic emulsion, as well
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9 as three for each commercial acrylic paint colour were made, in order to obtain a
10 sufficient number of samples for the tests in the UV chamber. After drying for 24 h at
11 room temperature (pure acrylic binding media and mixed with pigments) and for 3
12 months at room temperature (commercial acrylic paint colours), the glass plates were
13 arranged in the UV chamber, except for the standard samples representing the unaged
14 compositions. The commercial acrylic paints were left to dry for a longer period of time in
15 comparison to the pure and mixed acrylic binding media due to their higher film
16 thickness which required longer drying time [39,40].

21 2.2 UV exposure

22 UV exposure of the samples was carried out in a UV chamber, UVACUBE SOL 2/400F,
23 produced by Dr. Hönle GmbH UV-Technology, Germany. The UV light radiation source
24 was supplied by a 910 W/m² Xenon arc solar simulator with an incorporated H2 filter,
25 which provides radiation with wavelengths between 295 nm and 800 nm. The chamber
26 temperature was 48.8 °C. No control of the relative humidity (RH) was possible in the UV
27 exposure chamber used, therefore the RH varied between 30 and 35% depending on
28 the RH in the ambient atmosphere. Samples were aged for 31 and 83 days,
29 respectively.
30
31
32
33

34 2.3 Differential Scanning Calorimetry (DSC)

35 Differential scanning calorimetry analyses were performed with a DSC Q200
36 instrument (TA Instruments – Waters LLC Lukens Drive New Castle, DE 19720).
37 Approximately 7 mg of the sample material were scraped from each glass slide for the
38 analysis. The differential scanning calorimetry (DSC) analyses were performed at a
39 heating rate of 20 °C/min from -10 °C (held for 2 min) to 150 °C (held for 2 min), then
40 cooled to -10 °C (held for 2 min) at a heating rate of 20 °C/min and repeated for a
41 second time under a nitrogen air flow of 50 mL/min. TA Universal Analysis software (TA
42 Instruments, USA) was used for visualising the results. The inflection point was
43 considered for the calculation of the T_g using the TA program. The T_g was taken at the
44 second heating cycle.
45
46
47
48
49
50
51

52 2.4 Thermal Gravimetry (TG)

53 Thermal gravimetry analyses were performed with a TGA Q500 instrument (TA
54 Instruments – Waters LLC Lukens Drive New Castle, DE 19720). The TG instrument
55
56
57
58
59
60
61
62
63
64
65

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9 was equipped with an autosampler and an ultra-sensitive thermo balance. The nitrogen
10 gas flow was set at 40 mL/min for the tare and at 60 mL/min for the samples analyses.
11 The visualisation of the results was performed with the Universal Analysis software (TA
12 Instruments, USA). For the analyses approximately 15-12 mg of sample material were
13 scraped for each glass slide. Thermal gravimetric analyses were carried out at a
14 heating rate of 10 °C/min from 30 °C up to 800 °C.
15
16
17
18

19 3. Results and Discussion

20 ~~To evaluate the influence of three inorganic pigments on the photo-oxidative stability of a~~
21 ~~p(nBA/MMA) acrylic emulsion binding medium, each specimen (Table 1) was analyzed~~
22 ~~by differential scanning calorimetry (DSC) and thermal gravimetry (TG) analysis before~~
23 ~~and after UV exposure, respectively 31 and 83 days. Due to the need of a relatively high~~
24 ~~amount of sample material for DSC and TG analysis, it was not possible to investigate~~
25 ~~the pure acrylic binding medium Plextol® D498 after 31 and 83 days of UV ageing. By~~
26 ~~lightly scraping the paint film from the glass slide with the help of a scalpel, a higher~~
27 ~~brittleness and a decreased plasticity were observed, which could be considered as an~~
28 ~~effect of the photo-oxidative ageing.~~
29
30
31
32
33

Formatted: English (U.K.)

34 3.1 Differential Scanning Calorimetric analysis (DSC) results

35 ~~The determination of the glass transition temperature (T_g) by differential scanning~~
36 ~~calorimetry (DSC) is a useful method to define the state of an acrylic material at room~~
37 ~~temperature. Below the T_g the material is usually in a glassy and hard state and above~~
38 ~~the T_g is normally in a soft and rubbery state. Thus a change of the T_g , possibly due to~~
39 ~~the addition of a pigment or to the UV ageing, can indicate whether the material~~
40 ~~becomes more brittle and fragile (increase of the T_g) or more tacky and soft (decrease of~~
41 ~~the T_g).~~ DSC analysis of the unaged mock-ups indicated two material properties: 1) The
42 glass transition temperature T_g and 2) the melting temperature T_m of the surfactant. All
43 values are reported in Table 2. The pure acrylic binding medium as well as its mixture
44 with pigments shows the T_g around 10 °C. These results suggest that the addition of
45 pigments does not influence the T_g of the paint films extensively, which corresponds to a
46 value generally near or below room temperature. The low influence probably results from
47 the weak interaction between the pigments and the acrylic binder [4041]. The T_g
48 endothermic signal of the Plextol® D498 binding medium was followed by a peak at
49 around 55 °C. The detection of this peak corresponds to the melting temperature T_m of
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

the surfactant, previously identified as a polyethoxylated PEO-based non-ionic surfactant [2216]. The surfactant is an important component in the acrylic emulsions, mainly used to obtain a stable dispersion of the polymer particles in the water, lower the interfacial tension between the monomer and the water [22].

In contrast to these results from the pure acrylic material, the DSC curve of the acrylic binding medium when mixed with hydrated chromium oxide green did not show any endothermic peak. The interaction of the green pigment with the binding medium probably caused an early exudation stage of the surfactant from the matrix to the surface with a successive degradation or volatilization reactions. It is well known that the non-ionic surfactants have the tendency to migrate towards the surface of the acrylic emulsion paint films, causing changes in gloss and surface roughness [4442], and which may undergo total degradation under UV exposure [159, 2216, 4243]. It has to be stressed that the mock-ups were prepared only with a mixture of the acrylic emulsion binding medium with the inorganic pigment. No other components were added, although there probably would be additives in industrial products. These additives could possibly improve the stabilization stability of the chemical system which are probably used in industrial products.

Depending on the type of pigment mixed with the acrylic binding medium some different behaviors/behaviours could be noticed concerning the UV aged samples. In particular, the ultramarine blue pigment affected the photo-oxidative stability of the binding medium more than the other pigments. After UV ageing for 31 and 83 days the T_g increased by more than 7 °C, when the binder was mixed with the ultramarine blue pigment (Table 2). This is possibly related to cross-linking in the polymer network during the photo-oxidative ageing, which influences the motion of the segment chains in the macromolecules [2938]. On the other hand, the loss of organic material by the evaporation of low molecular weight/mass degradation products that would otherwise act as plasticizing agents, with a consequent increase of the T_g into the paint film [4327] could also take place. Normally, the soluble fraction of the acrylic emulsion decreases in molecular weight (MW)/mass during UV ageing [2418] by the loss of volatile scission products and other molecules that can evaporate or be lost. The loss of molecules is most probable/probably due to the formation of low molecular weight/mass molecules such as unspecific aldehyde, lactones, and acidic oxidation products found in these acrylic emulsions paints and demonstrated in the previous study by FTIR-ATR spectroscopy [2216]. Independently from the type of inorganic pigment, the endothermic

- Formatted: English (U.K.)
- Formatted: Font color: Auto, English (U.K.)
- Formatted: Font color: Auto
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: Font color: Auto, English (U.K.)
- Formatted: English (U.K.)
- Formatted: Font color: Auto, English (U.K.)
- Formatted: Font color: Auto
- Formatted: English (U.K.)
- Formatted: Font color: Auto, English (U.K.)
- Formatted: Font color: Auto
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: Font color: Auto, English (U.K.)
- Formatted: English (U.K.)
- Formatted: Font color: Auto, English (U.K.)
- Formatted: Font color: Auto
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: Font color: Auto, English (U.K.)
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: Font color: Auto, English (U.K.)
- Formatted: Font color: Auto
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: English (U.K.)
- Formatted: Font color: Auto
- Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

peak of the non-ionic surfactant totally disappeared after 31 and 83 days of UV ageing in all mock-ups, corresponding to the total loss of the surfactant in the acrylic material due to the photo-ageing reactions in accordance to a previous work [2216].

The comparison of the unaged and aged mock-ups with the unaged and aged commercial acrylic colours shows different behaviors/behaviours. Unlike the mock-ups, all unaged commercial acrylic paints showed two broad transitions, an exothermic one in the temperature range of approximately 0-50 °C, and one endothermic between 50-100 °C shown as example in Figure 1, for Liquitex® Blue. The initial broad exothermic transition affects the measurement and evaluation of the T_g that is related with a small change in heat capacity. This may be due to the interaction between organic and inorganic components in the paint film since most of the analyzed paints contain inorganic fillers (Table 1). These latter and especially nanofillers are known to interact strongly with the polymer forming an inter-phase region [4041]. Their interaction restricts the polymer chains mobility [4041] with a consequent complexity in the determination of the T_g . The diffuse endothermic process might be correlated to the loss of volatile components such as absorbed water.

In all unaged Liquitex® colours the T_m of the surfactant – previously identified as the PEO based non-ionic surfactant [159] – was detected in the first heat cycle at around 43 °C and accompanied at lower temperature (38 °C) by another endothermic peak with a smaller area (Fig. 1). This double-melting behavior/behaviour of the non-ionic surfactant may be due to a preliminary melting at low temperature of minor crystals. Double-melting peaks have been observed during a DSC analysis in many semicrystalline polymers [4444]. They are normally attributed to the melting of imperfect crystals formed during the annealing stage and their recrystallization [4444]. Furthermore, the presence of a poly(acrylic) type thickener or an anionic surfactant [159] which is used with non-ionic PEO surfactants to improve the electrostatic stabilization of the inorganic pigment in the emulsion [3736, 4445], likely also influences the melting point of the surfactant. The increase in the amount of the PEO surfactant in a non-ionic/anionic blend (PEO/Carbopol) with the subsequent variation of the melting peak of the PEO observed in the DSC curve has been reported [4646].

In contrast to these results, the DSC curves of all Rembrandt® colours do not show any surfactant melting peak, likely because of their very low concentration. The melting peak of the surfactant might also vary depending on the amount of the pigment added in the paint. For instance, Hagan et al. [4728] demonstrated by DSC analysis that the

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9 magnitude of the melting peak of the surfactant in a latex paint film diminishes in area by
10 increasing of the amount of TiO₂ in the mixture, suggesting that the pigment affects the
11 structure of the surfactant within the film.

12
13 By comparing the obtained results of the unaged and aged commercial acrylic paints
14 after 31 and 83 days of UV exposure, a general increase of the T_g was observed in all
15 acrylic paints. In particular, a significant increase in the T_g of almost 10 °C (see Table
16 2) was found in the Rembrandt® paints, which showed a lower stability in comparison to
17 the Liquitex® colour paints. Similarly, to the aged mock-ups, the increase in the T_g can be
18 related either to a major network change in the polymer binder due to some cross linking
19 reactions or to the evaporation of volatile degradation products. This alteration can
20 possibly explain the brittle handling behavior/behaviour of the aged paint films.

21
22 Moreover, the UV ageing affected the stability of the non-ionic surfactant in all Liquitex®
23 films in accordance to the results reported in a previous study [459]. Similar to the mock-
24 ups samples, the double melting peak was not visible anymore already after 31 days of
25 UV ageing.

3.2 Thermal Gravimetry (TG) results

32 ~~The thermal gravimetric analysis carried out under an inert atmosphere and non-~~
33 ~~isothermal mode have commonly been applied to understand the thermal degradation~~
34 ~~behavior and the challenging composition of different modern synthetic materials used in~~
35 ~~the field of modern and contemporary art [24, 25, 30, 43, 48, 49]. The organic~~
36 ~~component of acrylic paints, mainly based on the acrylic binding medium, usually~~
37 ~~decomposes in a range of temperature between 300 and 500 °C [50], where also~~
38 ~~several additives might thermally react. In contrast, the inorganic part, consisting of~~
39 ~~inorganic pigments and/or different fillers is quite stable at high temperature, although~~
40 ~~some decomposition reactions may occur depending on their type and origin.~~

41
42 The initial and final degradation temperature (°C) and the weightmass percentages (%)
43 of the final organic and inorganic-residue components of the analyzed pure binding
44 medium analyzed, its mixture with pigments and the commercial acrylic paints before
45 and after 31 and 83 days of UV ageing, are summarized in Table 3. In addition the
46 weightmass loss percentage (%) of the organic components for each unaged and aged
47 sample is shown in figure 2.

48
49 As it is reported in Table 3, the TG results of the unaged pure acrylic binding medium as
50 well as its mixture with the inorganic pigments (Fig. 3a, 3b) are mainly characterized by

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1
2
3
4
5
6
7
8
9 a single step degradation process between approximately 300 °C and 440 °C. The ~~weightmass~~ loss (%) at this step is mainly associated with the decomposition of the acrylic binder based on the co-polymer aqueous dispersion of poly(*n*-butyl acrylate/methyl methacrylate), p(*n*BA/MMA), ~~which is expected thermal degradation behavior of the acrylic polymers~~. Mostly monomers and oligomers are formed by the conversion of the macromolecular chains into volatile compounds at high temperatures [3026]. ~~For the unaged binding medium and its mixture with pigments it was possible to determine the final temperature of the single degradation process which was around 440 °C.~~ A small residue of about 8% of ~~weightmass~~ and an initial degradation temperature at 299 °C were observed in the TG curve of the unaged binding medium.

11 **Formatted:** English (U.K.)
12
13
14
15
16
17
18 In addition to the single step degradation process, the TG curve of the cadmium red film (Fig. 4) is characterized by a slight loss of ~~weightmass~~ at approximately 750 °C; this is probably related to the decomposition of the cadmium selenide [5447].

19 **Formatted:** Font color: Auto, English (U.K.)
20 **Formatted:** Font color: Auto
21 **Formatted:** English (U.K.)
22 **Formatted:** English (U.K.)
23
24 The comparison between the results obtained for the unaged and UV aged mock-ups showed that the p(*n*BA/MMA) co-polymer is more sensitive to the photo-oxidative reactions when ultramarine blue is added into the matrix (Fig. 3a). ~~While the final degradation temperature in the TG curves of the ultramarine blue films remained basically the same,~~ the initial temperature of decomposition in the TG curves of the ~~blue ultramarine films~~ decreased after 83 days of UV exposure, dropping from 311 to 121 °C (Table 3). This change in the thermal stability is accompanied by a decrease of the final ~~weightmass~~ percent of the organic component from approximately 64 to 45%, which can indicate a pronounced decomposition of the acrylic binding medium into volatile compounds through chain scission reactions during UV exposure and consequently loss of the volatile degradation species. The ultramarine blue pigment, which is known to decompose in aqueous solution and release sulfur species [5248], evidently reduced the thermal stability of the p(*n*BA/MMA) binder, acting as catalyst in the degradation of the paint film.

25 **Formatted:** Font color: Auto, English (U.K.)
26 **Formatted:** English (U.K.)
27 **Formatted:** English (U.K.)
28 **Formatted:** Font color: Auto, English (U.K.)
29 **Formatted:** Font color: Auto
30 **Formatted:** English (U.K.)
31 **Formatted:** Font color: Auto, English (U.K.)
32 **Formatted:** English (U.K.)
33 **Formatted:** English (U.K.)
34 **Formatted:** English (U.K.)
35 **Formatted:** Font color: Auto, English (U.K.)
36 **Formatted:** English (U.K.)
37 **Formatted:** English (U.K.)
38
39 A different ~~behaviorbehaviour~~ in the TG results was observed when the binder was mixed with the cadmium red pigment (Fig. 3b). The initial temperature of decomposition increased already after 31 days of UV ageing from 297 to 337 °C, instead of the decrease of the ultramarine blue film. ~~and~~ After 83 days it remained basically the same. Some cross linking reactions could have taken place in the polymer material with a consequent reduced mobility of the macromolecular chains and retardation in the thermal degradation.

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: Font color: Auto

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Liquitex® blue paint films (Fig. 4a) showed three main differences: 1) after 31 days of UV ageing the decomposition started at lower temperature which further decreased after 83 days with a total temperature difference of 50 °C. Some chain scission reactions could have taken place in the co-polymer binder during the UV exposure, resulting in a reduced thermal stability. 2) The final ~~weightmass~~ percent ~~decrease~~ of the organic part ~~decreased~~, corresponding to 5%, ~~which isis~~ probably due to photo-oxidizing processes of the paint film and a loss of volatile molecules. 3) No trace of the loosely bounded water, ~~previously found which was found~~ between 82 and 189 °C in the unaged sample, ~~was detected, was detected~~. All of these three effects of the UV ageing on the paint film were more accentuated in the Rembrandt® blue (Fig. 4b), including even a decrease of ~~7%~~ of the final organic part ~~of 7%~~. Additionally, a gradual increase of a new small transition step from 129 to 199 °C, which is related to the formation of an unassigned small peak in the derivative ~~weightmass~~ loss curve, was observed in the aged Rembrandt® blue sample.

Unlike ultramarine blue paints, the cadmium red paint films from Liquitex® and Rembrandt® (Fig. 5a), seemed to be less sensitive to the UV light. No trace of the loosely bounded water was observed, and the TG curves of the unaged and aged cadmium red acrylic materials were characterized by a small increase of the initial temperature of decomposition as well as ~~only~~ a small ~~increase decrease~~ of the final ~~weightmass~~ of the ~~in~~organic component. Similar to the cadmium red mock-up, some cross linking reactions between the molecular chains in the acrylic emulsion binding medium might have occurred, resulting in a consequent increased resistance of the material to high temperatures.

Concerning the green paints, the Liquitex® green showed a reduced stability based on the gradual ~~decreased~~ of the initial temperature of degradation (from 295 to 277 °C), as well as the decrease ~~of 5 %~~ on the final ~~weightmass~~ percentage of the organic compound ~~of 5 %~~ (Table 3), similar to the ultramarine paints.

Conclusions

The influence of ultramarine blue, hydrated/chromium oxide green and cadmium red pigments on the stability of a p(nBA/MMA) acrylic binding medium when aged under UV exposure for 31 and 83 days was studied by differential scanning calorimetry (DSC) and thermal gravimetry (TG) analyses. Generally, a reduced photo-oxidative stability of the p(nBA/MMA) acrylic binder was observed when mixed with ultramarine blue, as well as

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: Font color: Auto, English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9 for the Liquitex[®] and Rembrandt[®] blue paints containing p(*n*BA/MMA). The ultramarine
10 blue pigment seemed to promote some chain scission reactions in the polymer matrix
11 observed as the loss of organic material by the evaporation of volatile compounds. This
12 was shown by DSC as an increase in the T_g of the paint films after 83 days of UV
13 ageing, and further supported by the TG results which showed a decrease of the initial
14 degradation temperature, and an associated decrease of the final ~~weight~~mass
15 percentage of the organic compounds. A similar ~~behavior~~behaviour was shown by the
16 chromium oxide green, especially by the Liquitex[®] green, while the hydrated chromium
17 oxide green mixed with the p(*n*BA/MMA) acrylic binder remained basically stable.
18 In contrast to ultramarine blue and hydrated/chromium oxide green, the cadmium red
19 pigment seemed to promote a greater amount of cross linking in the acrylic film network.
20 This was indicated by the TG analysis that showed an increase of the initial degradation
21 temperature, as well as by the DSC analysis that showed a gradual increase in the T_g
22 temperatures. In these specimens not only the pigment can influence the photo-stability
23 of the binding medium, but also the fillers and other additives so far not identified, may
24 play an important role.
25
26
27
28
29
30
31

32 Acknowledgments

34 This work has been funded by Regione Sardegna (Italy), "Programma Master and Back
35 anno 2009" Alta Formazione and the Austrian Science Fund, Project no. L699-N17. We
36 are grateful to Chiara Riedo (Department of Chemistry and Nanostructures Interfaces
37 and Surfaces-Centre of Excellence, University of Torino, Italy) for carrying out some
38 thermal analyses.
39
40

41 References

- 42
43
44
45 [1] Herrera M, Matuschek G, Kettrup A. Fast identification of polymer additives by
46 pyrolysis-gas chromatography/mass spectrometry. *J Anal Appl Pyrol.* 2003;70:35-42.
47
48 ~~[2] Solomon DH, Hawthorne DG. Chemistry of Pigments and Fillers. Willey/Interscience,~~
49 ~~New York; 1983.~~
50
51 ~~[3] Braun JH. White pigments. In: Koleske JV, editor. The Gardner Sward Handbook:~~
52 ~~Paint and Coating Testing Manual. Vol 17. 14th ed. ASTM Manual MNL; 1995. p. 159.~~
53
54 ~~[4] Spathis P, Karagiannidou E, Magoula AE. Influence of Titanium Dioxide pigments on~~
55 ~~the Photodegradation of Paraloid Acrylic Resin. *Stud Conserv.* 2002;48:57-64.~~
56
57
58
59
60
61
62
63
64
65

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

~~[5] Day RE. The Role of Titanium Dioxide Pigments in the Degradation and Stabilisation of Polymers in the Plastics Industry. Polym Degrad Stab. 1990; 23:73-92.~~

~~[6] Zorll U. Waterbased acrylates for decorative coatings. Hannover: Vincent Verlag; 2001.~~

[72] Luescher M. Inorganic Pigments-Other. In: Surface Coatings Association of Australia editor. Surface Coatings – Raw materials and their usage, vol. 1. 3rd ed. London: Chapman & Hall; 1993. pp. 449-472.

[83] McGonigle F. Ultramarine Pigments. In: Lewis PA editor. Pigment Handbook, Vol. 1. New York: Wiley; 1988. pp. 367-374.

Formatted: English (U.K.)

Formatted: English (U.K.)

[94] Clark RJH, Dines TJ, Kurmo M. On the Nature of the Sulfur Chromophores in Ultramarine Blue, Green, Violet, and Pink and of the Selenium Chromophore in Ultramarine Selenium: Characterization of Radical Anions by Electronic and Resonance Raman Spectroscopy and the Determination of their Excited-State geometries. Inorg. Chem. 1983;22:2766-72.

[105] Barrer RM. Hydrothermal Chemistry of Zeolites. London, New York: Academic Press; 1982.

~~[11] Hark RR, Clark RJH. Raman Microscopy of Diverse Samples of Lapis Lazuli at Multiple Excitation Wavelengths. AIP Conference Proceedings. 2010;1267:315-6.~~

[126] Del Federico E, Schöfberger W, Schelvis J, Kapetanaki S, Tyne L, Jerschow A. Insight into Framework Destruction in Ultramarine Pigments. Inorg. Chem. 2006;45:1270-6.

[137] Uzelmeier CW. How Heat and Light Affect Pigmented Polypropylene. SPE Journal. 1970; 69-74.

Formatted: English (U.K.)

Formatted: English (U.K.)

[148] Allen NS. Photofading and light stability of dyed and pigmented polymers. Polym Degrad Stab. 1994;44:357-74.

Formatted: English (U.K.)

Formatted: English (U.K.)

[159] Pintus V, Wei S, Schreiner M. UV ageing studies: evaluation of lightfastness declarations of commercial acrylic paints. Anal Bioanal Chem. 2012; 402:1567-84.

[1610] Paulus J, Knuutinen U. Cadmium colours: composition and properties. Appl. Phys A. 2004;79:397-400.

[1711] Mlinac M, Rolich J, Bravar M. Photodegradation of colored polyethylene films. J. Polym. Sci. Part C. 1976;57:161-169.

[1812] Buxbaum G, Pfaff G. Industrial inorganic pigments. 3rd ed. Weinheim: WILEY-VCH; 2005.

Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9 [4913] Loya J. Cadmium Sulfide Pigments. In: Lewis PA editor. Pigment Handbook, Vol. 1. New York: Wiley; 1988. pp. 347-52.

10 [2014] Schiek RC. Chrome green. In: Lewis PA editor. Pigment Handbook, Vol. 1. New
11 York: Wiley; 1988. pp. 341-45.

12 [2415] Ranby B, Rabek JF. Photodegradation, Photooxidation and Photostabilization of
13 Polymers. Wiley/Interscience, London; 1975.

14 [2216] Pintus V, Schreiner M. Characterization and identification of acrylic binding
15 media: influence of UV light on the ageing process. Anal Bioanal Chem. 2011; 399:2961-
16 76.

Formatted: English (U.K.)

Formatted: English (U.K.)

17 [2317] Whitmore PM, Colaluca VG. The natural and accelerated aging of an acrylic
18 artists' medium. Stud Conserv. 1995; 40:51-64.

Formatted: English (U.K.)

19 [2418] Learner T, Chiantore O, Scalarone D. Ageing studies on acrylic emulsion paints,
20 Preprints ICOM Committee for Conservation 13th Triennial Meeting. James & James
21 (Science Publishers), Rio de Janeiro; 2002. pp. 911-19.

Formatted: English (U.K.)

22 [2519] Scalarone D, Chiantore O, Learner T. Ageing studies of acrylic emulsion paints.
23 Part II. Comparing formulations with poly(EA-co-MMA) and poly(nBA-co-MMA) binders,
24 Preprints ICOM Committee for Conservation 14th Triennial Meeting, James &
25 James/Earthscan, The Hague; 2005. pp. 350-58.

Formatted: English (U.K.)

26 [2620] Learner T. Modern Paints: Uncovering the Choices. In: Learner T, Smithen P,
27 Krueger JW, Schilling MR, editors. Modern paints uncovered. Los Angeles: The Getty
28 Conservation Institute; 2007. pp 3-16.

29 [21] Odlyha M. Introduction to the preservation of cultural heritage. J Thermal Anal
30 Calorim. 2011; 104:399-403.

31 [22] Prati S, Chiavari G, Cam D. DSC Application in the Conservation Field. J Thermal
32 Anal Calorim. J Therm Anal Calorim. 2001;66:315-27.

33 [23] Pires J, Cruz AJ. Techniques of thermal analysis applied to the study of cultural
34 heritage. J Therm Anal Calorim. 2007;87:411-5.

35 [24] Izzo FC, Zendri E, Biscontin G, Balliana E. TG-DSC analysis applied to
36 contemporary oil paints. J Thermal Anal Calorim. 2011; 104: 541-6.

37 [25] Burmester A. Investigation of Paint Media by Differential Scanning Calorimetry
38 (DSC). Stud Conserv. 1992; 37:73-81.

39 [26] Chiantore O, Scalarone D, Learner T. Characterization of Artists' Acrylic Emulsion
40 Paints. Int J Polym Anal Charact. 2003; 8:67-82.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65
- [27] Ploeger R, Scalarone D, Chiantore O. [Thermal analytical study of the oxidative stability of artists'alkyd paints. Polymer. 2009; 94: 2036-41.](#)
- [28] Hagan EWS, Charalambides MN, Young CRT, Learner TJS, Hackney S. [The viscoelastic properties of latex paint films in tension: influence of the inorganic phase and surfactants. Prog Org Coat. 2010; 69:73-81.](#)
- [29] Topcuoglu Ö, Altinkaya SA, Balkköse D. [Characterization of waterborne acrylic based paint films and measurement of their water vapor permeabilities. Prog Org Coat. 2006; 56:269-78.](#)
- [30] Neag CM. [Coatings Characterization by Thermal Analysis. In: Koleske JV, editor. Paint and Coating Testing Manual: fourteenth edition of the Gardner-Sward handbook. Philadelphia: American Society for Testing and Materials; 1995. pp. 841-64.](#)
- [31] Learner T. [The Analysis of synthetic paints by Pyrolysis-Gas Chromatography-Mass Spectrometry \(PyGCMS\). Stud Conserv. 2001; 46:225-41.](#)
- [32] Scalarone D, Chiantore O. [Separation techniques for the analysis of artists'acrylic emulsion paints. J Sep Sci. 2004; 27:263-74.](#)
- [33] Sonoda N, Rioux JP. [Identification des matériaux synthétiques dans les peintures modernes. 1, Vernis et liants polymères. Stud Conserv. 1990; 35:189-204.](#)
- [34] Learner T. [Analysis of modern paints. Los Angeles: The Getty Conservation Institute; 2004.](#)
- [35] Boon JJ, Learner T. [Analytical mass spectrometry of artists'acrylic emulsion paints by direct temperature resolved mass spectrometry and laser desorption ionisation mass spectrometry. J Anal Appl Pyrol. 2002; 64:327-44.](#)
- [36] Doménech-Carbó MT, Silva MF, Aura-Castro E, Fuster-López L, Kröner S, Martínez-Bazán ML, Más-Barberá X, Mecklenburg MF, Osete-Cortina L, Doménech A, Gimeno-Adelantado JV, Yusá-Marco DJ. [Study of behaviour on simulated daylight ageing of artists' acrylic and poly\(vinyl acetate\) paint films. Anal Bioanal Chem. 2011; 399:3155-304.](#)
- [37] Peris-Vicente J, Baumer U, Stege H, Lutzenberger K, Gimeno Adelantado JV. [Characterization of Commercial Synthetic Resins by Pyrolysis-Gas Chromatography/Mass Spectrometry: Application to Modern Art and Conservation. Anal Chem. 2009; 81:3180-7.](#)
- [38] Lazzari M, Scalarone D, Malucelli G, Chiantore O. [Durability of acrylic films from commercial aqueous dispersion: Glass transition temperature and tensile behavior as indexes of photooxidative degradation. Prog Org Coat. 2011; 70:116-21.](#)

1
2
3
4
5
6
7
8
9 [\[39\] ASTM International D2565 – 99 \(Reapproved 2008\) Standard Practice for Xenon-Arc Exposure of Plastics Intended for Outdoor Applications.](#)

10
11 [\[40\] Golden M, Hayes J, Gavett B. Dry Notes on Drying! Understanding How to Control the Drying Process of Acrylics. Just Paint Golden Artist Colors, Inc., New Berlin. 1996; 3: 1-6.](#)

12
13 [\[41\] Perera DY. Effect of pigmentation on organic coating characteristics. Prog Org Coat. 2004; 50: 247-62.](#)

14
15
16
17 [\[42\] Ormsby B, Kampasakali E, Miliani C, Learner T. An FTIR-Based exploration of the effects of wet cleaning treatments on artists' acrylic emulsion paint film. e-PS. 2009; 6:186-95.](#)

18
19 [\[43\] Whitmore PM, Colaluca VG. The natural and accelerated aging of an acrylic artists' medium. Stud Conserv. 1995; 40: 51-64.](#)

20
21 [\[44\] Scheirs J. Compositional and Failure Analysis of Polymers. England: John Wiley & Sons; 2000.](#)

22
23 [\[45\] Hellgren AC, Weissenborn P, Holmberg K. Surfactants in water-borne paints. Prog Org Coat. 1999; 35: 79-87.](#)

24
25
26
27 [\[46\] Kanis LA, Viel FC, Crespo JS, Bertolino JR, Pires ATN. Study of poly\(ethylene oxide\)/Carbopol blends through thermal analysis and infrared spectroscopy. Polymer. 2000; 3303-09.](#)

28
29 [\[47\] Feller RL. Artists' Pigments. A Handbook of their History and Characteristics Vol 6. Cambridge: Cambridge University Press; 1986.](#)

30
31 [\[48\] Barrer RM, Raitt JS. Ion exchange in ultramarine. J Chem Soc. 1954; 4: 4641-51.](#)

32
33
34
35 [\[27\] Chiantore O, Lazzari M. Photo-oxidative stability of paraloid acrylic protective polymers. Polymer. 2001; 42:17-27.](#)

36
37
38
39 [\[28\] Feller RL, Curran M. Photochemical Studies on Methacrylate Coatings for the Conservation of Museum Objects. In: Pappas SF, Winslow FH editors. Photodegradation and photostabilization of coatings. Washington DC: American Chemical Society, ACS Symposium Series 151; 1981. pp. 183-96.](#)

40
41
42
43
44
45
46
47 [\[29\] Lazzari M, Scalarone D, Malucelli G, Chiantore O. Durability of acrylic films from commercial aqueous dispersion: Glass transition temperature and tensile behavior as indexes of photooxidative degradation. Prog Org Coat. 2011; 70:116-21.](#)

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

[30] Chiantore O, Scalarone D, Learner T. Characterization of Artists' Acrylic Emulsion Paints. *Int J Polym Anal Charact.* 2003; 8:67-82.

[31] Burmester A. Investigation of Paint Media by Differential Scanning Calorimetry (DSC). *Stud Conserv.* 1992; 37:73-81.

[32] Learner T. The Analysis of synthetic paints by Pyrolysis-Gas Chromatography-Mass Spectrometry (PyGCMS). *Stud Conserv.* 2001; 46:225-41.

[33] Scalarone D, Chiantore O. Separation techniques for the analysis of artists' acrylic emulsion paints. *J Sep Sci.* 2004; 27:263-74.

[34] Sonoda N, Rioux JP. Identification des matériaux synthétiques dans les peintures modernes. 1, Vernis et liants polymères. *Stud Conserv.* 1990; 35:189-204.

[35] Learner T. *Analysis of modern paints.* Los Angeles: The Getty Conservation Institute; 2004.

[36] Boon JJ, Learner T. Analytical mass spectrometry of artists' acrylic emulsion paints by direct temperature resolved mass spectrometry and laser desorption ionisation mass spectrometry. *J Anal Appl Pyrol.* 2002; 64:327-44.

[37] Doménech Carbó MT, Silva MF, Aura-Castro E, Fuster López L, Kröner S, Martínez-Bazán ML, Más-Barberá X, Mecklenburg MF, Osete-Cortina L, Doménech A, Gimeno-Adelantado JV, Yusá-Marco DJ. Study of behaviour on simulated daylight ageing of artists' acrylic and poly(vinyl acetate) paint films. *Anal Bioanal Chem.* 2011; 399:3155-304.

[38] Paris-Vicente J, Baumer U, Stege H, Lutzenberger K, Gimeno Adelantado JV. Characterization of Commercial Synthetic Resins by Pyrolysis-Gas Chromatography/Mass Spectrometry: Application to Modern Art and Conservation. *Anal Chem.* 2009; 81:3180-7.

[39] Golden M, Hayes J, Gavett B. *Dry Notes on Drying! Understanding How to Control the Drying Process of Acrylics.* Just Paint Golden Artist Colors, Inc., New Berlin. 1996; 3: 1-6.

[40] Perera DY. Effect of pigmentation on organic coating characteristics. *Prog Org Coat.* 2004; 50: 247-62.

[41] Ormsby B, Kampasakali E, Miliani C, Learner T. An FTIR-Based exploration of the effects of wet cleaning treatments on artists' acrylic emulsion paint film. *e-PS.* 2009; 6:186-95.

[42] Whitmore PM, Colaluca VG. The natural and accelerated aging of an acrylic artists' medium. *Stud Conserv.* 1995; 40: 51-64.

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

[43] Ploeger R, Scalarone D, Chiantore O. Thermal analytical study of the oxidative stability of artists' alkyd paints. *Polymer*. 2009; 94: 2036-41.

[44] Scheirs J. *Compositional and Failure Analysis of Polymers*. England: John Wiley & Sons; 2000.

Formatted: English (U.K.)

[45] Hellgren AC, Weissenborn P, Holmberg K. Surfactants in water-borne paints. *Prog Org Coat*. 1999; 35: 79-87.

[46] Kanis LA, Viel FC, Crespo JS, Bertolino JR, Pires ATN. Study of poly(ethylene oxide)/Carbopol blends through thermal analysis and infrared spectroscopy. *Polymer*. 2000; 3303-09.

[47] Hagan EWS, Charalambides MN, Young CRT, Learner TJS, Hackney S. The viscoelastic properties of latex paint films in tension: influence of the inorganic phase and surfactants. *Prog Org Coat*. 2010; 69:73-81.

Formatted: English (U.K.)

[48] Topcuoglu Ö, Altinkaya SA, Balkköse D. Characterization of waterborne acrylic based paint films and measurement of their water vapor permeabilities. *Prog Org Coat*. 2006; 56:269-78.

[49] Izzo FC, Zendri E, Biscontin G, Balliana E. TG-DSC analysis applied to contemporary oil paints. *J Thermal Anal Calorim*. 2011; 104: 541-6.

[50] Neag CM. *Coatings Characterization by Thermal Analysis*. In: Koloske JV, editor. *Paint and Coating Testing Manual: fourteenth edition of the Gardner-Sward handbook*. Philadelphia: American Society for Testing and Materials; 1995. pp. 841-64.

[51] Feller RL. *Artists' Pigments. A Handbook of their History and Characteristics Vol 6*. Cambridge: Cambridge University Press; 1986.

Formatted: English (U.K.)

[52] Barrer RM, Raitt JS. Ion exchange in ultramarine. *J Chem Soc*. 1954; 4: 4641-51.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Formatted: English (U.K.)

Figure captions

Fig. 1 Differential scanning calorimetry (DSC) curves of the of the Liquitex® blue paint containing p(nBA/MMA) before ageing (black solid lines) and after UV ageing for 31 (green pointed lines) and 83 (red dashed lines) days

Formatted: English (U.K.)

Formatted: English (U.K.)

Fig. 2 Weight Mass/% percentage (%) of the final organic components of each unaged and aged commercial acrylic paints obtained by thermal gravimetry (TG) analysis. The ageing was carried out under UV exposure for 31 and 83 days, respectively

Formatted: English (U.K.)

Formatted: English (U.K.)

Fig. 3 Thermal gravimetry (TG) curves and their derivatives weight mass/(%) of Plextol® D498 p(nBA/MMA) mixed with ultramarine blue (a) and mixed with cadmium red (b) before ageing (black solid line), and after UV ageing for 31 (green pointed line) and 83 (red dashed line) days

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Fig. 4 Thermal gravimetry (TG) curves and their derivatives weight mass/(%) of the Liquitex® blue paint containing p(nBA/MMA) (a) and of the Rembrandt® blue paint containing p(nBA/MMA) (b) before ageing (black solid line), and after UV ageing for 31 (green pointed line) and 83 (red dashed line) days

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Fig. 5 Thermal gravimetry (TG) curves and their derivatives weight mass/(%) of the Rembrandt® red paint containing p(nBA/MMA) (a) and of the Rembrandt® green paint containing p(nBA/MMA) (b) before ageing (black solid line), and after UV ageing for 31 (green pointed line) and 83 (red dashed line) days

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49

| Sample | Colour | Pigment Classical Name | Chemical Composition | Colour Index: Generic Name |
|---|--------|-------------------------------|---|----------------------------|
| Plexto [®] D498 + ultramarine blue | Blue | Ultramarine blue | p(nBA/MMA) + Na ₈ Al ₆ Si ₆ O ₂₄ .Sx | PB 29 |
| Plexto [®] D498 + hydrated chromium oxide green | Green | Hydrated chromium oxide green | p(nBA/MMA) + Cr ₂ O ₃ · 2H ₂ O | PG 18 |
| Plexto [®] D498 + cadmium red | Red | Cadmium red medium | p(nBA/MMA) + CdS, xCdSe | PR 108 |
| Liquitex [®] Professional Acrylic artist color, USA/Canada | Blue | Ultramarine blue | p(nBA/MMA) + Na ₈ Al ₆ Si ₆ O ₂₄ .Sx + Kaolinite (Al ₂ Si ₂ H ₄ O ₉) | PB 29 |
| Liquitex [®] Professional Acrylic artist color, USA/Canada | Green | Chromium oxide green | p(nBA/MMA) + Cr ₂ O ₃ | PG 17 |
| Liquitex [®] Professional Acrylic artist color, USA/Canada | Red | Cadmium red light | p(nBA/MMA) + CdS, xCdSe | PR 108 |
| Rembrandt [®] Artists Quality Extra Fine, Holland | Blue | Ultramarine blue | p(nBA/MMA) + Na ₈ Al ₆ Si ₆ O ₂₄ .Sx + Kaolinite (Al ₂ Si ₂ H ₄ O ₉) | PB 29 |
| Rembrandt [®] Artists Quality Extra Fine, Holland | Green | Chromium oxide green | p(nBA/MMA) + Cr ₂ O ₃ + Calcite (CaCO ₃) | PG 17 |
| Rembrandt [®] Artists Quality Extra Fine, Holland | Red | Cadmium red light | p(nBA/MMA) + CdS, xCdSe + Calcite (CaCO ₃) | PR 108 |

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Table 1 List of the investigated mock-ups and commercial acrylic paints and their technical properties as declared by the companies. The chemical composition of the binding media and extender were identified in previous studies [159, 2216]

Formatted: English (U.K.)

Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49

| Sample | Colour | Pigment Classical Name | T_g /°C unaged | T_g /°C aged 31 days | T_g /°C aged 83 days | T_m /°C unaged |
|---|--------|-------------------------------|---------------------|---------------------------|---------------------------|---------------------|
| Plexto [®] D498 acrylic emulsion | | | 10.1 °C | | | 54.6 °C |
| Plexto [®] D498 + ultramarine blue | Blue | Ultramarine blue | 12.2 °C | 15.7 °C | 19.3 °C | 54.9 °C |
| Plexto [®] D498 + hydrated chromium oxide green | Green | Hydrated chromium oxide green | 10.3 °C | 12.5 °C | 16.8 °C | |
| Plexto [®] D498 + cadmium red | Red | Cadmium red medium | 11.8 °C | 11.8 °C | 13.5 °C | 58.3 °C |
| Liquitex [®] Professional Acrylic artist color, USA/Canada | Blue | Ultramarine blue | 7.0 °C | 10.2 °C | 10.7 °C | 39.0 °C / 43.3 °C |
| Liquitex [®] Professional Acrylic artist color, Usa/Canada | Green | Chromium oxide green | 10.3 °C | 11.6 °C | 19.3 °C | 38.6 °C / 43.8 °C |
| Liquitex [®] Professional Acrylic artist color, USA/Canada | Red | Cadmium red light | 6.4 °C | 10.4 °C | 10.8 °C | 38.5 °C / 44.9 °C |
| Rembrandt [®] Artists Quality Extra Fine, Holland | Blue | Ultramarine blue | 9.4 °C | 11.0 °C | 19.4 °C | |
| Rembrandt [®] Artists Quality Extra Fine, Holland | Green | Chromium oxide green | 10.8 °C | 19.7 °C | 19.6 °C | |
| Rembrandt [®] Artists Quality Extra Fine, Holland | Red | Cadmium red light | 9.8 °C | 18.5 °C | 18.7 °C | |

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Formatted: English (U.K.)

Table 2 Differential scanning calorimetry (DSC) results of the mock-ups and commercial acrylic paints before ageing and after UV ageing for 31 and 83 days: glass transition T_g /°C temperatures and melting temperature T_m /°C of the non-ionic surfactant

Formatted: English (U.K.)

Formatted: English (U.K.)

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49

| <u>Sample</u> | <u>T_{onset}/°C degradation unaged</u> | <u>Unaged Mass/% of the organic component</u> | <u>Unaged Mass/% of the residue component</u> | <u>T_{onset}/°C degradation aged 31 days</u> | <u>Aged 31 Mass/% of the organic component</u> | <u>Aged 31 Mass/% of the residue component</u> | <u>T_{onset}/°C degradation aged 83 days</u> | <u>Aged 83 Mass/% of the organic component</u> | <u>Aged 83 Mass/% of the residue component</u> |
|---|--|---|---|--|--|--|--|--|--|
| <u>Plexto[®] D498 acrylic emulsion</u> | <u>299</u> | <u>92</u> | <u>8</u> | | | | | | |
| <u>Plexto[®] D498 + ultramarine blue</u> | <u>311</u> | <u>64</u> | <u>36</u> | <u>264</u> | <u>64</u> | <u>36</u> | <u>121</u> | <u>45</u> | <u>55</u> |
| <u>Plexto[®] D498 + chromium oxide green</u> | <u>323</u> | <u>83</u> | <u>17</u> | <u>322</u> | <u>83</u> | <u>17</u> | <u>323</u> | <u>83</u> | <u>17</u> |
| <u>Plexto[®] D498 + cadmium red</u> | <u>297</u> | <u>80</u> | <u>20</u> | <u>335</u> | <u>80</u> | <u>20</u> | <u>337</u> | <u>81</u> | <u>19</u> |
| <u>Liquitex[®] / Blue Professional Acrylic artist color/ USA/Canada</u> | <u>82 / 189 / 300</u> | <u>47</u> | <u>53</u> | <u>251</u> | <u>44</u> | <u>56</u> | <u>250</u> | <u>42</u> | <u>58</u> |
| <u>Liquitex[®] / Green Professional Acrylic artist color/ Usa/Canada</u> | <u>84 / 185 / 295</u> | <u>43</u> | <u>57</u> | <u>290</u> | <u>39</u> | <u>61</u> | <u>277</u> | <u>38</u> | <u>62</u> |
| <u>Liquitex[®] / Red Professional Acrylic artist color/ USA/Canada</u> | <u>80 / 186 / 303</u> | <u>54</u> | <u>46</u> | <u>304</u> | <u>53</u> | <u>47</u> | <u>309</u> | <u>53</u> | <u>47</u> |
| <u>Rembrandt[®] / Blue Artists Quality Extra Fine/ Holland</u> | <u>86 / 178 / 298</u> | <u>55</u> | <u>45</u> | <u>274</u> | <u>52</u> | <u>48</u> | <u>239</u> | <u>48</u> | <u>52</u> |
| <u>Rembrandt[®] / Green Artists Quality Extra Fine/ Holland</u> | <u>86 / 170 / 275</u> | <u>37</u> | <u>63</u> | <u>310</u> | <u>38</u> | <u>62</u> | <u>311</u> | <u>37</u> | <u>63</u> |

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49

| | | | | | | | | | |
|--|-----------------|----|----|-----|----|----|-----|----|----|
| Rembrandt® / Red Artists Quality Extra Fine/ Holland | 82 / 176 304 | 64 | 36 | 326 | 63 | 37 | 328 | 63 | 37 |
|--|-----------------|----|----|-----|----|----|-----|----|----|

| Sample | T _{onset} degradation unaged (°C) | T _{endset} degradation unaged (°C) | Unaged Weight of the organic component (%) | Unaged Weight of the inorganic component (%) | T _{onset} degradation aged-31 days (°C) | T _{endset} degradation aged-31 days (°C) | Aged-31 Weight of the organic component (%) | Aged-31 Weight of the inorganic component (%) | T _{onset} degradation aged-83 days (°C) | T _{endset} degradation aged-83 days (°C) | Aged-83 Weight of the organic component (%) | Aged-83 Weight of the inorganic component (%) |
|---|--|---|--|---|---|--|---|--|---|--|---|--|
| Plextol® D498-acrylic emulsion | 299 | 420 | 92.33 | 7.67 | | | | | | | | |
| Plextol® D498+ ultramarine blue | 344 | 434 | 64.04 | 35.96 | 264 | 427 | 63.54 | 36.46 | 421 | 428 | 45.07 | 54.93 |
| Plextol® D498+ chromium oxide-green | 323 | 440 | 83.4 | 16.60 | 322 | 443 | 82.69 | 17.31 | 323 | 442 | 82.78 | 17.22 |
| Plextol® D498+ cadmium-red | 297 | 437 | 79.63 | 20.37 | 335 | 437 | 79.87 | 20.13 | 337 | 438 | 80.52 | 19.48 |
| Liquitex®— Blue Professional Acrylic artist color, USA/Canada | 82—189 300 | 443 | 47.24 | 52.79 | 261 | 444 | 44.49 | 55.51 | 250 | 440 | 42.14 | 57.86 |
| Liquitex®— Green Professional Acrylic artist color, USA/Canada | 84—185 295 | 436 | 42.53 | 57.47 | 290 | 435 | 39.47 | 60.53 | 277 | 435 | 37.92 | 62.08 |
| Liquitex®— Red Professional Acrylic artist color, USA/Canada | 80—186 303 | 434 | 53.73 | 46.27 | 304 | 432 | 52.55 | 47.45 | 309 | 430 | 52.72 | 47.03 |

Formatted: English (U.K.)
Formatted Table

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49

| | | | | | | | | | | | | |
|--|---------------|-----|-------|-------|-----|-----|-------|-------|-----|-----|-------|-------|
| Rembrandt® —Blue Artists Quality-Extra Fine, Holland | 86-178 298 | 437 | 55.19 | 44.81 | 274 | 430 | 52.01 | 47.99 | 239 | 431 | 47.83 | 52.17 |
| Rembrandt® —Green Artists Quality-Extra Fine, Holland | 86-170 275 | 405 | 36.99 | 63.01 | 310 | 421 | 37.73 | 62.27 | 311 | 422 | 37.37 | 62.63 |
| Rembrandt® —Red Artists Quality-Extra Fine, Holland | 82-176 304 | 420 | 63.66 | 36.34 | 326 | 420 | 62.71 | 37.29 | 328 | 422 | 62.67 | 37.33 |

Table 3 Thermal gravimetry (TG) results of the mock-ups and commercial acrylic paints before ageing and after UV ageing for 31 and 83 days: initial degradation temperature (T_{onset}), ~~final degradation temperature (T_{endset})~~, and ~~weight mass/%~~ loss percentage (%) of the organic and ~~inorganic residue~~ compounds

Formatted: English (U.K.)

Formatted: English (U.K.)

Figure 1

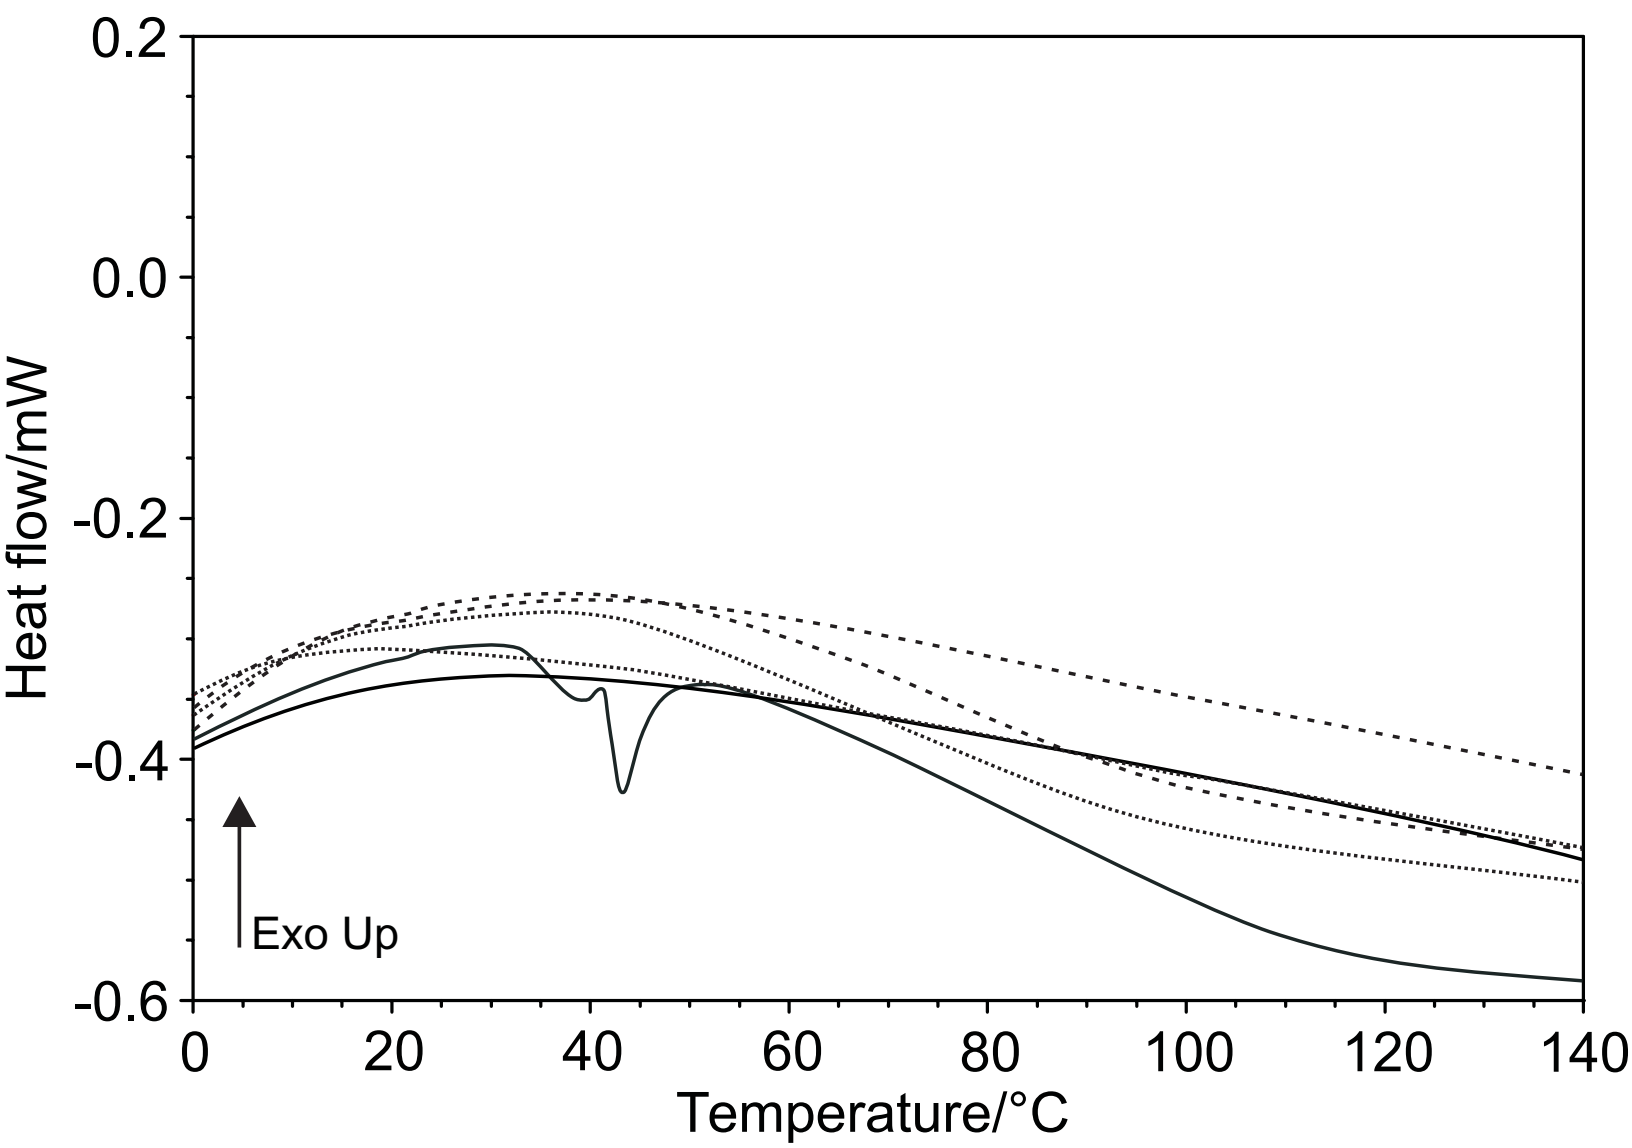


Figure 2

[Click here to download high resolution image](#)

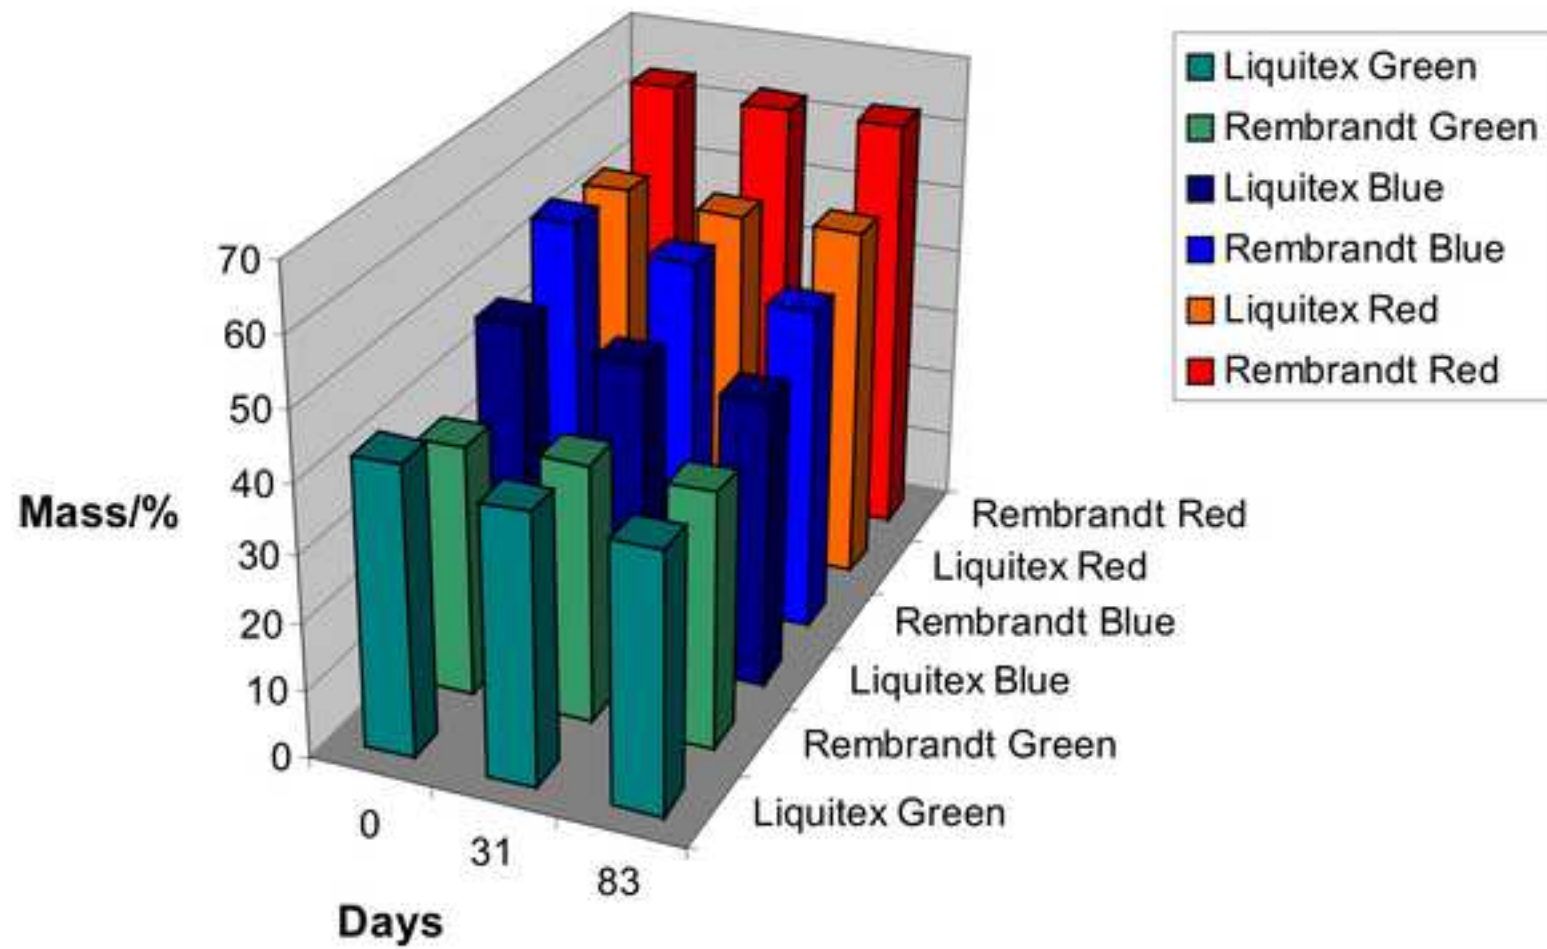


Figure 3



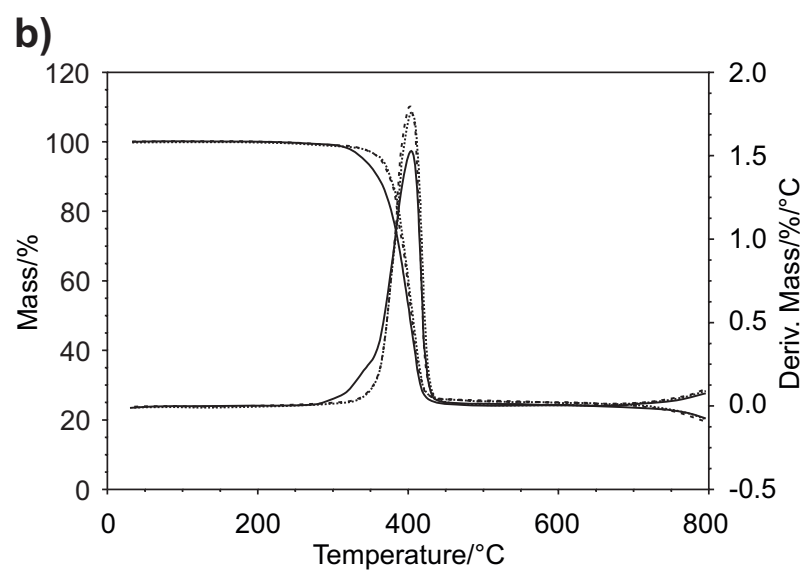


Figure 4

a)

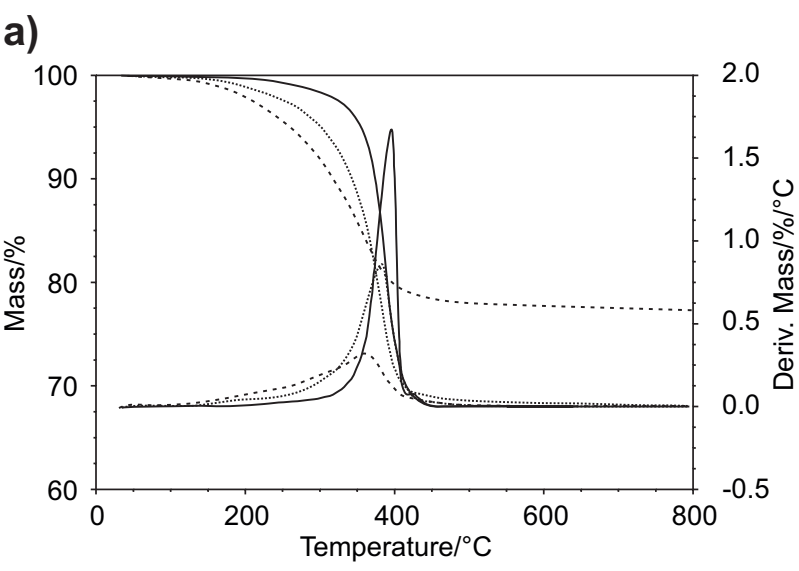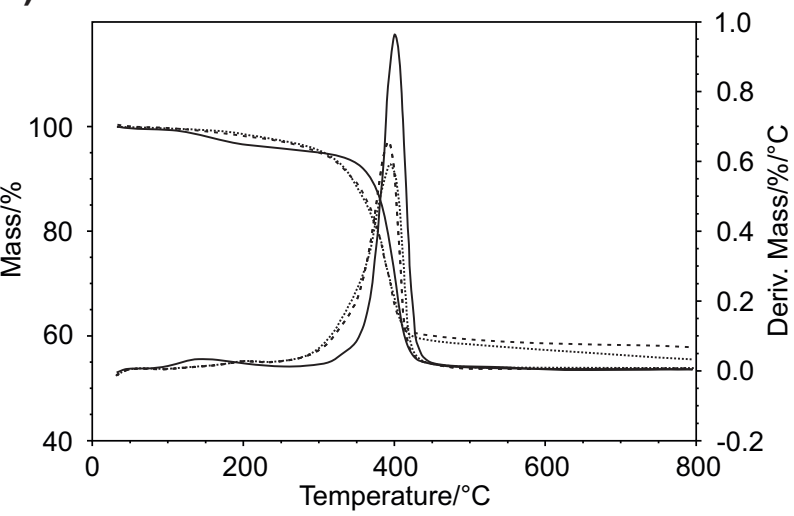

b)



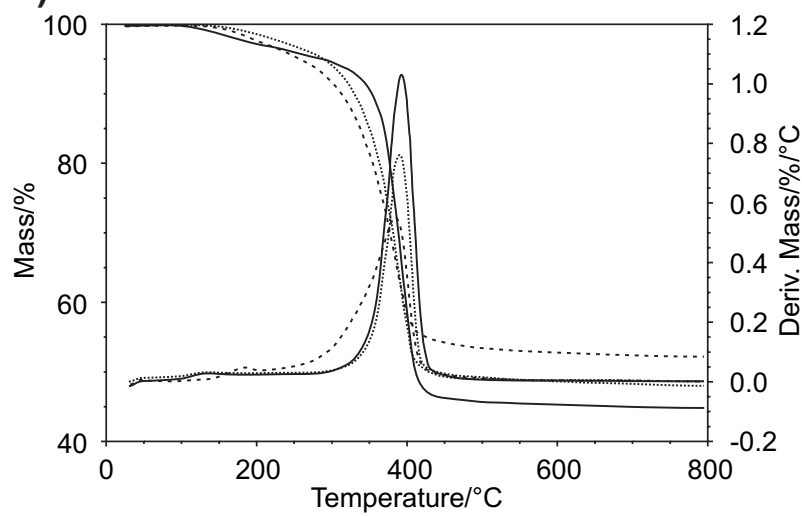


Figure 5

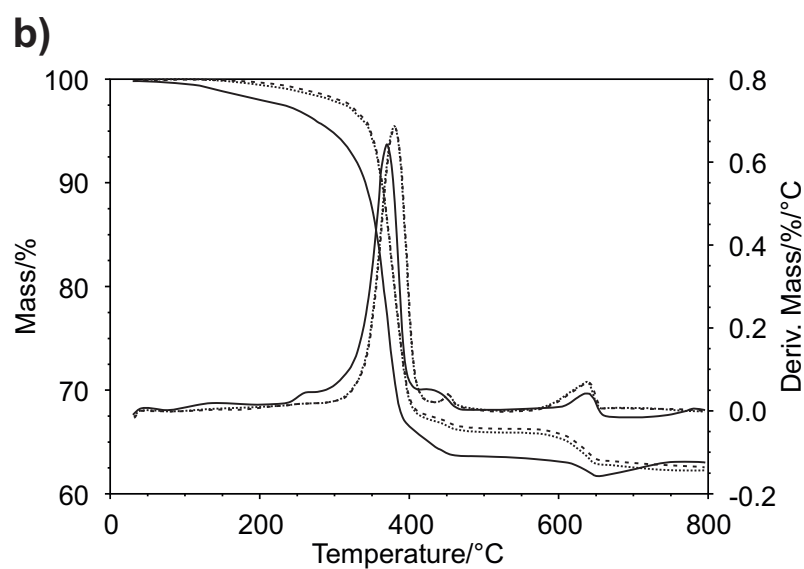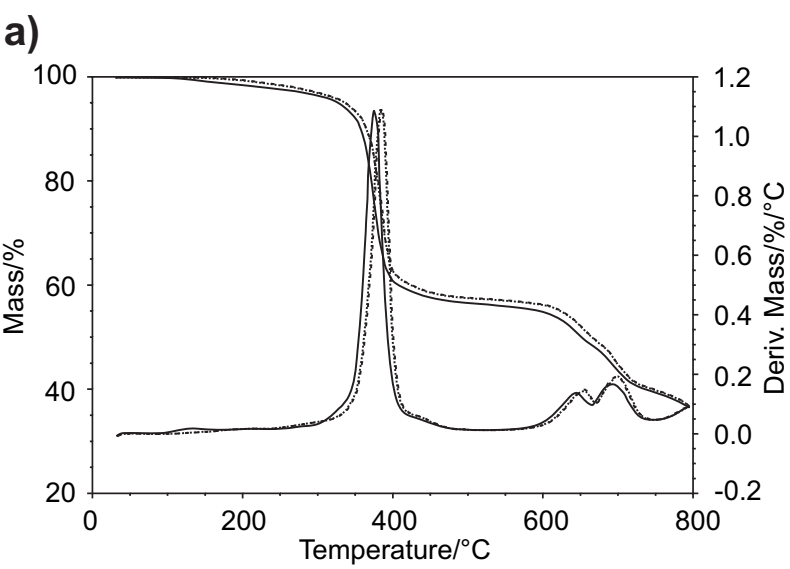

Copyright Transfer Statement

Publisher: Akadémiai Kiadó Zrt., Budapest, Hungary

The signed Copyright Transfer Statement please return to:
<http://www.editorialmanager.com/jtac/>

Author
 Name: VALENTINA PINTUS
 Address: SCHILLERPLATZ 3, A-1010 VIENNA, AUSTRIA
 E-mail address: v.pintus@akbild.ac.at

Article information

Title: THERMAL ANALYSIS OF THE INTERACTION OF INORGANIC PIGMENTS WITH (G) (B) (M) (M) ACRYLIC EMULSION BEFORE AND AFTER UV AGEING
 Journal title: Journal of Thermal Analysis and Calorimetry
 Co-authors: REBECCA PLOEGER, OSCAR CHIANTORE, SHUYA WEI, MANFRED SCHREINER

I. Transfer of copyright

By execution of the present Statement Author transfers copyright and assigns exclusively to Publisher all rights, title and interest that Author may have (for the extent transferable) in and to the Article and any revisions or versions thereof, including but not limited to the sole right to print, publish and sell the Article worldwide in all languages and media. Transfer of the above rights is referred to as those of the final and published version of the Article but does not restrict Author to self-archive the preprint version of his/her paper (see Section III).

II. Rights and obligations of Publisher

The Publisher's rights to the Article shall especially include, but shall not be limited to:

- ability to publish an electronic version of the Article via the website of the publisher Akadémiai Kiadó, www.akademiai.com (in Hungary), as well as the co-publisher's website, www.SpringerLink.com (outside of Hungary) or any other electronic format or means of electronic distribution provided by or through Akadémiai Kiadó or Springer from time to time, selling the Article world-wide (through subscriptions, Pay-per-View, single archive sale, etc.)
- transforming to and selling the Article through any electronic format
- publishing the Article in the printed Journals as listed on the official Website of Publisher
- transferring the copyright and the right of use of the Article onto any third party
- translating the Article
- taking measures on behalf of the Author against infringement, inappropriate use of the Article, libel or plagiarism.

Publisher agrees to send the text of the Article to the e-mail address of Author indicated in the present Statement for preview before the first publishing either in paper and/or electronic format (Proof). Author shall return the corrected text of the Article within 2 days to the Publisher. Author shall, however, not make any change to the content of the Article during the First Proof preview.

III. Rights and obligations of Author

The Author declares and warrants that he/she is the exclusive author of the Article – or has the right to represent all co-authors of the Article (see Section IV) – and has not granted any exclusive or non-exclusive right to the Article to any third party prior to the execution of the present Statement and has the right therefore to enter into the present Statement and entitle the Publisher the use of the Article subject to the present Statement. By executing the present Statement Author confirms that the Article is free of plagiarism, and that Author has exercised reasonable care to ensure that it is accurate and, to the best of Author's knowledge, does not contain anything which is libelous, or obscene, or infringes on anyone's copyright, right of privacy, or other rights. The Author expressly acknowledges and accepts that he/she shall be entitled to no royalty (or any other fee) related to any use of the Article subject to the present Statement. The Author further accepts that he/she will not be entitled to dispose of the copyright of the final, published version of the Article or make use of this version of the Article in any manner after the execution of the present Statement. The Author is entitled, however, to self-archive the preprint version of his/her manuscript. The preprint version is the Author's manuscript or the galley proof or the Author's manuscript along with the corrections made in the course of the peer review process. The Author's right to self-archive is irrespective of the format of the preprint (.doc, .tex, .pdf) version and self-archiving includes the free circulation of this file via e-mail or publication of this preprint on the Author's webpage or on the Author's institutional repository with open or restricted access. When self-archiving a paper the Author should clearly declare that the archived file is not the final published version of the paper, he/she should quote the correct citation and enclose a link to the published paper ([http://dx.doi.org/\[DOI of the Article without brackets\]](http://dx.doi.org/[DOI of the Article without brackets])).

IV. Use of third party content as part of the Article

When not indicating any co-authors in the present Statement Author confirms that he/she is the exclusive author of the Article. When indicating co-authors in the present Statement Author declares and warrants that all co-authors have been listed and Author has the exclusive and unlimited right to represent all the co-authors of the Article and to enter into the present Statement on their behalf and as a consequence all declarations made by Author in the present Statement are made in the name of the co-authors as well. Author also confirms that he/she shall hold Publisher harmless of all third-party claims in connection to non-authorized use of the Article by Publisher. Should Author wish to reuse material sourced from third parties such as other copyright holders, publishers, authors, etc. as part of the Article, Author bears responsibility for acquiring and clearing of the third party permissions for such use before submitting the Article to the Publisher for acceptance. Author shall hold Publisher harmless from all third party claims in connection to the unauthorized use of any material under legal protection forming a part of the Article.

V. Other provisions

Subject to the present Statement the Article shall be deemed as first published within the Area of the Hungarian Republic. Therefore the provisions of the Hungarian law, especially the provisions of Act LXXVI of 1999 on Copy Rights shall apply to the rights of the Parties with respect to the Article. For any disputes arising from or in connection with the present Statement Parties agree in the exclusive competence of the Central District Court of Pest or the Capital Court of Budapest respectively.

VALENTINA PINTUS *Valentina Pintus* 30/05/2012 VIENNA
 Author Signature Date and Place



<http://www.springer.com/journal/10973>

Journal of Thermal Analysis and Calorimetry

An International Forum for Thermal Studies

Editor-in-Chief: J. Simon

ISSN: 1388-6150 (print version)

ISSN: 1572-8943 (electronic version)

Journal no. 10973