

AperTO - Archivio Istituzionale Open Access dell'Università di Torino

CO₂ Hydrogenation over Pt-Containing UiO-67 Zr-MOFs - The Base Case

This is the author's manuscript

Original Citation:

Availability:

This version is available <http://hdl.handle.net/2318/1657661> since 2018-01-22T09:56:57Z

Published version:

DOI:10.1021/acs.iecr.7b01457

Terms of use:

Open Access

Anyone can freely access the full text of works made available as "Open Access". Works made available under a Creative Commons license can be used according to the terms and conditions of said license. Use of all other works requires consent of the right holder (author or publisher) if not exempted from copyright protection by the applicable law.

(Article begins on next page)

This is the author's final version of the contribution published as:

[Gutterød, Emil Sebastian; Øien-Ødegaard, Sigurd; Bossers, Koen; Nieuwelink, Anne-Eva; Manzoli, Maela; Braglia, Luca; Lazzarini, Andrea; Borfecchia, Elisa; Ahmadigoltapeh, Sajjad; Bouchevreau, Boris; Lønstad-Bleken, Bjørn Tore; Henry, Reynald; Lamberti, Carlo; Bordiga, Silvia; Weckhuysen, Bert M.; Lillerud, Karl Petter; Olsbye, Unni; CO₂ Hydrogenation over Pt-Containing UiO-67 Zr-MOFs - The Base Case, *Industrial & Engineering Chemistry Research*, 56 (45), 2017, 13206-13218, DOI: 10.1021/acs.iecr.7b01457]

The publisher's version is available at:

[<http://pubs.acs.org/doi/10.1021/acs.iecr.7b01457>]

When citing, please refer to the published version.

Link to this full text:

[<http://hdl.handle.net/2318/1657661>]

CO₂ hydrogenation over Pt-containing UiO-67 Zr-MOFs - the base case

Emil Sebastian Gutterød¹, Sigurd Øien-Ødegaard¹, Koen Bossers^{1,2}, Anne-Eva Nieuwelink^{1,2}, Maela Manzoli³, Luca Braglia^{3,4}, Andrea Lazzarini¹, Elisa Borfecchia³, Sajjad Ahmadigoltapeh¹, Boris Bouchevreau¹, Bjørn Tore Lønstad-Bleken¹, Reynald Henry¹, Carlo Lamberti^{3,4}, Silvia Bordiga^{1,3}, Bert M. Weckhuysen², Karl Petter Lillerud¹, Unni Olsbye^{1*}

¹Centre for Materials Science and Nanotechnology, Department of Chemistry, University of Oslo
Sem Saelandsvei 26, N-0315 Oslo, Norway. Email: unni.olsbye@kjemi.uio.no

²Inorganic Chemistry and Catalysis Group, Debye Institute for Nanomaterials Science, Utrecht
University, Universiteitsweg 99, 3584 CG Utrecht, The Netherlands.

³Department of Chemistry, NIS Interdepartmental Centre and INSRM reference centre, University of
Turin, via Quarello 15A, I-10135 Turin, Italy.

⁴IRC "Smart Materials", Southern Federal University, Zorge Street 5, 344090 Rostov-on-Don, Russia.

Abstract

CO₂ hydrogenation was carried out over Pt-containing UiO-67 Zr-MOFs at T=220-280°C and atmospheric pressure, with H₂/CO₂ ratios in the range 0.2-9 and contact times in the range 0.004-0.01 g_{cat}×min×ml⁻¹.


The catalysts were characterized by XRD, N₂ adsorption, FESEM, TEM and HRTEM, dissolution-NMR, CO chemisorption, IR spectroscopy and TGA. A positive correlation was observed between the degree of Pt reduction and CO₂ conversion. Contact time variation experiments showed that CO is a primary product of reaction, while CH₄ is a secondary product, formed via CO. The reaction orders in P(H₂) and P(CO₂) were 0.3 and 0.5, respectively, at 240-260 °C, suggesting high coverage of the Pt surface. Testing of catalyst crystals with 0.15 and 2.0 micron crystal size, respectively, revealed no influence of diffusion on the reaction rate. Comparison to a conventional Pt/SiO₂ catalyst showed very similar activation energy, with $E_a = 50 \pm 3$ kJ/mol. However, the turn-over frequency over Pt/SiO₂ was significantly lower, and Pt/SiO₂ did not yield methane as product.

The Pt-containing UiO-67 Zr-MOF catalyst showed stable activity during 60 hours testing.

1. Introduction

CO₂ is a key contributor to global warming and ocean acidification, and its recycling to valuable products by chemical conversion is an attractive research target. Thermodynamically, CO₂ is the most stable molecular product of carbon combustion, and its valorization is energy demanding¹. Therefore, to activate CO₂, a high energy-density carrying agent is required, in the form of photons, electrons or chemical energy. H₂ has a high gravimetric energy density of 143 MJ/kg, making it a suitable candidate for the chemical conversion of CO₂². Some key reactions for CO₂ and H₂ conversion are given below:


The reverse water gas shift reaction (RWGS):



$$\Delta H_{298\text{ K}} = 41.2 \text{ kJ mol}^{-1}$$

$$\Delta G_{298\text{ K}} = 28.6 \text{ kJ mol}^{-1}$$


Methanol formation:



$$\Delta H_{298\text{ K}} = -49.5 \text{ kJ mol}^{-1}$$

$$\Delta G_{298\text{ K}} = 3.8 \text{ kJ mol}^{-1}$$

CO₂ methanation:



$$\Delta H_{298\text{ K}} = -252.9 \text{ kJ mol}^{-1}$$

$$\Delta G_{298\text{ K}} = -113.5 \text{ kJ mol}^{-1}$$

The methanation reaction is thermodynamically favored, but a catalyst is needed to overcome the kinetic limitations. Ni-containing catalysts are used for the reverse reaction at high temperatures and are also active for Reaction (3)³⁻⁶. However, deactivation of Ni-based catalysts at low temperatures, by formation of mobile nickel subcarbonyls, is a major obstacle. Catalysts containing noble metals like Ru, Pd or Pt are more stable under these conditions and are therefore more active for CO₂ methanation³. In the current study, focus is set on Pt-based catalysts.

Roman-Martinez et al. studied Pt/C and Pt-M/C (M = Mg, Ca) as CO₂ hydrogenation catalysts and reported a negative correlation between Pt particle size and turn-over frequency for the RWGS reaction (Eq. 1) over Pt/C at 300-400 °C⁷. Later, Iglesia et al. studied the reverse methanation reaction (Eq. 3), i.e.; methane reforming to synthesis gas (CO, CO₂ and H₂) over supported Pt catalysts (γ-Al₂O₃, ZrO₂, ZrO₂-CeO₂ supports) at 550-800 °C, 0.1-1.0 atm total pressure). They reported that C-H bond breaking was the rate-determining step of methane reforming, and that the turn-over frequency (TOF) of methane activation increased with a decreasing Pt particle size; suggesting that C-H bond breaking is a structure-sensitive reaction; the low-coordinated sites being more active than sites in low-index planes⁸. Together, these two studies suggest that stabilisation of small Pt particles is an attractive target in the development of catalysts for the CO₂ hydrogenation catalysts, aiming at syngas or methane production., and led to the selection of a Zr-MOF support in the present study.

Metal Organic Frameworks (MOFs) are a class of crystalline, porous materials in which inorganic clusters are connected by organic linker molecules⁹⁻¹⁰. By adjusting the chemical nature of the clusters and the linker molecules, different architectures can be obtained from 2D to 3D porous networks, with a wide variety of pore sizes, from the microporous to the mesoporous region⁹. Furthermore, the linkers can be functionalized with different chemical groups, e.g. to enhance gas adsorption¹¹⁻¹³, or to mimic ligands in organometallic complexes, thereby stabilizing homogeneous metal organic complex catalysts in a solid matrix^{10, 14-15}. However, most MOF materials suffer from low thermal, chemical and mechanical stability¹⁶.

UiO-67 is a microporous MOF belonging to the UiO Zr-MOF series, and is built from Zr₆O₄(OH)₄ clusters connected by 1,1'-biphenyl-4,4'-dicarboxylic acid (bpdc) linker molecules¹⁶. UiO-67 has been reported to be kinetically stable up to 450 °C in N₂ atmosphere, after which it starts to break down due to cleavage of the C-C bond between the phenyl ring and the carboxylic acid group¹⁶. The material has both octahedral and tetrahedral cavities with sizes of 23 and 11.5 Å, respectively. UiO-67 has a remarkably high theoretical BET surface area of 2600 m²×g⁻¹. To incorporate metal species for catalysis, different functionalized linkers have been introduced into the network of UiO-67 together with bpdc. A variety of methods have been reported, such as premade linker synthesis (PMLS), post-synthetic functionalization (PSF) and one pot synthesis (OPS)^{10, 14-15}. These methods vary by the stage at which the metal species is introduced in the framework. OPS is the least sophisticated method, in which all precursors are mixed together as non-coordinated, individual components in a solvent to synthesize a modified UiO-67 framework. For PMLS, the metal species is first coordinated to a functionalized linker molecule and then mixed with the other components during UiO-67

synthesis. Finally, PSF involves the grafting of the metal species to a chelating linker after the synthesis of UiO-67.

Over the last few years, several studies have explored the UiO-series of Zr-MOFs for catalytic applications¹⁷. Much due to the high complexity and tunability of MOFs, catalysis may occur at various locations, such as at the Zr cluster¹⁸⁻¹⁹, metalated linker^{14, 20} or encapsulated metal particles²¹⁻²⁶. Here we focus on catalysis over UiO-MOFs containing PtCl_x entities and Pt nanoparticles (NPs).

To the best of our knowledge, the first study of Pt-containing Zr-MOFs was reported by Guo et al. in 2014²³. Pt NPs were formed inside the cavities of UiO-66-NH₂ during reduction (10 % H₂ in Ar at 200 °C for 1 hour) of K₂PtCl₄ impregnated MOF, and tested for liquid phase hydrogenation of cinnamaldehyde. After 42 hours of reaction, a conversion of 86 % with 88 % selectivity toward cinnamyl alcohol was achieved. When the reaction was performed over UiO-66-NH₂ with Pt NPs located on the external surface of the MOF, a lower selectivity (72 %) was observed.

In 2015, Choi et al. encapsulated Pt NPs (2.5 nm) inside pristine and functionalized UiO-66 (linkers functionalized with -SO₃H, -NH₃⁺, -SO₃Na and -NH₂), and tested it catalytically for the conversion of methylcyclopentane (MCP)²⁴. All the samples tested had their crystallinity, morphology and chemical functionalities intact after 8 hours of reaction. The nature and combination of the linker's functional groups was shown to greatly influence the catalytic pathway for MCP conversion, reactivity and selectivity.

Very recently, Hester et al. investigated UiO-67-Pt and UiO-67 with encapsulated Pt nanoparticles (both produced through the PMLS method) as catalysts for the oxidation of 5-hydroxymethylfurfural (HMF) to 2,5-furandicarboxylic acid (FDCA), and for reduction to 2,5-dimethylfuran²⁵. The catalytic reactions were performed at 60 °C in an autoclave reactor with 20 ml aqueous solution of HMF, pressurized to 20 bar (G) using O₂ and H₂ for the oxidation and reduction reaction, respectively. Although formation of FDCA was only observed in the presence of UiO-67-PtNP, consumption of HMF was also observed over UiO-67 and UiO-67-Pt. Hester et al. argued that the consumption over the UiO-67 MOFs without Pt NPs was due to adsorption of HMF on their hydrophobic and porous structures. Under reducing conditions, adsorption of HMF by UiO-67 was again observed, however, 2,5-dimethylfuran was formed over both Pt-containing MOFs. The activity of UiO-67-Pt was suggested as due to *in situ* reduction of Pt since 2,5-dimethylfuran was only observed after about 30 minutes at reaction conditions.

Zhuang et al. compared the activity of pristine UiO-67 for the CO oxidation with samples functionalized with 5-(4'-carboxyphenyl)picolinic acid or 2-aminobiphenyl-4-4'-dicarboxylic acid, all containing highly dispersed Pt NPs (PSF-type method)²⁶. Larger Pt NPs were identified for UiO-67-Pt as compared to the two functionalized samples (4.5 nm versus 2.5 nm), suggesting that the functional group of the organic linker molecule and the pore size of the MOF influences the Pt particle size. The highest activity toward CO oxidation was observed for the 5-(4'-carboxyphenyl)picolinic acid functionalized sample, followed by pristine UiO-67-Pt, while the 2-aminobiphenyl-4-4'-dicarboxylic acid functionalized sample gave lowest activity. Based on DFT calculations, it was argued that the 5-(4'-carboxyphenyl)picolinic acid functionalized sample was related to generation of a conjugate system between the pyridine N atom and the phenyl group, effectively adjusting the electronic structure of the MOF. In combination, the catalytic properties were concluded as dependent on both the size of the Pt NPs, and the nature of the support.

In the present study, UiO-67-Pt was prepared by the PMLS and PSF method and studied as catalyst for the CO₂ hydrogenation reaction in gas phase. The aim of the study was to elucidate two essential features of the catalysts: Their stability during catalytic operation, and the potential influence of the MOF lattice on the target reaction.

2. Experimental

2.1 Material synthesis

All chemicals were used as received. ZrCl₄ (Sigma-Aldrich) must be dry and of high purity for successful synthesis. PtCl₂(2,2'-bipyridine-5,5'-dicarboxylic acid) was synthesized using a previously reported method¹⁰. One batch of UiO-67-Pt by PMLS and three batches of UiO-67-Pt by PSF were prepared. One of the PSF batches was prepared in small scale, labeled UiO-67-Pt-PSF(M), while two were prepared in larger scale (2.5 L starting solution), labeled UiO-67-Pt-PSF(N) and UiO-67-Pt-PSF(SA). The detailed synthesis procedures are described in the SI.

In brief, samples of UiO-67-Pt were prepared by heating solutions of ZrCl₄, benzoic acid, H₂O, H₂bpydc, and either PtCl₂(H₂bpydc) (PMLS) or H₂bpydc (PSF) in dimethylformamide (DMF) at elevated temperatures for several days. The obtained powder (yellow in the PMLS sample, and white in the PSF samples) was first washed in hot DMF, and then thoroughly washed in either tetrahydrofuran (THF) or acetone, then dried at 150-200 °C.

The samples prepared using H₂bpydc were functionalized with Pt by submerging the MOF and K₂PtCl₄ in DMF and heating the solution overnight at 100 °C. The obtained yellow powder was washed twice in DMF (100 °C), then several times in either THF or acetone, and then dried at 150 °C.

2.2 Material characterization

Powder x-ray diffraction (XRD) patterns of the MOF samples before and after Pt-functionalization, mechanical stress, activation and operation, were obtained using a Bruker D8 Discover diffractometer with a Cu K α source and Lynx Eye silicon detector.

The specific surface area and pore volume of the samples were determined from N₂ adsorption isotherms at 77 K, performed with a BELSORP mini-II instrument. Prior to the measurement, the samples were heated at 80 °C for 1 hour and at 150 °C for 2 hours under vacuum.

A Hitachi SU8230 field emission scanning electron microscope (FESEM) with an XFlash 6|10 energy-dispersive X-ray (EDX) detector was utilized to assess the microstructure and the Pt/Zr ratio of the catalysts.

CO chemisorption measurements were performed using a pulse method²⁷⁻²⁸. Prior to the measurements, the samples were heated to 350 °C in a flow of 10 % H₂ in Ar (50 ml \times min⁻¹), followed by a 2 hour isotherm where the last hour was in a flow of Ar. The samples were subsequently cooled rapidly to room temperature in flow of Ar. Several CO pulses were introduced to a stream of Ar flowing through a reactor containing sample at room temperature and atmospheric pressure. The amount CO leaving the reactor was determined using a mass spectrometer (MS) (Pfeiffer Vacuum Omnistar QM200). Pulsing was continued until saturation. The MS response at saturation was used for calibration.

FT-IR spectra were collected on a Bruker Vertex80 instrument equipped with a MCT detector. Prior to the measurements, the samples were pressed into pellets without any dilution and heated to 150°C under vacuum. 50 mbar of H₂ was then dosed to the pellets, in order to remove the oxide layer present on the surface of the Pt nanoparticles of the catalysts. 40 mbar CO was dosed at room temperature as a probe to investigate the metal nanoparticles present on the catalysts; 32 spectra with a resolution of 2 cm⁻¹ were averaged for each single acquisition during CO desorption under dynamic vacuum. Solution state nuclear magnetic resonance (NMR) was utilized to estimate the amount of bipyridine linkers in the MOF samples. NMR samples were prepared by dissolving 20 mg MOF in 1 ml 1 M solution of NaOH in D₂O and leaving the mixture overnight to separate the solid inorganic phase from the aqueous solution by decantation. A ¹H-NMR spectrum was acquired from 0.6 ml of the remaining solution.

Thermogravimetric Analysis – Differential Scanning Calorimetry (TGA-DSC) was used to elucidate the stability of different MOF samples. The samples were heated from 20 °C to 900 °C at a rate of 5 °C×min⁻¹ under a flow of synthetic air (20 ml×min⁻¹ N₂ and 5 ml×min⁻¹ O₂).

Transmission electron microscopy (TEM) and high resolution (HR) TEM image were obtained by a Jeol 3010-UHR microscope operating at 300 kV equipped with a LaB₆ filament and with an Oxford Inca Energy TEM 300 EDS X-rays analyser by Oxford Link. Digital micrographs were acquired by an Ultrascan 1000 camera and processed by Gatan digital micrograph. Before the experiments, the samples, in the form of powders, were milled in an agate mortar and deposited on a copper grid covered with a lacey carbon film.

Histograms of the particle size distribution were obtained by considering 1545 nanoparticles, and the mean particle diameter (d_m) was calculated as $d_m = \sum d_i n_i / \sum n_i$, where n_i was the number of particles of diameter d_i . The counting was carried out on electron micrographs obtained starting from 150,000× instrumental magnification, where Pt particles well contrasted with respect to the UiO-67 framework were clearly detected.

2.3 Catalyst testing

Catalytic testing was performed in a fixed bed flow setup with a straight quartz tubular reactor (6 mm inner diameter), operated at atmospheric pressure. Dependent on the experimental aim, 0.1-0.2 g catalyst (177-250 μm or 250-425 μm mesh) was loaded in the reactor and activated at 350 °C (1 hour following ramp from room temperature) in a flow of 0, 3, or 10 % H₂ in Ar (50 ml×min⁻¹). Subsequently, the catalyst was cooled in inert (50 ml×min⁻¹) to 240 °C then brought to steady-state performance at a H₂/CO₂ ratio of 6 and contact time (τ) of 0.01 g_{cat}×min×mL⁻¹, for at least 6 hours before changing any parameters of operation. The respective steady-state conditions will be referred to as the *reference conditions*.

The influence of p_{CO_2} (0.08-0.40 bar), p_{H_2} (0.02-0.9 bar), T (220-280 °C) and τ (0.004-0.01 g_{cat}×min×mL⁻¹), on the catalytic activity was investigated by operating the catalyst at a given set of parameters in segments of 2 hours. After a series of 3-5 segments of variable conditions, a segment at the reference conditions were included. In this manner, any changes in the activity with time on stream (TOS) could be monitored. Qualitative analysis of the effluent gas was performed during catalyst activation using a quadrupole mass spectrometer (Pfeiffer Vacuum Omnistar QM200). Furthermore, the volumetric concentrations of products and reactants were quantified using a 2-channel micro-gas chromatograph (μGC 3000A, Agilent), equipped with a molecular sieve column with Ar as carrier gas and TCD detector, and a Plot U column with He as carrier gas and TCD detector.

3. Results and discussion

3.1 Catalyst characterization

Characterization data for fresh, pressed and sieved, pre-activated and tested catalysts are summarized in Table 1. More detailed analysis, considering XRD patterns, FESEM images, TEM and HRTEM images, and TG curves, are illustrated by the corresponding figures and graphs in Section 3.3

As a general comment to the data in Table 1, all materials had initial specific surface areas close to the theoretical value of $2800 \text{ m}^2 \times \text{g}^{-1}$ for UiO-67¹². Furthermore, as will be seen in Section 3.3, all samples were well-crystalline and contained only one crystalline phase. The crystal size and bipy content of all PMLS and PSF samples were similar, except for the crystal size of the UiO-67-Pt-PSF(SA) sample, which was an order of magnitude smaller than that of the other UiO-67-Pt-PSF and UiO-67-Pt-(PMLS) samples. The Pt/Zr of UiO-67-PSF(SA) sample was somewhat lower than that of UiO-67-PSF(N), resulting in an estimated Pt content of 1.2 and 1.5 wt%, for the two samples, respectively. The Pt content was derived from the Pt/Zr ratios and amount of defects estimated by TG of the supports (Figure S8 and S9)²⁹⁻³⁰. The Pt dispersion of the samples after activation in 10 % H₂ at 350 °C was low (5-10 %), suggesting either large Pt particle sizes or that a fraction of the Pt content is inaccessible for adsorption, e.g. due to incomplete reduction. By following the procedure described in Ref. ³¹, the theoretical dispersion of the Pt NPs of UiO-67-Pt can be estimated to 14 %, assuming complete reduction and spherical shaped NPs ($d = 2.6 \text{ nm}$ (Section 3.3.2)). However, as seen in Section 3.2.1 Figure 1, barely 40 % of the Pt is in the form of NPs after the reduction; when the incomplete reduction of Pt is considered, the Pt dispersion of the UiO-67-Pt samples increases to about 13 %, and is in good agreement with the theoretical value. For the Pt/SiO₂ sample, the average Pt NP size can be estimated from the 10 % dispersion to about 4 nm in diameter. This means that the samples were well suited for comparisons of catalytic performance and lattice stability.

Table 1. Sample characterization.

Sample	Sg (m ² ×g ⁻¹)	Vm (cm ³ ×g ⁻¹)	Crystal size (μm)	Bipyridine loading (%)	Pt/Zr ratio (%)	Pt dispersion (%)
UiO-67-Pt-PMLS	2442	0.96	2.5			
UiO-67-bipy(M)	2683	1.03	2.5	5.5		
UiO-67-Pt-PSF(M)	2633	1.05	2.6	4.2		
UiO-67-bipy(N)	2460	1.00	2	4.5		
UiO-67-Pt-PSF(N)	2392	0.97	2		2.6±0.3	5
UiO-67-Pt-PSF(N), pellets	2305	0.94	2			
UiO-67-Pt-PSF(N), tested for 52 hours	2343	1.01	2			8
UiO-67-Pt-PSF(SA)	1882	1.24	0.15	4	1.8±0.1	5
5 % Pt/SiO ₂ (Escat™ 2351, abcr)*	400					10

*) Pt content and specific surface area values obtained from provider.

3.2 Catalyst testing

3.2.1 Influence of activation atmosphere on catalyst activity

Recently, our team reported an *in situ* XAS study of the oxidation state and coordination of Pt in the UiO-67-Pt-PSF(M) sample studied here, during activation at 350 °C in pure He and in 10 % H₂/He, respectively (Figure 1)³². The XAS data revealed that Pt-Pt bonds, indicating Pt metal cluster formation, were only formed in the H₂-containing feed. The fraction of Pt being associated to another Pt atom was around 40 %, and was approaching an asymptotic limit after 3 hours activation at 350 °C in 10 % H₂/He. Under pure He feed, the fraction of Pt atoms coordinated to Cl and N decreased during heating, starting at 280 °C. At 350 °C, only 60 % of Pt remained in the original (bipy)-PtCl₂ coordination. However, no Pt-Pt bond formation was observed, even after continued heating to 480 °C³².

Recently, the Fourier transform of EXAFS data for the same material was monitored after activation in 10 % H₂/He at 350°C (green), further cooling to 250°C in He (lilac) and subsequently 1.30 hours in flow of CO₂ and H₂ (Figure 1a). The three spectra look very similar; there is a difference in intensity in the 2-3 Å range between the spectra obtained at different temperature, however, the difference is due to the Debye Waller factor effect. To confirm this, a comparison was made of the XANES spectra, which are not influenced by the temperature, after the end of the temperature ramp and after interaction with CO₂/H₂, respectively. The two spectra are precisely overlapped, suggesting that the CO₂/H₂ feed did not induce significant changes to the material under the relatively short interaction period of this experiment.

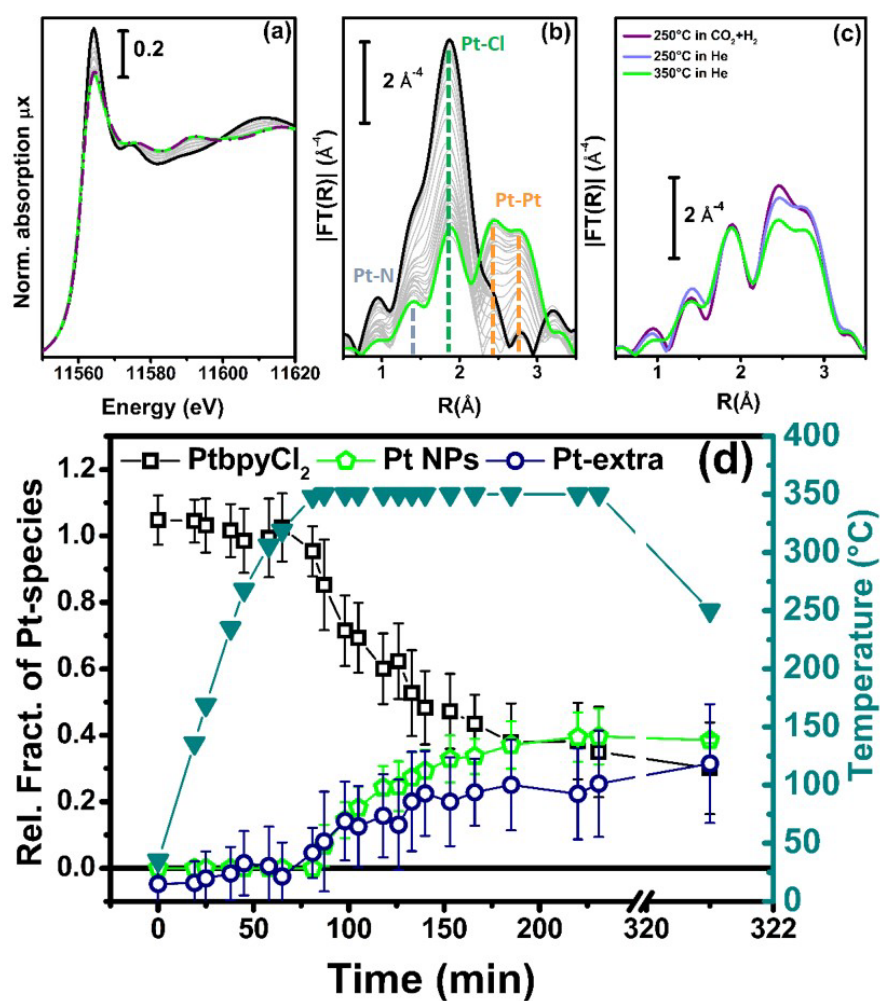


Figure 1. Part (a): Evolution of the Pt L₃-edge XANES spectra during in situ H₂-temperature programmed reduction experiment of UiO-67-Pt-PSF(M) performed in concentrated H₂ flow (10% H₂ in He) in the temperature range of 30-350 °C, followed by cooling in He to 250°C and catalytic testing in H₂/CO₂/He = 6:1:3 flow at 250°C. The XANES spectrum collected at 250°C after 1.30 hours of CO₂/H₂ feed is reported in dashed purple line. Part (b): as part (a) for the k³-weighted, phase uncorrected, FT of the corresponding EXAFS data. Also highlighted with blue, green and orange dashed lines are the typical positions of the Pt-N, Pt-Cl and Pt-Pt

contributions, respectively. Part (c): k^3 -weighted, phase uncorrected, FT of the sample activated at 350°C (green), cooled down to 250°C in He (lilac) and treated in CO₂ and H₂ at 250°C (purple). Part (d), empty black, green and blue symbols, left ordinate axis: fraction of the different Pt phases present in the sample, estimated from the N_{Pt-N} , N_{Pt-Cl} and N_{Pt-Pt} coordination numbers obtained from the parametric refinement of the whole set of EXAFS data. In the right ordinate axis is reported the evolution of the sample temperature with time, highlighting the linear increase up to 350°C in 65 min followed by a 2 h 55 min isotherm, and finally 1.30 hours under reaction conditions at 250 °C. Data obtained during pretreatment are reproduced from³². Data obtained under CO₂ hydrogenation conditions are new.

In this study, the conversion and product distribution of a H₂/CO₂/Ar = 6:1:3 feed over UiO-67-Pt-PSF(M) at T = 240 °C and WHSV = 1.10 g_{CO₂}×g_{cat}⁻¹×h⁻¹ was measured directly after activation in flows of 0, 3 and 10 % H₂/Ar for 1 hour at 350 °C in the home lab, to correctly reproduce the test conditions used during XAS measurements at the synchrotron. The results are shown in Figure 2. Activation performed in 0 % H₂ led to an initial conversion around 1.5 % which increased gradually to 3 % during the following 8 hours on stream. When the H₂ content was increased to 3 % during activation, a significantly higher initial conversion (5.5 %) was achieved, however only slight increase with TOS was observed. For the sample activated in 10 % H₂, the initial conversion was further increased as compared to the 0 and 3 % activated samples. It stabilized around 7.5 % and was nearly constant throughout the test. The pronounced dependence of the activity on the pre-activation atmosphere strongly indicates that the active component of UiO-67-Pt for CO₂ hydrogenation is the Pt NPs formed during activation in reducing atmosphere. The correlation between Pt metal particle formation and catalytic activity for CO₂ reduction is in agreement with recent literature, which demonstrated a substantial activity difference between supported, individual Pt atoms and Pt metal clusters, respectively, for CO oxidation to CO₂ with either O₂ or H₂O as the oxidizing agent³³. The observed increase in CO₂ conversion with time on stream, being strongest for the 0 % H₂/Ar sample, strongly suggests that migration of Pt entities to form Pt-Pt bonds continues under test conditions.

In the 0 % H₂ activated sample, CO was initially the only product formed. However, after 2 hours on stream, the selectivity towards CH₄ increased to around 2 %. The scattering observed in the selectivity data is presumably due to a CH₄ concentration close to the detection limit, resulting in a high uncertainty. Activation in 3 % and 10 % H₂ led to a slightly lower CO selectivity (97 %) and a correspondingly higher selectivity towards CH₄ (3 %), as compared to the inert activated sample.. A slight increase in CO selectivity was observed with increasing time on stream, which may suggest that the reaction atmosphere influences the structure of the Pt NPs (*vide infra*)⁷. Conversion and selectivity data for the reference catalyst Pt/SiO₂ is also shown in Figure 2. Similar conversion was obtained over this catalyst as over UiO-67-Pt-PSF(M), in spite of higher Pt content and dispersion

(Table 1). In contrast to the UiO-67-Pt samples, CO was the only product was observed for the CO₂ hydrogenation reaction over Pt/SiO₂. The high CO selectivity of the reaction over Pt/SiO₂ is mainly attributed to a significant destabilization of CO adsorbed on the interface between the support and the Pt NPs through interactions with OH-groups on the support³⁴. Thus, the shifted product selectivity of the UiO-67-Pt samples toward CH₄ formation hints to a strong metal-support interaction in the Zr-MOF supported catalyst. Previous literature emphasizes the role of the support (Al₂O₃, CeO₂ and TiO₂) and Pt-support interface as CO₂ activation site³⁴⁻³⁷.

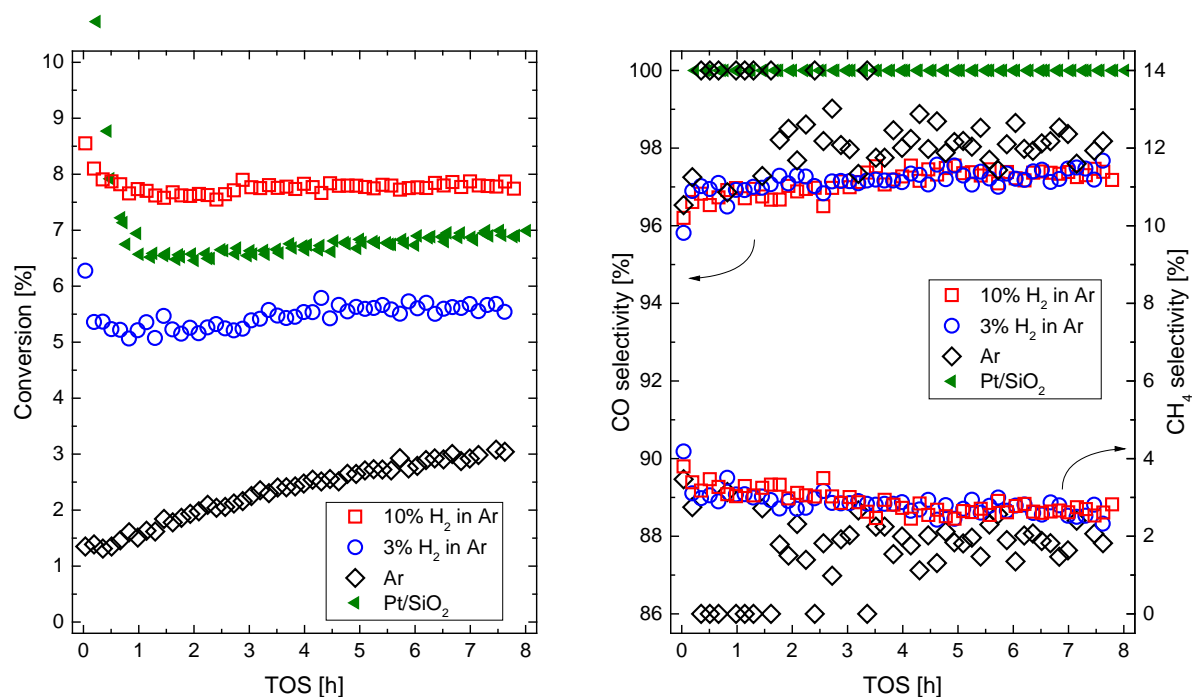


Figure 2. Left: conversion (%) versus time on stream (h) observed for UiO-67-Pt-PSF(M) under reference conditions after pre-activation at 350 °C (1 hour) in flow of Ar with 0, 3 and 10 % H₂ (50 ml× min⁻¹ total flow). The respective CO and CH₄ selectivities are shown in the figure to the right. The conversion and CO selectivity observed for Pt/SiO₂ is marked with green tilted triangles.

To further investigate the differences between UiO-67-Pt-PSF(N) and Pt/SiO₂, FT-IR measurements were performed. Carbon monoxide is well known for its strong interaction with d-orbitals of transition metals and its IR spectral features are strongly influenced by the surroundings of its chemisorption sites. For this reason, CO has been extensively employed for the study of metals surfaces (either in the bulk or in the nanoparticle forms)³⁸⁻⁴³. IR spectra of chemisorbed CO on three samples (Pt/SiO₂ reference, UiO-67-Pt-PSF(N) as activated and after the reaction) are shown in Figure 3. The details for spectra deconvolution are available in the supporting information in Figures S5, S6 and S7 and in Tables S2, S3 and S4.

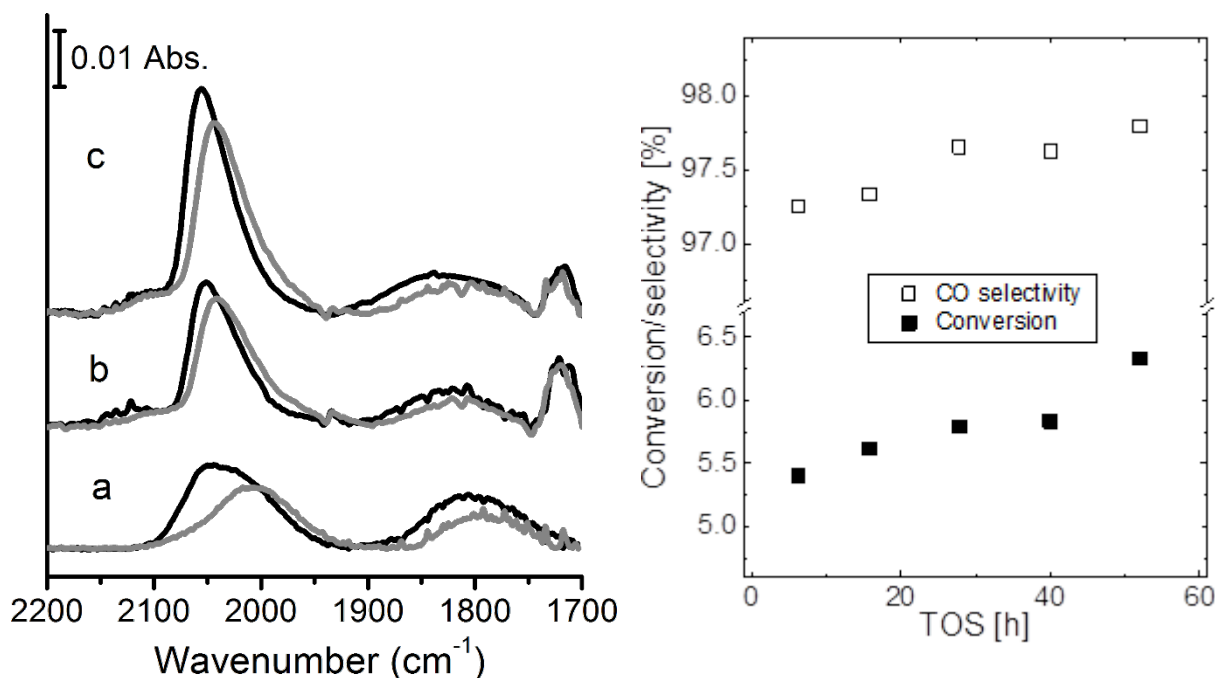


Figure 3. Left: FT-IR spectra of CO adsorbed on Pt nanoparticles supported on SiO₂ (x2, a) and on UiO-67-Pt(N) after pre-activation in 10 % H₂ (b) and after testing for the CO₂ hydrogenation reaction under 10-20 ml×min⁻¹ flow of H₂/CO₂/Ar = 6:1:3 at temperatures in range 220-280 °C for 52 hours (c). The spectra are focused on the spectral region of CO vibrational modes and are shown after subtraction of the spectrum of the samples prior to CO adsorption. Right: Test results obtained for the sample shown in FT-IR spectra (c): conversion and CO selectivity is plotted versus time on stream.

All the samples show the typical spectral features of CO linearly adsorbed on one single Pt atom between 2100 and 1950 cm⁻¹ and CO adsorbed on two adjacent Pt atoms (bridged) between 1900 and 1750 cm⁻¹ ⁴⁴⁻⁴⁸. In the former region it is possible to distinguish two signals: i) the feature centered around 2050 cm⁻¹, ascribable to carbon monoxide linearly adsorbed on the edges of crystalline plains ^{44-45, 48}; ii) the peak at 2020-2030 cm⁻¹, related to carbon monoxide linearly adsorbed on the kink positions of Pt nanoparticles ^{45-46, 48}. The position of the peak in the latter region is typical for CO bridged between two atoms at the edges of the particle. For both samples, the features related to CO linearly adsorbed on crystalline faces of the nanoparticles in the region 2100-2070 cm⁻¹ are absent ⁴⁴⁻⁴⁶. We could relate this information with the extremely small dimensions of the particles in both the systems, for which is not possible describe a crystalline structure, as evidenced by XRD and TEM data (Section 3.3.2).

For the MOF catalyst two other additional signals are present: the first one is a small feature around 2120-2110 cm⁻¹, belonging to CO adsorbed on isolated Pt atoms ^{10, 49-51}; this kind of sites are due to the not complete aggregation of Pt into the nanoparticles during the activation procedure, which remains in the atomic form coordinated by N atoms of bipy ligands¹⁰, in agreement with the XAFS

data in Figure 1. The second signal is a sharp feature centered at 1720 cm^{-1} , ascribable to CO adsorbed on Pt atoms in close vicinity to the support, and in particular to the aromatic rings of the ligands of UiO-67⁴⁵.

Test results obtained during 52 hours on stream for the UiO-67-Pt-PSF(N) sample are shown in Figure 3, right. An increasing CO₂ conversion as well as CO selectivity was observed with time on stream. The increased conversion is consistent with the observed increase in Pt dispersion after testing (Table 1), and suggests that Pt is further reduced under test conditions. Considering the IR spectra, it is difficult to find clear differences in the active phase UiO-67-Pt-(N) after pre-activation, and after long-term operation under reaction conditions, which can justify the changes observed in activity and selectivity during time on stream. One possibility could be a different degree of desorption of CO: it is noticeable that, in the sample after H₂ activation, carbon monoxide is adsorbed more strongly, as suggested by a smaller difference in the total area between first and last desorption step, compared to the sample after performing the reaction (Table S3 and S4). This fact could improve the turnover of CO adsorbed on the catalyst surface leading to an increase in activity.

3.2.2 Kinetic investigation

Crystal size variation

A major concern with micro- and nano-porous catalysts is the possible influence of diffusion restrictions. To ensure, first, that the test rig was operated under reaction limited conditions, the catalytic activity towards the hydrogenation of CO₂ was measured at various reactor loadings. The results are presented in Supporting Information, Figure S4, and show that the observed CO₂ conversion rates were not influenced by external or inter-crystalline diffusion. To investigate the influence of intra-crystalline diffusion, two batches of UiO-67-Pt catalyst with different crystal size (UiO-67-Pt-PSF(N) and UiO-67-Pt-PSF(SA)) were prepared and compared. The first batch (UiO-67-Pt-PSF(SA)) had an average crystal size of 150 nm, whereas the second batch (UiO-67-Pt-PSF(N)) had an average crystal size of 2 μm (Table 1). Testing of the samples under standard conditions showed that the smaller crystals were less active than the larger crystals (Figure S1). This difference correlates very well with the lower Pt content and similar dispersion of the (SA) as compared to the (N) sample (Table 1). More importantly, the catalysts were subjected to temperature variation tests, in order to compare their apparent activation energy for the title reaction. An $\ln(\text{rate})$ versus $1/T$ plot comprising both catalysts is shown Figure 4. The apparent activation energy is very similar for the two catalysts

in the full temperature range, clearly suggesting that the observed reaction rates are limited by reaction kinetics, and not by intra-crystalline diffusion.

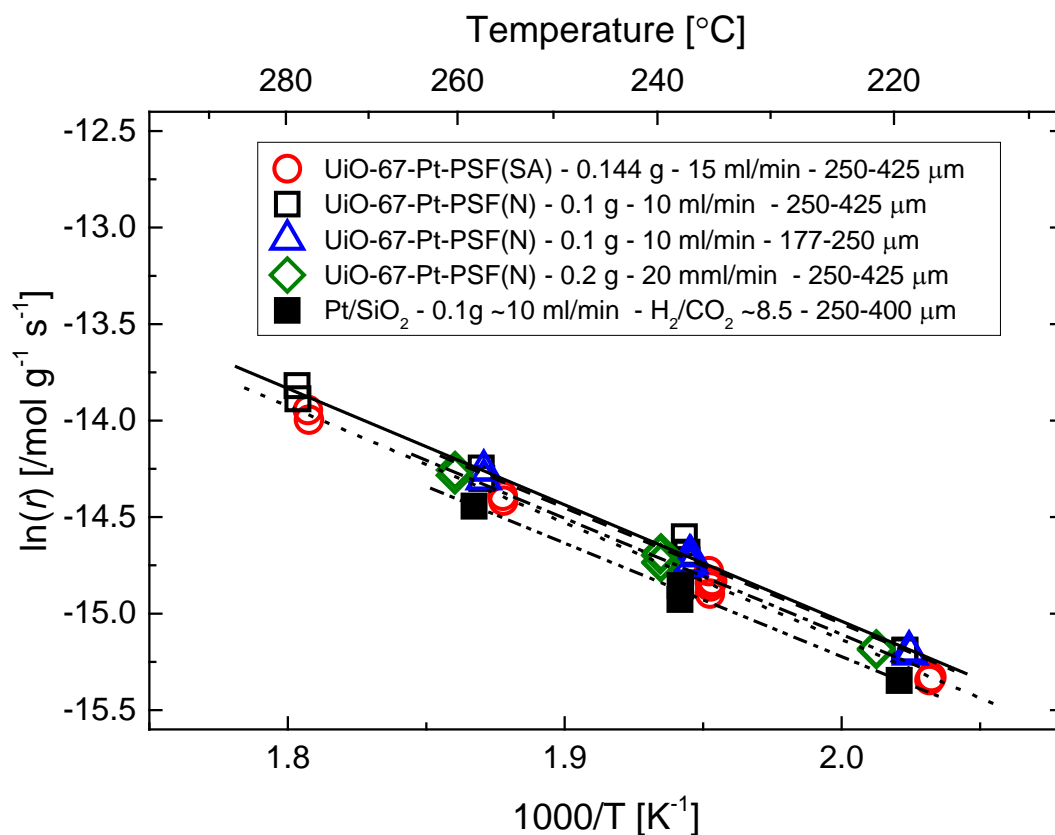


Figure 4. Arrhenius type plot of the rate of CO₂ conversion in the temperature range 220–280 °C, at $p_{\text{CO}_2} = 0.1$ bar, $p_{\text{H}_2} = 0.6$ bar, $\tau = 0.01 \text{ g}_{\text{cat}} \times \text{min} \times \text{ml}^{-1}$. Test series of UiO-67-Pt-PSF(N) are marked with squares, triangles and diamonds. The test of the small crystallite UiO-67-Pt-PSF(SA) sample is marked by circles, and the test of Pt/SiO₂ is marked by filled squares.

Contact time variation

To elucidate whether CO and CH₄ were formed sequentially or in parallel, the catalyst was subjected to contact time variation experiments in the temperature range 220–280 °C. The yield of CO and CH₄ is plotted as function of conversion in Figure 5. The selectivity to CO is high (>95 %) under all tested conditions, leading to a linear CO yield versus conversion plot which crosses the origin. The CH₄ yield, on the other hand, is low and crosses the abscissa at conversions higher than zero at all temperatures. This result shows that CH₄ is a secondary product formed from CO, suggesting a reverse-water-gas shift (RWGS) reaction followed by CO methanation pathway³⁴. It is interesting to note that the CH₄ yield versus conversion plot crosses the abscissa at higher values with increasing temperature; thereby suggesting that the relative rates of the CO-forming and CO-consuming

reactions is shifted towards CH₄ formation at lower temperatures. This shift is not induced by thermodynamics; methane formation is strongly favored in the full temperature range, and the conversion level of the RWGS reaction (1) is further from equilibrium at the lower temperatures.

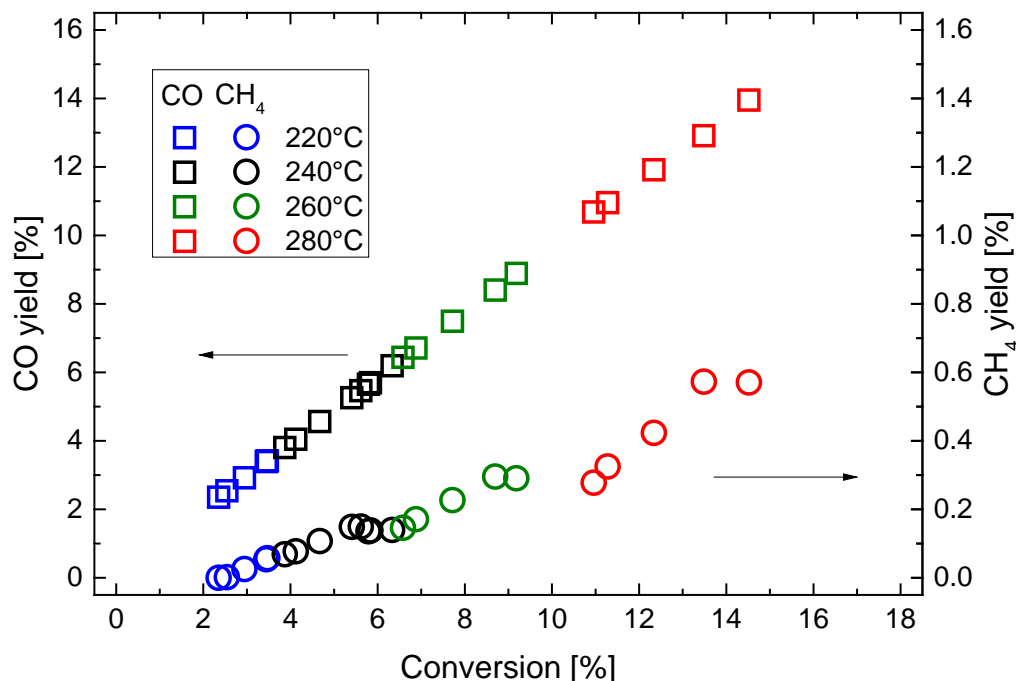


Figure 5. The yield (%) of CO (left axis) and CH₄ (right axis) versus conversion (%) obtained over UiO-67-Pt-PSF(N) under flow of H₂/CO₂ = 6 and $\tau = 0.004\text{-}0.01 \text{ g}_{\text{cat}}\times\text{min}\times\text{ml}^{-1}$, in the temperature range 220-280°C.

Having established that the RWGS reaction is the first step in CO₂ hydrogenation under the conditions studied here, it follows that CO₂ is initially consumed through a single reaction; a fact that simplifies the following kinetic analysis.

Partial pressure variation

The effect of CO₂ partial pressure on the rates of CO and CH₄ formation at 240 and 260°C is presented in Figure 6. Constant reaction orders with respect to p_{CO_2} are observed in the entire pressure range ($p_{\text{CO}_2} = 0.07\text{-}0.4$) at each temperatures. The reaction orders of CO formation are 0.45 and 0.5 at 240 and 260°C, respectively; which is slightly lower than the order in CO₂ for the reaction over Pt/TiO₂ (0.79 at 350 °C and 3.4 atm)³⁷, and in good agreement with Pt-Ca/C (0.45 at 220 °C and 1 atm)⁵². In oxygen deficient supports, such as Al₂O₃, CeO₂ and TiO₂, CO₂ is adsorbed on either the support³⁶ or at the interface between Pt and the support, facilitated in both mechanisms by an oxygen vacancy³⁴⁻³⁵. Similarly, on hydroxylated support surfaces (e.g. SiO₂), CO₂ binds at the interface

between Pt and the support, stabilized by OH-groups³⁴. In Pt-Ca/C, the activity—and presumably also the mechanism of reaction—is influenced by Pt-Ca and Ca-CO₂ interactions⁷. As highly similar orders in CO₂ for UiO-67-Pt-PSF(N) and Pt-Ca/C are observed, it may suggest that the interaction between the CO₂ and the catalyst are of similar nature.

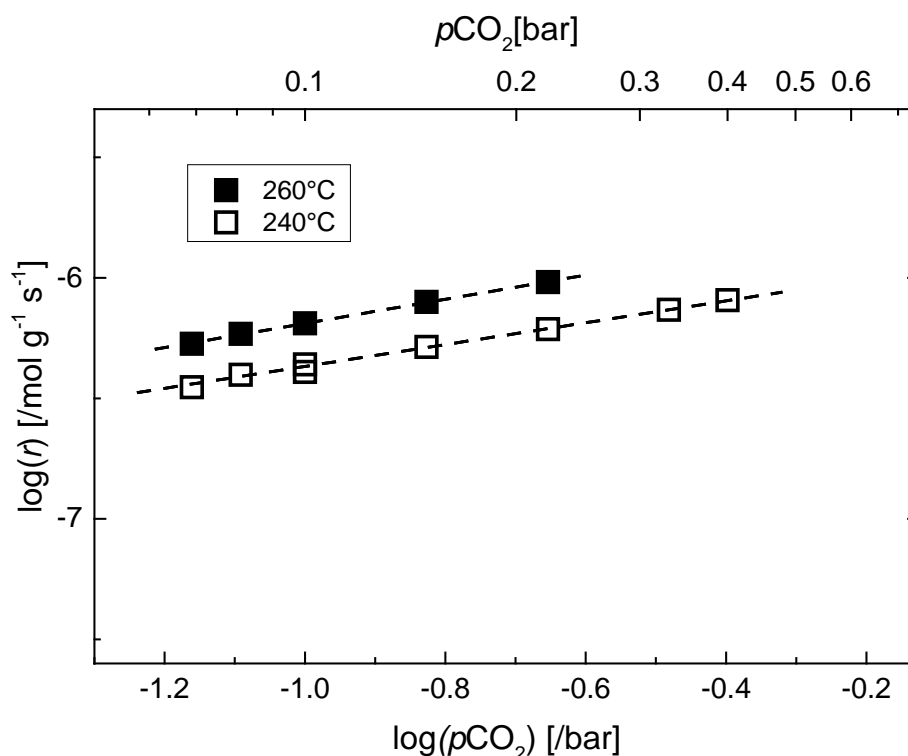


Figure 6. The $p\text{CO}_2$ dependence of the CO rate of formation over UiO-67-Pt-PSF(SA) at 240 °C (open) and 260 °C (filled). $p\text{H}_2 = 0.6$ bar and $\tau = 0.01$ g_{cat}×min×ml⁻¹.

The effect of H₂ partial pressure on the rate of CO and CH₄ formation at 240 and 260°C is presented in Figure 7. At both temperatures, the reaction order of CO formation with respect to $p\text{H}_2$ is 0.3, which is in good agreement with 0.25 reported for Pt/TiO₂ (at 350 °C and 3.4 atm)³⁷ and slightly lower than the reported order of 0.46 over Pt-Ca/C⁵². The marginal influence of $p\text{H}_2$ on the rate of CO formation suggests that the catalyst surface is largely covered by hydrogen, readily available for reaction even at low partial pressure.

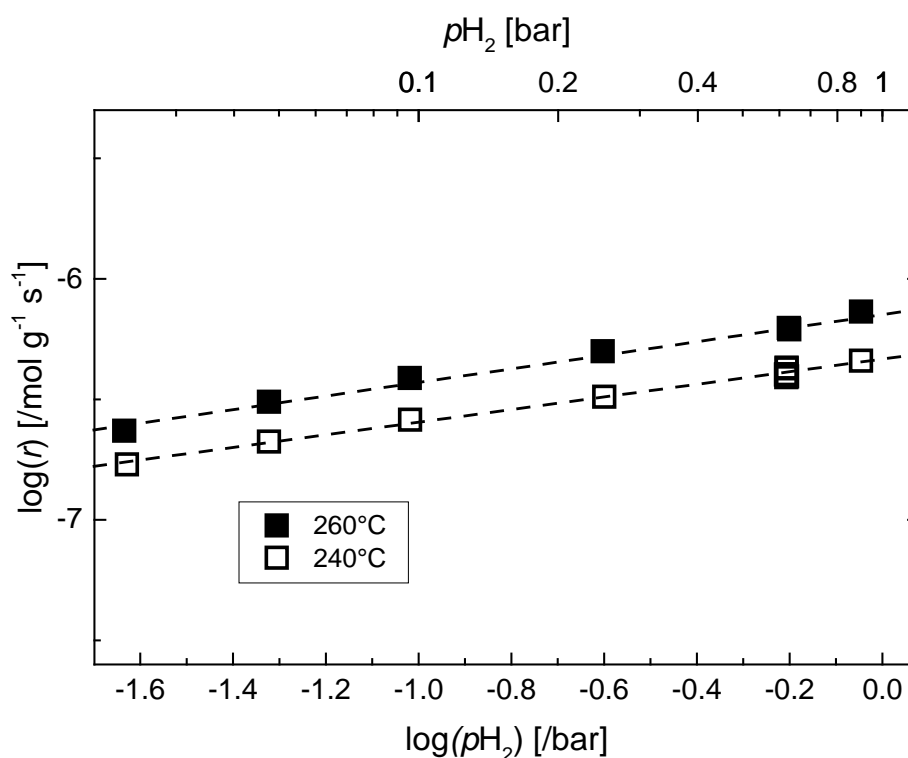


Figure 7. The p_{H_2} dependence of the CO rate of formation over UiO-67-Pt-PSF(N) at 240 °C (open) and 260 °C (filled). $p_{CO_2} = 0.1$ bar and $\tau = 0.01$ g_{cat}×min×ml⁻¹.

Apparent activation energy

The apparent activation energy (E_{app}) of CO₂ conversion was elucidated by performing experiments in the temperature range 220-280 °C at constant p_{CO_2} (0.1 bar), p_{H_2} (0.6 bar) and τ (0.01 g_{cat}×min×ml⁻¹). The results are presented as an Arrhenius type plot in Figure 4. The E_{app} of CO₂ conversion over all the UiO-67-Pt samples, and the Pt/SiO₂ sample, is calculated to 49-50 kJmol⁻¹ (Table 2), suggesting that the rate determining step of CO₂ hydrogenation is the same for all the materials. The lower activity of the Pt/SiO₂ material could be related to lower coverage of reactants or to the larger Pt particles. Considering the difference in CH₄ selectivity over the two materials, the IR measurements suggests that CO is more readily desorbed from the Pt/SiO₂ material, in agreement with the higher abundance of OH-groups present on the SiO₂ surface³⁴. Such reasoning could also be applied to the negative effect of time on stream and reaction temperature on CH₄ selectivity over the UiO-67-Pt-PSF material: CO was more easily desorbed from the used catalyst (Figure 3), and a lower CO coverage is expected at higher temperature due to entropy effects. However, the results of this study do not preclude a more direct involvement of the UiO-67-bipy framework in the CO₂ hydrogenation reaction.

Table 2. Apparent activation energies of CO₂ conversion over various samples of UiO-67-Pt-PSF and Pt/SiO₂, estimated from the Arrhenius plot in Fig. 4.

Sample	E_{app} (kJ×mol ⁻¹)
UiO-67-Pt-PSF(SA) - 0.14 g, 15 ml×min ⁻¹ , 250-425 μm	50 (±1.1)
UiO-67-Pt-PSF(N) – 0.1 g, 10 ml×min ⁻¹ , 250-425 μm	50 (±1.5)
UiO-67-Pt-PSF(N) – 0.1 g, 10 ml×min ⁻¹ , 177-250 μm	50 (±1.3)
UiO-67-Pt-PSF(N) – 0.1 g, 10 ml×min ⁻¹ , 250-425 μm	50 (±1.1)
Pt/SiO ₂ – 0.1 g, ~10 ml×min ⁻¹ , H ₂ /CO ₂ ~ 8.5, 250-400 μm	49 (±2.6)

3.3 Catalyst stability

3.3.1 The UiO-67-Pt-PSF(N) sample

Figure 8 shows XRD patterns and N₂ adsorption isotherms the UiO-67-Pt-PSF(N) sample before (A) and after (B) pressing at 0.5 tons, and after pre-activation followed by testing for 52 hours (C). XRD patterns and N₂ adsorption isotherms of UiO-67-bipy(N) are included for comparison (D). The XRD pattern is fully consistent with the UiO-67 structure. No apparent change in the microcrystalline structure is identified from the XRD patterns after various treatments, suggesting that the lattice of UiO-67-Pt-PSF(N) is stable under the respective conditions. In agreement with the XRD results, only minor differences are observed in the N₂ adsorption isotherms of UiO-67-bipy(N) and UiO-67-Pt-PSF(N) after pressing pre-activation and testing (Table 1, Figure 8). The lattice stability under reaction conditions is particularly noteworthy, since water is formed in the reaction and UiO-67 has previously been shown to have limited steam stability at room temperature¹². The reason for the higher stability under reaction conditions could be the lower affinity for water at the reaction temperature (250 °C). Literature studies show that, starting at 250 °C, the Zr₆O₆ cluster is reversibly dehydrated by the removal of two H₂O molecules¹⁶.

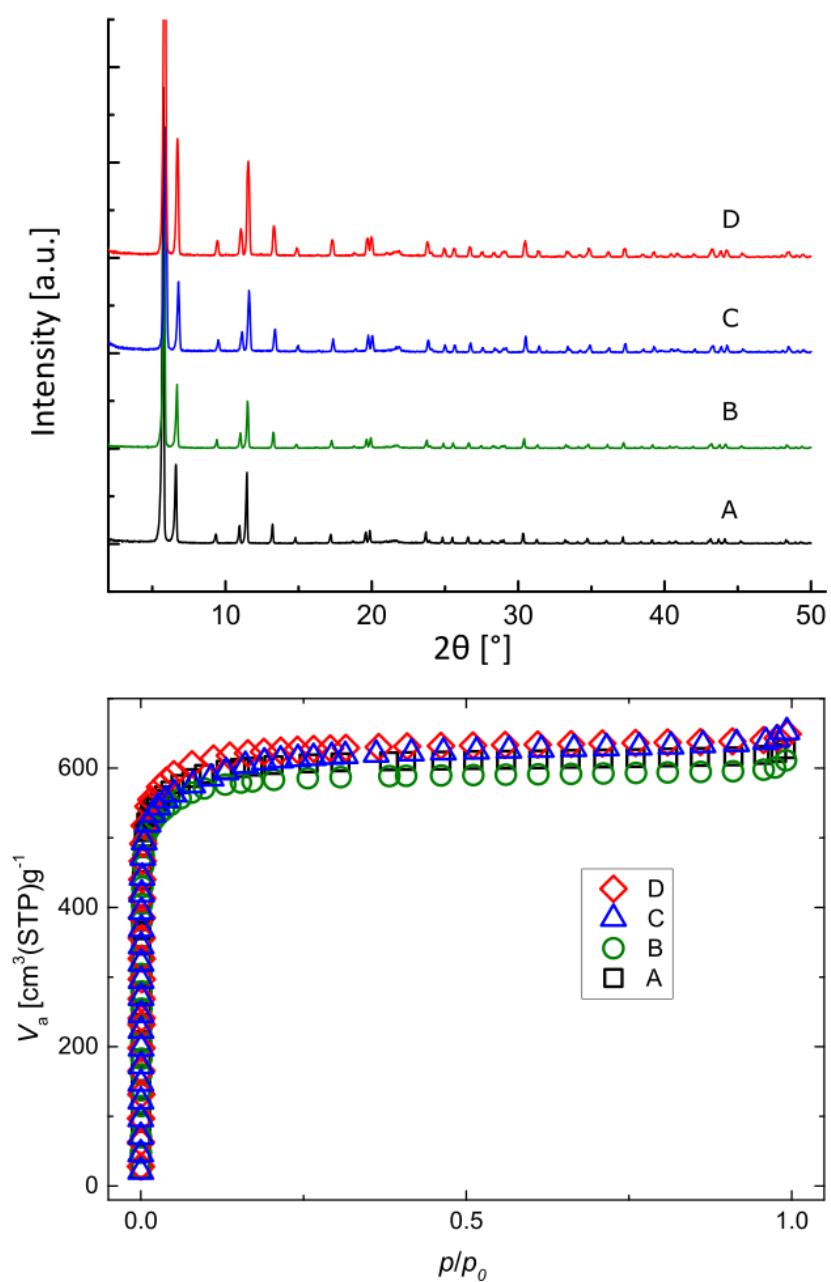


Figure 8. XRD patterns and N_2 adsorption isotherms of UiO-67-Pt-PSF(N) in the form of powder (A), pellets (B, pressed at 0.5 tons) and after pre-activation in 10 % H_2 followed by testing for the CO_2 hydrogenation reaction under 10-20 ml \times min⁻¹ flow of $H_2/CO_2/Ar = 6:1:3$ at temperatures in range 220-280 °C for 52 hours (C). UiO-67-bipy(N) (D).

Thermogravimetric (TG) measurements obtained during heating of UiO-67, UiO-67-bipy and UiO-67-Pt-PSF(N) are shown in Figure 9. Similar temperature behavior was observed for the UiO-67 and UiO-67-bipy samples, suggesting that the introduction of 5% bipy linker in the lattice had minor influence

on lattice stability. However, the Pt-containing samples degraded at a lower temperature than the other two samples. This difference probably results from slight changes introduced in the lattice with the grafting of PtCl_2 to the bipy linker, which are likely to induce mechanical stress⁵³. Pt may also possibly play a more active role as a catalyst of lattice degradation. No significant change in decomposition temperature was observed for the UiO-67-Pt-PSF(N) sample after pre-activation in 10 % H_2 followed by testing for the CO_2 hydrogenation reaction under $10\text{-}20 \text{ ml}\times\text{min}^{-1}$ flow of $\text{H}_2/\text{CO}_2/\text{Ar} = 6:1:3$ at temperatures in range $220\text{-}280 \text{ }^\circ\text{C}$ for 52 hours. Thus, Pt-containing UiO-67 exhibits a remarkable thermal stability in oxidizing conditions even after thermal treatment at $350 \text{ }^\circ\text{C}$ in reducing conditions, and long term testing for the title reaction at temperatures as high as $280 \text{ }^\circ\text{C}$.

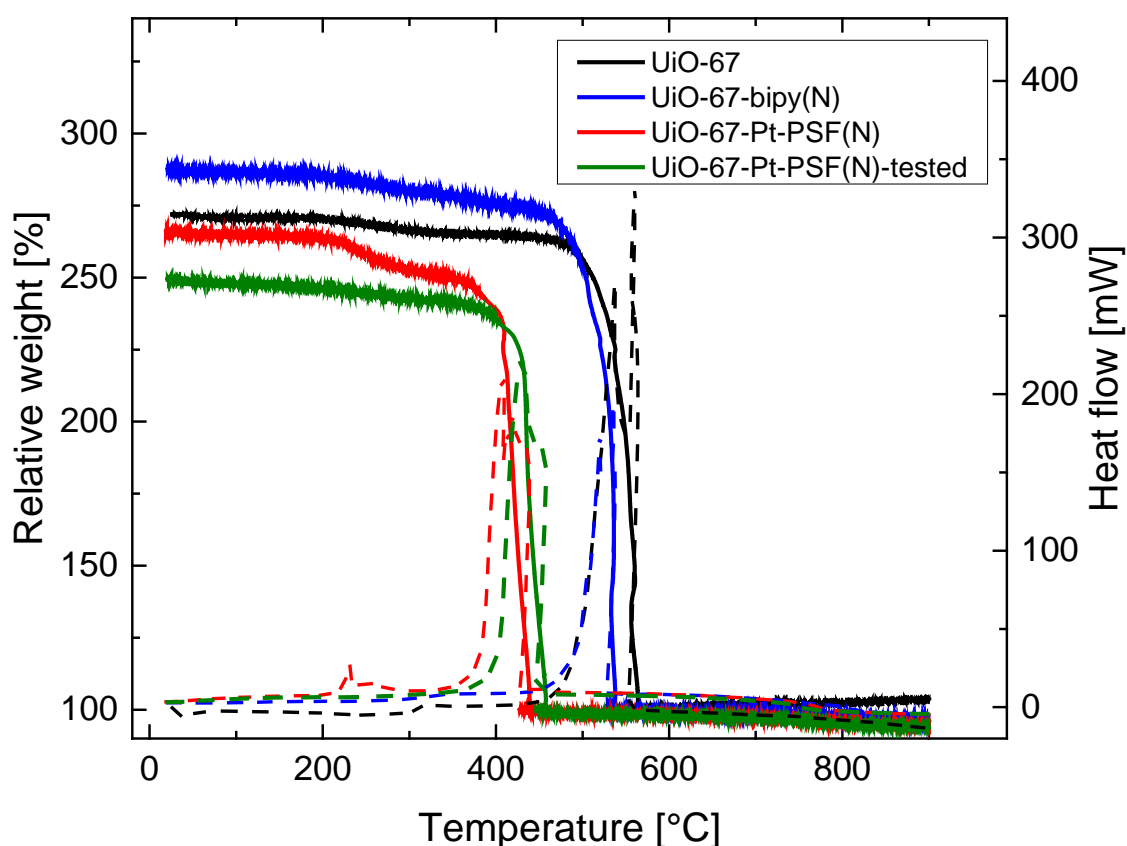


Figure 9. TG curves (solid lines) and differential thermal analysis (DTA) curves (dashed lines) of UiO-67 (black), UiO-67-bipy(N) (blue) and UiO-67-Pt-PSF(N) before (red) and after (green) pre-activation in 10 % H_2 followed by testing for the CO_2 hydrogenation reaction under $10\text{-}20 \text{ ml}\times\text{min}^{-1}$ flow of $\text{H}_2/\text{CO}_2/\text{Ar} = 6:1:3$ at temperatures in range $220\text{-}280 \text{ }^\circ\text{C}$ for 52 hours. The samples were heated from $20 \text{ }^\circ\text{C}$ to $900 \text{ }^\circ\text{C}$ at $5 \text{ }^\circ\text{C}\times\text{min}^{-1}$ under flow of synthetic air ($20 \text{ ml}\times\text{min}^{-1} \text{ N}_2$ and $5 \text{ ml}\times\text{min}^{-1} \text{ O}_2$).

FESEM images of the UiO-67-Pt-PSF(N) sample are shown in Figure 10, after drying in air at 150 °C (A), pressing at 0.5 tons (B) and after pre-activation in 10 % H₂/Ar at 350 °C for 1 hour followed by testing for the CO₂ hydrogenation reaction at 220-280 °C for 52 hours (C). As a first note, the crystal morphology was maintained during testing, including pressing and sieving prior to testing (See Section 2.3). Furthermore, the surface topology was intact after pressing; however, some lines were observed on the crystal surfaces after testing. They could represent scratches from the pressing and sieving treatment, or have been formed during testing. Finally, no Pt particle formation was observed on the outer crystal surface after 52 hours testing, thereby suggesting that the Pt nanoparticles which were formed during the pre-activation step (*vide ultra*) were stabilized inside the crystal lattice.

In conclusion, the UiO-67-Pt-PSF(N) sample showed excellent stability under the test conditions used in this study.

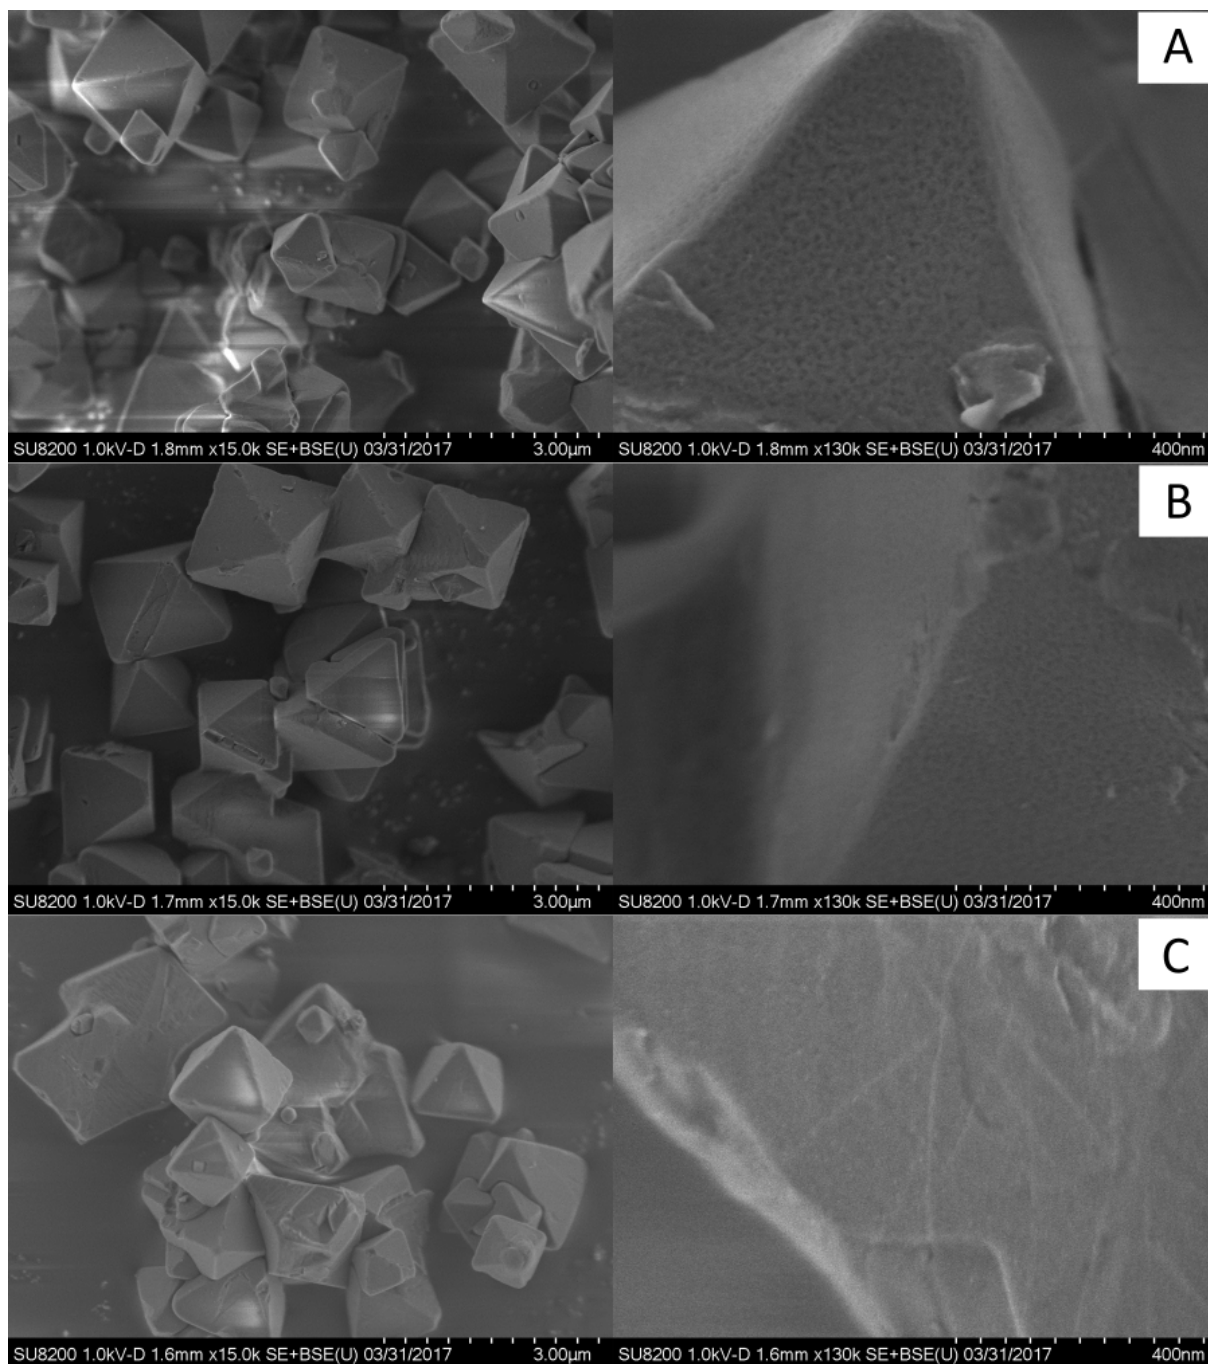


Figure 10. FESEM images of UiO-67-Pt-PSF(N) powder (A), pellets pressed at 0.5 tons (B), and after pre-activation in 10 % H₂ followed by testing for the CO₂ hydrogenation reaction under 10-20 ml×min⁻¹ flow of H₂/CO₂/Ar = 6:1:3 at temperatures in range 220-280 °C for 52 hours (C). Instrumental magnification: 15000× (left column) and 130000× (right column).

3.3.2 The UiO-67-Pt-PMLS sample

Detailed characterization was also performed for a sample prepared by the PMLS method. In order to follow the lattice stability before and after pre-activation and testing by FESEM, it was decided to test it without pressing and sieving it to a given particle size, to avoid mechanical damage of the crystal surface. This means that the flow conditions during catalytic testing were not optimal, and for that reason, the catalytic test data are not reported here. However, UiO-67-Pt-PMLS catalyst performed very similarly to the UiO-67-Pt-PSF(M) catalyst, reported in Section 3.2.1 and S3, with respect to activity, selectivity and stability.

X-ray diffractograms of the UiO-67-Pt-PMLS sample after pre-activation and after testing for 16 hours are shown in Figure 11. The diffractograms clearly indicate that the UiO-67-Pt-PMLS lattice is stable under reducing as well as reaction conditions.

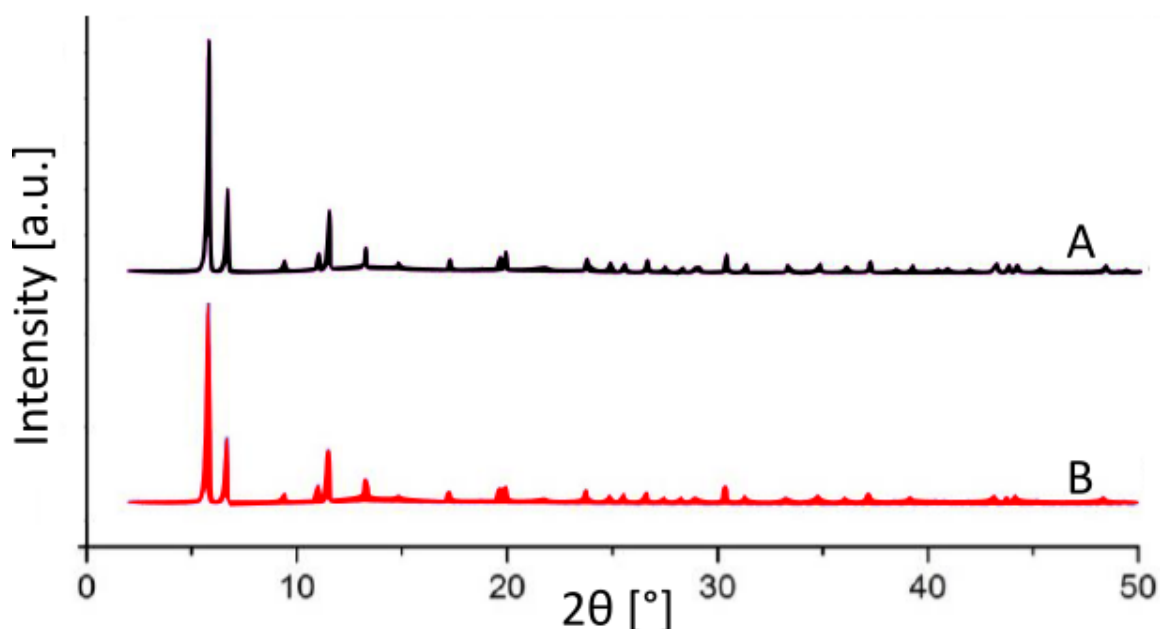


Figure 11. XRD patterns of UiO-67-Pt-PMLS after activation in 10 % H₂ (A) and operation under flow of H₂/CO₂/Ar = 3:1:6 at 250 °C for 16 hours (B).

TEM images of the UiO-67-Pt-PMLS sample after pre-activation at 350 °C in 10 % H₂/He flow are shown in Figure 12. The crystallinity of the UiO-67 framework was pointed out by the appearance of diffraction fringes with spacing of 14 Å (the same spacing as that related to the main diffraction peak in the XRD pattern of the UiO-67-Pt-PMLS sample (Figure 5)) observed at low magnification (A). At the same time, roundish Pt nanoparticles, well contrasted with respect to UiO-67, were clearly detected. Moreover, the analysis at higher magnification (B) put in evidence the presence of

crystalline Pt nanoparticles (signalled by blue circles in the figure) with d spacing of 2.25 Å related to the 1 1 1 face of the cubic phase (JCPDS File number 00-001-1194).

The Pt particle size distribution is shown in Figure 3C. Highly dispersed Pt nanoparticles, with average size of 2.6 ± 0.8 nm, were observed. The particle size distribution is quite narrow and a large fraction (> 50 %) of counted nanoparticles has size 2.5 nm; strikingly close to the size of the octahedral cavities in the UiO-67 structure (2.3 nm). Despite the high dispersion, these nanoparticles did not coalesce after prolonged time under the electron beam, meaning that they are stabilised within the UiO MOF framework.

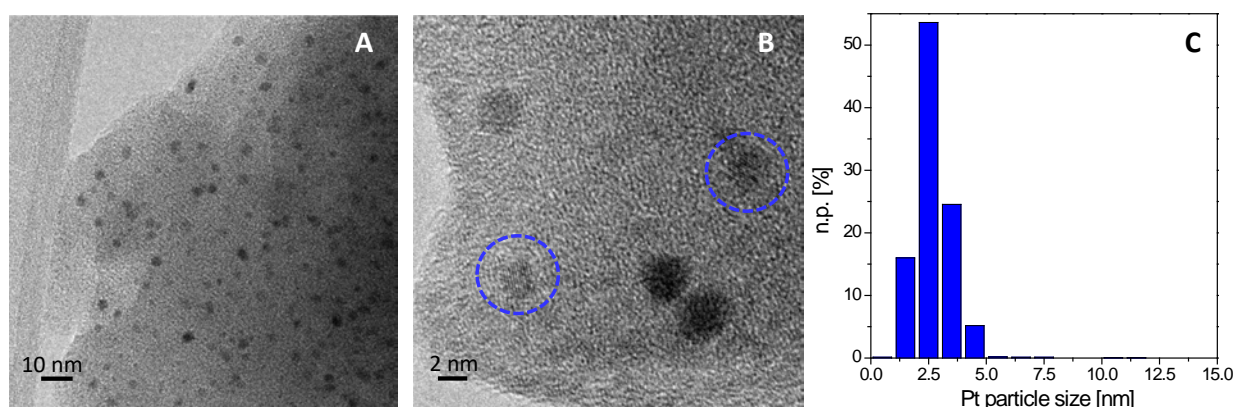


Figure 12. Low magnification (A) and high magnification (B) TEM images of UiO-67-Pt-PMLS after pre-activation at 350 °C in 10 % H₂/He flow. Pt particle size distribution (C). Instrumental magnification: 150000× (A) and 600000× (B).

FESEM images of the UiO-67-Pt-PMLS sample are shown in Figure 13, after pre-activation in 10 % H₂/He at 350 °C for 1 hour (A1,A2), and after testing for the CO₂ hydrogenation reaction at 250 °C for 16 hours (B) and 60 hours (C). As a first note, comparison between Figure 13 A1) and C) suggests that the crystal morphology was maintained during pre-activation and testing. Furthermore, the surface topology seemed intact after pre-activation and testing for 16 hours. A slight roughening of the crystal surfaces could be suggested from the lower resolution FESEM image of the sample tested for 60 hours, but a close-up image revealed no damage of the surface. Finally, no Pt particle formation was observed on the outer crystal surface after any of the treatments, thereby suggesting that the Pt nanoparticles which were formed during the pre-activation step (Figure 12) were stabilized inside the crystal lattice, in agreement with the TEM findings. In conclusion, the PMLS synthesis procedure yielded a material with excellent stability under CO₂ hydrogenation conditions, in line with the PSF method.

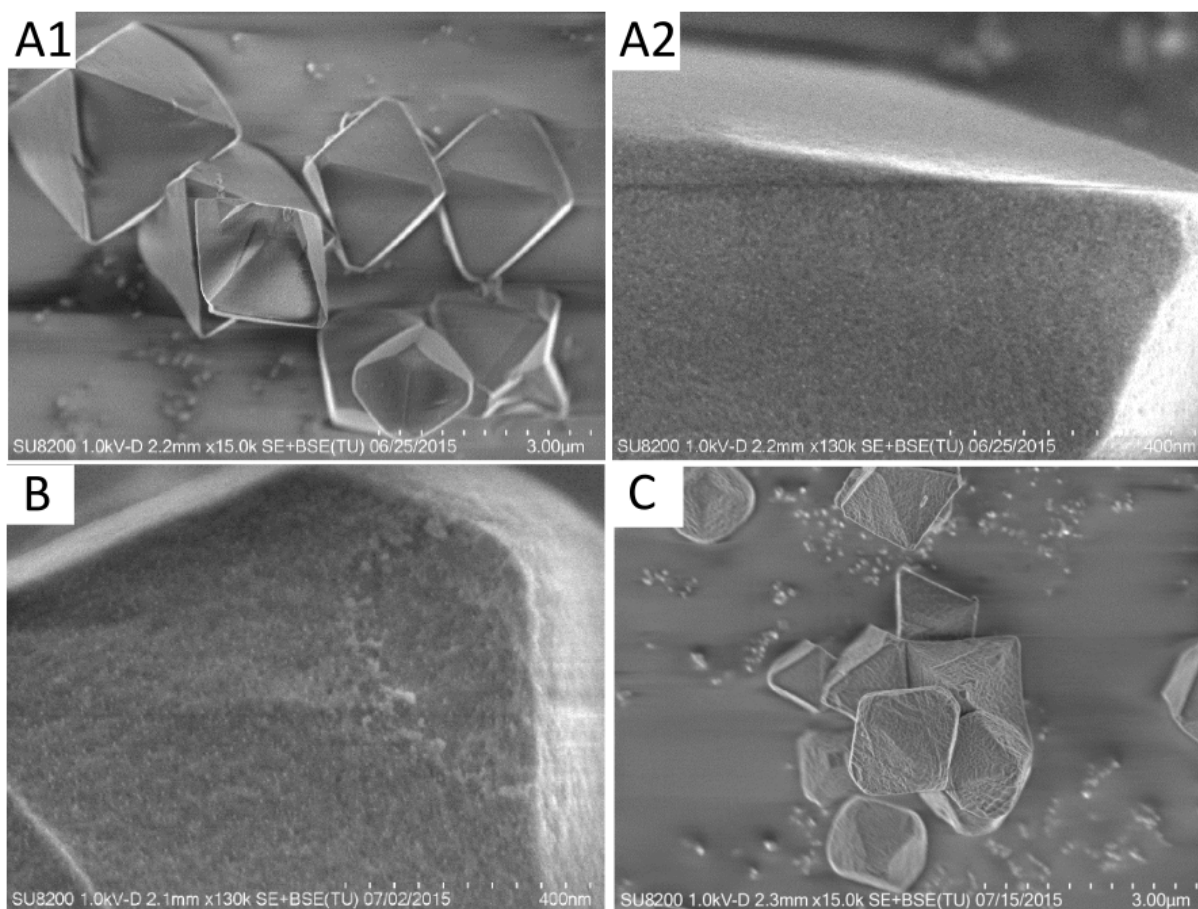


Figure 13. FESEM images of UiO-67-Pt-PMLS after activation in 10 % H₂ (A1, A2) and operation under flow of H₂/CO₂/Ar = 3:1:6 at 250 °C for 16 hours (B) and for 60 hours (C). Instrumental magnification: 15000× (A1,C) and 130000× (A2,B).

Conclusion

In this work, Pt was introduced to the UiO-67 Zr-MOF framework by grafting it to a bipyridine-based linker, which constituted 5 % of the framework linkers. Pt nanocrystals were obtained by pre-activation in flowing H₂/Ar at 350 °C. Thorough characterization of as-made, pre-activated and tested material (T=220-280 °C and atmospheric pressure, with H₂/CO₂ ratios in the range 0.2-9 and contact times in the range 0.004-0.01 g_{cat}×min×ml⁻¹ for up to 60 hours) showed that the UiO-67 Zr-MOF framework was stable during all treatments.

Catalytic testing for the CO₂ hydrogenation reaction showed that CO₂ conversion is positively correlated with the degree of Pt reduction, in accordance with recent literature. CO selectivity above 90 % was obtained under all tested conditions, contact time variation experiments showed that CO is a primary product of reaction, while CH₄ is a secondary product, formed via CO. A low reaction order

in P(H₂) was observed, suggesting high coverage of the Pt surface, whereas the reaction order in P(CO₂) was. Testing of catalyst crystals with 0.15 and 2.0 micron crystal size, respectively, revealed no influence of diffusion on the reaction rate. Comparison to a conventional Pt/SiO₂ catalyst showed very similar activation energy, with $E_a = 50 \pm 3 \text{ kJ} \times \text{mol}^{-1}$ suggesting that CO₂ hydrogenation follows the same mechanism over the two materials.

Overall, this study shows that the partially bipy-functionalized UiO-67 Zr-MOF framework is well suited as support for the Pt-catalyzed reverse water gas shift reaction, and is able to stabilize Pt metal nanoparticles of similar size as the framework cavities. Comparison to a conventional Pt/SiO₂ catalyst further demonstrated that the Zr-MOF framework facilitated hydrogenation of CO to CH₄. Future introduction of a second functionality in the Zr-MOF material, aimed at the stabilization of Pt-CO entities, is expected to further promote this reaction.

References

- (1) Jiang, Z.; Xiao, T.; Kuznetsov, V. L.; Edwards, P. P., Turning carbon dioxide into fuel. *Philos. Trans. R. Soc., A* **2010**, *368* (1923), 3343-3364.
- (2) Chen, Z.; Deutsch, T. G.; Dinh, H. N.; Domen, K.; Emery, K.; Forman, A. J.; Gaillard, N.; Garland, R.; Heske, C.; Jaramillo, T. F.; Kleiman-Shwarsctein, A.; Miller, E.; Takahabe, K.; Turner, J., UV-Vis Spectroscopy. In *Photoelectrochemical Water Splitting: Standards, Experimental Methods, and Protocols*, Springer New York: New York, NY, 2013; pp 49-62.
- (3) Wang, W.; Wang, S.; Ma, X.; Gong, J., Recent advances in catalytic hydrogenation of carbon dioxide. *Chem. Soc. Rev.* **2011**, *40*, 3703-3727.
- (4) Westermann, A.; Azambre, B.; Bacariza, M. C.; Graça, I.; Ribeiro, M. F.; Lopes, J. M.; Henriques, C., Insight into CO₂ methanation mechanism over NiUSY zeolites: An operando IR study. *Appl. Catal., B* **2015**, *174-175*, 120-125.
- (5) Aldana, P. A. U.; Ocampo, F.; Kobl, K.; Louis, B.; Thibault-Starzyk, F.; Daturi, M.; Bazin, P.; Thomas, S.; Roger, A. C., Catalytic CO₂ valorization into CH₄ on Ni-based ceria-zirconia. Reaction mechanism by operando IR spectroscopy. *Catal. Today* **2013**, *215*, 201-207.
- (6) Gao, J.; Liu, Q.; Gu, F.; Liu, B.; Zhong, Z.; Su, F., Recent advances in methanation catalysts for the production of synthetic natural gas. *RSC Adv.* **2015**, *5* (29), 22759-22776.
- (7) Román-Martínez, M. C.; Cazorla-Amorós, D.; Salinas-Martínez de Lecea, C.; Linares-Solano, A., Structure Sensitivity of CO₂ Hydrogenation Reaction Catalyzed by Pt/Carbon Catalysts. *Langmuir* **1996**, *12*, 379-385.

- (8) Wei, J.; Iglesia, E., Mechanism and Site Requirements for Activation and Chemical Conversion of Methane on Supported Pt Clusters and Turnover Rate Comparisons among Noble Metals. *J. Phys. Chem. B* **2004**, *108*, 4094-4103.
- (9) Sumida, K.; Rogow, D. L.; Mason, J. A.; McDonald, T. M.; Bloch, E. D.; Herm, Z. R.; Bae, T.-H.; Long, J. R., Carbon Dioxide Capture in Metal–Organic Frameworks. *Chem. Rev.* **2012**, *112*, 724-781.
- (10) Øien, S.; Agostini, G.; Svelle, S.; Borfecchia, E.; Lomachenko, K. A.; Mino, L.; Gallo, E.; Bordiga, S.; Olsbye, U.; Lillerud, K. P.; Lamberti, C., Probing Reactive Platinum Sites in UiO-67 Zirconium Metal–Organic Frameworks. *Chem. Mater.* **2015**, *27*, 1042-1056.
- (11) Huang, H.; Zhang, W.; Yang, F.; Wang, B.; Yang, Q.; Xie, Y.; Zhong, C.; Li, J.-R., Enhancing CO₂ adsorption and separation ability of Zr(IV)-based metal–organic frameworks through ligand functionalization under the guidance of the quantitative structure–property relationship model. *Chem. Eng. J.* **2016**, *289*, 247-253.
- (12) Øien-Ødegaard, S.; Bouchevreau, B.; Hylland, K.; Wu, L.; Blom, R.; Grande, C.; Olsbye, U.; Tilset, M.; Lillerud, K. P., UiO-67-type Metal–Organic Frameworks with Enhanced Water Stability and Methane Adsorption Capacity. *Inorg. Chem.* **2016**, *55*, 1986-1991.
- (13) Wang, B.; Huang, H.; Lv, X.-L.; Xie, Y.; Li, M.; Li, J.-R., Tuning CO₂ Selective Adsorption over N₂ and CH₄ in UiO-67 Analogues through Ligand Functionalization. *Inorg. Chem.* **2014**, *53*, 9254-9259.
- (14) Wang, C.; Xie, Z.; deKrafft, K. E.; Lin, W., Doping Metal–Organic Frameworks for Water Oxidation, Carbon Dioxide Reduction, and Organic Photocatalysis. *J. Am. Chem. Soc.* **2011**, *133*, 13445-13454.
- (15) Katz, M. J.; Brown, Z. J.; Colon, Y. J.; Siu, P. W.; Scheidt, K. A.; Snurr, R. Q.; Hupp, J. T.; Farha, O. K., A facile synthesis of UiO-66, UiO-67 and their derivatives. *Chem. Commun.* **2013**, *49*, 9449-9451.
- (16) Cavka, J. H.; Jakobsen, S.; Olsbye, U.; Guillou, N.; Lamberti, C.; Bordiga, S.; Lillerud, K. P., A New Zirconium Inorganic Building Brick Forming Metal Organic Frameworks with Exceptional Stability. *J. Am. Chem. Soc.* **2008**, *130*, 13850-13851.
- (17) Rimoldi, M.; Howarth, A. J.; DeStefano, M. R.; Lin, L.; Goswami, S.; Li, P.; Hupp, J. T.; Farha, O. K., Catalytic Zirconium/Hafnium-Based Metal–Organic Frameworks. *ACS Catal.* **2017**, *7*, 997-1014.
- (18) Vermoortele, F.; Vandichel, M.; Van de Voorde, B.; Ameloot, R.; Waroquier, M.; Van Speybroeck, V.; De Vos, D. E., Electronic Effects of Linker Substitution on Lewis Acid Catalysis with Metal–Organic Frameworks. *Angew. Chem., Int. Ed.* **2012**, *51*, 4887-4890.

- (19)Liu, Y.; Klet, R. C.; Hupp, J. T.; Farha, O., Probing the correlations between the defects in metal-organic frameworks and their catalytic activity by an epoxide ring-opening reaction. *Chem. Commun.* **2016**, *52*, 7806-7809.
- (20)Toyao, T.; Miyahara, K.; Fujiwaki, M.; Kim, T.-H.; Dohshi, S.; Horiuchi, Y.; Matsuoka, M., Immobilization of Cu Complex into Zr-Based MOF with Bipyridine Units for Heterogeneous Selective Oxidation. *J. Phys. Chem. C* **2015**, *119*, 8131-8137.
- (21)Li, X.; Guo, Z.; Xiao, C.; Goh, T. W.; Tesfagaber, D.; Huang, W., Tandem Catalysis by Palladium Nanoclusters Encapsulated in Metal–Organic Frameworks. *ACS Catal.* **2014**, *4*, 3490-3497.
- (22)An, B.; Zhang, J.; Cheng, K.; Ji, P.; Wang, C.; Lin, W., Confinement of Ultrasmall Cu/ZnOx Nanoparticles in Metal–Organic Frameworks for Selective Methanol Synthesis from Catalytic Hydrogenation of CO₂. *J. Am. Chem. Soc.* **2017**, *139*, 3834-3840.
- (23)Guo, Z.; Xiao, C.; Maligal-Ganesh, R. V.; Zhou, L.; Goh, T. W.; Li, X.; Tesfagaber, D.; Thiel, A.; Huang, W., Pt Nanoclusters Confined within Metal–Organic Framework Cavities for Chemoselective Cinnamaldehyde Hydrogenation. *ACS Catal.* **2014**, *4*, 1340-1348.
- (24)Choi, K. M.; Na, K.; Somorjai, G. A.; Yaghi, O. M., Chemical environment control and enhanced catalytic performance of platinum nanoparticles embedded in nanocrystalline metal–organic frameworks. *J. Am. Chem. Soc.* **2015**, *137*, 7810-7816.
- (25)Hester, P.; Xu, S.; Liang, W.; Al-Janabi, N.; Vakili, R.; Hill, P.; Muryrn, C. A.; Chen, X.; Martin, P. A.; Fan, X., On thermal stability and catalytic reactivity of Zr-based metal–organic framework (UiO-67) encapsulated Pt catalysts. *J. Catal.* **2016**, *340*, 85-94.
- (26)Zhuang, G.-l.; Bai, J.-q.; Zhou, X.; Gao, Y.-f.; Huang, H.-l.; Cui, H.-q.; Zhong, X.; Zhong, C.-L.; Wang, J.-g., The Effect of N-Containing Supports on Catalytic CO Oxidation Activity over Highly Dispersed Pt/UiO-67. *Eur. J. Inorg. Chem.* **2017**, *2017*, 172-178.
- (27)Freel, J., Chemisorption on supported platinum. *Journal of Catalysis* **1972**, *25*, 139-148.
- (28)Haneda, M.; Watanabe, T.; Kamiuchi, N.; Ozawa, M., Effect of platinum dispersion on the catalytic activity of Pt/Al₂O₃ for the oxidation of carbon monoxide and propene. *Appl. Catal., B* **2013**, *142–143*, 8-14.
- (29)Valenzano, L.; Civalleri, B.; Chavan, S.; Bordiga, S.; Nilsen, M. H.; Jakobsen, S.; Lillerud, K. P.; Lamberti, C., Disclosing the Complex Structure of UiO-66 Metal Organic Framework: A Synergic Combination of Experiment and Theory. *Chem. Mater.* **2011**, *23*, 1700-1718.
- (30)Shearer, G. C.; Forselv, S.; Chavan, S.; Bordiga, S.; Mathisen, K.; Bjørgen, M.; Svelle, S.; Lillerud, K. P., In Situ Infrared Spectroscopic and Gravimetric Characterisation of the Solvent Removal and Dehydroxylation of the Metal Organic Frameworks UiO-66 and UiO-67. *Top. Catal.* **2013**, *56*, 770-782.

- (31) Råberg, L. B.; Jensen, M. B.; Olsbye, U.; Daniel, C.; Haag, S.; Mirodatos, C.; Sjøstad, A. O., Propane dry reforming to synthesis gas over Ni-based catalysts: Influence of support and operating parameters on catalyst activity and stability. *J. Catal.* **2007**, *249*, 250-260.
- (32) Braglia, L.; Borfecchia, E.; Lomachenko, K. A.; Bugaev, A. L.; Guda, A. A.; Soldatov, A. V.; Bleken, B. T. L.; Oien, S.; Olsbye, U.; Lillerud, K. P.; Bordiga, S.; Agostini, G.; Manzoli, M.; Lamberti, C., Tuning Pt and Cu sites population inside functionalized UiO-67 MOF by controlling activation conditions. *Faraday Discuss.* **2017**, DOI: 10.1039/c7fd00024c
- (33) Ding, K.; Gulec, A.; Johnson, A. M.; Schweitzer, N. M.; Stucky, G. D.; Marks, L. D.; Stair, P. C., Identification of active sites in CO oxidation and water-gas shift over supported Pt catalysts. *Science* **2015**, *350*, 189-192.
- (34) Kattel, S.; Yan, B.; Chen, J. G.; Liu, P., CO₂ hydrogenation on Pt, Pt/SiO₂ and Pt/TiO₂: Importance of synergy between Pt and oxide support. *J. Catal.* **2016**, *343*, 115-126.
- (35) Ferri, D.; Burgi, T.; Baiker, A., Probing boundary sites on a Pt/Al₂O₃ model catalyst by CO₂ hydrogenation and in situ ATR-IR spectroscopy of catalytic solid-liquid interfaces. *Phys. Chem. Chem. Phys.* **2002**, *4*, 2667-2672.
- (36) Goguet, A.; Meunier, F. C.; Tibiletti, D.; Breen, J. P.; Burch, R., Spectrokinetic investigation of reverse water-gas-shift reaction intermediates over a Pt/CeO₂ catalyst. *J. Phys. Chem. B* **2004**, *108*, 20240-20246.
- (37) Kim, S. S.; Lee, H. H.; Hong, S. C., A study on the effect of support's reducibility on the reverse water-gas shift reaction over Pt catalysts. *Appl. Catal., A* **2012**, *423*, 100-107.
- (38) Crossley, A.; King, D. A., Infrared spectra for CO isotopes chemisorbed on Pt "111": Evidence for strong adsorbate coupling interactions. *Surface Science* **1977**, *68*, 528-538.
- (39) Hayden, B. E.; Kretschmar, K.; Bradshaw, A. M.; Greenler, R. G., An infrared study of the adsorption of CO on a stepped platinum surface. *Surface Science* **1985**, *149* (2), 394-406.
- (40) Hayden, B. E.; Bradshaw, A. M., The adsorption of CO on Pt(111) studied by infrared reflection—Absorption spectroscopy. *Surface Science* **1983**, *125*, 787-802.
- (41) Hoffmann, F. M.; Bradshaw, A. M., IR reflection-absorption spectroscopy of CO adsorbed on platinum and palladium. *J. Catal.* **1976**, *44*, 328-331.
- (42) Krebs, H.-J.; Lüth, H., Evidence for two different adsorption sites of CO on Pt(111) from infrared reflection spectroscopy. *Appl. Phys.* **1977**, *14*, 337-342.
- (43) Shigeishi, R. A.; King, D. A., Chemisorption of carbon monoxide on platinum {111}: Reflection-absorption infrared spectroscopy. *Surface Science* **1976**, *58*, 379-396.
- (44) Brandt, R. K.; Hughes, M. R.; Bourget, L. P.; Truszkowska, K.; Greenler, R. G., The interpretation of CO adsorbed on Pt/SiO₂ of two different particle-size distributions. *Surface Science* **1993**, *286*, 15-25.

- (45) Cheah, S. K.; Bernardet, V. P.; Franco, A. A.; Lemaire, O.; Gelin, P., Study of CO and Hydrogen Interactions on Carbon-Supported Pt Nanoparticles by Quadrupole Mass Spectrometry and Operando Diffuse Reflectance FTIR Spectroscopy. *J. Phys. Chem. C* **2013**, *117*, 22756-22767.
- (46) Coloma, F.; Coronado, J. M.; Rochester, C. H.; Anderson, J. A., Infrared study of crotonaldehyde and CO adsorption on a Pt/TiO₂ catalyst. *Catal. Lett.* **1998**, *51*, 155-162.
- (47) Haaland, D. M., Infrared studies of CO adsorbed on Pt/Al₂O₃: Evidence for CO bonded in 3-fold coordination. *Surface Science* **1987**, *185*, 1-14.
- (48) Raskó, J., CO-induced surface structural changes of Pt on oxide-supported Pt catalysts studied by DRIFTS. *J. Catal.* **2003**, *217*, 478-486.
- (49) Chakarova, K.; Mihaylov, M.; Hadjiivanov, K., FTIR spectroscopic study of CO adsorption on Pt-H-ZSM-5. *Microporous and Mesoporous Mater.* **2005**, *81*, 305-312.
- (50) Chakarova, K.; Mihaylov, M.; Hadjiivanov, K., Polycarbonyl species in Pt/H-ZSM-5: FTIR spectroscopic study of ¹²CO-¹³CO co-adsorption. *Catal. Commun.* **2005**, *6*, 466-471.
- (51) Kubanek, P.; Schmidt, H. W.; Spliethoff, B.; Schüth, F., Parallel IR spectroscopic characterization of CO chemisorption on Pt loaded zeolites. *Microporous and Mesoporous Mater.* **2005**, *77*, 89-96.
- (52) Román-Martínez, M. C.; Cazorla-Amoròs, D.; Linares-Solano, A.; Salinas-Martínez de Lecea, C., CO₂ hydrogenation under pressure on catalysts Pt/Ca/C. *Appl. Catal., A* **1996**, *134*, 159-167.
- (53) Gonzalez, M. I.; Bloch, E. D.; Mason, J. A.; Teat, S. J.; Long, J. R., Single-Crystal-to-Single-Crystal Metalation of a Metal-Organic Framework: A Route toward Structurally Well-Defined Catalysts. *Inorg. Chem.* **2015**, *54*, 2995-3005.