

AperTO - Archivio Istituzionale Open Access dell'Università di Torino

**Encapsulation of the glyphosate herbicide in mesoporous and soil-affine sorbents for its prolonged release**

**This is the author's manuscript**

*Original Citation:*

*Availability:*

This version is available <http://hdl.handle.net/2318/1833769> since 2022-06-27T11:53:09Z

*Published version:*

DOI:10.1016/j.cej.2021.134225

*Terms of use:*

Open Access

Anyone can freely access the full text of works made available as "Open Access". Works made available under a Creative Commons license can be used according to the terms and conditions of said license. Use of all other works requires consent of the right holder (author or publisher) if not exempted from copyright protection by the applicable law.

(Article begins on next page)

# Encapsulation of the glyphosate herbicide in mesoporous and soil-affine sorbents for its prolonged release

*L. Rivoira<sup>1\*</sup>, S. Frassati<sup>1</sup>, S. Cordola<sup>2</sup>, M. Castiglioni<sup>1</sup>, B. Onida<sup>2</sup>, S. Ronchetti<sup>2</sup>, I. Ingrando<sup>1</sup>,  
M.C. Bruzzoniti<sup>1\*</sup>*

<sup>1</sup> *Department of Chemistry, University of Torino, Via Pietro Giuria 7, 10125, Torino, Italy*

<sup>2</sup> *Department of Applied Science and Technology, Polytechnical University of Torino,  
Corso Duca degli Abruzzi 24, 10129, Torino, Italy*

\*Corresponding authors:

E-mail address: [luca.rivoira@unito.it](mailto:luca.rivoira@unito.it) (L. Rivoira) and [mariaconcetta.bruzzoniti@unito.it](mailto:mariaconcetta.bruzzoniti@unito.it) (M.C. Bruzzoniti). Address: Via Pietro Giuria 7, 10125, Torino (Italy). Phone number: +39 0116705245. Fax number: +39 0112305245

Keywords: encapsulation; weed control; Al pillared montmorillonite; herbicide; prolonged release, glyphosate

Abstract

The increase in herbicide consumption, in particularly glyphosate, is causing considerable health and environmental concerns, due to its possible carcinogenic effects. Indeed, its widespread and intensive use promotes its diffusion in the surrounding environment. Additionally, the operator's exposure to the herbicide is not negligible.

In this work the encapsulation of glyphosate into three selected, eco-friendly silica- and clay- based supports, namely SBA-15, montmorillonite (MMT) and Al pillared montmorillonite (Al-MMT) to promote both a punctual application and a prolonged release of glyphosate is innovatively presented.

Preliminary, substrates were characterized pre and post encapsulation through XRD and nitrogen adsorption measurements, to assess the incorporation of the herbicide. Release studies were performed in aqueous matrices of different composition, namely ultrapure water, 0.02M oxalic pH 3 (simulating acid rains) and 0.01M CaCl<sub>2</sub> solution (simulating soil salinity). Within all these media, Al-MMT exhibited a slow-releasing mechanism, with about 10-20% of glyphosate still retained on the support after 7 days, ascribed to complexation and electrostatic interactions.

Three different kinetic models usually applied within controlled-releasing processes, i.e. zero order, pseudo-first order and Korsmeyer–Peppas models, were used to describe glyphosate release from Al-MMT in CaCl<sub>2</sub> solutions, with Korsmeyer–Peppas model providing the best fit to experimental data ( $R^2 > 0.990$ ). Finally, a water/soil bench-scaled system was efficiently tested, confirming the successfully applicability of Al-MMT in the prolonged release of glyphosate in real systems.

## 1. Introduction

Weed control is the botanical component of pest control that is used to prevent weeds from reaching a matured crop which is ready for cultivation [1]. Both physical and chemical methods are exploited to reduce weeds that are harmful to agricultural plants and fodder. Among them, herbicides are the dominant tool used for weed control in modern agriculture.

Nowadays, it is recognized that, to ensure the effectiveness of crop production, herbicides are often applied at exceeding dosages [2] and that current formulations generally release the compound into the environment practically instantaneously [3].

In the light of the information described above, a wide use of herbicides is evident, thus leading all the countries of the world to face different problems, such as the rapid evolution of herbicide-resistant weeds [4, 5], the environmental impact of these compounds, [6], and the impact on human health, with particular attention to worker exposure [7, 8], with 170,000 workers worldwide employed in the agricultural died every year. On these incidences, a correlation between deaths and exposure to toxic pesticides through spray, drift and direct contact cannot be excluded [9].

In order to prevent the above-mentioned issues and given the public pressure to reduce the overall pesticide use, new integrated weed management strategies are now strongly encouraged [10, 11]. Among these, an important part is devoted to the development of new methods for the application of herbicides on soils.

Among the several herbicide formulations that are applied, glyphosate is probably the most used in the world (about 720k tons production in 2012) [12]. Glyphosate (N-(phosphonomethyl)glycine) is a broadspectrum post-emergence herbicide used both in agriculture and for the conservation of green spaces, such as parks and gardens [13]. The more common methods of glyphosate use include broadcast, aerial, spot, and directed spray applications [14]. It should be remarked that despite glyphosate is typically spread on leaves, its absorption through roots has been clearly assessed [15] and application to soils are also reported, i.e. for fungicidal aims [16].

Despite its huge consumption, glyphosate has been the subject of controversial discussions over its impact on the environment and human health in recent years, with IARC (International Agency for Research on Cancer) classifying glyphosate as *a probable human carcinogen compound* (class 2A), oppositely to EFSA (European Food Safety Authority) stating that this herbicide *is unlikely to pose a carcinogenic hazard to humans*.

Despite this still-open discussion, on December 12, 2019 European Union renewed the licence for the sale of glyphosate for five years [17], even if some countries (for example Italy) has already introduced some restrictions on the use of this herbicide [18].

The impact of glyphosate on the environment has been extensively studied, as traces of glyphosate and its metabolites could be found both in water basins, in soils and even in the atmosphere [19]. Therefore, selected approaches are nowadays exploited to face the emergency caused by the use of glyphosate. Most of them are post-use remedies, and are mainly based on the development of new technologies for the removal of the herbicide from the environmental compartments [20, 21]. However, it is also appropriate to evaluate some approaches defined "a priori" which, on the contrary, are based on the reduction of the quantity of glyphosate released into the environment.

The incorporation of active formulations inside specific carriers to obtain a controlled release in the environment has been extensively explored for agricultural applications, in order to set-up the concentration of the active principle within a range spanning from the minimum effective concentration to the maximum concentration safe for the operator [22]. Applications reporting the encapsulation of fungicides [23], herbicides [24], insecticides [25], acaricides [26], as well as of compounds intended for the stimulation of plant growth and productivity [27] are frequently presented in the scientific literature. Conversely, research concerning glyphosate is under-investigated and light controlled [28] and supramolecular [29] systems are the only solutions proposed.

Mesoporous silica and clay based materials exhibit adsorption properties that were exploited for the preparation of sorptive substrates [30, 31] and in water remediation technologies [32, 33]. In

particular, the removal of herbicides using both types of supports through selective bonds between silica or clay supports with the active compounds is demonstrated [34].

Hence, this work aimed at the innovative encapsulation of glyphosate into selected silica- and clay- based supports. The encapsulation of the herbicide allows the application of the loaded support, promoting both a punctual application and the controlled release of glyphosate, thus limiting human exposure to glyphosate, during application. To the best of our knowledge, this manuscript represents the first study specifically devoted to the encapsulation of glyphosate into mesoporous sorbents, which indeed have a structure affine to the composition of the soil.

For this study, three different types of environmental-friendly mesoporous silica and clay-based supports were selected, namely: SBA-15, montmorillonite (MMT) and Al pillared montmorillonite (Al-MMT). MMT and Al-MMT can be also considered low cost and then their use appears feasible in the proposed application. After physicochemical characterization of the pre- and post-impregnated supports, tests on the release of glyphosate were performed simulating different environmental conditions, such as acid rains or soil leaching. Data obtained within release tests were fitted to kinetics models typically used to describe desorption of active principles from mesoporous supports. Finally, the sorbent showing the best releasing performances was chosen for a real sample application, in a water/soil bench-scaled system.

## **2. Experimental**

### 2.1 Materials and reagents

A highly stable mesoporous silica sieve (Santa Barbara Amorphous, hereafter called SBA-15), montmorillonite K-10 (MMT) and Al pillared montmorillonite (Al-MMT) were purchased from Sigma-Aldrich (Darmstadt, Germany).

Glyphosate, sodium hydroxide solution (grade >98%), ethanol, hydrochloride acid (40%), oxalic acid (98%) and calcium chloride were from Sigma-Aldrich (Darmstadt, Germany).

High purity water (18.2 M $\Omega$  cm resistivity at 25 °C), produced by an Elix Milli Q Academic system (Millipore, Vimodrone, MI, Italy) was used for standard and eluent preparation.

## 2.2 Instrumental setup and calibration

The release profiles of glyphosate from the tested substrates were evaluated by means of suppressed ion chromatography as recently optimized by our research group [20]. A DX-100 ion chromatograph (25- $\mu$ L injection loop) from Dionex, Thermo Scientific, (Sunnyvale, CA, USA) equipped with a conductivity detector was used. An IonPac AG16 (50  $\times$  4 mm) and IonPac AS16 (250  $\times$  4 mm) were used as guard and analytical columns, respectively. Mobile phase was 35 mM NaOH at a flow rate of 1.0 mL/min. Detection was performed by electrochemical suppressed conductivity (100mA current set-up) using a 4-mm ESRS-300 membrane suppressor. Chromatographic data were collected by PeakNet 2.8 software.

For calibration curve, a 100 mg/L glyphosate stock solution was used to prepare standard solutions (six levels, from 0.5 to 15 mg/L). Each level was injected in triplicate and a new calibration curve was run, weekly. Limits of detection and limits of quantifications of the chromatographic method were calculated according to Shrivastava and Gupta and were 0.1 mg/L and 0.3 mg/L, respectively [35].

## 2.3 Impregnation of the supports with glyphosate

The impregnation of supports with glyphosate was achieved using water as solvent through the incipient wetness impregnation technique [36], by which a volume of a solution containing the active ingredient to be incorporated is put in contact with the support itself. Consequently, the solution is forced to spread by capillary within the available pores, by means of a manual or a

mechanical mixing. Finally, the impregnated material is dried as to evaporate the excess of solvent and to allow the deposition of the desired molecules inside the support.

In detail, a saturated solution of glyphosate was prepared by dissolving 0.4 g of glyphosate in 33 mL of water (solubility=12 g/L, at room temperature [37]). Subsequently, 1 mL of such solution was added dropwise to 0.6 g of each support, thus obtaining a homogenous slurry, which was finally oven dried at 60°C for 24 hours. The impregnation procedure was performed at room temperature and was repeated until the glyphosate saturated solution was totally consumed. The procedure allowed to obtain 40% glyphosate impregnation in respect to the total weight of the support.

#### 2.4 Physicochemical characterization of the supports pre- and post-impregnation

X-ray diffraction (XRD) patterns were obtained using a PANalytical X'Pert Powder (Cu K $\alpha$  radiation) diffractometer. The measurements were performed by means of a circular sample holder with diameter of 30 mm and thickness of 2 mm. Field Emission Scanning Microscopy (FESEM) images were recorded with a Merlin instrument (Zeiss, Germany). Nitrogen adsorption isotherms were measured using a Quantachrome (FL, USA) AUTOSORB-1 instrument. Prior to nitrogen adsorption, samples were outgassed (393 K, 5 h). BET specific surface areas (SSA) were calculated in the relative pressure range 0.04–0.1.

#### 2.5 Release of glyphosate from supports in aqueous solutions

The release of encapsulated glyphosate from the different tested supports in aqueous solutions, was evaluated simulating different environmental conditions. In detail, 0.25 g of each impregnated material was put in contact with 15 mL of the following aqueous solutions: i) ultrapure water, pH 6.5; ii) 0.02 M oxalic acid (pH 3), to simulate acid rains; iii) 0.01 M CaCl<sub>2</sub> solution, to simulate soil salinity (experiments were performed both at neutral and acidic pH). The suspension was stirred in an orbital shaker up to 7 days at room temperature, withdrawing 100  $\mu$ L-aliquots from each solution at scheduled times, namely: 0 and 30 seconds, 1, 2, 5, 10, 30, 60, 1140 (1 day), 2880 (2 days), 4320 (3



days), 8640 (6 days) and 10080 minutes (7 days). The cumulative sampled volume was less than 5% of the initial volume (15 mL), thus it can be assumed that the influence of the volume change on the release pattern is negligible. Release tests were performed separately for each support, in order to avoid any competitive equilibrium, and were repeated in triplicates.

Each sampled solution was then diluted 1:1000 with ultrapure water prior to IC analysis. The concentration of the glyphosate released ( $C_r$ ) was derived through the calibration curve previously commented. The percentage of glyphosate released (*Release %*) was calculated according to the following equation:

$$Release\% = \left( \frac{1000 * C_r}{C_{max}} \right) * 100.$$

Where  $C_{max}$  is the maximum concentration that could be released from each support, according to the encapsulation procedure and the nominal glyphosate content (i.e. 40 % w/w), namely 6400 mg/L. This concentration was chosen to match the content of glyphosate in commercial formulations (e.g. 64-66% for granular RoundUp product) in consideration of the amount of commercial product to be applied in real applications (about 10 g of granules per liter, according to the manufacturer indications).

## 2.6 Mathematical modelling of glyphosate release

The profiles of glyphosate release from the studied supports were mathematically modelled to better understand the dissolution profile. Within this work, several models were evaluated, as hereafter listed. Even if all models were originally developed for drug delivery from polymeric and non-polymeric supports, they are commonly applied for the release of herbicides [38, 39] as well.

### Zero-order model (*Release %* vs. time) [40]

The release rate is supposed to be independent from the concentration of herbicide, And the same amount of compound is expected to be released per unit of time, according to eq. 1.

$$C_t = C_0 + K_0 t \quad (1)$$

where  $C_t$  is the amount of herbicide (mg/L) dissolved at the time  $t$  (expressed in hours),  $C_0$  is the initial amount of the herbicide dissolved in the solution and  $K_0$  is the zero-order release constant, expressed as mg/L/h.

Pseudo first-order model (log of *Release %* vs. time) [41]

Differently to the zero-order model, in the first-order kinetic, the release rate depends on the concentration. The linearized model is expressed by eq. 2:

$$\log C_t = \log C_0 - Kt/2.303 \quad (2)$$

where  $C_t$  is the concentration of herbicide (mg/L) released at  $t$  time (expressed in hours),  $C_0$  (mg/L) is the initial dissolved concentration of herbicide in the media and  $K$  is first order constant (1/hour).

Korsmeyer and Peppas model (log of *Release %* vs. log of time) [42]

The Korsmeyer-Peppas model (eq. 4) can be used to discriminate between Fickian diffusion or non-Fickian (anomalous) diffusion [43]. The linear relation is expressed by eq. 3

$$\log C_t = \log K + n \log t \quad (3)$$

where  $C_t$  is the concentration of drug released at time  $t$  (mg/L),  $K$  ( $\text{hour}^{-n}$ ) is the release rate constant and  $n$  is the diffusional exponent (adimensional). This kinetic equation is claimed valid only for the first 60% of the released active principle [42].

For a dispersed, non-swellable system, the value of  $n$  gives an indication of the release mechanism, as hereafter listed [44]: i)  $n < 0.5$ , quasi-Fickian diffusion, ii)  $n = 0.5$ , Fickian diffusion mechanism, iii)  $0.5 < n < 1$ , non-Fickian diffusion, iv)  $n = 1$ , case II transport (zero-order release), v)  $n > 1$ , super case II transport.

It should be noted that for  $n=0.5$ , a Fickian diffusion is present. Accordingly, eq. 3 simplifies into the Higuchi's equation (eq.4):

$$C_t = K_H t^{0.5} \quad (4)$$

where  $C_t$  is the amount of drug released (mg/L) at time  $t$  (expressed in hours) and  $K_H$  is the release rate constant of  $H$  ( $\text{hour}^{-1/2}$ ).

## 2.7 Water/soil bench-scaled system

The release of glyphosate from the most promising support among the four tested (Al-MMT) was evaluated in a real soil/water system and compared in parallel with the release of glyphosate from a commercial formulation. Soil was collected from a public garden in the town of Torino (Valentino Park) and was chosen to have the representative composition of typical soils intended for horticulture uses [45], where glyphosate is mostly employed. In detail, 0.25 g of each formulation was added to 15 g soil/15 ml tap water dispersion in a glass bottle. pH of the suspension was measured and was equal to 6.8. At selected times after herbicide application (from 0 min to 7 days, as for the water release studies), the bottles were hand-shaken, the contents were allowed to settle, and 100  $\mu$ L of the supernatant solution were filtered and analysed by IC to determine the glyphosate concentration released. The periodic sampling of such a small amount of supernatant was assumed not to have any influence on the release pattern. Release kinetics were evaluated in triplicate.

## **3. Results and Discussions**

### **3.1 Physicochemical characterization**

The Incipient Wetness Impregnation technique is a protocol frequently exploited for the encapsulation of active principles in supporting materials, since it does not require specific reagents or procedures, and since it guarantees quantitative impregnation of the supports [6].

To investigate how glyphosate was encapsulated in the tested materials, physicochemical characterization of SBA-15, MMT and Al-MMT was performed.

Particle size and morphology of SBA-15, MMT and Al-MMT were evaluated by FESEM analysis (Figs. S1, S2 and S3 in the Supplementary Material, respectively). MMT and Al-MMT are characterized by irregular and heterogenous particles (with size ranging roughly from about 40 nm to 200 nm). Conversely, SBA-15 showed its typical hexagonal, elongated particle shape, with length from sub-micron size up to a few  $\mu$ m.

Specific surface area ( $SSA_{\text{BET}}$ ) and pore volume of each substrate, obtained by nitrogen sorption analysis before and after impregnation (Figure S4, S5 and S6 in the Supplementary Material) are reported in Table 1.

*Table 1. Specific surface area (SSA) and pore volume of the four tested materials, before and after the encapsulation of glyphosate. Brunauer–Emmett–Teller (BET) model was used for calculations.*

	<b><math>SSA_{\text{BET}}</math></b> <b>(<math>m^2/g</math>)</b>	<b>Pore volume</b> <b>(<math>m^3/g</math>)</b>
<b>SBA-15</b>	701	0.99
<b>SBA-15 impregnated</b>	492	0.74
<b>MMT</b>	279	0.42
<b>MMT impregnated</b>	83	0.15
<b>Al-MMT</b>	250	0.26
<b>Al-MMT impregnated</b>	6	0.017

The three sorbents cover a wide range of porosity (from 0.26 to 0.99  $m^3/g$  pore volume and from 250 to 700  $m^2/g$  SSA).

The impregnation with glyphosate resulted, for all the supports, in a significant modification of nitrogen adsorption-desorption isotherms (Figure S4, S5 and S6 in the Supplementary Material) and a reduction of SSA and pore volume (Table 1). These results indicate the location of glyphosate molecules inside the mesopores of the materials. This evidence is dramatic for Al-MMT (around 98% and 96% reduction of SSA and pore volume, respectively), suggesting that in this case the original mesoporous structure has been fully occupied by the herbicide. Indeed, the adsorption-desorption isotherms of  $N_2$  on Al-MMT (Figure S4) reveal that the hysteresis loop, typical of disordered mesoporous materials, almost disappeared after the inclusion of glyphosate (red-triangled line).

The almost complete filling of pore volume for Al-MMT by glyphosate, at variance with SBA-15 and MMT, is in agreement with the lowest pore volume measured for Al-MMT ( $0.26 \text{ m}^3/\text{g}$ ) when compared to those of SBA-15 ( $0.99 \text{ m}^3/\text{g}$ ) and MMT ( $0.42 \text{ m}^3/\text{g}$ ), considering that the same amount of glyphosate ( $0.40 \text{ g}$ ) per gram of support is present in the three impregnated materials.

In order to characterize the glyphosate in SBA-15, MMT and Al-MMT, XRD measurements were also performed (Figure 1).

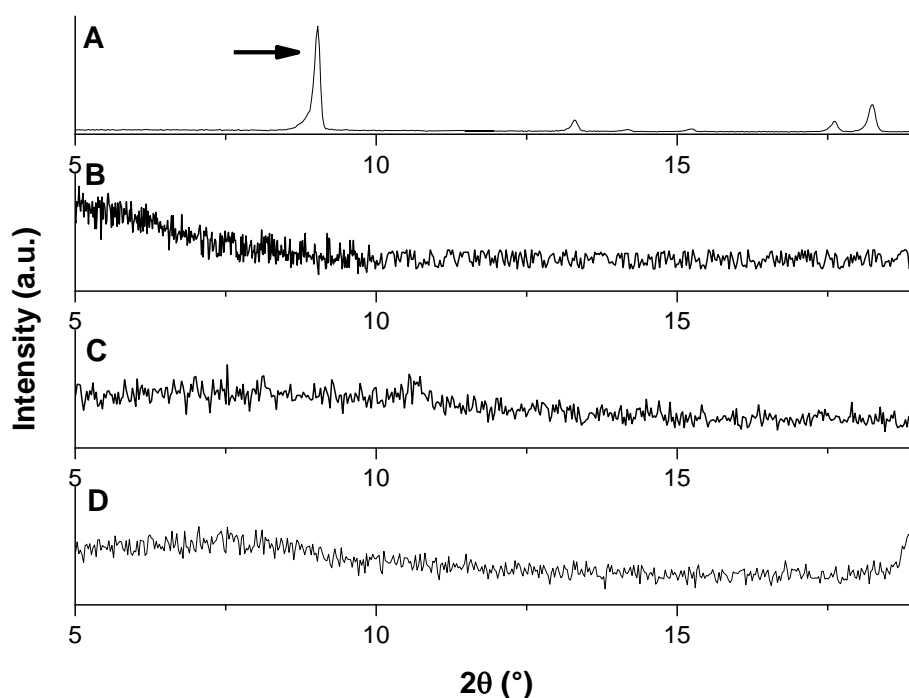


Figure 1. XRD patterns of glyphosate (A) and post-impregnated support: B - SBA-15, C- MMT, D- Al-MT. Black arrow points the main peak of crystalline glyphosate ( $2\theta = 8.9^\circ$ )

Results showed that the main peak of crystalline glyphosate ( $2\theta = 8.9^\circ$ , Fig.1A) is absent for all sorbents (1B, 1C, 1D). The lack of crystalline glyphosate signal is indicative for a complete amorphization of glyphosate. This is ascribed to the location of molecules inside materials mesopores, preventing crystallization [46], and to their interaction with the surface sorbents.

The location of glyphosate molecules inside mesopores was confirmed by small angle XRD patterns (see Supplementary Material). In details, to what concern SBA-15 a decrease of the intensity of the

peak (100) is observed (Figure S7), being indicative of the pore filling, in agreement with the decrease of the scattering contrast between the pores and the walls [47]. As far as MMT (Figure S8) and Al-MMT (Figure S9) are concerned, the location of glyphosate molecules in the interlayer spacing of the clays is evidenced by the vanishing of the typical basal peak (related to d001), indicating that the interlayer has expanded due to the inclusion of glyphosate [46].

### 3.2 Desorption tests in ultrapure water

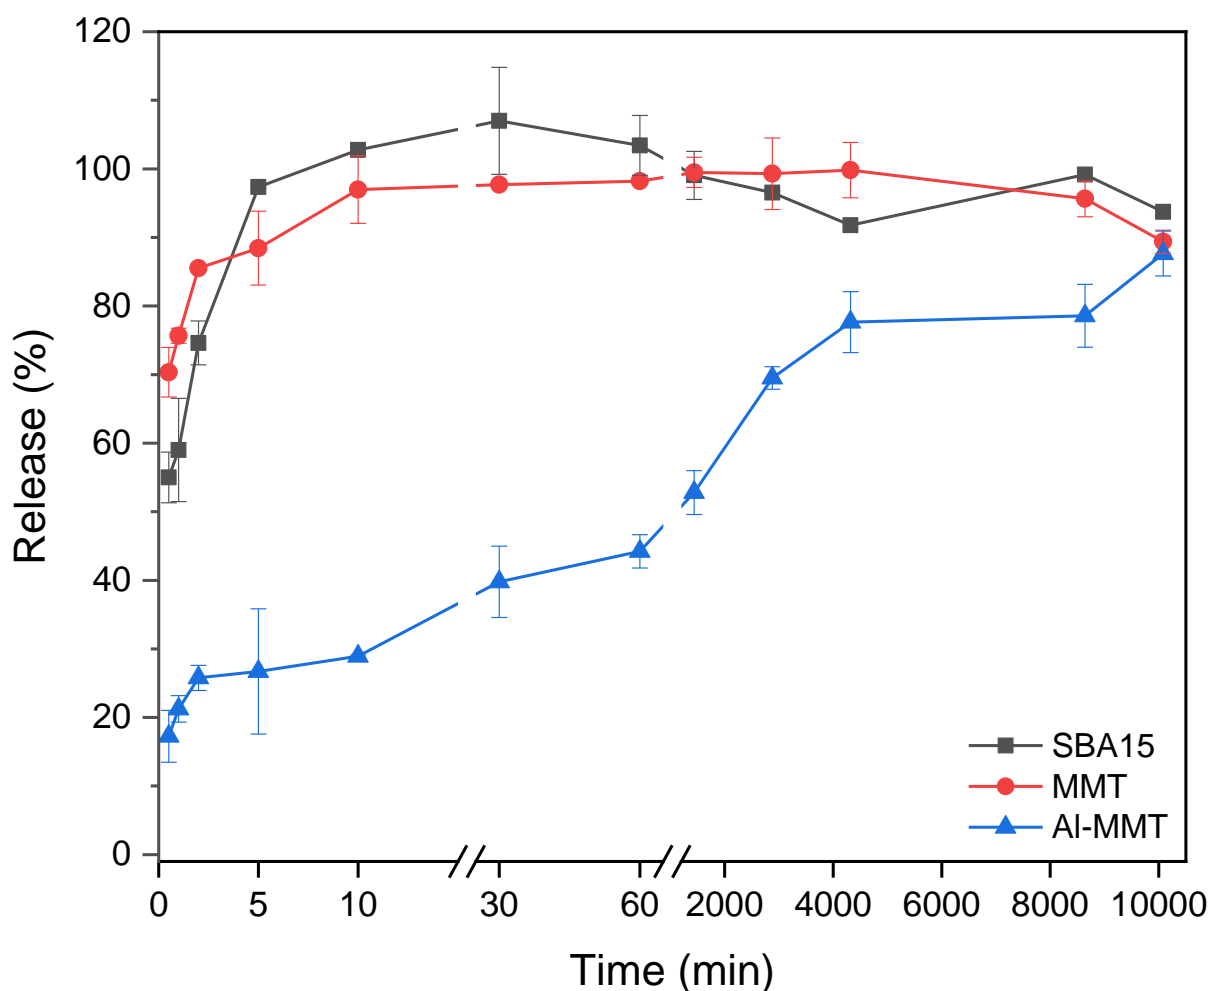


Figure 2. Desorption kinetics of glyphosate in ultrapure water from impregnated supports SBA-15, MMT and Al-MMT. For an easier comprehension, sampling time is expressed both as minutes and

*hours in the lower and upper X axis, respectively. Experimental conditions are detailed in Experimental Section.*

Ultrapure water (pH 6.5) was chosen as the first aqueous medium to be tested in order to avoid any competition of external species which could affect the release of glyphosate from supports.

The dissolution profiles of glyphosate in ultrapure water from SBA-15, MMT and Al-MMT are shown in Figure 2. The values on the left y-axis are given as percentages of the total amounts of glyphosate present in the dissolution vessel and, for all release curves, a 100% release corresponds to 6400 mg/L glyphosate concentration (for more details, see Experimental Section, §2).

When focusing on the short sampling times, it is observed that more than 50% of the glyphosate is released from both SBA-15 and MMT after only 30 seconds, reaching a quantitative release after 10 minutes. Hence, no prolonged release of the herbicide was observed for such sorbents. For SBA-15, less than 10% of the herbicide is still retained after 5 minutes and a complete release is observed after 10 minutes of contact with water, suggesting that weak interactions occur between glyphosate molecules and SBA-15 surface. This behaviour is in agreement with adsorption results previously obtained [20], showing negligible interactions between glyphosate and SBA-15 at neutral pH, whereas partial adsorption was observed only at acidic pH (see next paragraph).

A similar behaviour was observed also for MMT (96.9% release after 10 minutes). Despite several works report that selective interactions between glyphosate and MMT can occur, in particular at acidic pH (< 4) [48, 49], desorption tests here presented are performed at a neutral pH, which is higher than the point of zero charge (PZC) of MMT (about 3.4). In such conditions, the clay mineral surface is negative [48] and the negatively charged glyphosate [20] could hardly be retained by the negatively charged surface adsorption sites due to electrostatic repulsion. Such behavior is responsible for the fast and quantitative release rate of glyphosate within the short sampling time.

Differently to what previously discussed for MMT and SBA-15, the trend of Al-MMT indicate a slower kinetic release. Indeed, after 2 minutes only 28% (of impregnated glyphosate was released

in the solution from Al-MMT, suggesting that the interactions between the herbicide and the support are stronger than those occurring in SBA-15 and MMT. To explain this behavior, it should be mentioned that Al-MMT is characterized by the presence of Al<sup>3+</sup> ions that could be complexed with glyphosate, mainly through phosphate-Al interaction [50], forming monomeric and dimeric complexes [51]. This interaction is, therefore, proposed to be responsible for the slower release of the herbicide from Al-MMT. As regards the releasing mechanism, it should be mentioned that the complexation constants of Al-glyphosate are lower than Al-H<sub>2</sub>O constants [51]. Hence, a competition of water molecules, interacting with aluminium, could occur.

Al-MMT system exhibits a prolonged release of glyphosate which appears appealing for the proposed application. The slow release observed for Al-MMT is ascribed to strong interactions between glyphosate molecules and internal surface of the support. Moreover, the diffusion of glyphosate molecules from the internal pore structure may at same extent control the release. The location of glyphosate molecules in the interlayer spacing of the pillared clay is evidenced by the XRD pattern at small angles (Figure S6 in the Supplementary Material), as previously discussed. The release of glyphosate by Al-MMT is in agreement with the work of Siepmann and co-workers, in which the drug release was shown to be kinetically longer for supports in which the active principle was encapsulated in the material core [52].

The performances of Al-MMT (20% of the herbicide still inside the support after 7 days) were compared with those reported in the only two literature papers on the release of glyphosate. Data show that Al-MMT exhibits better or at least similar prolonged release performances (i.e. slower dissolution profiles) than biochar-attapulgite (quantitative glyphosate release of glyphosate after 2 hours) [28], and supramolecular organic guest intercalated layered double hydroxides (40% release after 24 hours) [29] systems, respectively.

### **3.3 Desorption tests in simulated acid rain solution**



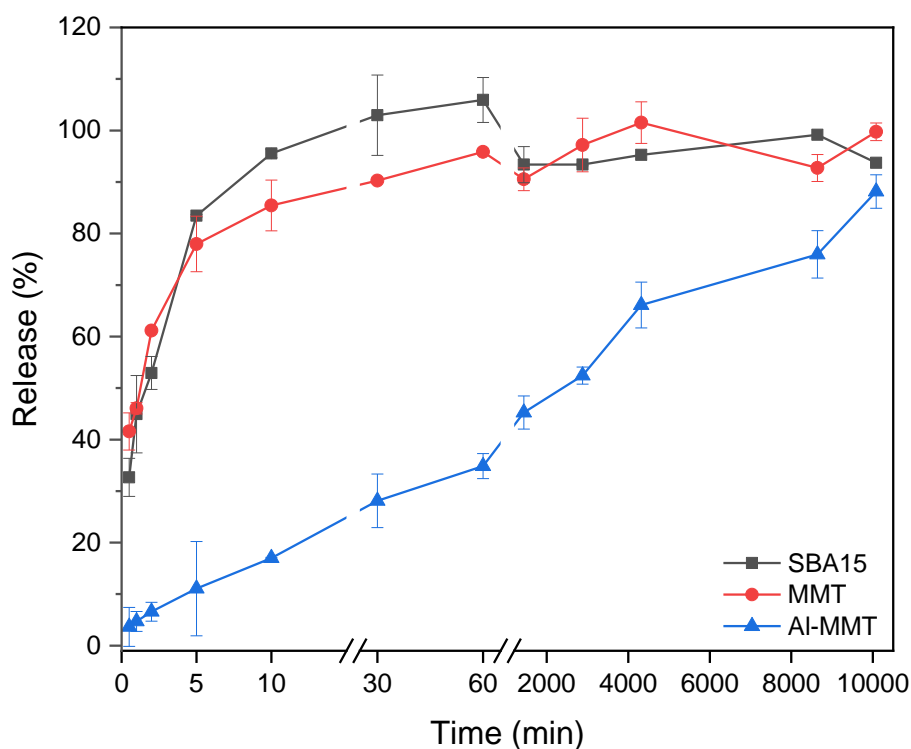


Figure 3. Desorption kinetics of glyphosate in 0.02M oxalic acid (pH=3) from SBA-15, MMT and Al-MMT. For an easier comprehension, sampling time is expressed both as minutes and hours in the lower and upper X axis, respectively. Experimental conditions are detailed in Experimental Section.

Once assessed the desorption behaviours in ultrapure water, the same tests were replicated at pH 3, simulating worst conditions of rain acidity [53] (Figure 3).

The dissolution profiles of Figure 3 showed that, also at acidic conditions, Al-MMT was the only support characterized by a prolonged release of glyphosate (about 13% still retained after 7 days), with a partial slowdown of the kinetic in comparison to the one obtained in ultrapure water (Table 2, column A vs B). A slowdown was also observed for pure MMT (Table 2, column C vs D), despite this support quantitatively release glyphosate after 60 minutes.

*Table 2. Comparison of glyphosate release up to 3 days between ultrapure water medium (UP) and 0.02M oxalic acid, pH3 (pH3). Gray cells show sampling times in which quantitative release of glyphosate is reached.*

<b>Glyphosate release (%)</b>				
	<b>Al-MMT</b>		<b>MMT</b>	
	<b>pH3 (A)</b>	<b>UP (B)</b>	<b>pH3 (C)</b>	<b>UP (D)</b>
<b>0.5 min</b>	3.6	17.3	41.6	70.3
<b>1 min</b>	4.7	21.2	46.1	75.7
<b>2min</b>	6.6	25.8	61.2	85.5
<b>5min</b>	11.1	26.7	78.0	88.4
<b>10min</b>	17.0	28.9	85.4	97.0
<b>30min</b>	28.1	39.8	90.3	97.7
<b>60 min</b>	34.9	44.2	95.9	98.2
<b>1 day</b>	45.3	52.8	90.5	99.5
<b>2 days</b>	52.4	69.5	97.2	99.3
<b>3 gg</b>	66.1	77.6	101.5	99.8

To explain the slowdown of Al-MMT and MMT kinetics, both acid-base equilibrium of glyphosate and surface properties of montmorillonite should be considered. Indeed, at pH 3 glyphosate is present with a protonated carboxylic, and a monovalent phosphonic group (Figure 4A).

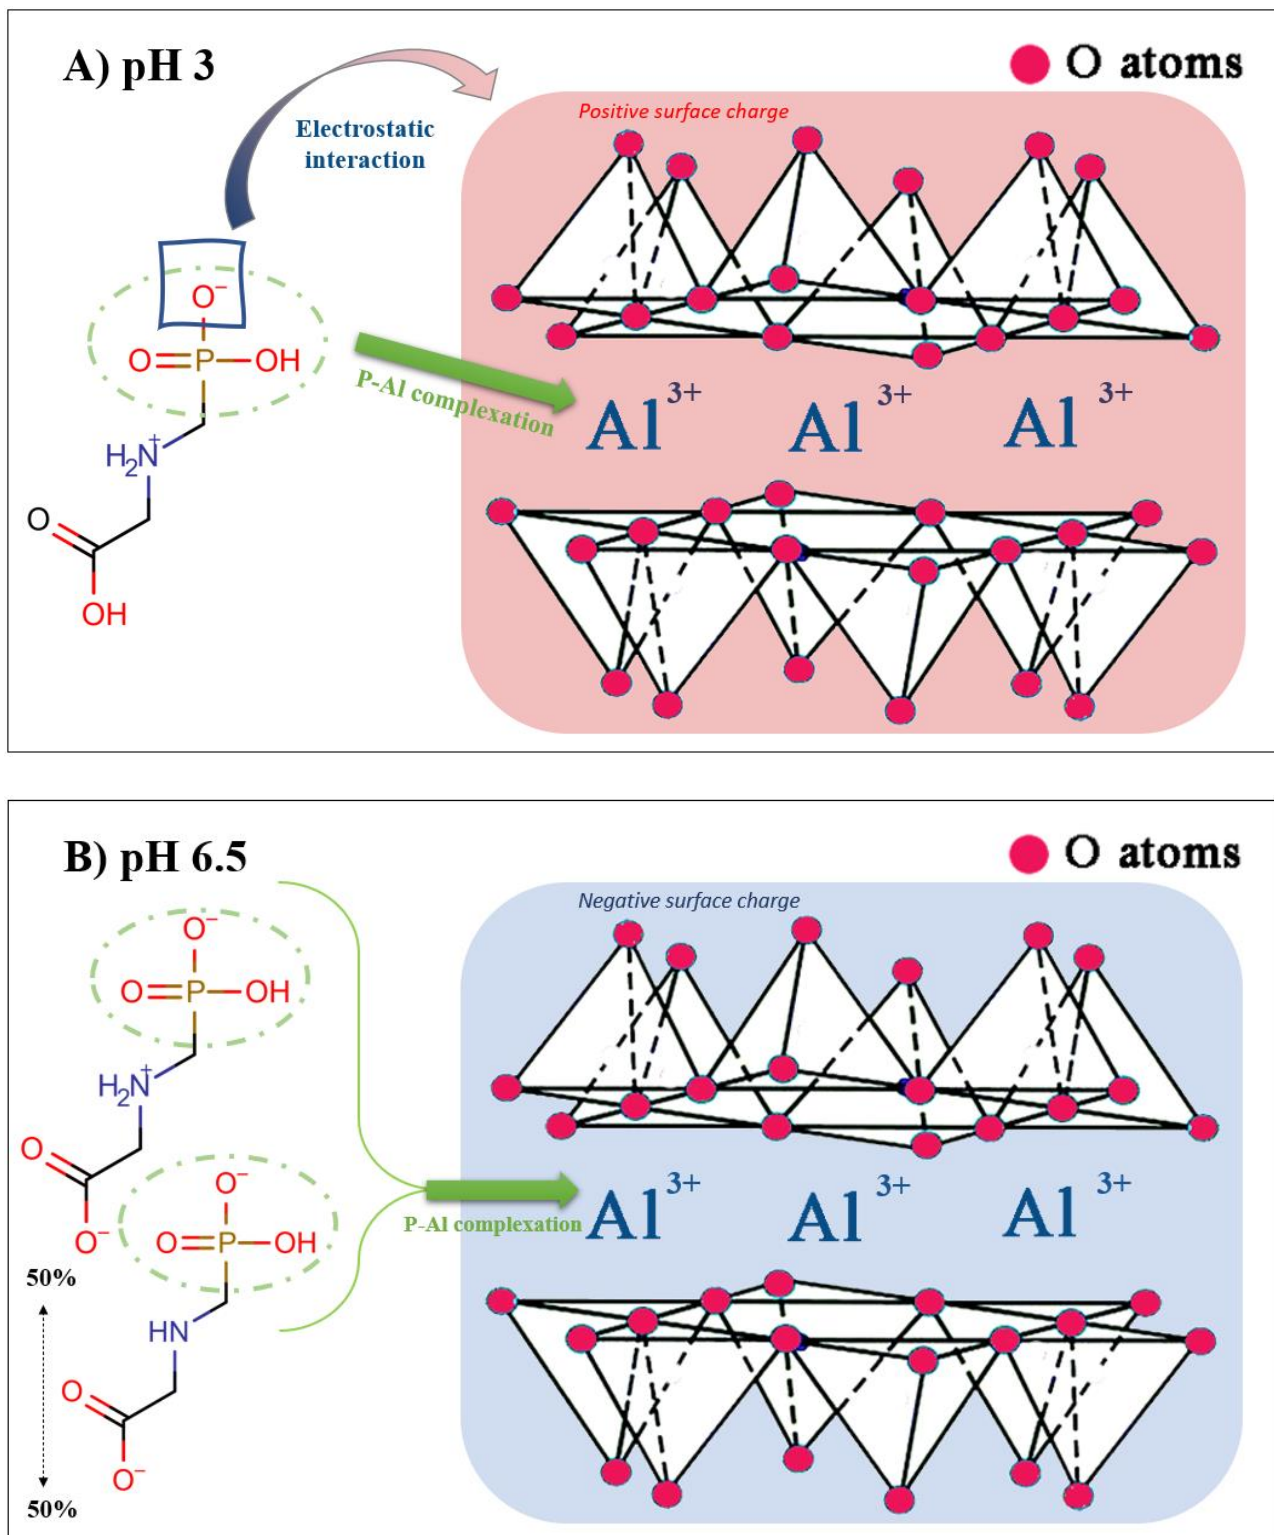


Figure 4. Surface charge of Al-MMT and chemical dissociation of glyphosate at pH 3 (A) and pH 6.5 (B). Main interaction occurring at both pH values are also highlighted.

Since pH conditions are lower than Al-MMT PZC (about 4.3 [54]), the surface of montmorillonite has to be considered positively charged (Figure 4A). Conversely, in ultrapure water (pH around 6.5) glyphosate is present with the same monovalent phosphonic group but with the deprotonated carboxylic, (Figure 4B) and the surface of montmorillonite has to be considered negatively charged, being above its PZC. Therefore, electrostatic repulsions occur in ultrapure water, which instead are not present at pH 3.

Summarizing, for Al-MMT at pH values close to neutrality, the effect of both P-Al interactions and electrostatic repulsion influence the release of glyphosate, thus justifying the lower retention of glyphosate, and hence the faster kinetic release, observed in respect to acidic pH conditions where only P-Al interactions occur. Moreover, despite the zwitterionic form of glyphosate at pH3, electrostatic attractive interactions between the negative phosphonic group and the positive surface of Al-MMT may give a further contribution to the retention, besides the complexation of Al<sup>3+</sup> ions by glyphosate.

A fast release was observed for SBA-15 since more than 85% of glyphosate is released after 5 minutes. However, after 30 seconds about 35% release was observed at pH 3, against 55% in ultrapure water, thus supporting the role of surface charge also in the interaction between SBA-15 and negatively charged glyphosate. Indeed, pH 3 may be considered below the PZC of SBA-15 PZC (5.2), whereas at pH around 6.5 the surface of SBA-15 has to be considered mainly negatively charged [55].

### **3.4 Desorption tests in simulated soil conditions**

Previous tests were performed without considering any competing species. However, the presence of the soil matrix can affect the release of glyphosate from encapsulating support. Competitive interactions between surface moieties and soil salts, such as calcium chloride [56], can be established, with charged species potentially promoting a faster release of the herbicide.

Experiments were performed on Al-MMT only, since MMT and SBA-15 were shown to exhibit a fast release, not compatible with prolonged applications. Glyphosate desorption from Al-MMT in 0.01M CaCl<sub>2</sub> solution was studied, roughly simulating the ionic strength of soil solutions [56].

Dissolution profiles obtained in 0.01M CaCl<sub>2</sub> at pH conditions acidic (pH=3) and close to neutrality (pH=6.7) are reported in Figure 5 (triangled blue- and squared black- lines, respectively), together with desorption profiles obtained in ultrapure water and oxalic acid solution (starred green- and pointed red- lines, respectively) for a better comparison.

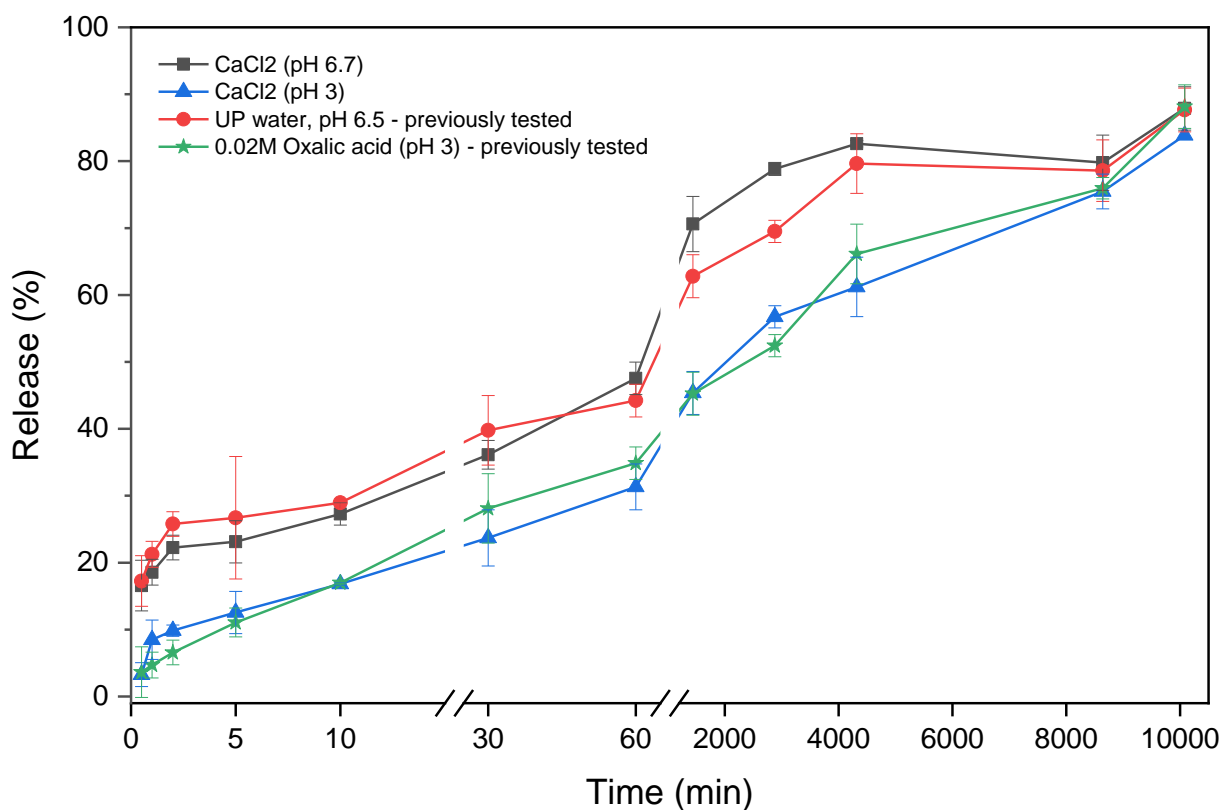


Figure 5. Desorption profiles of glyphosate 0.01M CaCl<sub>2</sub> solution, at acidic (pH 3) and almost neutral (pH 6.7) conditions. Release percentage in ultrapure water (UP water) and 0.02 oxalic acid solution are overlaid. For an easier comprehension, sampling time is expressed both as minutes and

hours in the lower and upper X axis, respectively. Experimental conditions are detailed in Experimental Section.

Results confirmed that, within the standard deviation of the measurements, glyphosate release is not affected by CaCl<sub>2</sub>, thus suggesting the absence of significant competitive interactions between Al-MMT and CaCl<sub>2</sub>. It is important to highlight that after 7 days, about 10-15% of the herbicide is still adsorbed on the support and that the prolonged release of Al-MMT is confirmed also when simulating soil salinity conditions. Furthermore, the slower kinetic in acidic conditions (as discussed in the “Desorption tests in simulated acid rain solution” paragraph) is still confirmed in CaCl<sub>2</sub> solution (green and blue lines -obtained in 0.02M oxalic acid solution and in CaCl<sub>2</sub>, pH3 respectively- have a similar trend and are well separated from red and black ones -obtained at neutral conditions-).

### 3.5 Computational treatment of release data through kinetic models

The release data of glyphosate from Al-MMT in soil simulating conditions (at both neutral and acid conditions) were fitted to different kinetic models, namely zero-order, first order and Korsmeyer–Peppas models described in Paragraph “Mathematical modelling of glyphosate release” (Experimental section). For each of the above-mentioned model, fitting equation, R<sup>2</sup> values and release constants were determined (Table 3).

*Table 3. Modelling of glyphosate release data from Al-MMT in 0.01 CaCl<sub>2</sub>, at pH 6.7 and pH*

3

<b>Kinetic model</b>	<b>Test conditions</b>	<b>Linearized fitting equation</b>	<b>R<sup>2</sup></b>	<b>K</b>
----------------------	------------------------	------------------------------------	----------------------	----------

<b><i>Zero-order</i></b>	CaCl <sub>2</sub> , pH 6.7	$C_t = 34.61 + 0.39t$	0.6526	0.39
	CaCl <sub>2</sub> , pH3	$C_t = 19.45 + 0.43t$	0.8362	0.43
<b><i>Pseudo first-order</i></b>	CaCl <sub>2</sub> , pH 6.7	$\log C_t = 1.80 - 0.005t$	0.6764	0.12
	CaCl <sub>2</sub> , pH3	$\log C_t = 1.90 - 0.004t$	0.8398	0.09
<b><i>Korsmeyer–Peppas</i></b>	CaCl <sub>2</sub> , pH 6.7	$\log C_t = 1.61 + 0.21 \log t$	0.9902	0.94
	CaCl <sub>2</sub> , pH3	$\log C_t = 1.48 + 0.32 \log t$	0.9947	0.33

Results clearly show that glyphosate released from Al-MMT follows the Korsmeyer–Peppas kinetic equation. Indeed, for both neutral and acidic pH conditions, R<sup>2</sup> for zero-order and first-order model ranges from 0.65 to 0.84, while the first seven datapoints (representing release of up to approximately 60% of the loaded glyphosate) showed a R<sup>2</sup> value higher than 0.99 when computed by Korsmeyer–Peppas model.

Korsmeyer–Peppas *n* diffusional exponent was consequently calculated, obtaining *n*=0.21 and 0.32 for neutral and acidic pH conditions, respectively. Accordingly, the release of glyphosate from Al-MMT support appears to be diffusion controlled, following a quasi-Fickian model.

Finally, the release rate constant (*K*) is equal to 0.94 hours<sup>-0.21</sup> and 0.33hours<sup>-0.32</sup> for neutral and acid pH, respectively. The kinetic parameters obtained were used to calculate release of glyphosate according to the Korsmeyer and Peppas model (Figure 6) which was in satisfactory agreement with the experimental data.

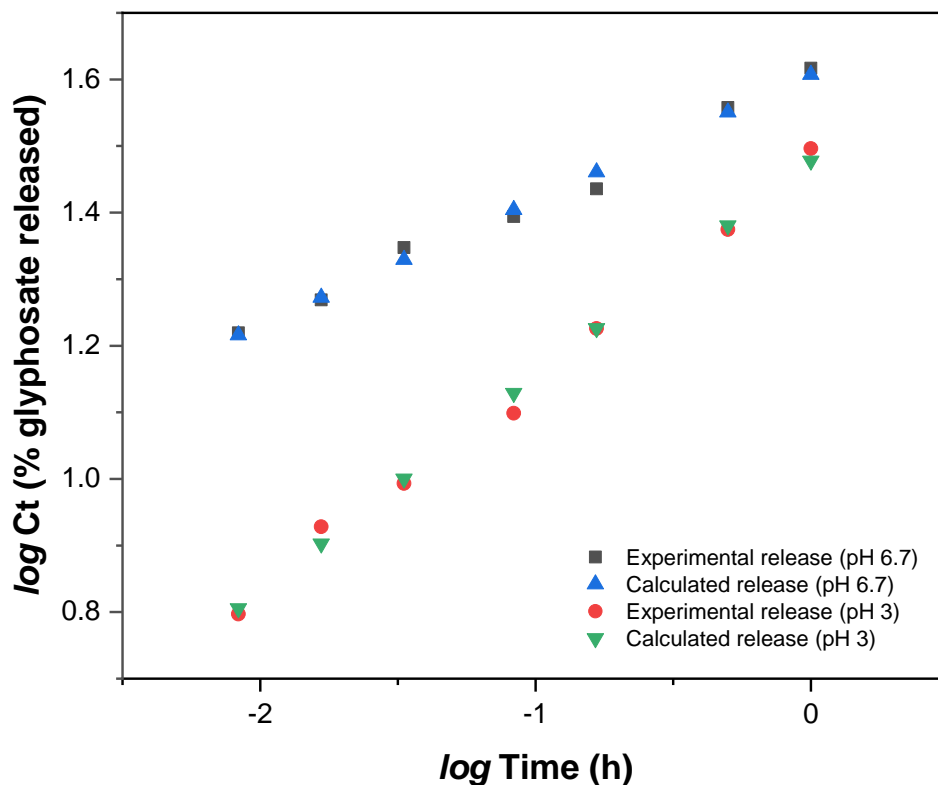


Figure 6. Release kinetics for glyphosate from Al-MMT. Experimental and calculated values according to linearized Korsmeyer and Peppas model.


To the best of our knowledge, no other studies investigating the kinetic models describing the release of glyphosate in controlled release applications are nowadays present in literature.

### 3.6 Real sample application

The efficacy of Al-MMT in the controlled release of glyphosate was finally tested in a bench scale plant. A laboratory self-made system was setup with a glass bottle filled with a known aliquot of tap water (typically used for irrigation) and soil according to the procedure previously described (see “Water/soil bench-scaled system” paragraph in Materials and Method Section, §2.7). Through this apparatus, the release of the herbicide was assessed considering not only the dissolution in water medium, but also the competitive adsorption equilibrium of soil, thus simulating a real application in



field or in a flowerpot. Releasing performances of impregnated Al-MMT were compared with those of a glyphosate commercial formulation and both kinetic plots are represented in Figure 7:

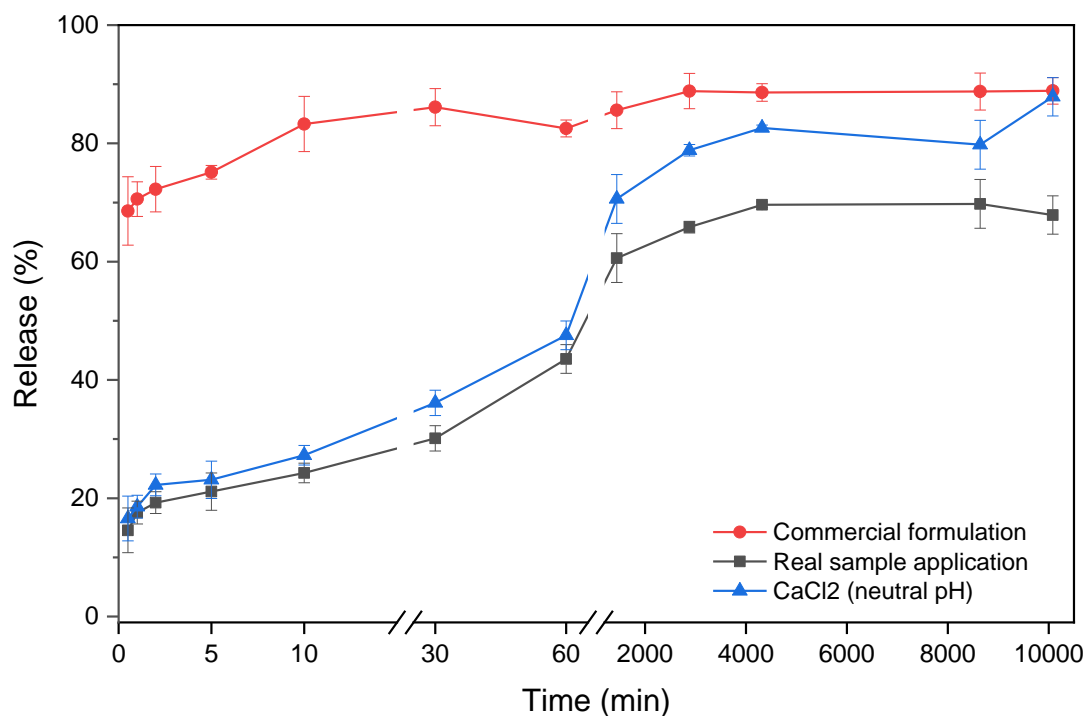

*Figure 7: Desorption profile of glyphosate in bench scaled system (tap water/soil suspension, pH 6.8) from Al-MMT. Releases from glyphosate commercial formulation and from Al-MMT in CaCl<sub>2</sub> media, at pH 6.7 were compared. For an easier comprehension, sampling time is expressed both as minutes and hours in the lower and upper X axis, respectively. Experimental conditions are detailed in Experimental Section.*

As shown by the dissolution curves, the bench system confirmed the good performances of Al-MMT as support for the prolonged release of glyphosate, with about 40% of the herbicide still retained after 3 days. The presence of a complex matrix such as real soil particles does not significantly affect the release trend. Moreover, the releasing kinetic of Al-MMT is clearly slower than the one obtained with the commercial formulation, which was almost quantitatively dissolved within 30 seconds after its application (89%). It should be remarked how, in the presence of soil

particles, the observed final release of glyphosate applied as commercial formulation is less than 100%, probably due to the herbicide adsorption by the soil particles [57].

#### 4. Conclusions

Mesoporous silica and clay supports were innovatively presented as releasing systems of glyphosate for application in soils. This practice has the advantage to avoid air-dispersion pollution and worker exposure to glyphosate. This study highlighted that the enhancement of interactions between the support and glyphosate is of paramount importance to achieve a prolonged release of the herbicide. In this regard, the Al-MMT system proved to be the most promising encapsulating support due to: i) Al-glyphosate complexation (through phosphorous moiety); ii) electrostatic interactions between glyphosate and clay surface. Release performances of Al-MMT support (about 10-20% of glyphosate still retained on the support after 7 days) were confirmed both in ultrapure water, and in experimental conditions simulating acid rains and soil composition and was poorly affected by any competitive interaction between the Al-MMT surface and other species. The non-uniform particle size distribution of Al-MMT promoted a semi-Fickian diffusion mechanism which is responsible for the release of glyphosate from the support, as described by the Korsmeyer–Peppas equation (n diffusion exponential < 0.5). The bench scale application of Al-MMT in a tap water/ soil suspension system fully demonstrated the applicability of Al-MMT in the prolonged release of glyphosate in real world applications.

#### **Authorship contribution statement**

**Luca Rivoira:** data validation and interpretation, conceptualization, manuscript writing and revision. **Stefano Frassati:** investigation and writing – original draft. **Silvia Cordola:** investigation. **Michele Castiglioni:** data validation and interpretation. **Barbara Onida:** data interpretation, manuscript revision and revision. **Silvia Ronchetti:** data interpretation, review and manuscript

editing and revision. **Irene Ingrando**: visualization; **Maria Concetta Bruzzone**: conceptualization, data interpretation, manuscript revision, funding acquisition.

### **Declaration of Competing Interest**

No conflict of interest exists in the submission of this manuscript, and manuscript is approved by all authors for publication.

### **Acknowledgements**

Financial supports from Ministero della Ricerca e dell'Università (MUR, Italy), PRIN 2017 (017PMR932) and Ex-60% is gratefully acknowledged.

## References

- [1] K.N. Harker, J.T. O'Donovan, Recent weed control, weed management, and integrated weed management, *Weed Technology* 27(1) (2013) 1-11.
- [2] F.P. Carvalho, Pesticides, environment, and food safety, *Food and Energy Security* 6(2) (2017) 48-60.
- [3] B. Huang, F. Chen, Y. Shen, K. Qian, Y. Wang, C. Sun, X. Zhao, B. Cui, F. Gao, Z. Zeng, Advances in targeted pesticides with environmentally responsive controlled release by nanotechnology, *Nanomaterials* 8(2) (2018) 102.
- [4] J.F. Egan, B.D. Maxwell, D.A. Mortensen, M.R. Ryan, R.G. Smith, 2, 4-dichlorophenoxyacetic acid (2, 4-D)-resistant crops and the potential for evolution of 2, 4-D-resistant weeds, *Proceedings of the National Academy of Sciences* 108(11) (2011) E37-E37.
- [5] S.B. Powles, J.M. Matthews, Multiple herbicide resistance in annual ryegrass (*Lolium rigidum*): a driving force for the adoption of integrated weed management, *Resistance'91: Achievements and Developments in Combating Pesticide Resistance*, Springer 1992, pp. 75-87.
- [6] M.T. Rose, T.R. Cavagnaro, C.A. Scanlan, T.J. Rose, T. Vancov, S. Kimber, I.R. Kennedy, R.S. Kookana, L. Van Zwieten, Impact of herbicides on soil biology and function, *Advances in agronomy* 136 (2016) 133-220.
- [7] N.E. Korres, Herbicide effects on humans: exposure, short and long-term effects and occupational hygiene, *Weed control: sustainability, hazards, and risks in cropping systems worldwide*. CRC Press, Taylor Francis Group, Boca Raton, FL 14 (2018).
- [8] B.G. Da Silva Pinto, T.K.M. Soares, M.A. Linhares, N. de Castilhos Ghisi, Occupational exposure to pesticides: Genetic danger to farmworkers and manufacturing workers—A meta-analytical review, *Science of The Total Environment* (2020) 141382.
- [9] International Labour Organization (ILO), *Agriculture: a hazardous work*, 2015.

- [10] A.A. Bajwa, G. Mahajan, B.S. Chauhan, Nonconventional weed management strategies for modern agriculture, *Weed science* 63(4) (2015) 723-747.
- [11] B.S. Chauhan, Weed ecology and weed management strategies for dry-seeded rice in Asia, *Weed Technology* 26(1) (2012) 1-13.
- [12] X.-x. Wang, M. Wang, Y.-x. Jia, T.-t. Yao, The feasible study on the reclamation of the glyphosate neutralization liquor by bipolar membrane electro dialysis, *Desalination* 300 (2012) 58-63.
- [13] S.O. Duke, S.B. Powles, Glyphosate: a once-in-a-century herbicide, *Pest Management Science: formerly Pesticide Science* 64(4) (2008) 319-325.
- [14] International Agency for Research on Cancer (IARC), IARC Monographs Volume 112: evaluation of five organophosphate insecticides and herbicides, 2015.
- [15] L.E. Saunders, R. Pezeshki, Glyphosate in runoff waters and in the root-zone: a review, *Toxics* 3(4) (2015) 462-480.
- [16] J.G. Zaller, F. Heigl, L. Ruess, A. Grabmaier, Glyphosate herbicide affects belowground interactions between earthworms and symbiotic mycorrhizal fungi in a model ecosystem, *Scientific reports* 4(1) (2014) 1-8.
- [17] European Commission, Glyphosate report. Available at: [https://ec.europa.eu/food/plant/pesticides/glyphosate\\_en](https://ec.europa.eu/food/plant/pesticides/glyphosate_en), 2019.
- [18] Ministero della Salute (Italia), Decreto 9 agosto 2016: Revoca di autorizzazioni all'immissione in commercio e modifica delle condizioni d'impiego di prodotti fitosanitari contenenti la sostanza attiva «glifosate», in attuazione del regolamento di esecuzione (UE) 2016/1313 della Commissione del 1° agosto 2016, 2016.
- [19] Istituto Superiore per la Protezione e la Ricerca Ambientale (ISPRA), Rapporto nazionale pesticidi nelle acque. Dati 2017 - 2018, 2020.

- [20] L. Rivoira, M. Appendini, S. Fiorilli, B. Onida, M. Del Bubba, M.C. Bruzzoniti, Functionalized iron oxide/SBA-15 sorbent: investigation of adsorption performance towards glyphosate herbicide, *Environmental Science and Pollution Research* 23(21) (2016) 21682-21691.
- [21] S. Fiorilli, L. Rivoira, G. Calì, M. Appendini, M.C. Bruzzoniti, M. Coisson, B. Onida, Iron oxide inside SBA-15 modified with amino groups as reusable adsorbent for highly efficient removal of glyphosate from water, *Applied Surface Science* 411 (2017) 457-465.
- [22] E.V.R. Campos, J.L. de Oliveira, L.F. Fraceto, Applications of controlled release systems for fungicides, herbicides, acaricides, nutrients, and plant growth hormones: a review, *Advanced Science, Engineering and Medicine* 6(4) (2014) 373-387.
- [23] K. Qian, T. Shi, S. He, L. Luo, Y. Cao, Release kinetics of tebuconazole from porous hollow silica nanospheres prepared by miniemulsion method, *Microporous and mesoporous materials* 169 (2013) 1-6.
- [24] R. Grillo, N.Z.P. dos Santos, C.R. Maruyama, A.H. Rosa, R. de Lima, L.F. Fraceto, Poly ( $\epsilon$ -caprolactone) nanocapsules as carrier systems for herbicides: Physico-chemical characterization and genotoxicity evaluation, *Journal of hazardous materials* 231 (2012) 1-9.
- [25] M. Paradelo, P. Pérez-Rodríguez, M. Arias-Estévez, J.E. López-Periago, Influence of pore water velocity on the release of carbofuran and fenamiphos from commercial granulates embedded in a porous matrix, *Journal of contaminant hydrology* 142 (2012) 75-81.
- [26] J. Zhao, X. Fu, S. Zhang, W. Hou, Water dispersible avermectin-layered double hydroxide nanocomposites modified with sodium dodecyl sulfate, *Applied clay science* 51(4) (2011) 460-466.
- [27] A.C. de Campos Bernardi, P.P.A. Oliviera, M.B. de Melo Monte, F. Souza-Barros, Brazilian sedimentary zeolite use in agriculture, *Microporous and Mesoporous Materials* 167 (2013) 16-21.
- [28] C. Chen, G. Zhang, Z. Dai, Y. Xiang, B. Liu, P. Bian, K. Zheng, Z. Wu, D. Cai, Fabrication of light-responsively controlled-release herbicide using a nanocomposite, *Chemical Engineering Journal* 349 (2018) 101-110.

- [29] J. Meng, H. Zhang, D.G. Evans, X. Duan, Novel layered pesticide slow/controlled release materials—supramolecular structure and slow release property of glyphosate intercalated layered double hydroxides, *Chinese Science Bulletin* 50(8) (2005) 745-751.
- [30] M.C. Bruzzoniti, E. Mentasti, C. Sarzanini, B. Onida, B. Bonelli, E. Garrone, Retention properties of mesoporous silica-based materials, *Analytica chimica acta* 422(2) (2000) 231-238.
- [31] M. Kowalska, H. Güler, D.L. Cocke, Interactions of clay minerals with organic pollutants, *Science of the total environment* 141(1-3) (1994) 223-240.
- [32] M.C. Bruzzoniti, R.M. De Carlo, C. Sarzanini, D. Caldarola, B. Onida, Novel insights in Al-MCM-41 precursor as adsorbent for regulated haloacetic acids and nitrate from water, *Environmental Science and Pollution Research* 19(9) (2012) 4176-4183.
- [33] B. Biswas, J. Labille, B. Prelot, *Clays and modified clays in remediating environmental pollutants*, Springer, 2020.
- [34] M.C. Bruzzoniti, R.M. De Carlo, L. Rivoira, M. Del Bubba, M. Pavani, M. Riatti, B. Onida, Adsorption of bentazone herbicide onto mesoporous silica: application to environmental water purification, *Environmental Science and Pollution Research* 23(6) (2016) 5399-5409.
- [35] A. Shrivastava, V. Gupta, Methods for the determination of limit of detection and limit of quantitation of the analytical methods, *Chronicles of young scientists* 2(1) (2011) 21-21.
- [36] Krijn de Jong, *Synthesis of solid catalysts*, John Wiley & Sons 2009.
- [37] S. Kim, J. Chen, T. Cheng, A. Gindulyte, J. He, S. He, Q. Li, B.A. Shoemaker, P.A. Thiessen, B. Yu, PubChem in 2021: new data content and improved web interfaces, *Nucleic Acids Research* 49(D1) (2021) D1388-D1395.
- [38] C. Huayao, L. Yueshun, Z. Hongjun, Z. Xinhua, G. Sheng, X. Hua, Highly efficient alginate sodium encapsulated chlorpyrifos/copper (II) Schiff base mesoporous silica sustained release system with pH and ion response for pesticide delivery, *RSC advances* 6(115) (2016) 114714-114721.

- [39] G. Lin, H. Zhou, J. Lian, H. Chen, H. Xu, X. Zhou, Preparation of pH-responsive avermectin/feather keratin-hyaluronic acid with anti-UV and sustained-release properties, *Colloids and Surfaces B: Biointerfaces* 175 (2019) 291-299.
- [40] S. Baveja, K.R. Rao, K.P. Devi, Zero-order release hydrophilic matrix tablets of  $\beta$ -adrenergic blockers, *International journal of pharmaceutics* 39(1-2) (1987) 39-45.
- [41] S.K. Lagergren, About the theory of so-called adsorption of soluble substances, *Sven. Vetenskapsakad. Handlingar* 24 (1898) 1-39.
- [42] P.L. Ritger, N.A. Peppas, A simple equation for description of solute release I. Fickian and non-fickian release from non-swellable devices in the form of slabs, spheres, cylinders or discs, *Journal of controlled release* 5(1) (1987) 23-36.
- [43] P. Zhang, T.Z.G. De La Torre, J. Forsgren, C.A. Bergström, M. Strømme, Diffusion-controlled drug release from the mesoporous magnesium carbonate Upsalite®, *Journal of pharmaceutical sciences* 105(2) (2016) 657-663.
- [44] A. Olejnik, A. Kapuscinska, G. Schroeder, I. Nowak, Physico-chemical characterization of formulations containing endomorphin-2 derivatives, *Amino acids* 49(10) (2017) 1719-1731.
- [45] H.R. Schulten, P. Leinweber, C. Sorge, Composition of organic matter in particle-size fractions of an agricultural soil, *Journal of soil science* 44(4) (1993) 677-691.
- [46] P. Gurikov, I. Smirnova, Amorphization of drugs by adsorptive precipitation from supercritical solutions: A review, *The Journal of Supercritical Fluids* 132 (2018) 105-125.
- [47] J. Gu, J. Shi, L. Xiong, H. Chen, L. Li, M. Ruan, A new strategy to incorporate high density gold nanowires into the channels of mesoporous silica thin films by electroless deposition, *Solid state sciences* 6(7) (2004) 747-752.
- [48] G.A. Khoury, T.C. Gehris, L. Tribe, R.M.T. Sánchez, M. dos Santos Afonso, Glyphosate adsorption on montmorillonite: An experimental and theoretical study of surface complexes, *Applied Clay Science* 50(2) (2010) 167-175.



- [49] E. Morillo, T. Undabeytia, C. Maqueda, Adsorption of glyphosate on the clay mineral montmorillonite: effect of Cu (II) in solution and adsorbed on the mineral, *Environmental science & technology* 31(12) (1997) 3588-3592.
- [50] F. Gérard, Clay minerals, iron/aluminum oxides, and their contribution to phosphate sorption in soils—A myth revisited, *Geoderma* 262 (2016) 213-226.
- [51] M. Purgel, Z. Takács, C.M. Jonsson, L. Nagy, I. Andersson, I. Bányai, I. Pápai, P. Persson, S. Sjöberg, I. Tóth, Glyphosate complexation to aluminium (III). An equilibrium and structural study in solution using potentiometry, multinuclear NMR, ATR-FTIR, ESI-MS and DFT calculations, *Journal of Inorganic Biochemistry* 103(11) (2009) 1426-1438.
- [52] J. Siepmann, R.A. Siegel, M.J. Rathbone, *Fundamentals and applications of controlled release drug delivery*, Springer 2012.
- [53] R. Casiday, R. Frey, *Acid Rain: Inorganic Reactions Experiment*, 1998.  
<http://www.chemistry.wustl.edu/~edudev/LabTutorials/Water/FreshWater/acidrain.html>.
- [54] K. Sakurai, A. Teshima, K. Kyuma, Changes in zero point of charge (ZPC), specific surface area (SSA), and cation exchange capacity (CEC) of kaolinite and montmorillonite, and strongly weathered soils caused by Fe and Al coatings, *Soil science and plant nutrition* 36(1) (1990) 73-81.
- [55] M. Kokunešoski, J. Gulicovski, B. Matović, M. Logar, S.K. Milonjić, B. Babić, Synthesis and surface characterization of ordered mesoporous silica SBA-15, *Materials Chemistry and Physics* 124(2-3) (2010) 1248-1252.
- [56] V. Houba, E. Temminghoff, G. Gaikhorst, W. Van Vark, Soil analysis procedures using 0.01 M calcium chloride as extraction reagent, *Communications in soil science and plant analysis* 31(9-10) (2000) 1299-1396.
- [57] R. Celis, M.C. Hermosín, M.J. Carrizosa, J. Cornejo, Inorganic and organic clays as carriers for controlled release of the herbicide hexazinone, *Journal of Agricultural and Food Chemistry* 50(8) (2002) 2324-2330.

# Encapsulation of the glyphosate herbicide in mesoporous and soil-affine sorbents for its prolonged release

L. Rivoira<sup>1\*</sup>, S. Frassati<sup>1</sup>, S. Cordola<sup>2</sup>, M. Castiglioni<sup>1</sup>, B. Onida<sup>2</sup>, S. Ronchetti<sup>2</sup>, I. Ingrando<sup>1</sup>,  
M.C. Bruzzoniti<sup>1\*</sup>


<sup>1</sup> Department of Chemistry, University of Torino, Via Pietro Giuria 7, 10125, Torino, Italy


<sup>2</sup> Department of Applied Science and Technology, Polytechnical University of Torino,  
Corso Duca degli Abruzzi 24, 10129, Torino, Italy

\*Corresponding authors:



E-mail address: [luca.rivoira@unito.it](mailto:luca.rivoira@unito.it) (L. Rivoira) and [mariaconcetta.bruzzoniti@unito.it](mailto:mariaconcetta.bruzzoniti@unito.it) (M.C. Bruzzoniti)

## SUPPLEMENTARY INFORMATION

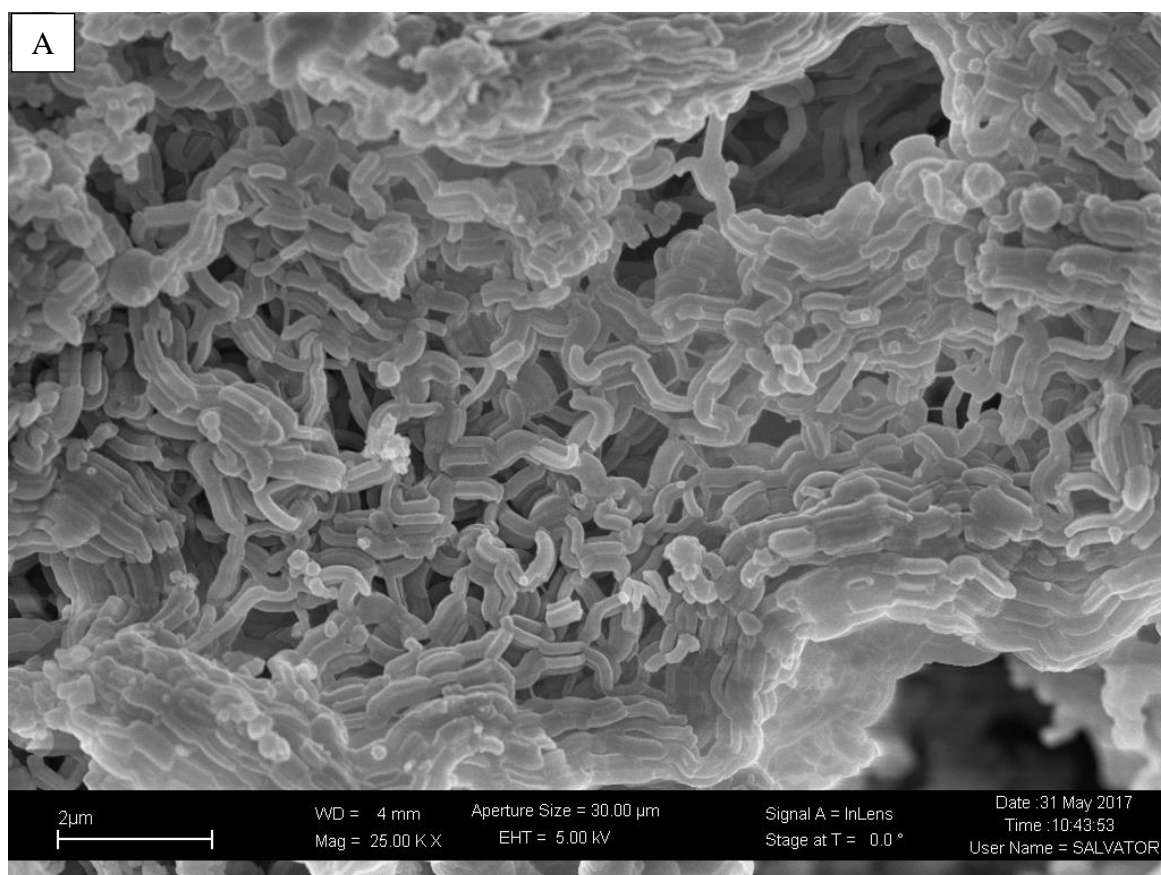


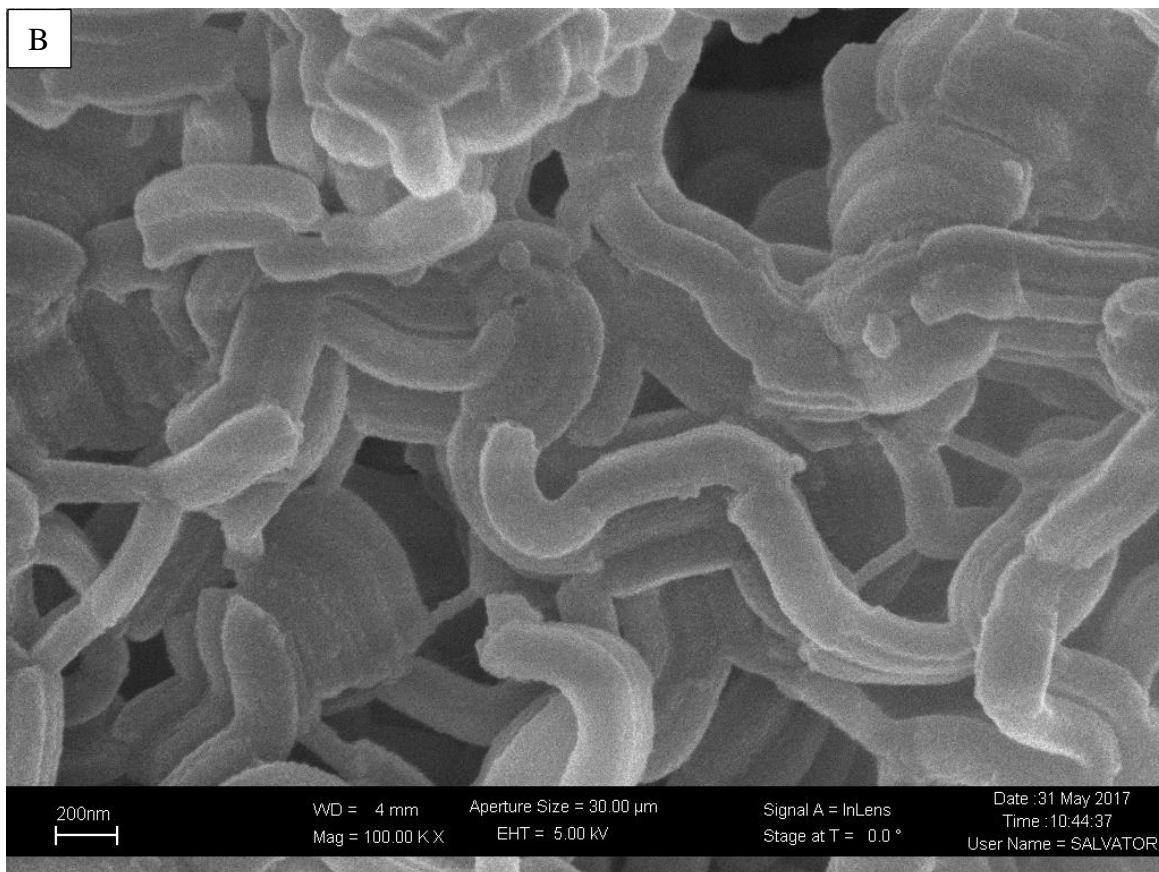


**Figure S1.** Field emission scanning electron microscopy (FESEM) image of pristine SBA-15. Magnification=25 KX (A) and 100 KX (B), Working Distance=4mm, Aperture size= 30μm, Acceleration voltage=5.00kV.

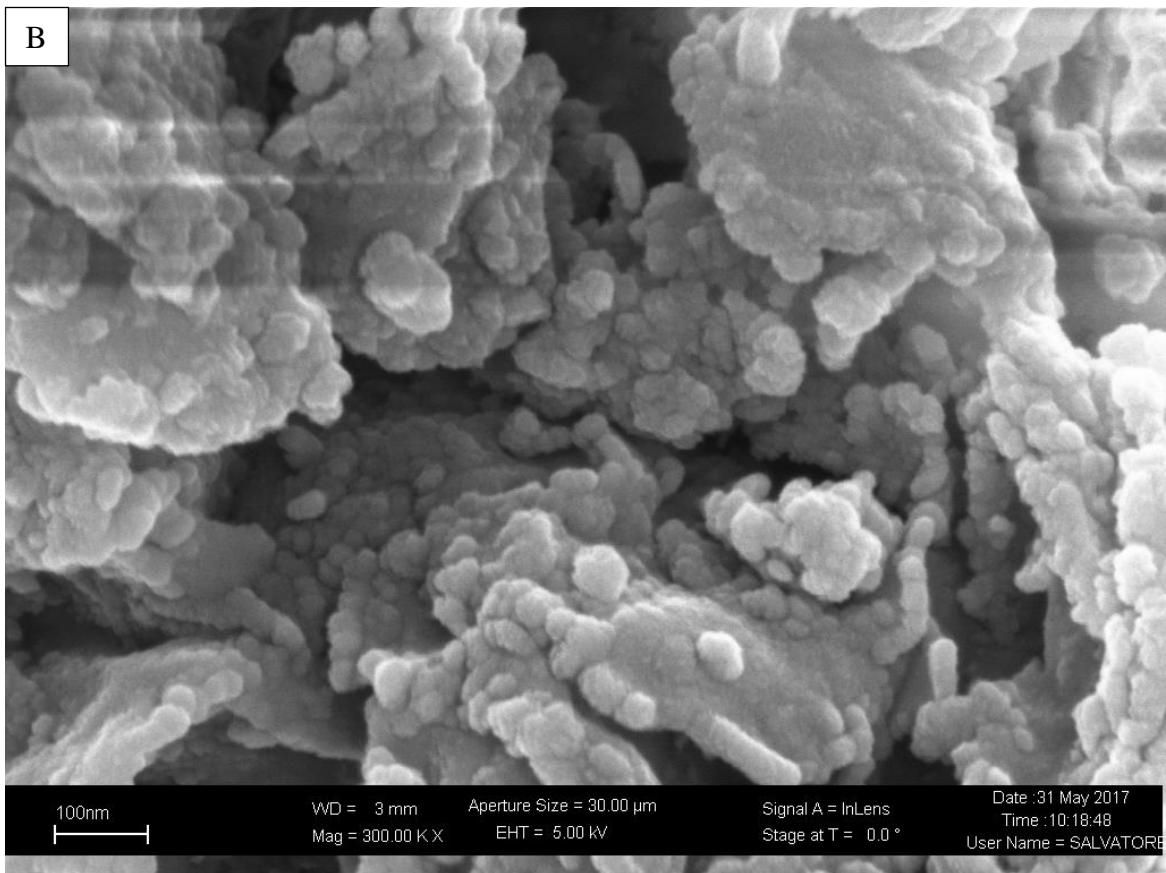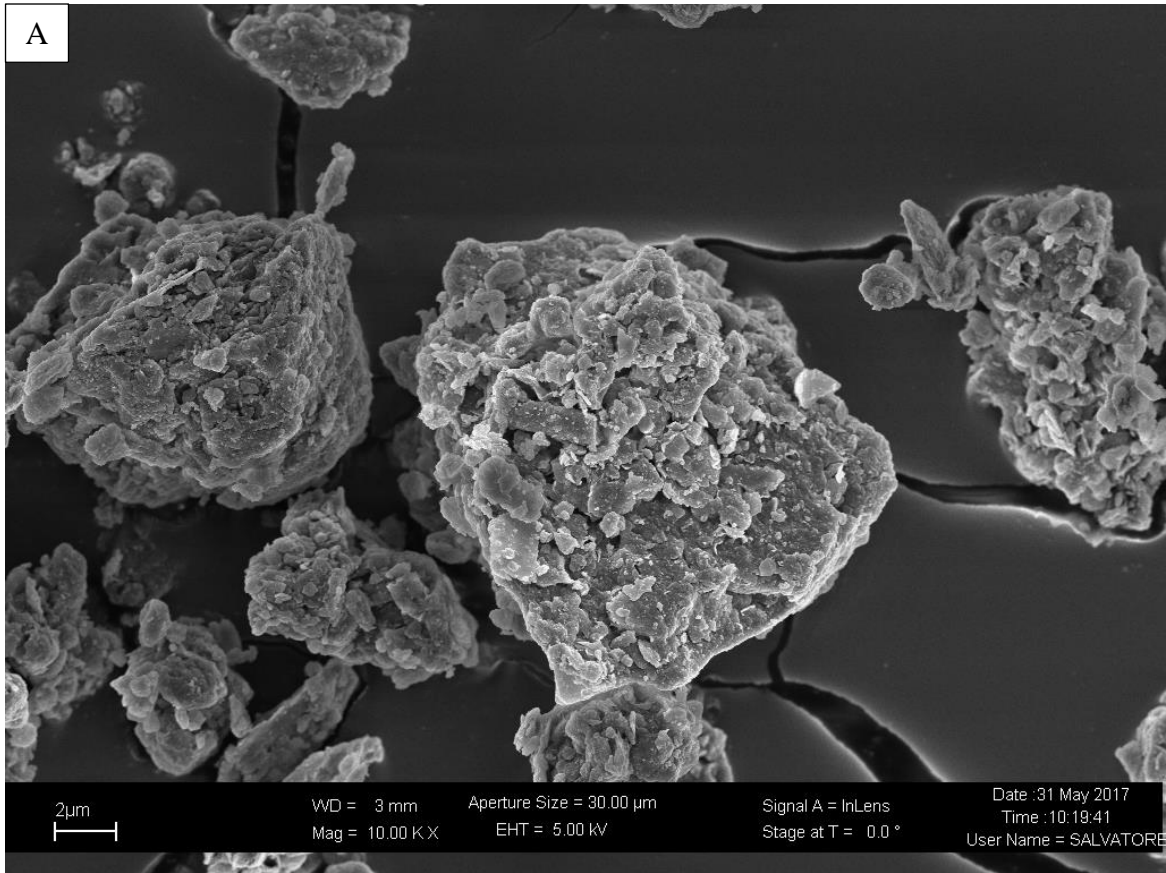

**Figure S2.** Field emission scanning electron microscopy (FESEM) image of pristine MMT. Magnification=10 KX (A) and 300 KX (B), Working Distance=3mm, Aperture size= 30 $\mu$ m, Acceleration voltage=5.00kV.

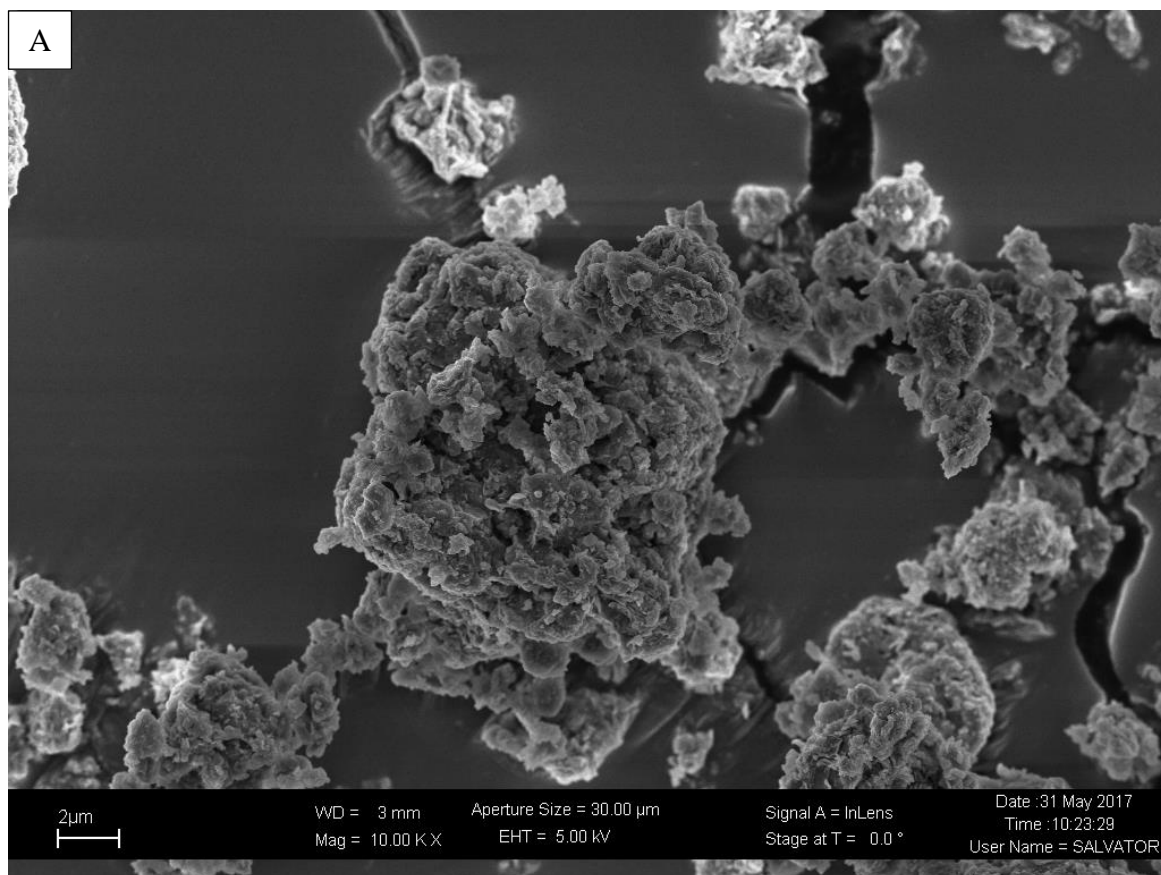

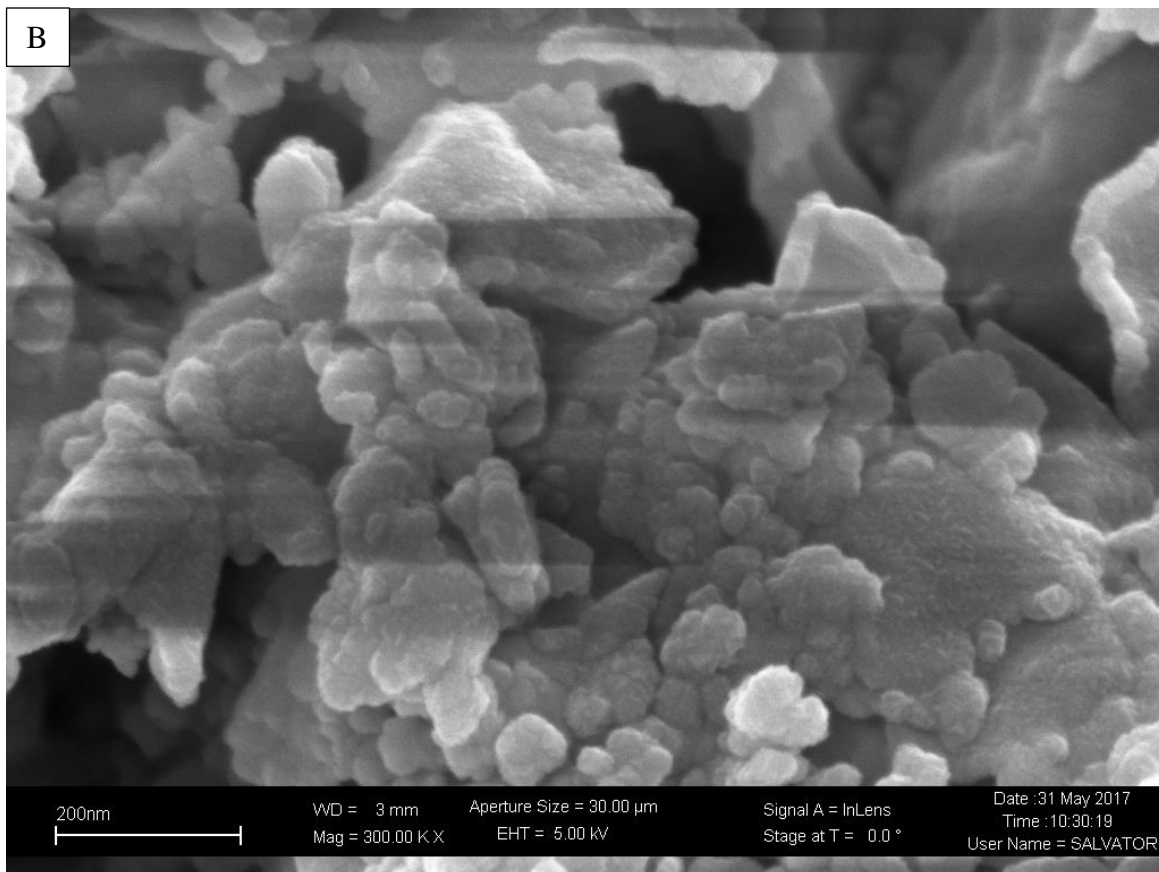

**Figure S3.** Field emission scanning electron microscopy (FESEM) image of pristine Al-MMT. Magnification=10 KX (A) and 300 KX (B), Working Distance=3mm, Aperture size= 30 $\mu$ m, Acceleration voltage=5.00kV.

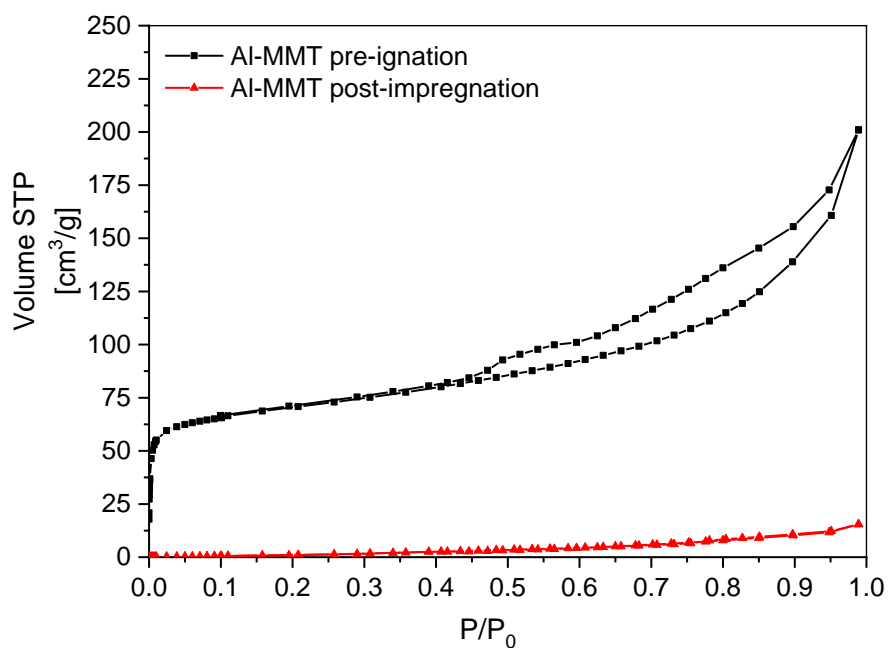


Figure S4. Adsorption-desorption isotherm curves of N<sub>2</sub> on Al-MMT surface



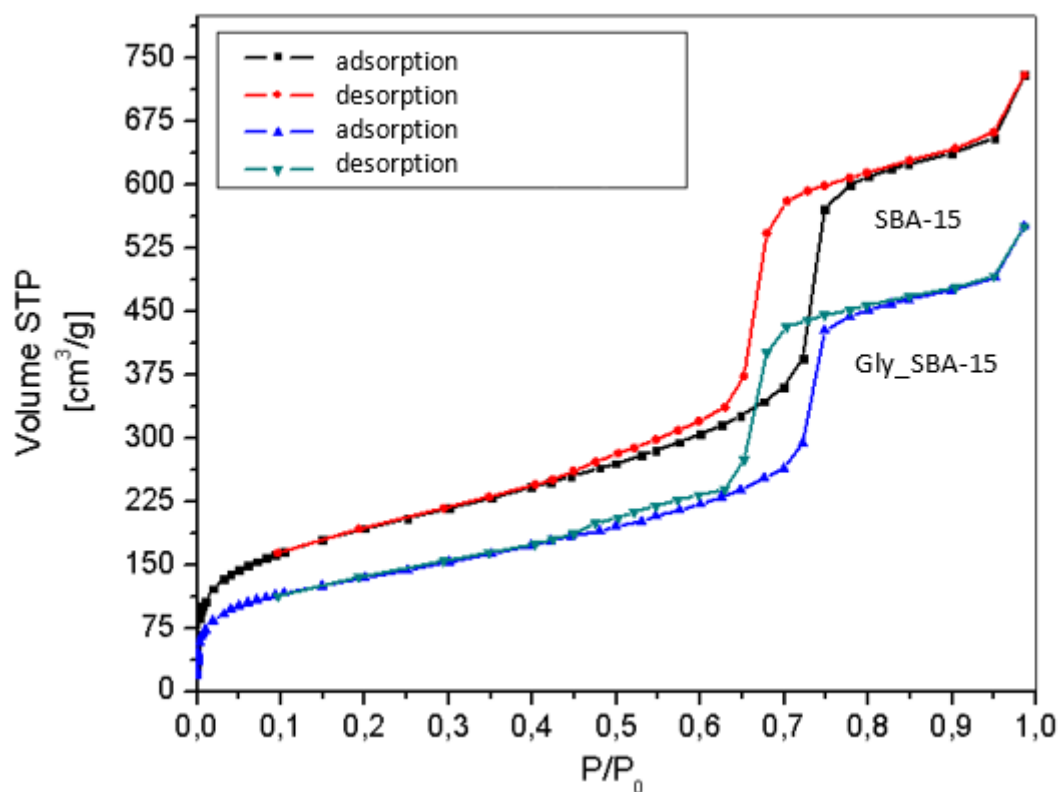



Figure S5. Nitrogen adsorption-desorption isotherms of SBA-15 as such (SBA-15), impregnated SBA-15 (Gly\_SBA-15)

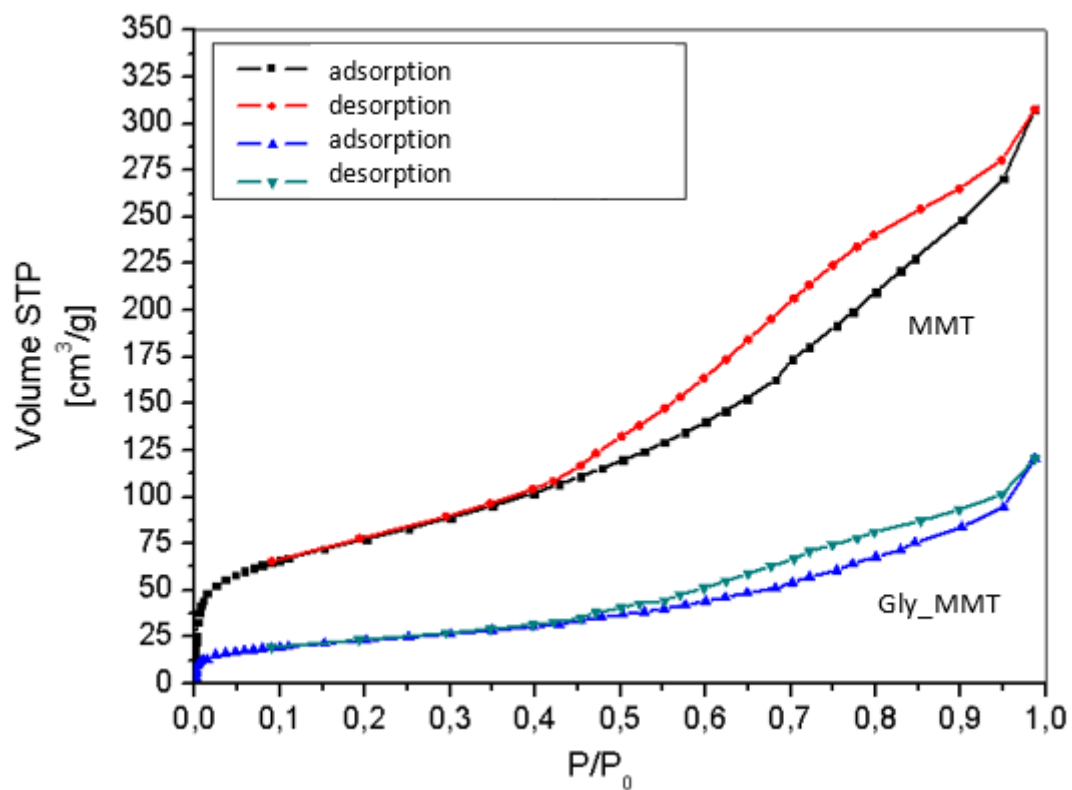

**Figure S6.** Nitrogen adsorption-desorption isotherms of MMT as such (MMT) and impregnated MMT (Gly\_MMT).

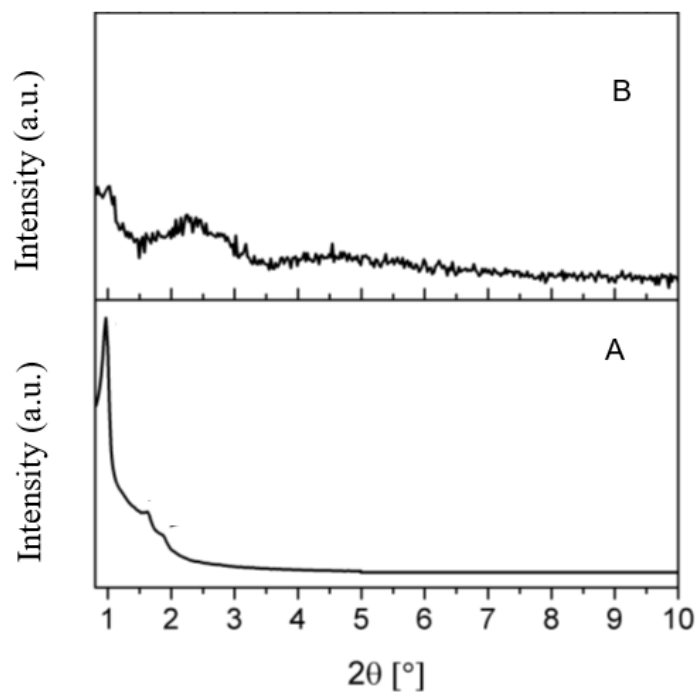


**Figure S7.** XRD patterns of SBA-15 (A) and SBA-15 after impregnation with glyphosate (B).

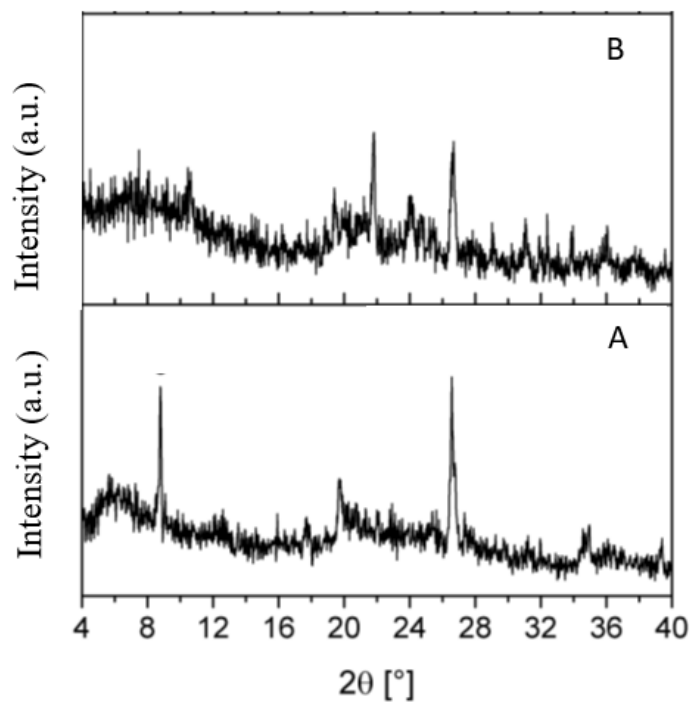

**Figure S8:** XRD patterns of MMT (A) and MMT after impregnation with glyphosate (B).



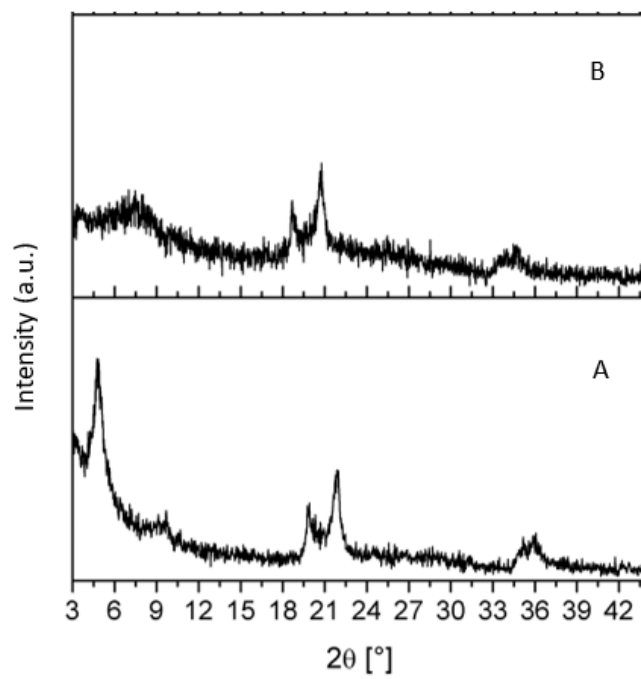

**Figure S9:** XRD patterns of Al-MMT (A) and Al-MMT after impregnation with glyphosate (B).