

AperTO - Archivio Istituzionale Open Access dell'Università di Torino

Biomimetic engineering of the cardiac tissue through processing, functionalization, and biological characterization of polyester urethanes

This is the author's manuscript

Original Citation:

Availability:

This version is available <http://hdl.handle.net/2318/1670831> since 2021-09-29T15:54:31Z

Published version:

DOI:10.1088/1748-605X/aaca5b

Terms of use:

Open Access

Anyone can freely access the full text of works made available as "Open Access". Works made available under a Creative Commons license can be used according to the terms and conditions of said license. Use of all other works requires consent of the right holder (author or publisher) if not exempted from copyright protection by the applicable law.

(Article begins on next page)

BIOMIMETIC ENGINEERING OF THE CARDIAC TISSUE THROUGH PROCESSING, FUNCTIONALISATION AND BIOLOGICAL CHARACTERIZATION OF POLYESTERURETHANES.

Federico Vozzi¹, Federica Logrand², Manuela Cabiati¹, Claudia Cicione³, Monica Boffito⁴, Irene Carmagnola⁴, Nicoletta Vitale², Manuele Gori³, Mara Brancaccio², Silvia Del Ry¹, Dario Gastaldi⁵, Emanuele Cattarinuzzi⁵, Pasquale Vena⁵, Alberto Rainer³, Claudio Domenici¹, Gianluca Ciardelli⁴, Susanna Sartori⁴

¹ Institute of Clinical Physiology, IFC-CNR, Via Moruzzi 1, 56124 Pisa, Italy

² Department of Molecular Biotechnology and Health Sciences, University of Turin, Via Verdi 8, 10124 Turin, Italy

³ Università Campus Bio-Medico di Roma, Via Álvaro del Portillo 21, 00128 Rome, Italy

⁴ Department of Mechanical and Aerospace Engineering, Polytechnic of Turin, Corso Duca degli Abruzzi 24, 10129 Turin, Italy

⁵ Department of Chemistry, Materials and Chemical Engineering “Giulio Natta”, Polytechnic of Milan, Piazza Leonardo da Vinci 32, 20133 Milan, Italy

KEYWORDS

Polyurethane, Cardiac Tissue Engineering, Cardiomyocytes, Biomimetic, Scaffold, Phenotypic modulation

ABSTRACT

Three-dimensional (3D) tissue models offer new tools in the study of diseases. In the case of the engineering of the cardiac muscle, a realistic goal would be the design of a scaffold able to replicate the tissue-specific architecture, mechanical properties and chemical composition, so that it recapitulates the main functions of the tissue. This work is focused on the design and the preliminary biological validation of an innovative polyesterurethane (PUR) scaffold mimicking cardiac tissue properties.

The porous scaffold was fabricated by Thermally Induced Phase Separation (TIPS) from poly(ϵ -caprolactone) diol, 1,4-butane diisocyanate and L-lysine ethyl ester. Morphological and mechanical scaffolds characterization was accomplished by confocal microscopy and micro-tensile and –compression techniques. Scaffolds were then functionalized with fibronectin by plasma treatment and the surface treatment was studied by XPS, ATR-FTIR and contact angle measurements. Primary rat neonatal cardiomyocytes were seeded on scaffolds and their colonization, survival and beating activity were analyzed for 14 days. Signal transduction pathways and apoptosis involved in cell, structural development of the heart and in its metabolism were analyzed.

PUR scaffolds showed porous-aligned structure and mechanical properties consistent with that of the myocardial tissue. Cardiomyocytes plated on the scaffolds showed a high survival rate and a stable beating activity. AKT and ERK phosphorylation was higher in cardiomyocytes cultured on the PUR scaffold compared to those on tissue culture plates. RT-PCR analysis showed a significant modulation at 14 days of cardiac muscle (MYH7, ET-1), hypertrophy-specific (CTGF) and metabolism-related (SLC2a1, PFKL) genes in PUR scaffolds.

Introduction

Cardiovascular disease (CVD) is one of the major causes of deaths in the world and the set of related pathologies, as hypertension, heart failure, atherosclerosis, represents a huge cost for healthcare systems [1,2]. Several approaches have been studied to contrast these diseases and new therapies in terms of drugs, medical devices and surgical solutions have been developed. One of the newest supports to study CVD physiopathology is represented by in-vitro 3D models, which can replicate the cardiac structure by definition of tissue-specific architecture and mechanical properties [3,4], and mimic the myocardial extracellular matrix through the incorporation of ECM molecules (e.g. laminin, fibronectin and collagen). This approach can ensure a 3D model able to support cardiac cell attachment and function [5].

Currently, the cell culture platforms for studying cardiac physiology are systems based on: (i) hydrogels, mainly constituted by ECM proteins as collagen, fibrin, matrigel organized as ring- or strip-shaped microtissues with aligned cells (namely, Engineered heart tissues (EHT)); (ii) self-organized cell aggregates made of cardiac stem cells (namely, organoids); (iii) pre-fabricated scaffolds, generally made of synthetic biocompatible polymers, with a well-defined structure in terms of fiber alignment and porosity. Each one has specific advantages and limitations: EHTs, for their nature, show a high biocompatibility by the use of natural polymers but, on the other hand, they present limited mechanical properties and low oxygen/nutrients diffusion [xx]. Organoids are able to form compact tissues-like systems with a strong cell-cell interaction, able to mimic cardiac physiology [xx]: their main limitation is the small size causing a diffusion barrier for oxygen and nutrients [xx]. Lastly, 3D scaffolds can be designed to recapitulate architecture of the native tissue in terms of structure and mechanical properties [xx] also if degradation products of synthetic polymers could generate unfavorable tissue responses (i.e., inflammation) [xx].

Cardiac muscle shows a Young's modulus of about 10–20 kPa at the diastole initial stages (strain<10%) that increases up to 50 kPa in healthy myocardium and 200–300 kPa in failing heart at the diastole end (strain≈15–22%) [6]. Cardiac tissue tensile stress and strain are in the ranges 3–15

kPa [6] and 22-90% [7], respectively. Furthermore, scaffolds for cardiac tissue engineering have to bear the contractile and expansive forces produced at each cardiac cycle. For this purpose, scaffolds with elastomeric properties are more suitable: elastomeric polymers, such as polyurethanes (PURs), may serve as appropriate raw materials [8].

The scaffolds requirements include also an appropriate porosity (to drive cell colonization and attachment, and to facilitate the exchange of nutrients, mainly oxygen and metabolites) and hierarchical structure (pore orientation and anisotropy) [6,9]. The adult mammalian heart is composed of several cell types, the most abundant being cardiomyocytes (CMs), fibroblasts (FBs), endothelial cells (ECs). Since cardiomyocytes, fibroblast and endothelial cells have dimensions in the ranges 10–100 μm , 10-15 μm and 8–12 μm respectively, scaffold pore size should be between tens to hundreds of micrometers [10]. The myocardium bears mechanical loads along a preferred direction [11]; this property results in an anisotropic structure, characterized by fiber alignment along the direction of the applied stresses. Scaffolds with control of fiber alignment can be obtained by electrospinning onto a rotating mandrel or by laser excimer ablation: however, these techniques have some limitations in terms of pore size [10] or correct connectivity [12]. Thermally Induced Phase Separation (TIPS) has been employed to fabricate oriented scaffolds. This technique allows pore size and morphology tuning to be achieved by modulating polymer concentration, quenching temperature, thermal gradient, and solvent type [10]. Fiber alignment supports cardiomyocytes in the generation of a tissue-like structure also acting on cell function in terms of calcium handling, action potentials and conductional velocities, influencing the cardiac maturation in neonatal cardiomyocytes [13,14] and differentiation process in human Embryonic Stem Cells (hESC) [15].

As previously stated, in addition to the morphology and mechanical properties described above, an effective cardiac model should incorporate growth factors, extracellular matrix (ECM) proteins (i.e., laminin, fibronectin and collagen) or their epitopes (i.e., RGD, IKVAV, YIGSR sequences). Among ECM proteins, fibronectin content is important for cardiac tissue engineering, since it influences cell growth, development, integration, adhesion, cytoskeletal organization and tissue remodeling

[16,17]. In our previous work [18] we developed a family of biodegradable polyesterurethanes (PURs). In these series, the most promising polymer for muscle tissue engineering was that synthesized from poly(ϵ -caprolactone) (PCL) diol ($M_n=2000$ g/mol), 1,4-butane diisocyanate (BDI) and L-lysine ethyl ester, due to its low Young's modulus and elastomeric behavior. This PUR was also used to obtain porous scaffolds by TIPS [19]. The PUR scaffolds turned out to be suitable for cardiac tissue engineering, since their mechanical and structural properties at both the macro- and nano-scale were in accordance with the properties required for this application. The PUR was synthesized with the same building block described above (PCL diol ($M_n=2000$ g/mol), BDI and L-lysine ethyl ester) and processed by TIPS to produce porous scaffolds. Scaffold functionalization was performed by plasma treatment with acrylic acid, which led to the formation of a polyacrylic acid layer, followed by the activation of carboxylic groups and the grafting of fibronectin. Plasma surface modification was conducted to alter surface chemical functionalities of the scaffold without affecting bulk properties [20]. Cardiomyocytes (CM) constitute one third of the cells in the myocardium (80-90% of the total volume) [21], representing the key cell source to develop and validate cardiac models. Primary neonatal cardiomyocytes deriving from Sprague-Dawley rats were allowed to seed on the biomimetic scaffold and their adhesion, beating and survival were analyzed. Moreover, signal transduction pathways involved in cell survival (ERK1/2 and AKT) as well as genes involved in apoptosis (Bcl2-associated X protein, B-cell CLL/lymphoma), in structural development (Natriuretic Peptides system, Endothelin-1, Actin alpha Cardiac Muscle 1, Myosin Heavy Chain 7, Myosin Heavy Chain 6, Troponin I Type 3, Connective Tissue Growth Factor), and in the balance between glucose and fatty acid metabolism (Glucose Transporter 1, Phosphofructokinase, Glucokinase Regulator, Pyruvate Dehydrogenase Kinase, Isozyme 4, Peroxisome Proliferator-Activated Receptor δ , Peroxisome Proliferator-Activated Receptor α , Peroxisome Proliferator-Activated Receptor γ , Coactivator 1 α) were analyzed and compared to cardiomyocytes seeded on tissue culture plates (TCP).

Methods

Materials

Poly(ϵ -caprolactone) diol ($M_n = 2000$ g/mol), dibutyltindilaurate (DBTDL), triethylamine, L-lysine ethyl ester dihydrochloride, 1-ethyl-3-(3-dimethylaminopropyl) carbodiimide and N-hydroxysuccinimide were purchased by Sigma Aldrich, USA. 1,4-butanediisocyanate was purchased by Molekula, Italy, and distilled under reduced pressure before use. In order to remove the residual water, poly(ϵ -caprolactone) diol and L-lysine ethyl ester dihydrochloride were dried overnight under reduced pressure at 100°C and 40°C, respectively. The glassware used in PUR synthesis was also dried under reduced pressure at 100°C overnight. All solvents were purchased by Sigma–Aldrich, Italy in the analytical grade. 1,2-dichloroethane (DCE) was stored over activated 4Å molecular sieves under a nitrogen atmosphere for at least 24 hours before use, in order to reduce the water content below 20 ppm. Fibronectin (human) was purchased by YO Proteins (YO Proteins AB, Sweden).

Synthesis of PURs

PCL was dissolved in DCE and azeotropically dried by refluxing under nitrogen over molecular sieves for at least 8 h. BDI was then added to the solution and reacted (2:1 molar ratio with respect to PCL diol) with the macrodiol, in the presence of the catalyst (DBTDL) to form the pre-polymer. At the end of this first step (150 min, 80 °C), the chain extender was dissolved in anhydrous DCE and added at 1:1 molar ratio with respect to the macrodiol at room temperature. Triethylamine was also added to induce chain extender neutralization. The chain extension reaction was stopped after 16 h by addition of methanol. The polymer was then collected by precipitation in petroleum ether and purified by dissolution in dimethylformamide (DMF) followed by precipitation in methanol. The dissolution-precipitation step was repeated twice. Finally, the polymer was dried under vacuum at 60°C for 24 h.

Scaffolds production

PUR was processed into scaffolds by TIPS according to the following procedure. The polymer was dissolved in dimethyl sulfoxide (DMSO ACS Reagent, Sigma-Aldrich, Italy) (8% w/v) at 50 °C. The solution was poured in parallelepiped stainless steel molds (50mm x 25mm x 30mm) and quenched at -80°C for 3 hours. The frozen solution was then washed in ethanol/water (70/30 v/v) for 3 days and finally lyophilized.

Scaffolds functionalization

Cylindrical scaffolds (diameter: 8 mm, thickness: 2 mm) were obtained by cutting the specimens after freezing in liquid nitrogen. Argon plasma activation was performed in a plasma reactor (Pico, Diener Electronic, Germany) operating at a gas pressure of 0.7 mbar and a power of 70 W. The plasma treatment time was 60 s. Thereafter, acrylic acid vapors were allowed to flow in the process chamber until the final pressure of 0.05 mbar was reached; the plasma treatment was performed for 15 minutes. The scaffolds were then washed with distilled water three times to remove unreacted monomer. We will further indicate these scaffolds as PUR-PAA. Fibronectin immobilization was performed according to the following protocol. PUR-PAA scaffolds were placed in 5 mg/ml of an aqueous solution (pH 5.0) of 1-ethyl-3-(3-dimethylaminopropyl) carbodiimide in the presence of 1.25 mg/ml N-hydroxysuccinimide at 4°C for 20 h, washed and immersed into fibronectin solution at 4°C for 20 h. Concentration and pH of the fibronectin solution were 100 mg/ml and 5.0, respectively. Scaffolds were finally washed three times with distilled water to remove not covalently bound protein. We will further indicate these scaffolds as PUR-PAA-Fibronectin: only this type of scaffold will be tested for biological evaluation.

Infrared spectroscopy

Attenuated Total Reflectance Fourier Transform InfraRed Spectra (ATR-FTIR) of PUR was obtained at room temperature in the spectral range from 4000 to 400 cm^{-1} using a Perkin–Elmer Spectrum 100 equipped with an ATR accessory (UATR KRS5) with diamond crystal. The spectra, obtained as a result of 16 scans with a resolution of 4 cm^{-1} , were analyzed using the Perkin–Elmer

Spectrum Software. The same procedure was used to analyze the surface of PUR, PUR-PAA and PUR-PAA-Fibronectin scaffolds, with the only exception of Germanium accessory instead of Diamond one.

Molecular weight and distribution: SEC analysis

PUR Number Average and Weight Average Molecular Weights (M_n and M_w) and molecular weight distribution (M_w/M_n) were estimated by Size Exclusion Chromatography (SEC) (1200 Series, Agilent Technologies, Santa Clara, CA, USA). The instrument was equipped with a Refractive Index (RI) detector and two Waters Styragel columns (HT2 and HT4) conditioned at 35°C. Tetrahydrofuran (THF; inhibitor free, for HPLC, 99.9%; Sigma–Aldrich, Italy) was used as mobile phase at a flow rate of 0.5 ml/min. M_n and M_w were determined by the Agilent ChemStation Software relative to the universal calibration curve. The latter was constructed based on 10 narrow polystyrene standards ranging in M_n from 740 to 18×10^4 g/mol. PUR was dissolved in THF (2 mg/ml) and filtered through a 0.45 μm syringe filter (Whatman) before analysis.

X-ray Photoelectron Spectroscopy (XPS)

X-ray Photoelectron Spectroscopy/Electron Spectroscopy for Chemical Analysis (XPS/ESCA) was performed with a PHI 5000 Versa Probe Instrument (Physical Electronics, Chanhassen, MN, USA) in a high vacuum chamber at a power of 25.6 W and at a voltage of 23.5 eV, with a scanning area of $500 \times 500 \mu\text{m}^2$. Analysis of XPS spectra was performed using XPSPEAK 4.1 software. The aliphatic carbon (C–C, C–H) at a binding energy of 285 eV (C 1s photoline) was used to determine the charging.

Morphological characterization

To quantitatively assess the scaffolds porosity and wall thickness, a Confocal laser scanning was performed by means of the confocal laser microscope LEXT400 by Olympus.

The scans were performed on 80 μm thick samples, which were obtained by sectioning samples kept at low temperature and fixed on glass slides by means of a viscous fluid (Killik, bio-optica). Sections were made by means of a criotome (HM 525, MICROM). All sections were deposited on a slide and let the killik to evaporate.

The images where taken by using a 20X objective lens and 6 adjacent images were stitched to cover the central area of the samples. The height maps obtained through the laser scanning were acquired on all sections. A thresholding algorithm has been applied with the purpose to quantify porosity, average pore radii and wall thickness.

Tensile characterization

The micro-tensile characterization was performed by means of an in-house developed micro-tensile equipment featuring a 5 N load (Honeywell Model, maximum error $< 0.1\%$) and a displacement actuator with a resolution of 50 nm.

Five samples were obtained by using a cutting blade out of a larger 2.0 mm thick PUR scaffolds. Samples width was 2.0 mm, sample length was greater than 7.5 mm to ensure a proper gripping region at the two ends of the samples; the distance between the gripped region was 7.5 mm.

Displacement driven tests were performed at 1 $\mu\text{m/s}$ loading rate until rupture of the sample occurred.

Micro-compression characterization

Unidirectional quasi-confined compression tests have been carried out on PUR scaffolds in dry and wet conditions at room temperature. Samples were cut taking care that the sample size was suitably larger than the probe size with the purpose to avoid size or boundary effects. Sample thickness was about 7 mm, one order of magnitude larger than the maximum penetration depth. Stainless steel flat circular punches with diameter 2 mm were used. The wet conditions were obtained by soaking the sample in water for 24 hours before testing and holding the samples in a liquid cell throughout the test. The displacement-controlled tests were performed by applying 20 incremental steps of 10 μm

at a constant displacement rate (50 nm/s) with a holding phase of 10 s and partial unloading of 5 μm at 100 μs at each step; a maximum penetration depth of 2100 μm was achieved at the end of the test. At least 5 repetitions of the compression tests were performed on different location of the scaffold. The unloading branches were used to estimate the slope of the force-displacement curve $S=dF/du$. The unloading slope was estimated through linear fitting of force-displacement data within the 80% and 20% of the current maximum load. The reduced modulus was obtained as $E_r=S/2R$ with R being the punch radius. Under the assumption of linearized isotropy, the reduced modulus is related to the Young's modulus and Poisson's ratio as $E_r=E/(1-\nu^2)$. As a comparison with the elastic modulus obtained through the tensile tests is of interests, the elastic modulus in compression was evaluated at the same equivalent strain ($\epsilon \approx 10\%$); this is achieved by estimating S at a penetration depth u_c of approx. $u_c = \epsilon_t H$ where H is an effective thickness which is here assumed to be $H=2R$.

Contact Angle measurements

Static Contact Angle measurements were carried out on scaffolds (three points for each sample) using a KSV CAM2000 (KSV Instruments LTD, Finland) system equipped with a liquid dispenser, video camera, and Attension Theta software, by sessile drop method in advancing mode. Distilled water drops of 5 μl were gently deposited onto 5 regions of the sample surfaces. Attension Theta software performed automated curve fitting of the drop profile based on the Young & Laplace equation.

Scanning Electron Microscopy (SEM)

Scanning Electron Microscopy was performed using a LEO 1420 microscope (Zeiss, Germany) at 20 kV and a working distance of 15 mm. Longitudinal and cross sections were obtained by cutting the specimens after freezing in liquid nitrogen. Micrographs of these sections were recorded with magnifications of 150, 250, 1000 and 1500x.

Primary cardiomyocytes isolation and culture

The procedure of cardiomyocytes isolation was in agreement with the Guide for the Care and Use of Laboratory Animals published by the US National Institutes of Health and was approved by the Animal Care and Use Committee of Turin University. Neonatal rat ventricular myocytes were isolated from 2/3-day-old Sprague-Dawley rat hearts by several rounds of digestion with collagenase type II (Worthington Biochemicals, Lakewood, NJ, USA) and pancreatine (Sigma-Aldrich, Italy) as previously described [22]. Briefly, hearts from neonatal rats were collected, atria excised, and the ventricles minced in ADS buffer (116 mM NaCl, 20 mM HEPES, 1 mM NaH₂PO₄, 5.4 mM KCl, 5.5 mM glucose, 0.8 mM MgSO₄, pH 7.35) containing 432 µg/ml collagenase type II and 666 µg/ml pancreatine. Six rounds of digestion were performed at 37°C for 10 minutes each. Fibroblasts were removed by two rounds of pre-plating for 1 hour each on plastic tissue culture dishes. Cardiomyocytes were seeded on fibronectin-coated plastic tissue culture plates (TCP) (n=6) and on PUR-PAA-Fibronectin scaffolds (n=6) placed in a 48-well plate and allowed to adhere for 2 days. Cardiomyocytes were maintained in DMEM–M199 medium, 10% horse serum (Gibco, Italy) and 5% New Calf serum (Gibco, Italy). During the third and fourth days of culture, cardiomyocytes were maintained in the presence of 1 µg/ml of Ara-C to inhibit fibroblasts proliferation.

Viability assay

Cell Titer Blue was mixed to cell culture medium at a concentration of 20% (v/v). At each time point, cardiac constructs cultured in 48-well plates were washed with phosphate buffered saline (PBS, pH 7.4) to remove the medium, then 500 µl of the assay mixture was added to each sample. After 1 hour, 100 µl were removed from the plates and fluorescence was measured in a 96-well plate using GloMax-Multidetection System (Promega, Milan, Italy) at $\lambda_{ex}=525$ nm and $\lambda_{em}=580-640$ nm.

Analysis of scaffold colonization and beating activity

Immunofluorescence staining was performed on primary cultures to assess the percentage of cardiomyocytes and fibroblasts. F-Actin was revealed with FITC-labeled phalloidin (F432, Thermo

Fisher Scientific) diluted 1:400; sarcomeric α -actinin was stained using the mouse monoclonal Ab (EA-53, ab9465, Abcam, UK) diluted 1:50. As secondary antibodies Alexa Fluor 488 goat anti-mouse (Thermo Fisher Scientific, USA) and Alexa Fluor 546 goat anti-rabbit (Thermo Fisher Scientific) were used. At each samples DAPI (4',6-diamidino-2-phenylindole, Sigma Aldrich, USA) at 1:1000, was added to highlight nuclei. For beating activity, cardiomyocytes were stained with Cell Tracker Orange (Invitrogen, Milan, Italy) following the manufacturer's instructions. 1×10^6 cardiomyocytes were plated on each scaffold. Video microscopy acquisitions were performed using Zeiss Observer Z1 microscopy equipped with AxioVision 4.8 software.

Western blot

Hearts were lysed in Tris-buffered saline with 1% SDS, containing Roche complete protease inhibitor cocktail, 10 mM NaF, 1 mM PMSF and 1 mM Na_3VO_4 . Protein extracts were prepared as previously described [23]. Western blot band quantifications were performed with Quantity One software (Bio-Rad Laboratories Inc., Hercules, CA, USA). For Western blot analysis antibodies against the following proteins were used: phospho-T202/Y204 ERK1/2 (Cell Signaling, Danvers, MA, USA), total ERK1 (Santa Cruz Biotechnology, Dallas, TX, USA), phospho-S473-AKT and total AKT (Cell Signaling, Danvers, MA, USA). Western blot band quantifications were performed with Quantity One software (Bio-Rad Laboratories Inc., Hercules, CA, USA).

RNA extraction and Reverse Transcription for RT-qPCR analysis.

After 14 days in culture, cardiomyocytes were recovered from the scaffolds and tissue culture dishes by repeated flushing with TRI Reagent (Sigma-Aldrich, Milan, Italy) on ice. Total RNA was extracted using the acid guanidinium thiocyanate-phenol-chloroform method by RNeasy Mini kit (Qiagen S.p.A, Italy, MI). The RNA concentration and purity were spectrophotometrically determined and 1 μg of total RNA was reverse-transcribed in cDNA according to the manufacturer's protocol (Thermo Fisher Scientific, USA). Probes and primer pairs specific for all genes analyzed and for housekeeping genes were designed with specific software (Applied Biosystems Primer

Express Version 2.0) and reported in Table 1. Reaction conditions of all primer pairs or probes were optimized, and Real-Time PCR analysis was performed in triplicate following accurate and standardized protocols.

GENE	GenBank, accession #	AMPLICON LENGTH
TBP	NM_001004198	75 bp
PPIA	NM_017101	149 bp
RPL13A	NM_173340	66 bp
ACTC1	NM_019183.1	79 bp
MYH7	NM_017240.2	76 bp
MYH6	NM_017239.2	71 bp
TNNI3	NM_017144.2	59 bp
CTGF	NM_022266.2	59 bp
BAX	NM_017059.2	57 bp
BCL2	NM_016993.1	104 bp
SLC2A1	NM_138827.1	73 bp
PFKL	NM_013190.4	60 bp
GCKR	NM_013120.2	67 bp
PDK4	NM_053551.1	76 bp
PPAR-δ	NM_013141.2	94 bp
PPAR-α	NM_013196.1	98 bp
PGC1-α	NM_031347.1	94 bp
TBP	NM_001004198	123 bp
PPIA	NM_017101	135 bp
RPL13A	NM_173340	130 bp
ANP	NM_012612	118 bp
BNP	NM_031545	187 bp
CNP	NM_053750	201 bp
NPR-A	NM_012613	81 bp
NPR-B	NM_053838	89 bp
Pre-proET-1	NM_012548	98 bp

Table 1. Designed primer/probe set for structural, apoptosis, glucose and fatty acid metabolism, natriuretic peptides and biological receptors, endothelin-1 genes, as well as housekeeping genes. TBP: TATA box binding protein; PPIA: Peptidylprolyl Isomerase A (Cyclophilin A); RPL13a: Ribosomal Protein L13a; ACTC1: Actin, alpha, cardiac muscle 1; MYH7: Myosin Heavy Chain 7, cardiac muscle beta; MYH6: Myosin Heavy Chain 6, cardiac muscle alpha; TNNI3: Troponin I3, cardiac type; CTGF: Connective Tissue

Growth Factor; BAX: BCL2 associated X, apoptosis regulator; BCL2: BCL2 apoptosis regulator; SLC2A1: Solute Carrier family 2 member 1; PFKL: Phosphofructokinase, Liver type; GCKR: Glucokinase (hexokinase 4) Regulator; PDK4: Pyruvate Dehydrogenase Kinase, isozyme 4; PPAR- δ : Peroxisome Proliferator-Activated Receptor delta; PPAR- α : Peroxisome Proliferator-Activated Receptor alpha; PGC1- α : coactivator 1 alpha; ANP: atrial natriuretic peptide; BNP: B-type (or brain) natriuretic peptide; CNP: C-type natriuretic peptide; NPR-A: Natriuretic peptide receptor A; NPR-B: Natriuretic peptide receptor B; Pre-proET-1: Endothelin 1 gene

Statistical Data Analysis

Differences between more than two independent groups were analyzed by Fisher's test after ANOVA or by Bonferroni's test when indicated. Results are expressed as mean \pm SEM and p-value was considered significant when < 0.05 . GeNorm software was used to define the most stably expressed gene set (TATA binding protein (TBP), peptidylprolyl isomerase A (PPIA), and ribosomal protein L13a (Rpl13a); the geometric mean of the latter was used for normalization of real-time PCR results. Relative quantification of each target gene studied was calculated by the Δ Ct method using Bio-Rad CFX96 manager software (CFX-96 Real-Time PCR detection systems, Bio-Rad Laboratories Inc., Hercules, CA, USA). Differences between more than two independent groups were analyzed by Fisher's test after ANOVA using Statview 5.0.1 software released for Windows Statistical (SAS Institute, Inc., Cary, NC, USA). The results are expressed as mean \pm SEM and p-value was considered significant when < 0.05 .

Results

Polyurethane Characterization

PUR was successfully synthesized as confirmed by ATR-FTIR spectroscopy and SEC analysis. The formation of urethane linkages was evidenced by the appearance of two absorption bands, one at 1629 cm^{-1} , due to C=O stretching (amide I) and the other at 1535 cm^{-1} attributed to N-H bending vibrations (amide II). The urethane group also showed absorption at 3330 cm^{-1} , ascribed to N-H stretching. The strong absorption at 1725 cm^{-1} was attributed to the stretching of the carboxyl group in the macrodiol (PCL). Another strong peak was observed at 1160 cm^{-1} and was due to the stretching of the C-O-C linkage. The PUR number average molecular weight (M_n) measured by SEC was 70.5 KDa and the polydispersity index D (M_w/M_n) was 1.3.

Scaffold Characterization

Morphological, tensile and micro-compression scaffold characterization

The morphological characterization of the porous scaffold performed through the confocal laser microscopy has shown an average porosity of $37 \pm 3\%$. The average radius of the pores was similar for all samples: $37.2 \pm 3.0 \mu\text{m}$. The wall thickness was $10.7 \pm 3.9 \mu\text{m}$ and $6.0 \pm 1.5 \mu\text{m}$ (Figure 1).

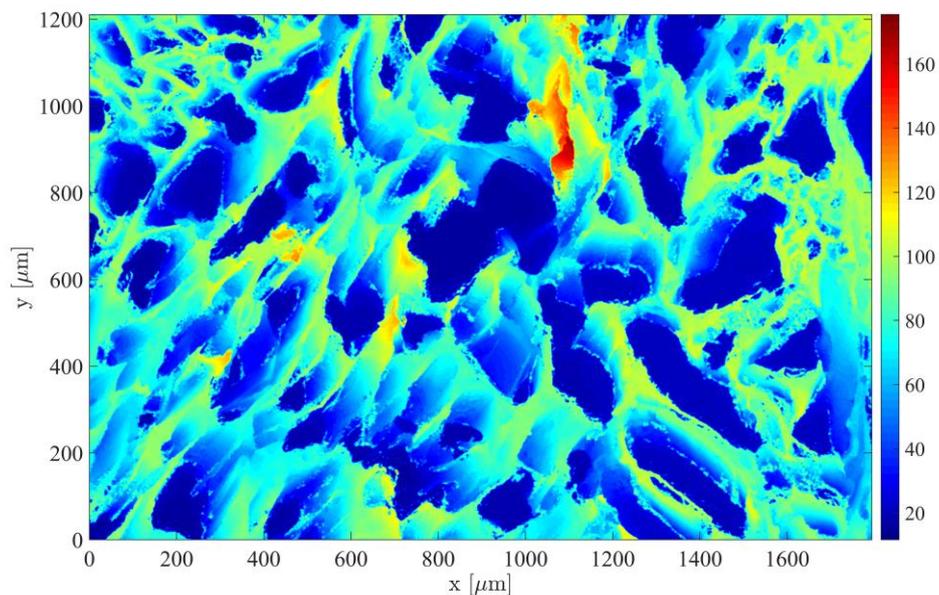


Figure 1. Transverse cross section of the PU scaffold; color scale refers to height measures obtained through the Confocal Laser Scanning Microscope.

All measures presented a standard deviation within 10% with exception of the wall thickness: for this standard deviation was up to 38%.

Under uniaxial tensile load, PUR scaffold showed an elastic modulus in dry state in the order of 1 MPa, while the maximum stress achieved was 0.28 MPa.

The stress strain curves showed a scattered response; however, standard deviation estimated on the elastic modulus was within 25% of the average values. The unloading branches of microcompression tests were used to assess the elastic modulus upon compression. The elastic indentation moduli estimated under compression at approximately 10% of compression strain were

0.62 ± 0.16 MPa and 0.34 ± 0.19 MPa for dry and liquid environment, respectively. The difference in indentation modulus between dry and liquid conditions was statistically significant ($p < 0.05$). Elastic modulus of sample tested in wet environment was about 50% of sample tested in the dry state: this behavior can be ascribed to the plasticizing effect of the aqueous environment [24]. The stiffness of myocardial tissue was evaluated in the range 10–20 kPa at the beginning and 200–500 kPa at the end of diastole [6]. Hence, the properties found in this work are consistent with that of the myocardial tissue. It should be observed that similar scaffolds studied in a previous work [19] showed an elastic modulus under tension of 1.5 MPa and 0.3 MPa in dry and wet conditions, respectively. These values are consistent with those found in the present study.

ATR-FTIR studies

Figure 2 shows the ATR-FTIR spectra of PUR, PUR-PAA and PU-PAA-Fibronectin scaffolds in the range $2000\text{--}900\text{ cm}^{-1}$.

This range was selected to better elucidate the slight variation in the three spectra. The ATR-FTIR spectrum of the PUR-PAA and PU-PAA-Fibronectin scaffolds showed characteristic absorptions of both polyurethane and polyacrylic polymers, indicating an average coating thickness below the one measured by this method (about $0.65\text{ }\mu\text{m}$). The spectra of PUR-PAA and PUR-PAA-Fibronectin scaffolds were very similar. The main differences between these spectra and the one of PUR scaffold, can be observed in the region of the C=O stretching. The spectrum of PUR scaffold showed a strong absorption at 1725 cm^{-1} , attributed to the ester group of the polyurethane backbone, and a weak peak at 1629 cm^{-1} due to the urethane linkage. The spectra of PUR-PAA and PUR-PAA-Fibronectin scaffolds showed the main peak and a broad shoulder at lower frequencies, due to signal overlapping of urethane, carboxyl and amide groups. Moreover, compared to PUR scaffold, the functionalised scaffolds showed a higher intensity of the C-O-C stretching peak (1160 cm^{-1}), which can be ascribed to the presence of carbonyl groups.

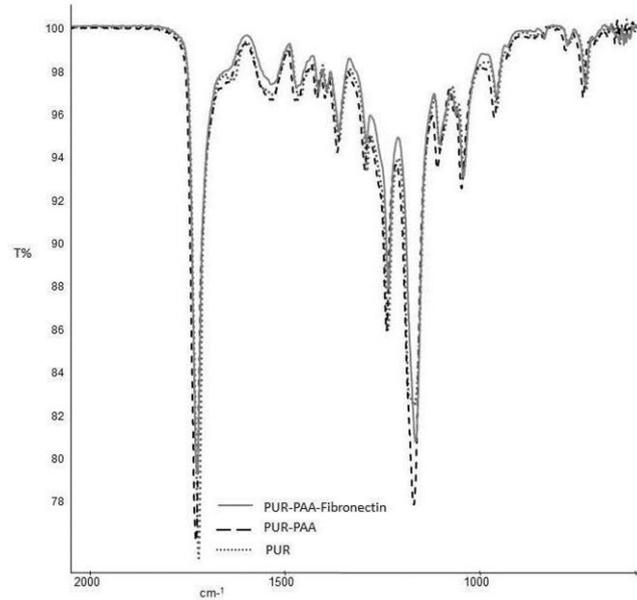


Figure 2. ATR-FTIR spectra of PUR, PUR-PAA, PUR-PAA-Fibronectin scaffolds.

X-ray Photoelectron Spectroscopy (XPS)

In Table 2, the concentrations of the main elements present on the scaffold surfaces are summarized, as obtained through XPS. XPS analysis (figure 3) confirmed the surface immobilization of fibronectin by the observed changes in both chemical composition and C1s signal deconvolution shape of samples before and after the functionalization step. The O/C ratio showed the highest value in PUR-PAA surface, according to the presence of a layer rich in carboxyl groups. However, the PUR-PAA surface had an oxygen composition lower than the theoretical value (27.5% instead of 40%) and an abnormal presence of nitrogen, probably due to two different reasons: a) plasma induced graft polymerization generated a cross-linked layer of poly(acrylic acid) instead of a linear polymeric chain, b) the PAA layer had a thickness that was below XPS sampling depth, including the PUR substrate, as observed in our previous work [25].

Sample	C(%)	O(%)	N(%)
PUR	71.6	21.6	5.4
PUR-PAA	67.0	27.5	2.4

PUR-PAA-Fibronectin	63.4	22.0	11.8
----------------------------	------	------	------

Table 2. XPS atomic composition of PUR, PUR-PAA and PUR-PAA-Fibronectin scaffolds.

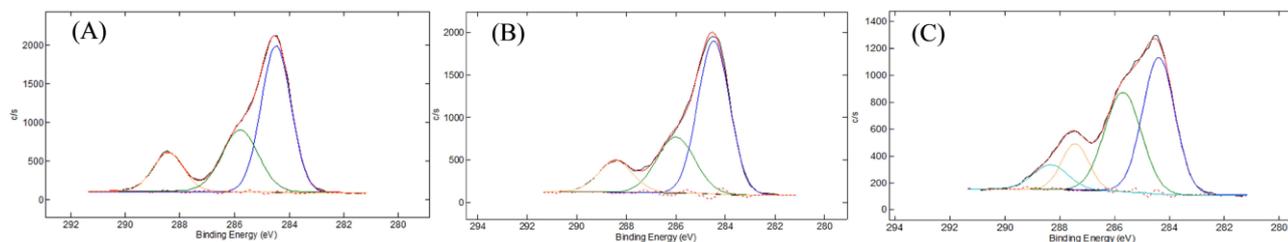


Figure 3. Deconvolution of XPS core level C1s spectra of PUR (a), PUR-PAA (b) and PUR-PAA-Fibronectin (c) scaffolds.

The highest N/C ratio was observed in PUR-PAA-Fibronectin sample, which is in agreement with the presence of the protein. The deconvolution of the core level C1s peaks on pristine PUR and PUR-PAA surface (Table 3) showed three contributions at 284.5, 286.0 and 288.5 eV, which may be assigned respectively to the aliphatic C–H and C–C, to the C–O and C–N bond, and to the COOR and COOH group, respectively.

SCAFFOLDS	C			
	C-C, C-H	C-O, C-N	CONH	COOH, COOR
PUR	15.6	29.6	-	54.9
PUR-PAA	14.2	26.4	-	59.4
PUR-PAA-Fibronectin	8.4	35.7	12.3	43.6

Table 3. Relative intensity data of the deconvoluted C1s core level spectra of PUR, PUR-PAA and PUR-PAA-Fibronectin scaffolds.

The peak at 288.5 eV showed the higher values in virgin PUR and in PUR-PAA surfaces, due to the presence of several ester groups in the macrodiol component of PUR, and of carboxylic groups in the poly(acrylic acid) acid layer. The relative intensity of COOH–COOR groups in the PUR-PAA surface was 14.2%, lower than theoretical value of pure (close to 33%) and confirmed that the thickness of the fibronectin layer is thinner than the XPS sampling depth (a few nanometers). The PUR-PAA-Fibronectin sample showed an additional peak at 287.4 eV, which can be assigned to the amide carbon; compared to PUR and PUR-PAA scaffolds, the PUR-PAA-fibronectin exhibited a higher percentage of C bonded to N and O and a lower content of C bonded to C and H and C of

ester and carboxylic group, according to the protein chemical composition. In conclusion, XPS analysis (figure 3) confirms the success of the fibronectin immobilization in a layer with a few nanometer thickness.

Contact Angle

Table 4 summarizes the water contact angle measurements. The water contact angle values on PUR and PUR-PAA scaffolds were around 113°, indicating that the surfaces were hydrophobic.

Scaffold	Angle (°)
PUR	113.3 ± 3.7
PUR-PAA	113.0 ± 3.3
PUR-PAA-Fibronectin	109.8 ± 2.5

Table 4. Scaffold contact angle results.

It has to be observed that the corresponding value for the PUR film is around 79.3°. The higher hydrophobicity of scaffold can be explained by the scaffold fiber-like structure [26]. No significant differences can be observed after fibronectin immobilization: this result is in agreement considering the hydrophobic nature of fibronectin surfaces [27].

Scanning Electron Microscopy

Figure 4 shows the micrographs of PUR scaffolds (a), PUR-PAA scaffolds (b) and PUR-PAA-Fibronectin scaffolds (c).

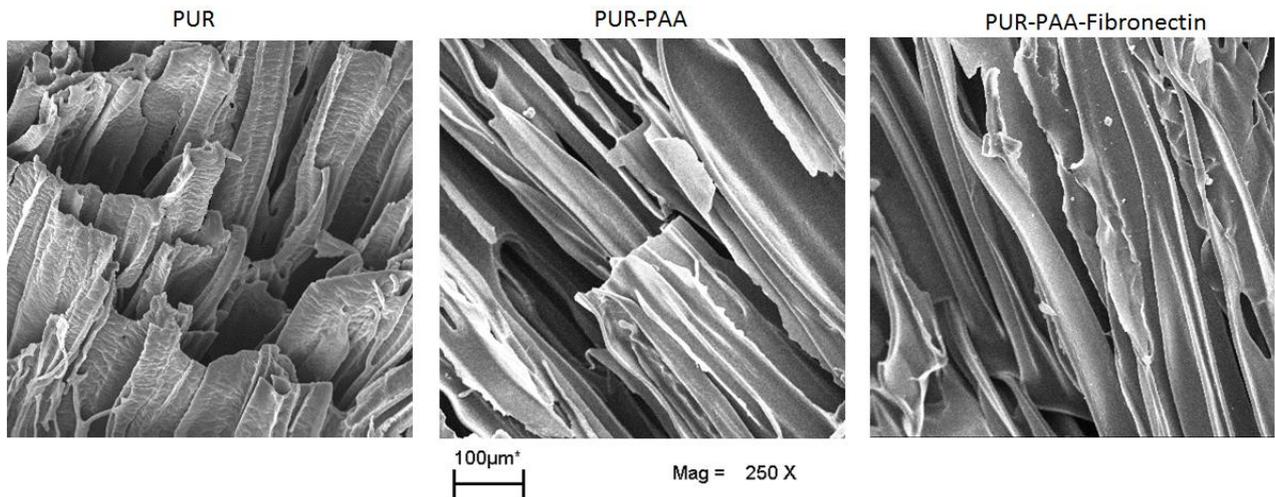


Figure 4. Micrographs of PUR scaffolds (a), PUR-PAA scaffolds (b) and PUR-PAA-Fibronectin scaffolds (c).

In detail, figure shows an oriented parallel pore structure, resembling the histoarchitecture of the myocardium. PUR-PAA and PUR-PAA-Fibronectin micrographs shows the pore inner morphology, which exhibit a lamellar substructure. A similar morphology was observed by Guan and colleagues [28].

Characterization of primary cardiomyocyte population

Once structurally and mechanically characterized, capacity of scaffolds to support primary cardiomyocytes was assessed, as described in “Primary cardiomyocytes isolation and culture” paragraph. Immunofluorescence analysis with an anti-sarcomeric actinin antibody and phalloidin was performed to characterize the cell population and to determine the ratio of myocyte to non-myocyte cells. Our analysis demonstrated that the percentage of cardiomyocytes was higher than 80% during the 14 days of experiment (figure 5).

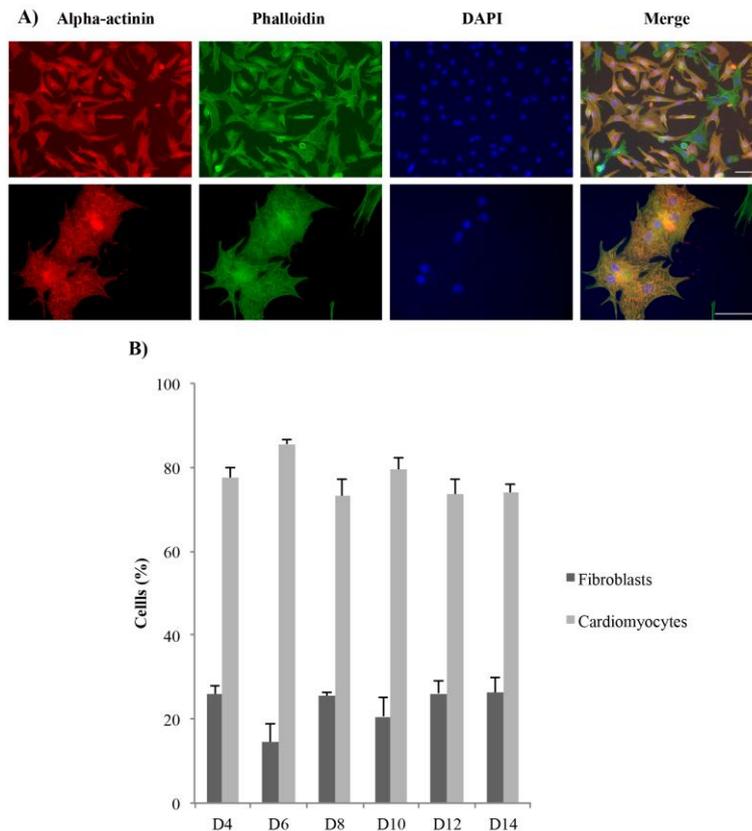


Figure 5. Characterization of primary cardiomyocytes population. Purity of primary neonatal heart cell culture. Figure 5(a) Primary neonatal heart cells were subjected to immunofluorescence analysis using anti-sarcomeric α -actinin (red) and phalloidin (green) staining to evaluate the percentage of cardiomyocytes. Cells positive for sarcomeric α -actinin, were identified as cardiomyocytes. The pictures refer to cells stained after 4 days from the isolation. Cell nuclei were counterstained with DAPI (blue) (Bars=50 μ m). Figure 5(b) The graphs show the percentage of cardiomyocytes present in the culture from day 2 (D2) to day 14 (D14). No significant differences were found among % of cardiomyocytes or fibroblasts at the different time points ($p > 0.05$). Instead, significant differences ($p < 0.001$) were found between fibroblasts and cardiomyocytes at each time point. Statistical analysis was performed using one way ANOVA followed by Bonferroni post test.

Cardiomyocytes colonization and survival on the PUR-PAA-Fibronectin scaffold

Primary cells colonized the scaffold surface and remained adherent to it for more than 50 days (figure 6(a)). Furthermore, the histological analysis with haematoxylin and eosin staining, performed on constructs after 14 days of culture, showed the presence of multiple cell layers on the scaffold surface (white arrows in figure 6(b)). Moreover, cell viability remained high and stable until day 14 (figure 6(c)).

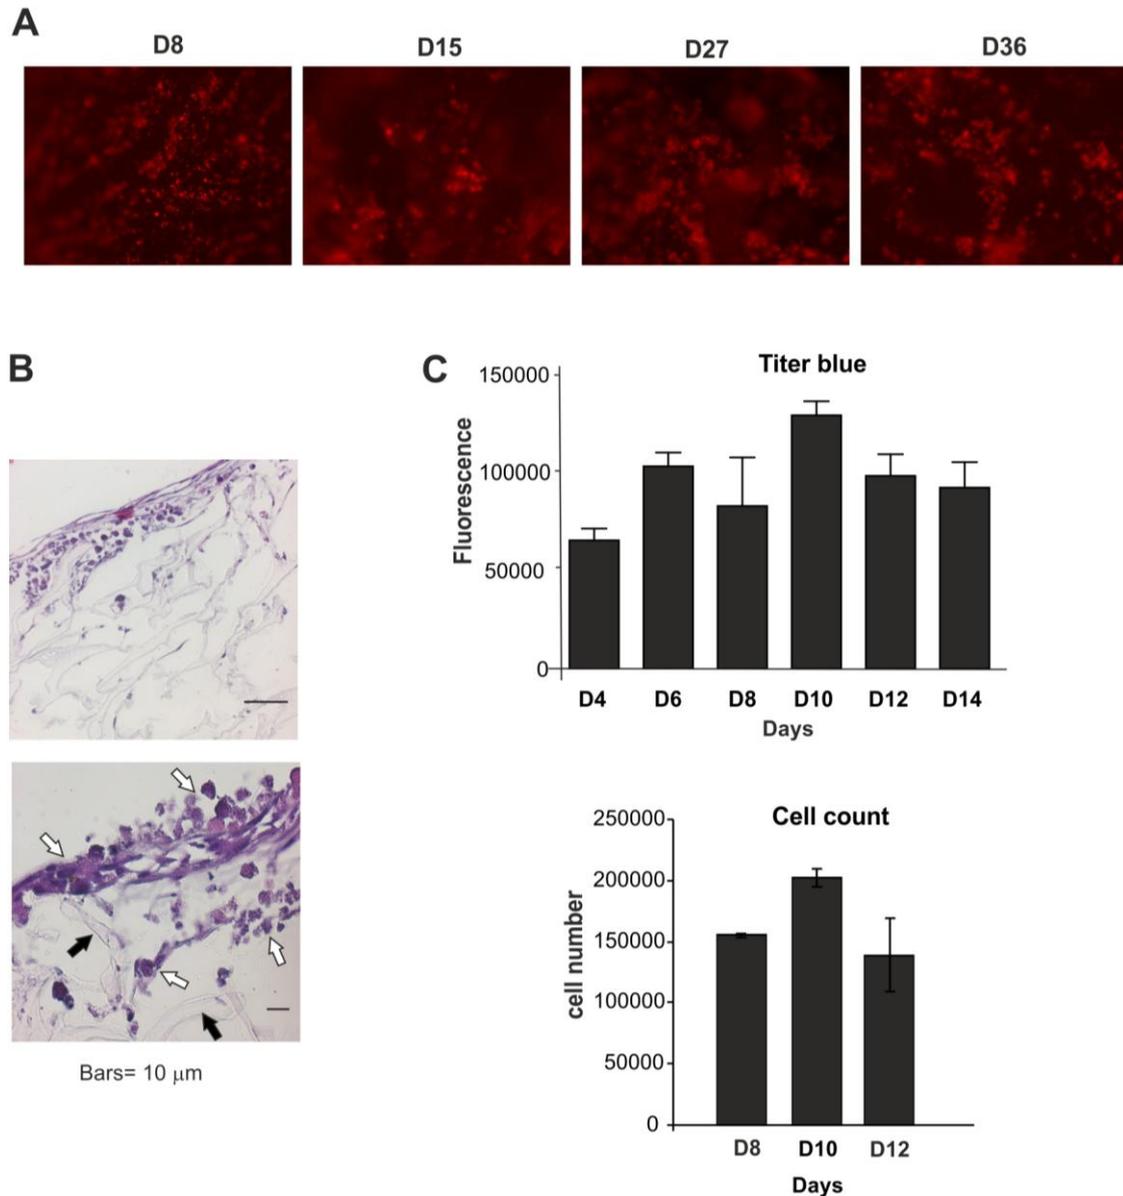


Figure 6. Adhesion and viability of cardiomyocytes on the scaffold. Figure 6(a) Primary cells were stained with Acridine Orange and then seeded on the scaffolds and allowed to adhere for two days. From 4 days after cell seeding, constructs were analyzed using fluorescence microscopy to evaluate the scaffold colonization. Figure 6(b) Serial sections from cardiac constructs after 2 weeks of culture were obtained and stained with haematoxylin and eosin. White arrows indicate cardiomyocytes, while black arrows mark scaffold fibers. Bars= 10 μ m. Figure 6(c) The graph shows the results of Cell Titer Blue assay performed from day 4 (D4) to day 14 (D14) on the cardiac constructs (n=3). Differences were not statistically significant. Cell count analysis performed from day 8 to day 12 (D8-D12) have been also performed on cardiomyocytes cultured on the scaffolds. Significant differences ($p < 0.001$) were found using one way ANOVA followed by Bonferroni post test.

Cardiomyocytes beating activity

Video microscopy acquisition demonstrated that cardiomyocytes seeded on the scaffolds beat synchronously for over 50 days (see Supplementary Material Movie S1). These results demonstrated that cardiomyocytes survived and showed an intense beating activity on scaffolds.

Signal transduction activity of cardiac constructs.

As shown in figure 7, the activation of two important signaling pathways, the PI3K/AKT and the MAPK pathways, was analyzed. Results demonstrated that the phosphorylation of AKT and ERK1/2 was higher in cardiomyocytes cultured on the scaffold compared to those cultured on plastic plates.

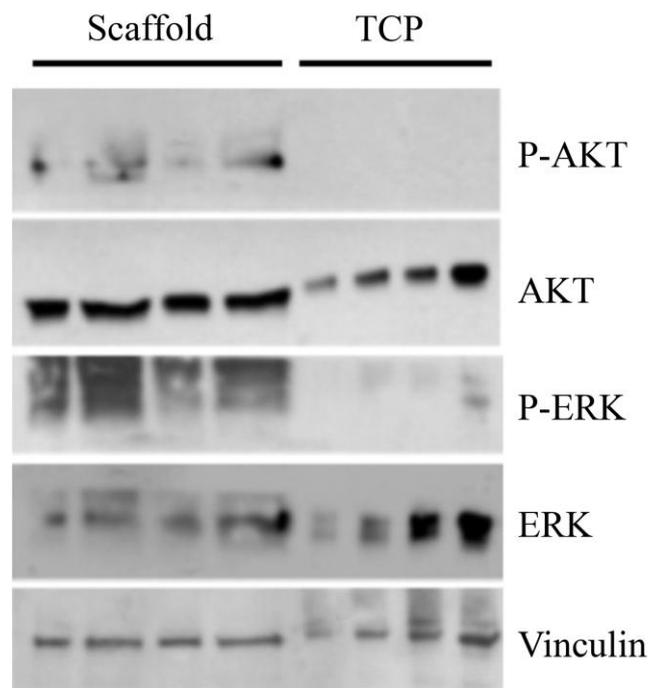


Figure 7. Signal transduction activity of cardiac constructs. Western blot analysis of P-ERK, total ERK, P-AKT and total AKT on primary cells grown on 3D scaffolds or on TCP for 14 days. The graph shows densitometry quantification of western blot bands (n=5)

Gene expression profiling

The global mRNA expression changes between TCP and scaffold groups of Natriuretic Peptides (ANP, BNP and CNP) together with their specific guanylate cyclase receptors (NPR-A and NPR-B) and Endothelin-1 (pre-pro ET-1) are reported in figure 8 and figure 9.

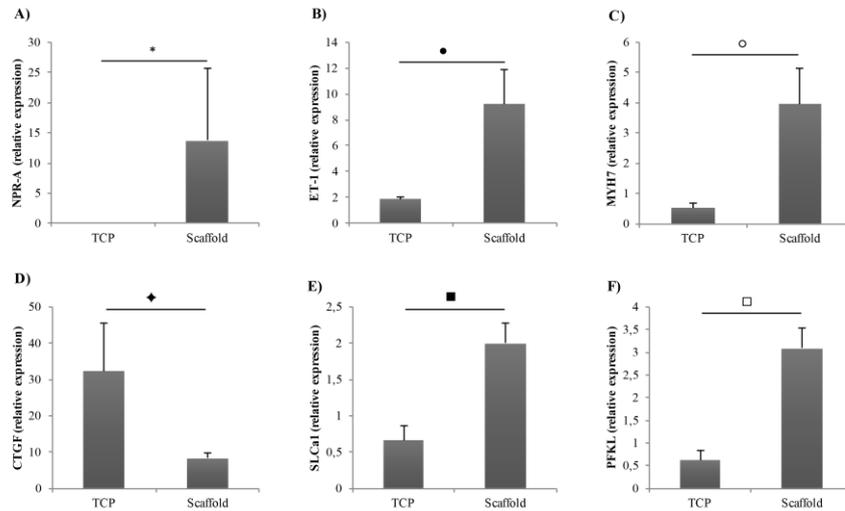


Figure 8. Analysis of significant modulation in cardiomyocyte gene expression. Expression of NPR-A (figure 8(a)), ET-1 (figure 8(b)) heart development and differentiation (figure 8(c,d)) and heart glucose (figure 8(e,f)) genes in cardiomyocytes grown on scaffolds and on TCP for 14 days. Results are the mean \pm SEM. * $p = 0.018$, • $p = 0.035$, ◦ $p < 0.05$, ♦ $p < 0.01$, ■ $p < 0.001$, □ $p < 0.001$.

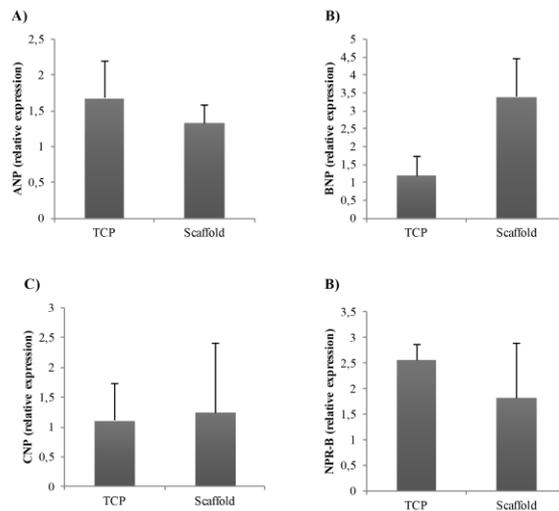


Figure 9. Analysis of cardiomyocyte gene expression: NP system gene expression. Expression of NP system (figure 9(a-d)) genes in cardiomyocytes grown on scaffolds and on TCP for 14 days. Results are the mean \pm SEM. No statistical significance was found ($p > 0.05$).

No statistical differences were observed for the three natriuretic peptides expression in TCP compared with scaffolds (figure 9(a-c)), while NP receptors were counter-regulated with respect to their related biological ligands, significantly only for NPR-A expression ($p=0.018$) (figure 8(a)). In the same samples, a statistical significance was observed for pre-pro ET-1 mRNA expression (figure 8(b)), which resulted to be higher ($p= 0.035$) after 14 days of culture on scaffold surface.

Cardiac muscle- and hypertrophy-specific genes, involved in heart development and function, resulted to be modulated between cells grown for 14 days on scaffolds and on TCPs. In particular,

MYH7 was significantly upregulated on scaffolds compared to plates (figure 8(c)). ACTC1 (figure 10(a)) and apoptotic genes (i.e. BAX, BCL2) did not show any statistically significant difference (figure 10(b)).

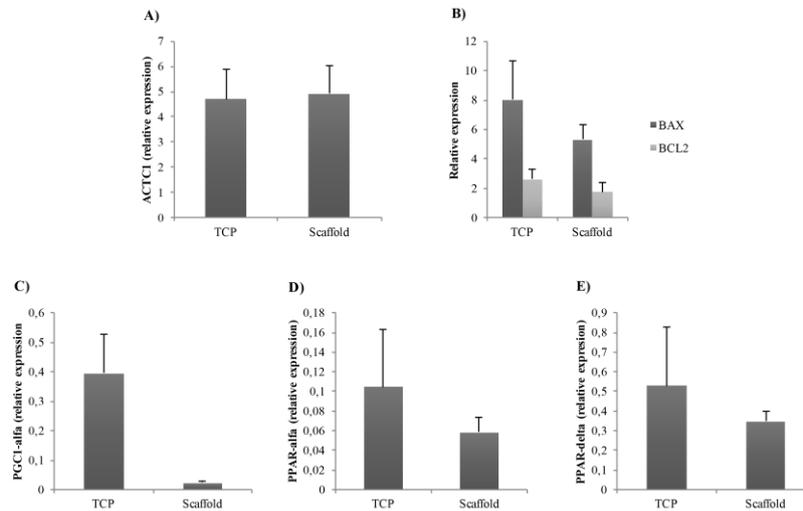


Figure 10. Analysis of cardiomyocyte gene expression: heart development, differentiation and apoptosis genes, fatty acid metabolism genes. Expression of heart development and differentiation (figure 10(a)), apoptosis (figure 10(b)) and fatty acid metabolism (figure 10(c-e)) genes in cardiomyocytes grown on scaffolds and on TCP for 14 days. Results are the mean \pm SEM. No statistical significance was found.

The hypertrophy-related gene (CTGF) was upregulated on plate at 14 days compared to scaffolds (figure 8(d)). Metabolic specific genes resulted to be differentially regulated between cells grown on scaffolds and on plates. Glucose metabolism showed a statistically significant upregulation (SLC2a1 and PFKL genes in figure 8(e) and 8(f), respectively) in cells on scaffolds compared to TCP. On the other hand, fatty acid oxidation was not significantly modulated (PGC1- α , PPAR- α and PPAR- δ genes in figure 10(c), 10(d) and 10(e), respectively) in cells grown on scaffolds compared to TCP.

Discussion

The development of efficient cardiac models is a challenge in Tissue Engineering for the particular characteristics of the cardiac muscle, which is continuously subjected to several stimuli (neural and hormonal signals, ion currents, changes in preload and afterload) able to modify its cellular

responses. The use of classic 2D cell cultures of rat cardiomyocytes has produced great advances [29] on cardiac cell function knowledge. On the other hand, the lack of their tissue-level organization characterized by cell interactions with the extracellular matrix and mechanical forces, which are important to maintain cell morphology, maturity and function [30,31], have led to reproduce the 3D environment. In fact, 3D engineered tissues have been demonstrated to (i) induce or recreate pathological situations, (ii) provide measurable indicators to monitor damaging or healing processes, (iii) supply accurate evaluation of drug safety and, therefore, eliminate toxic and ineffective compounds at an earlier stage and (iv) reproduce the ECM properties at different ageing levels to better understand the effects of age and/or pathological conditions on tissue properties and functionality [32].

The Tissue Engineering approach used in this work allowed building an in-vitro model able to recapitulate various physiological functions of the myocardial tissue. The present PUR-based 3D in-vitro model was characterized to ensure the replication of the cardiac structure from the morpho-mechanical and biological point of view: the first goal was obtained by mimicking the tissue-specific architecture and mechanical properties [3,4], the second one by the use of appropriate cell types (primary cardiomyocytes) and the integration of ECM proteins.

The tensile tests showed that the scaffold elastic modulus in the dry state is about 1 MPa, while the compression elastic moduli in dry and wet conditions were 620KPa and 340KPa, respectively. These mechanical properties are consistent with that of the myocardial tissue [6].

ATR-FTIR, contact angle, and XPS analysis confirmed the formation of a nanometric fibronectin layer after plasma treatment. This result is important since the low thickness of the modified surface is crucial, to avoid affecting the scaffold mechanical properties.

Finally, scaffold analysis was directed to evaluate its microstructure: SEM images showed an aligned pore structure and confocal images indicated an average diameter and porosity (around 75 μm and 37%, respectively), similar to that of the heart. The pore size and porosity percentage are appropriate [10], and, once scaffold will be implanted in-situ, it is expected to promote the

regeneration of blood vessels [33,34] as well as fibroblasts proliferation: these are crucial steps for the regeneration of a cardiac-like tissue [35].

The functionalised scaffold proposed as myocardial model is highly hydrophobic as shown by contact angle measurements. Several studies report that hydrophilic surfaces are suitable for cell attachment [36]. However, these observations are valid in case of flat or relatively smooth surfaces, but in case of porous scaffolds the correlation between hydrophilicity and cell adhesion is more complex. Several publications demonstrate that substrates from a hydrophobic material showing submicron roughness turn out to be highly hydrophobic [37,38]. The high hydrophobicity of the proposed scaffolds can then be attributed to their fiber-like structure but this surface property does not affect cell adhesion negatively.

The biological characterization of PUR-PAA-Fibronectin scaffolds was carried out using primary cardiomyocytes from rat neonatal hearts as a reference system. Cardiomyocytes showed good surface colonization, as well as high and stable viability, comparable to the results observed by Rockwood [39]. Notably, cardiomyocytes beating activity was still present after 7 weeks of culture, while cardiomyocytes cultured on TCP did not survive more than 3 weeks.

Signal transduction is crucial in cardiomyocytes to sense mechanical stretch as well as humoral stimuli leading to hypertrophic growth, cardiomyocytes survival and metabolic adaptation. In particular, our focus was directed to two main specific pathways, PI3K/AKT and the MAPK: their activation protects cardiomyocytes from damage and apoptosis induced by myocardial infarction [40-42], pressure overload [43], hypoxia [44] or hypoglycemia [45]. Notably, AKT and ERK1/2 phosphorylation in cardiomyocytes cultured on scaffolds was higher than in cells cultured on culture plates, thus providing a molecular explanation for the increased survival and functionality of cardiomyocytes cultured on scaffolds.

Biological characterization of scaffolds also involved the analysis of cell behavior correlated to important cardiac endogenous mediators, the cardiac Natriuretic Peptides. These are constituted by a family of peptide hormones and neurotransmitters, including ANP, BNP and CNP. NPs play a

role during physiological growth of the heart and, mainly ANP/BNP, are able to stimulate proliferation and differentiation of fetal cardiomyocytes into mature ones [46,47]. In this study, NPs are monitored to evaluate the potential maturation phenotype of cardiomyocytes. A trend in ANP reduction and an increase of both BNP and CNP expression in scaffolds was observed, in line with the fetal action of NPs and their guanylate cyclase-linked receptors NPR-A and NPR-B, known to be functionally redundant during early cardiovascular development [48]. In this paper, a different behavior of the three cardiac natriuretic peptides in modulating cardiomyocyte proliferation by a counter-balancing of the two NP receptors, NPR-A and NPR-B was observed. In fact, they resulted increased (NPR-A) or decreased (NPR-B) in cardiomyocytes seeded on scaffolds compared to TCP, confirming their down regulation with respect to their biological ligands (BNP and CNP, respectively). Moreover, for the first time a modulation of CNP, which expression reflects those of BNP, was observed, underlining that during cardiomyocyte maturation NPs are modified in a different manner. These results are in line with a previous study where it was hypothesized that their trend during phenotype differentiation is probably caused by differences in sequence genes, rate of transcription and differential stabilization of the mRNA [49].

Analysis of cell response to scaffolds involved also the evaluation of Endothelin-1 (ET-1), a peptide secreted by many cell types (endothelial and epithelial cells, macrophages, fibroblasts) [50,51] with potent vasoconstrictor as also growth factor activity for a variety of cells, including cardiomyocytes [52,53]. The ET-1 is involved in regulating cell cycle and, in cardiomyocytes, induces a premature cardiomyocyte transition in the developing heart [50]. Our results suggested that ET-1 could promote a premature transition of fetal cardiomyocytes to a more mature phenotype.

A further biological characterization of the cardiomyocytes that colonized scaffolds was performed, analyzing specific apoptotic, cardiac muscle, hypertrophy- and metabolism-related genes. A non significant modulation of apoptosis-related genes (BAX, BCL2) was observed between scaffolds and TCP, showing a cell behavior that is in line with data from the literature [54,55]. Cardiac muscle (MYH7) and hypertrophy-specific (CTGF) genes were, on the other hand, significantly

modulated in scaffolds, in accordance with normal cardiac development and function [56-59], thus confirming an incipient process of cardiomyocyte maturation. Interestingly, glucose metabolism genes (SLC2a1, PFKL) were upregulated on scaffolds compared to plates while no statistically significant differences could be observed for fatty acid metabolism ones (PGC1- α , PPAR- α and PPAR- δ). After 14 days on scaffolds, the absence of upregulation of fatty acid oxidation-related genes suggested a permanence of the myocardial cells in a fetal-like phenotype, still relying on glycolytic metabolism for their energy demand, and a delayed differentiation toward the adult phenotype [60,61] that is instead characterized by a switch to the fatty acid β -oxidation route as a major source of energy [62]. Hence, the maintenance of high glycolytic rates in our developing cardiomyocytes grown on scaffolds seems to reflect cellular wellness, as they maintain indeed a good survival and proliferative state as observed before [63-65].

Conclusion

In this work the feasibility of functionalised PUR-based scaffolds as cardiac tissue model, has been demonstrated, with a particular focus on the structural and mechanical mimicry offered by the biomaterial and on the biological behavior showed by seeded cells. In fact, success of plasma-treatment to engraft fibronectin on PUR scaffolds was observed via XPS analysis. Structural analysis showed a pore-aligned scaffold configuration, with mechanical properties and histoarchitecture resembling the myocardium. The biological characterization highlighted a stable viability along 14 days of experimentation, good beating activity and cell adhesion of cardiomyocytes. The increased levels of phosphorylation of AKT and ERK1/2 explained the prolonged cell survival, and consequent beating activity, of cardiomyocytes cultured on scaffolds vs TCP control. The modulation of cardiac muscle (ET-1, MYH7, CTGF) and of glucose metabolism (SLC2a1, PFKL) genes indicates a transition phase in cardiomyocyte maturation, with an initial evolution to an adult phenotype as indicated by the first and, still, a permanence of some fetal characteristics shown by the sustained expression of the second. These results represent the initial

step to develop a new generation of tissue model systems with tunable structural and mechanical characteristics able to reproduce basic functional parameters of the entire heart and to study cardiac physiology and pathophysiological mechanisms.

Acknowledgments

There are no conflicts of interest to declare by all authors. The study was funded by “Engineering physiologically and pathologically relevant organ Models for the INvestigation of age related Diseases (MIND)” Project, PRIN 2010-2011 of Ministry of Education, University and Research (grant agreement 2010J8RYS7). This work is dedicated to Prof. Guido Tarone, brilliant scientist and dear colleague. Alessandra Piccito and Giulia Quagliato are acknowledged for their support in sample preparation and characterization, respectively.

REFERENCES

- [1] Mendis S, Davis S and Norrving B 2015 Organizational update: the world health organization global status report on noncommunicable diseases 2014; one more landmark step in the combat against stroke and vascular disease. *Stroke* **46** e121–2
- [2] Mozaffarian D, Benjamin E J, Go A S, Arnett D K, Blaha M J, Cushman M, de Ferranti S, Després J-P, Fullerton H J, Howard V J, Huffman M D, Judd S E, Kissela B M, Lackland D T, Lichtman J H, Lisabeth L D, Liu S, Mackey R H, Matchar D B, McGuire D K, Mohler E R, Moy C S, Muntner P, Mussolino M E, Nasir K, Neumar R W, Nichol G, Palaniappan L, Pandey D K, Reeves M J, Rodriguez C J, Sorlie P D, Stein J, Towfighi A, Turan T N, Virani S S, Willey J Z, Woo D, Yeh R W, Turner M B American Heart Association Statistics Committee and Stroke Statistics Subcommittee 2015 Heart disease and stroke statistics--2015 update: a report from the American Heart Association. *Circulation* **131** e29–322
- [3] Engler A J, Carag-Krieger C, Johnson C P, Raab M, Tang H-Y, Speicher D W, Sanger J W, Sanger J M and Discher D E 2008 Embryonic cardiomyocytes beat best on a matrix with heart-like elasticity: scar-like rigidity inhibits beating. *Journal of Cell Science* **121** 3794–802
- [4] Jacot J G, McCulloch A D and Omens J H 2008 Substrate stiffness affects the functional maturation of neonatal rat ventricular myocytes. *Biophys. J.* **95** 3479–87
- [5] Wobma H and Vunjak-Novakovic G 2016 Tissue Engineering and Regenerative Medicine 2015: A Year in Review. *Tissue Engineering. Part B, Reviews* **22** 101–13
- [6] Chen Q-Z, Harding S E, Ali N N, Lyon A R and Boccaccini A R 2008 Biomaterials in cardiac tissue engineering: Ten years of research survey *Materials Science and Engineering: R: Reports* **59** 1–37
- [7] Hidalgo-Bastida L A, Barry J J A, Everitt N M, Rose F R A J, BATTERY L D, Hall I P, Claycomb W C and Shakesheff K M 2007 Cell adhesion and mechanical properties of a flexible scaffold for cardiac tissue engineering. *Acta Biomaterialia* **3** 457–62
- [8] Silvestri A, Boffito M, Sartori S and Ciardelli G 2013 Biomimetic materials and scaffolds for myocardial tissue regeneration. *Macromol Biosci* **13** 984–1019
- [9] Davis M E, Hsieh P C H, Grodzinsky A J and Lee R T 2005 Custom design of the cardiac microenvironment with biomaterials. *Circ Res* **97** 8–15
- [10] Boffito M, Sartori S and Ciardelli G 2013 Polymeric scaffolds for cardiac tissue engineering: requirements and fabrication technologies *Polym. Int.* **63** 2–11
- [11] de Mulder E L W, Buma P and Hannink G 2009 Anisotropic Porous Biodegradable Scaffolds for Musculoskeletal Tissue Engineering *Materials* **2** 1674–96
- [12] Kowligi R R, Maltzahn Von W W and Eberhart R C 1988 Fabrication and characterization of small-diameter vascular prostheses *Journal of biomedical materials research. Part A* **22** 245–56

- [13] Thomas S P, Bircher-Lehmann L, Thomas S A, Zhuang J, Saffitz J E and Kleber A G 2000 Synthetic Strands of Neonatal Mouse Cardiac Myocytes : Structural and Electrophysiological Properties *Circ Res* **87** 467–73
- [14] Pong T, Adams W J, Bray M-A, Feinberg A W, Sheehy S P, Werdich A A and Parker K K 2011 Hierarchical architecture influences calcium dynamics in engineered cardiac muscle. *Exp. Biol. Med. (Maywood)* **236** 366–73
- [15] Azarin S M, Lian X, Larson E A, Popelka H M, de Pablo J J and Palecek S P 2012 Modulation of Wnt/ β -catenin signaling in human embryonic stem cells using a 3-D microwell array *Biomaterials* **33** 2041–9
- [16] To W S and Midwood K S 2011 Plasma and cellular fibronectin: distinct and independent functions during tissue repair. *Fibrogenesis Tissue Repair* **4** 21
- [17] Brancaccio M, Cabodi S, Belkin A M, Collo G, Koteliansky V E, Tomatis D, Altruda F, Silengo L and Tarone G 1998 Differential onset of expression of alpha 7 and beta 1D integrins during mouse heart and skeletal muscle development. *Cell Adhes. Commun.* **5** 193–205
- [18] Sartori S, Boffito M, Serafini P, Caporale A, Silvestri A, Bernardi E, Sassi M P, Boccafoschi F and Ciardelli G 2013 Synthesis and structure–property relationship of polyester-urethanes and their evaluation for the regeneration of contractile tissues *Reactive and Functional Polymers* **73** 1366–76
- [19] Boffito M, Bernardi E, Sartori S, Ciardelli G and Sassi M P 2015 A mechanical characterization of polymer scaffolds and films at the macroscale and nanoscale. *J Biomed Mater Res A* **103** 162–9
- [20] Shahidi S, Wiener J and Ghoranneviss M 2013 Surface Modification Methods for Improving the Dyeability of Textile Fabrics *Eco-Friendly Textile Dyeing and Finishing (InTech)*
- [21] Soonpaa M H and Field L J 1998 Survey of studies examining mammalian cardiomyocyte DNA synthesis. *Circ Res* **83** 15–26
- [22] De Acetis M, Notte A, Accornero F, Selvetella G, Brancaccio M, Vecchione C, Sbroggiò M, Collino F, Pacchioni B, Lanfranchi G, Aretini A, Ferretti R, Maffei A, Altruda F, Silengo L, Tarone G and Lembo G 2005 Cardiac overexpression of melusin protects from dilated cardiomyopathy due to long-standing pressure overload. *Circ Res* **96** 1087–94
- [23] Sbroggiò M, Bertero A, Velasco S, Fusella F, De Blasio E, Bahou W F, Silengo L, Turco E, Brancaccio M and Tarone G 2011 ERK1/2 activation in heart is controlled by melusin, focal adhesion kinase and the scaffold protein IQGAP1. *Journal of Cell Science* **124** 3515–24
- [24] Pan Z and Ding J 2012 Poly(lactide-co-glycolide) porous scaffolds for tissue engineering and regenerative medicine *Interface Focus* **2** 366–77
- [25] Sartori S, Rechichi A, Vozzi G, D'acunto M, Heine E, Giusti P and Ciardelli G 2008 Surface modification of a synthetic polyurethane by plasma glow discharge: Preparation and characterization of bioactive monolayers *Reactive and Functional Polymers* **68** 809–21

- [26] Ballester-Beltrán J, Rico P, Moratal D, Song W, Mano J F and Salmerón-Sánchez M 2011 Role of superhydrophobicity in the biological activity of fibronectin at the cell–material interface *Soft Matter* **7** 10803–11
- [27] Hayashi-Nagai A, Kitagaki-Ogawa H, Matsumoto I, Hayashi M and Seno N 1991 Hydrophobic properties of porcine fibronectin and its functional domains. *J. Biochem.* **109** 83–8
- [28] Guan J, Fujimoto K L and Wagner W R 2008 Elastase-sensitive elastomeric scaffolds with variable anisotropy for soft tissue engineering. *Pharm Res* **25** 2400–12
- [29] Louch W E, Sheehan K A and Wolska B M 2011 Methods in cardiomyocyte isolation, culture, and gene transfer *Journal of Molecular and Cellular Cardiology* **51** 288–98
- [30] Akins R E, Rockwood D, Robinson K G, Sandusky D, Rabolt J and Pizarro C 2010 Three-dimensional culture alters primary cardiac cell phenotype. *Tissue engineering Part A* **16** 629–41
- [31] Kira Y, Nakaoka T, Hashimoto E, Okabe F, Asano S and Sekine I 1994 Effect of long-term cyclic mechanical load on protein synthesis and morphological changes in cultured myocardial cells from neonatal rat. *Cardiovasc Drugs Ther* **8** 251–62
- [32] Vacanti J 2010 Tissue engineering and regenerative medicine: from first principles to state of the art. *J. Pediatr. Surg.* **45** 291–4
- [33] Oliviero O, Ventre M and Netti P A 2012 Functional porous hydrogels to study angiogenesis under the effect of controlled release of vascular endothelial growth factor. *Acta Biomaterialia* **8** 3294–301
- [34] Madden L R, Mortisen D J, Sussman E M, Dupras S K, Fugate J A, Cuy J L, Hauch K D, Laflamme M A, Murry C E and Ratner B D 2010 Proangiogenic scaffolds as functional templates for cardiac tissue engineering. *Proc Natl Acad Sci US A* **107** 15211–6
- [35] Rnjak-Kovacina J, Wise S G, Li Z, Maitz P K M, Young C J, Wang Y and Weiss A S 2011 Tailoring the porosity and pore size of electrospun synthetic human elastin scaffolds for dermal tissue engineering *Biomaterials* **32** 6729–36
- [36] Chang H-I and Wang Y 2011 Cell Responses to Surface and Architecture of Tissue Engineering Scaffolds *Regenerative Medicine and Tissue Engineering - Cells and Biomaterials* (InTech)
- [37] Ballester-Beltrán J, Rico P, Moratal D, Song W, Mano J F and Salmerón-Sánchez M 2011 Role of superhydrophobicity in the biological activity of fibronectin at the cell-material interface *Soft Matter* **7** 10803–11
- [38] Erbil H Y 2003 Transformation of a Simple Plastic into a Superhydrophobic Surface *Science* **299** 1377–80
- [39] Rockwood D N, Akins R E, Parrag I C, Woodhouse K A and Rabolt J F 2008 Culture on electrospun polyurethane scaffolds decreases atrial natriuretic peptide expression by cardiomyocytes in vitro. *Biomaterials* **29** 4783–91

- [40] Unsöld B, Kaul A, Sbroggiò M, Schubert C, Regitz-Zagrosek V, Brancaccio M, Damilano F, Hirsch E, van Bilsen M, Munts C, Sipido K, Bito V, Detre E, Wagner N M, Schäfer K, Seidler T, Vogt J, Neef S, Bleckmann A, Maier L S, Balligand J L, Bouzin C, Ventura-Clapier R, Garnier A, Eschenhagen T, El-Armouche A, Knöll R, Tarone G and Hasenfuß G 2014 Melusin protects from cardiac rupture and improves functional remodelling after myocardial infarction. *Cardiovasc Res* **101** 97–107
- [41] Fujio Y, Nguyen T, Wencker D, Kitsis R N and Walsh K 2000 Akt promotes survival of cardiomyocytes in vitro and protects against ischemia-reperfusion injury in mouse heart. *Circulation* **101** 660–7
- [42] Penna C, Brancaccio M, Tullio F, Rubinetto C, Perrelli M-G, Angotti C, Pagliaro P and Tarone G 2014 Overexpression of the muscle-specific protein, melusin, protects from cardiac ischemia/reperfusion injury. *Basic Res. Cardiol.* **109** 418
- [43] Sbroggiò M, Carnevale D, Bertero A, Cifelli G, De Blasio E, Mascio G, Hirsch E, Bahou W F, Turco E, Silengo L, Brancaccio M, Lembo G and Tarone G 2011 IQGAP1 regulates ERK1/2 and AKT signalling in the heart and sustains functional remodelling upon pressure overload. *Cardiovasc Res* **91** 456–64
- [44] Matsui T, Li L, del Monte F, Fukui Y, Franke T F, Hajjar R J and Rosenzweig A 1999 Adenoviral gene transfer of activated phosphatidylinositol 3'-kinase and Akt inhibits apoptosis of hypoxic cardiomyocytes in vitro. *Circulation* **100** 2373–9
- [45] Ricci C, Jong C J and Schaffer S W 2008 Proapoptotic and antiapoptotic effects of hyperglycemia: role of insulin signaling. *Can. J. Physiol. Pharmacol.* **86** 166–72
- [46] Sergeeva I A and Christoffels V M 2013 Regulation of expression of atrial and brain natriuretic peptide, biomarkers for heart development and disease. *Biochim Biophys Acta* **1832** 2403–13
- [47] Del Ry S, Cabiati M and Clerico A 2014 Natriuretic peptide system and the heart. *Front Horm Res* **43** 134–43
- [48] McGrath M F and de Bold A J 2005 Determinants of natriuretic peptide gene expression. *Peptides* **26** 933–43
- [49] Ernest S, Jankowski M, Mukaddam-Daher S, Cusson J and Gutkowska J 1998 Altered regulation of natriuretic peptides in the rat heart by prenatal exposure to morphine. *The Journal of Physiology* **506** (Pt 3) 867–74
- [50] Kohan D E, Rossi N F, Inscho E W and Pollock D M 2011 Regulation of blood pressure and salt homeostasis by endothelin. *Physiological Reviews* **91** 1–77
- [51] Battistini B, Chaillet P, D'Orléans-Juste P, Brière N and Sirois P 1993 Growth regulatory properties of endothelins. *Peptides* **14** 385–99
- [52] Suzuki T, Hoshi H and Mitsui Y 1990 Endothelin stimulates hypertrophy and contractility of neonatal rat cardiac myocytes in a serum-free medium. *FEBS Lett* **268** 149–51
- [53] Ito H, Hirata Y, Hiroe M, Tsujino M, Adachi S, Takamoto T, Nitta M, Taniguchi K and Marumo F 1991 Endothelin-1 induces hypertrophy with enhanced expression of muscle-specific genes in cultured neonatal rat cardiomyocytes. *Circ Res* **69** 209–15

- [54] Carrier L, Boheler K R, Chassagne C, la Bastie de D, Wisnewsky C, Lakatta E G and Schwartz K 1992 Expression of the sarcomeric actin isogenes in the rat heart with development and senescence. *Circ Res* **70** 999–1005
- [55] Jiang H-K, Qiu G-R, Li-Ling J, Xin N and Sun K-L 2010 Reduced ACTC1 expression might play a role in the onset of congenital heart disease by inducing cardiomyocyte apoptosis. *Circ J* **74** 2410–8
- [56] Lompre A M, Nadal-Ginard B and Mahdavi V 1984 Expression of the cardiac ventricular alpha- and beta-myosin heavy chain genes is developmentally and hormonally regulated. *J Biol Chem* **259** 6437–46
- [57] Gunning P, O'Neill G and Hardeman E 2008 Tropomyosin-based regulation of the actin cytoskeleton in time and space. *Physiological Reviews* **88** 1–35
- [58] Tang W, Blair C A, Walton S D, Málnási-Csizmadia A, Campbell K S and Yengo C M 2016 Modulating Beta-Cardiac Myosin Function at the Molecular and Tissue Levels. *Frontiers in Physiology* **7** 659
- [59] Touvron M, Escoubet B, Mericskay M, Angelini A, Lamotte L, Santini M P, Rosenthal N, Daegelen D, Tuil D and Decaux J-F 2012 Locally expressed IGF1 propeptide improves mouse heart function in induced dilated cardiomyopathy by blocking myocardial fibrosis and SRF-dependent CTGF induction. *Disease Models & Mechanisms* **5** 481–91
- [60] Porter G A, Hom J, Hoffman D, Quintanilla R, de Mesy Bentley K and Sheu S-S 2011 Bioenergetics, mitochondria, and cardiac myocyte differentiation. *Prog. Pediatr. Cardiol.* **31** 75–81
- [61] Rosenblatt-Velin N, Lerch R, Papageorgiou I and Montessuit C 2004 Insulin resistance in adult cardiomyocytes undergoing dedifferentiation: role of GLUT4 expression and translocation. *FASEB J* **18** 872–4
- [62] Lopaschuk G D and Jaswal J S 2010 Energy metabolic phenotype of the cardiomyocyte during development, differentiation, and postnatal maturation. *J. Cardiovasc. Pharmacol.* **56** 130–40
- [63] Chung S, Dzeja P P, Faustino R S, Perez-Terzic C, Behfar A and Terzic A 2007 Mitochondrial oxidative metabolism is required for the cardiac differentiation of stem cells. *Nat Clin Pract Cardiovasc Med* **4 Suppl 1** S60–7
- [64] Cho Y M, Kwon S, Pak Y K, Seol H W, Choi Y M, Park D J, Park K S and Lee H K 2006 Dynamic changes in mitochondrial biogenesis and antioxidant enzymes during the spontaneous differentiation of human embryonic stem cells. *Biochem Biophys Res Commun* **348** 1472–8
- [65] St John J C, Ramalho-Santos J, Gray H L, Petrosko P, Rawe V Y, Navara C S, Simerly C R and Schatten G P 2005 The expression of mitochondrial DNA transcription factors during early cardiomyocyte in vitro differentiation from human embryonic stem cells. *Cloning Stem Cells* **7** 141–53