

AperTO - Archivio Istituzionale Open Access dell'Università di Torino

Single-Photon Emitters in Lead-Implanted Single-Crystal Diamond

This is a pre print version of the following article:

Original Citation:

Availability:

This version is available <http://hdl.handle.net/2318/1684828> since 2021-09-20T15:31:53Z

Published version:

DOI:10.1021/acsp Photonics.8b01013

Terms of use:

Open Access

Anyone can freely access the full text of works made available as "Open Access". Works made available under a Creative Commons license can be used according to the terms and conditions of said license. Use of all other works requires consent of the right holder (author or publisher) if not exempted from copyright protection by the applicable law.

(Article begins on next page)

Single-Photon Emitters in Lead-Implanted Single-Crystal Diamond

S. Ditalia Tchernij^{1,2}, T. Lühmann³, T. Herzig³, J. Küpper⁴, A. Damin⁵, S. Santonocito¹, M. Signorile⁵, P. Traina⁶, E. Moreva⁶, F. Celegato⁶, S. Pezzagna³, I.P. Degiovanni⁶, P. Olivero^{1,2}, M. Jakšić⁴, J. Meijer³, M. Genovese^{6,2}, J. Forneris^{2,4*}

¹Physics Department and "NIS" Inter-departmental Centre - University of Torino, Italy

²Istituto Nazionale di Fisica Nucleare (INFN), Sez. Torino, Italy

³Department of Nuclear Solid State Physics, University Leipzig, Germany

⁴Ruder Bošković Institute, Zagreb, Croatia

⁵Chemistry Department and "NIS" Inter-departmental Centre - University of Torino, Italy

⁶Istituto Nazionale di Ricerca Metrologica (INRiM), Italy

* corresponding author. Email: forneris@to.infn.it

Abstract

We report on the creation and characterization of Pb-related color centers in diamond upon ion implantation and subsequent thermal annealing. Their optical emission in photoluminescence (PL) regime consists of an articulated spectrum with intense emission peaks at 552.1 nm and 556.8 nm, accompanied by a set of additional lines in the 535-700 nm range. The attribution of the PL emission to stable Pb-based defects is corroborated by the correlation of its intensity with the implantation fluence of Pb ions, while none of the reported features is observed in reference samples implanted with C ions. Furthermore, PL measurements performed as a function of sample temperature (143-300 K range) and under different excitation wavelengths (532 nm, 514 nm, 405 nm) suggest that the complex spectral features observed in Pb-implanted diamond might be related to a variety of different defects and/or charge states.

This work follows from previous reports on optically active centers in diamond based on group IV impurities, such as Si, Ge and Pb. In perspective, a comprehensive study of this set of defect complexes could bring significant insight on the common features involved in their formation and opto-physical properties, thus offering a solid basis for the development of a new generation of quantum-optical devices.

Main text

Diamond is a promising platform for the development of solid state quantum devices with applications in quantum information processing and sensing [1-5]. In recent years, the search for optically active defects with appealing properties has led to the discovery of several classes of color centers [6-11] alternative to the widely investigated negatively charged nitrogen-vacancy complex (NV⁻ center) [12]. This is motivated by the fact that the NV⁻ defect, although extremely promising for its unique spin features [13], is limited in several applications by sub-optimal opto-physical properties such as a spectrally broad emission with intense phonon sidebands, the presence of charge state blinking, and a relatively low emission rate [14-16]. Particularly, the silicon-vacancy center (SiV) [17] has attracted significant attention due to a near transform-limited emission [18,19], good photon indistinguishability [19], the capability of coherently control its spin properties [21-24] and the emergence of reliable techniques for its deterministic fabrication [25-28].

The recent exploration of additional emitters related to group-IV impurities, such as the germanium-related (GeV) [29-31] and tin-related (SnV) color centers [32,33], characterized by similar defect structure and opto-physical properties to those of the SiV center (photo-stability, narrow zero-phonon line - ZPL, relatively small phonon coupling, high emission rate) brings further interest in this class of optically active defects. In particular, these recent discoveries open the question on whether the whole set of group-IV-based complexes (SiV, GeV, SnV, and now PbV) result in stable optically-active emitters, and secondly whether the properties of these color centers exhibit any common features.

In this work, we present the evidence of photoluminescence (PL) emission from color centers created upon the implantation of Pb ions in diamond followed by thermal annealing. To the best of the authors' knowledge, in a recent work [34] promisingly similar results were obtained from low-fluence Pb implantations in diamond, although with several differences which could be ascribed to different experimental conditions (excitation wavelengths, spectral filtering, measurement temperature).

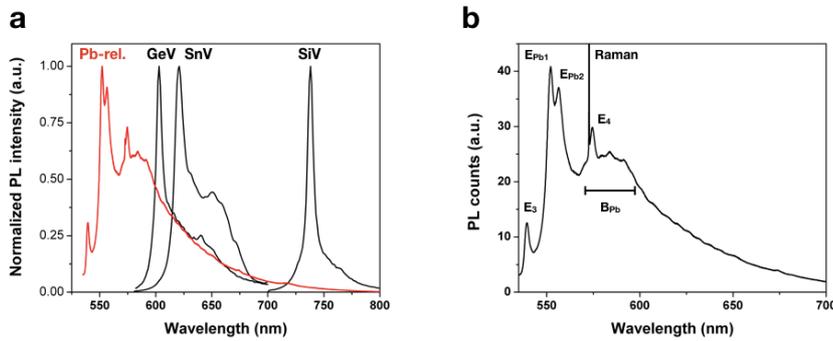


Figure 1: **a)** PL emission spectra from group-IV-related impurities upon ion implantation in the $1\text{-}10\times 10^{12}$ cm $^{-2}$ fluence range: SiV (ZPL at 738 nm), GeV (602 nm), SnV (620 nm) and the newly reported Pb-related (main emission line at ~ 552 nm, red curve) centers. **b)** Typical PL spectrum of a detector grade diamond substrate (Sample #1) implanted with 30 keV PbO $_2^-$ ions at a 2×10^{13} cm $^{-2}$ fluence.

Samples processing. The defects fabrication was performed by implanting 35 keV PbO $_2^-$ and 20 keV Pb $^-$ ions at different fluences in two CVD-grown single-crystal Ila diamond substrates supplied by ElementSix. The substrates were characterized respectively by “electronic” (substitutional N and B concentration: [N $_s$] < 5 ppb, [B $_s$] < 5 ppb, Sample #1 in the following) and “optical” ([N $_s$] < 1 ppm, [B $_s$] < 0.05 ppm, Sample #2) grades. The utilization of a PbO $_2^-$ beam was motivated by the low electron affinity of Pb, resulting in relatively small currents achievable for the implantation of elemental ions [35]. The chosen molecular beam thus ensured the achievement of relatively higher implantation fluences for the ensemble characterization of Pb-related defects. Additional implantations of group-IV related elements were performed to provide a suitable comparison in the present study: 50 keV Si $^-$ (5×10^{12} cm $^{-2}$ ion fluence, Sample #1), 40 keV Ge $^-$ (1×10^{13} cm $^{-2}$, Sample #2) and 60 keV Sn $^-$ (1×10^{12} cm $^{-2}$, Sample #1). The implantation was followed by a thermal annealing at 1200 °C in vacuum (2 hours) and by an oxygen plasma treatment, which ensured the removal of background fluorescence associated with graphitic and organic contaminations of the samples surface.

Room-temperature PL emission. A typical room-temperature PL spectrum acquired in confocal microscopy from an ensemble of centers in Sample #1 (2×10^{13} cm $^{-2}$ implantation fluence) under 532 nm laser excitation is reported in **Fig. 1** (red line), together with those of SiV (ZPL at 738 nm), GeV (602 nm), and SnV (620 nm) centers (black lines). The most apparent spectral features associated with Pb implantation (**Fig. 1b**) consist of an intense doublet at 552.1 nm (E $_{Pb1}$ peak in the following) and 556.8 nm (E $_{Pb2}$), followed by a broader emission band (B $_{Pb}$) roughly comprised between 565 nm and 600 nm. These spectral structures show a striking resemblance with that observed for the SiV, GeV and SnV centers, where the emission is mainly concentrated at the ZPL, with a less pronounced phonon sideband. Indeed, a common trend in the reported spectra is represented by the fact that the intensity of the phonon sidebands increases with for heavier impurities (**Fig. 1a**). Furthermore, the heaviest known group-IV-related center reported before the present work, i.e. the SnV defect, also displays a ZPLs doublet fine structure, indicating that the center could have a split ground (and/or excited) state. Apart from this, it is worth remarking that the ZPL wavelength does not follow a systematic red/blue-shift when considering progressively heavier impurities. In addition to the afore-mentioned spectral features, less intense sharp lines are observed at 539.4 nm and 574.5 nm (E $_3$ and E $_4$ peaks in the following).

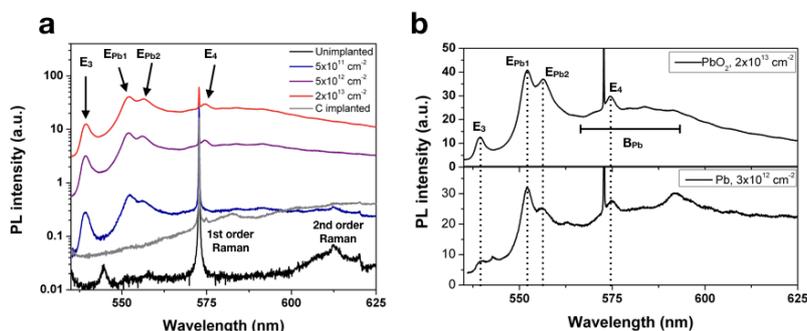


Figure 2: a) PL emission spectra of PbO_2^- -implanted diamond (Sample #1) at increasing ion fluences in the $5\text{--}200 \times 10^{11} \text{ cm}^{-2}$ range. Additional PL spectra acquired from different regions of the same substrate are reported for sake of comparison: unirradiated diamond (black line), and implanted with 15 keV C^- ($3 \times 10^{15} \text{ cm}^{-2}$ fluence, gray line) b) PL spectra of diamond implanted with 30 keV PbO_2^- (Sample #1) 15 keV Pb^- ions (Sample #2), respectively at $2 \times 10^{13} \text{ cm}^{-2}$ and $3 \times 10^{12} \text{ cm}^{-2}$ fluences.

A spectral feature similar to the E_3 line has previously been reported in natural diamond upon ion irradiation and high temperature ($>1400 \text{ }^\circ\text{C}$) annealing, and tentatively attributed to interstitial-carbon-related defect complexes [16]. However, these previous observations were limited to the cathodoluminescence regime and the lack of clear evidence of its activity under PL excitation cannot rule out the attribution of the E_3 spectral line to a Pb-related defect. Only measurements at the single-photon emission level could provide an insight in the correlation of the E_3 PL peak with the $E_{\text{Pb1}}\text{--}E_{\text{Pb2}}$ emission lines.

Conversely, the E_4 emission is not reported in previous works, to the best of the authors' knowledge. Its spectral position within the B_{pb} band might suggest a similar role to the 640.8 nm peak observed for the GeV center [30]. According to this interpretation, the E_4 line would be related to the E_{Pb1} emission by a phonon component of $\sim 80 \text{ meV}$ (i.e. $\sim 705 \text{ cm}^{-1}$).

Attribution to Pb-related lattice defects. In order to attribute the spectral features reported in **Fig. 1** to Pb-related color centers, in Sample #1 we correlated the intensity of the PL emission with the implantation fluence in the $5\text{--}200 \times 10^{11} \text{ cm}^{-2}$ range. The corresponding PL spectra are shown in **Fig. 2a**. The afore-mentioned $E_{\text{Pb1}}\text{--}E_{\text{Pb2}}$ and B_{pb} features are absent in the spectrum acquired from a pristine reference region of the substrate, and conversely they exhibit a systematically increasing intensity at increasing implantation fluences. Furthermore, the absence of the E_{Pb1} , E_{Pb2} lines is apparent in a control spectrum acquired from a region of the same diamond substrate, implanted with 15 keV C^- ions ($3 \times 10^{15} \text{ cm}^{-2}$ fluence, **Fig. 2a**). It is also worth remarking that the E_{Pb1} and E_{Pb2} emission lines have never been observed in previous reports on diamond plates implanted with light (H, He) or carbon ions, as well as with other heavier ion species [5,6,16,36], thus indicating that these spectral features cannot be attributed to intrinsic radiation-induced defects and that the Pb impurities are directly involved in the formation of stable color centers.

Pb^- vs PbO_2^- ion implantation. The afore-mentioned data were acquired on a PbO_2^- -implanted substrate. We show in **Fig. 2b** that the reported spectral features (E_{Pb1} , E_{Pb2} , E_3 , E_4) are left unchanged for both PbO_2^- and Pb^- ion implantations. This represents an additional experimental evidence that confirms their attribution to Pb-related optical centers, and that the presence of implanted O ions does not modify the relevant emission features. This result also has a significant technical relevance, as it confirms the possibility of fabricating Pb-related color centers with PbO_2^- ions, i.e. by taking advantage of more stable ion beams and higher currents.

Temperature-dependent PL emission. In order to better investigate the fine structure of the spectral features observed in Pb-implanted diamond, PL spectra under 514 laser excitation were acquired at temperatures in the range comprised between 143 K (**Fig. 3a**) and 273 K (**Fig. 3b**). As typically observed in low-temperature PL experiments, the E_{Pb1} , E_{Pb2} , E_3 and E_4 PL peaks increase in intensity and reduce their spectral width with respect to room temperature. All the relevant Pb-related emission peaks displayed a blue shift at decreasing temperature (**Fig. 3c-3e**). This observation is in agreement with the attribution of the PL peaks to stable lattice defects, whose chemical bonds are shortened at decreasing temperature [37]. It is worth noting that the main emission peak E_{Pb1} overlaps with the first-order Raman line (552.4 nm) under 514 nm excitation at 273 K, and its spectral position can be accurately determined only at temperatures below 233 K. As temperature decreases, its position reaches a value of 550.9 nm at 143 K; similarly, at the same temperature the E_{Pb2} and

the E_4 peak blue-shift to 554.9 nm and 573.7 nm (**Fig. 3c**), respectively. None of these emissions exhibits a fine structure in the probed temperature range. Conversely, the E_3 peak reveals a splitting in two separate lines (537.5 nm and 538.2 nm at 143 K, **Fig. 3d**). An additional emission peak located at ~592 nm is superimposed to the second-order Raman scattering (~590-600 nm), and lies in the same spectral position of radiation-induced defects in diamond based on interstitial atoms [38]. Therefore an estimation of its intensity trend at decreasing temperatures and its unambiguous interpretation in relation to the E_{Pb1} - E_{Pb2} lines was not possible.

Finally **Fig. 3a** shows the presence of two additional spectral lines (640.4 nm and 649.8 nm, E_5 and E_6 in the following) at 143 K, which could not be observed at room temperature. Consistently with the above reported peaks, these spectral features also exhibit a blue-shift at decreasing temperatures. Furthermore, they were also detected under 405 nm laser excitation, as will be discussed in the following.

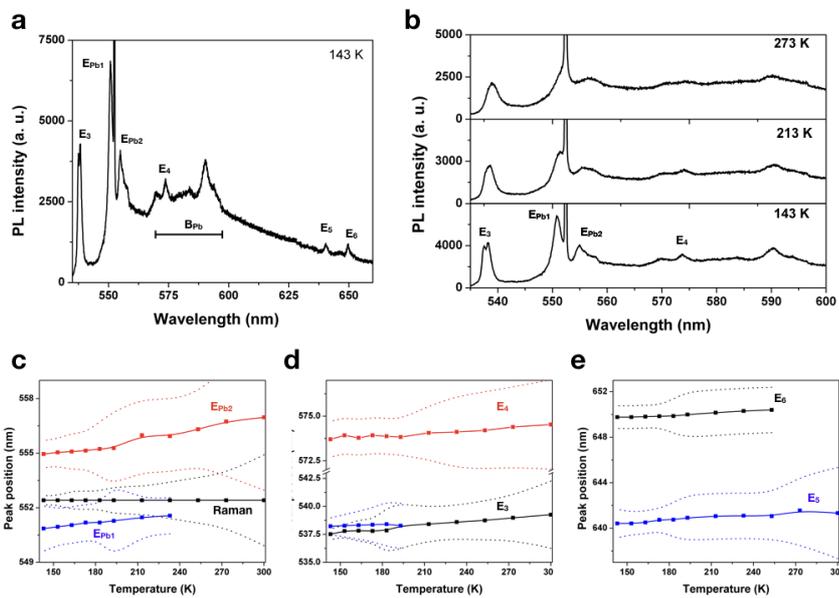


Figure 3: Temperature-dependent PL spectroscopy from PbO_2^- implanted diamond: **a)** PL spectrum under 514 nm laser excitation at 143 K. **b)** Pb-related emission in the 535-600 nm spectral range at 273 K, 213 K, 143 K; temperature-dependent ZPL position of **c)** E_{Pb1} , E_{Pb2} , and first-order Raman emission; **d)** E_3 emission, with fine structure at $T < 200$ K, and E_4 emission; **e)** E_5 , E_6 emissions. The dotted lines delimit the peaks' FWHM of the corresponding lines.

PL under 405 nm laser excitation. **Fig. 4** shows a typical PL spectrum in the 535-675 nm range acquired under 405 nm laser excitation. The E_{Pb1} , E_{Pb2} , E_3 peaks are still visible, although with a reduced intensity with respect to the E_4 spectral line. It is worth mentioning that E_{Pb1} and E_{Pb2} are convoluted due to the limited spectral resolution of the experimental system adopted for these measurements (~4 nm). The presence of the relevant Pb-related lines confirm the excitability of the optical centers at >3 eV excitation energy.

Furthermore, an intense emission from the previously mentioned E_5 (641.8 nm at room temperature) and E_6 (647.8 nm) peaks, together with an additional feature at 670.8 nm, is evident. These lines are not observable under 532 nm and 514 nm excitations at room temperature and barely detectable at 143 K under the same excitation wavelengths, while they instead represent the main spectral components of an articulated series of peaks in the 600-700 nm range under 405 nm excitation. While several radiation-induced defects have been studied in this spectral region [16], to the best of the authors' knowledge no simultaneous detection of both E_5 and E_6 has been reported in the scientific literature, to the best of the authors' knowledge. Therefore, their attribution to Pb-related defects cannot be ruled out, although such an attribution is still fairly tentative and undoubtedly requires further verification. The significant increase in the E_5 and E_6 lines intensity under higher excitation energy might also suggest their interpretation as a different charge state of the same defect(s) associated with the E_{Pb1} - E_{Pb2} emission.

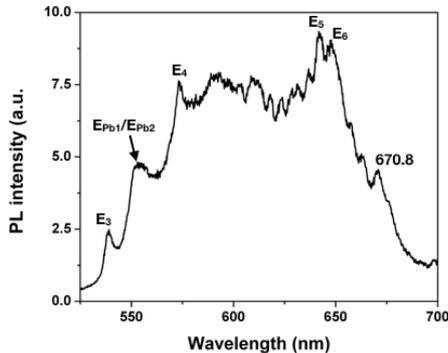


Figure 4: Ensemble PL emission from Sample #1 (PbO_2^- implantation fluence: $2 \times 10^{13} \text{ cm}^{-2}$) acquired under 405 nm laser excitation.

The spectral separation of the E_{Pb1} and E_{Pb2} emission lines is apparent at room temperature. Should their attribution to the same optical center be confirmed by further studies at the single-photon emitter level, it is worth remarking that such energy difference ($\sim 16 \text{ meV}$) is smaller than the energy of quasi-local vibration expected for a Pb-related center (estimated as $\sim 21 \text{ meV}$ for ^{208}Pb [16,32,39]) and therefore could be interpreted in terms of a significant splitting of the excited state levels of the defect [33]. Under this (yet to be demonstrated) hypothesis, the energy difference between the E_{Pb1} and E_{Pb2} spectral components at 143 K would correspond to a $\sim 3900 \text{ GHz}$ between the split levels of the excited state. Notably, this value lies in the same range as that identified for the energy splitting of the excited state of the SnV center ($\sim 3000 \text{ GHz}$ [33]). Such similarity is somewhat surprising, as a significant increase in the ground-state splitting for the other group-IV-related color centers in diamond could be expected, the spin-orbit coupling constant increasing with the atomic number of the impurity [40]. An additional open question is represented by the attribution of the E_3 emission. On one hand, it cannot be ruled out that this peak corresponds to a secondary center, which anneals out at higher temperatures, similarly to the 593.5 nm emission in Sn-implanted diamond [32,33]. On the other hand, its splitting at low temperatures might also indicate a common origin from the very same Pb defect responsible for the E_{Pb1} and E_{Pb2} emissions. This hypothesis might be supported by the observation of a $\sim 750 \text{ GHz}$ splitting the E_3 emission, i.e. comparable with what observed for the ground state of the SnV center ($\sim 850 \text{ GHz}$, [33]). Conversely, according to this interpretation the significant energy difference ($\sim 55 \text{ meV}$) between the E_{Pb1} and the E_3 peaks would imply the existence of additional physical effects, to be identified only by means of a dedicated modeling of the defect structure.

Conclusions. We reported on the formation of optically-active centers in diamond upon the introduction of Pb impurities by ion implantation. The emission intensity of the observed PL lines in the 535-675 nm spectral range strongly correlates with the implantation fluence, thus providing a solid indication that such emission originates from stable Pb-containing lattice defects. The number of emission peaks and the complexity of the PL spectra do not enable, on the basis of the current set of measurement, an unambiguous attribution of each one of the observed spectral features to specific defects and corresponding electronic configurations. The most intense emission peaks at room temperature are located at 552.1 nm (E_{Pb1}) and 556.8 nm (E_{Pb2}), and could possibly correspond to a significant splitting of the defect ground state, related to the high atomic number of the Pb impurity. The relation of such emission lines with additional spectral features, including a doublet at 539.4 nm and a peak at 574.5 nm, is currently unclear. Furthermore, two PL peaks at 641.8 and 647.8 nm (E_5, E_6), barely excitable under 514 nm excitation and conversely displaying an intense luminescence under 405 nm excitation, could consist of an alternative charge state of the very same defect responsible for the E_{Pb1} - E_{Pb2} emission lines. On the basis of these results, a full understanding of the spectral features of Pb-related defects comparatively with the available reports on the other group-IV impurities seems not straightforward. A disambiguation on the photo-physical properties of these defects will require a thorough comparison with dedicated theoretical modeling and simulations of the defect's structure, additional spectral analysis on a wider temperature range and most importantly an unambiguous characterization of the centers at the single-photon emitter level.

These results represent a significant step towards completing the picture on the optical activity of diamond defects related to group IV impurities. Future studies on the defects' properties at the single-photon emitter level could lead to appealing perspectives in the fields of applied sciences and quantum information processing. Furthermore, from a fundamental point of view, the mapping and thorough understanding of a general pattern in the opto-physical properties of color centers associated with impurities of the whole group IV could provide an important reference for the study of defects related to other chemical species.

Acknowledgements

This research activity was supported by the following projects: "DIESIS" project funded by the Italian National Institute of Nuclear Physics (INFN) - CSN5 within the "Young research grant" scheme; Coordinated Research Project "F11020" of the International Atomic Energy Agency (IAEA); EMPIR Project. No. 17FUN06 "SIQUST" and 17FUN01 "BECOME" (the EMPIR initiative is co-funded by the EU H2020 and the EMPIR Participating States).

T.L., S.P. and J.M. gratefully acknowledge the support of VolkswagenStiftung. S.D. gratefully acknowledges the "Erasmus Traineeship 2016-2017" program for the financial support to the access to the ion implantation facilities of the University of Leipzig. P.O. acknowledges support from the project "Departments of Excellence" (L. 232/2016), funded by the Italian Ministry of Education, University and Research (MIUR).

References

- [1] S. Praver, I. Aharonovich, *Quantum Information Processing with Diamond: Principles and Applications*. (Woodhead Publishing, 2014).
- [2] I. Aharonovich, D. Englund, M. Toth, *Solid-state single-photon emitters*, *Nature Photonics* 10, 631–641 (2016) doi:10.1038/nphoton.2016.186.
- [3] S. Pezzagna, D. Rogalla, D. Wildanger, J. Meijer, A. Zaitsev, *Creation and nature of optical centres in diamond for single-photon emission—overview and critical remarks*, *New J. Phys.* 13 (2011) 035024.
- [4] T. Schröder, S. L. Mouradian, J. Zheng, M. E. Trusheim, M. Walsh, E. H. Chen, L. Li, I. Bayn, D. Englund, *Quantum nanophotonics in diamond*, *J. Opt. Soc. Am. B* 33 (4) (2016) B65.
- [5] J.O. Orwa, A.D. Greentree, I. Aharonovich, A.D.C. Alves, J. Van Donkelaar, A. Stacey, S. Praver, *Fabrication of single optical centres in diamond—a review*, *J. Lumin* 130 (2010) 1646.
- [6] J. Forneris, A. Tengattini, S. Ditalia Tchernij F. Picollo, A. Battiato, P. Traina, I.P. Degiovanni, E. Moreva, G. Brida, V. Grilj, N. Skukan, M. Jakš, M. Genovese, P. Olivero, *Creation and characterization of He-related color centers in diamond*, *J. Lumin.* 179, 59 (2016). doi: 10.1016/j.jlumin.2016.06.039.
- [7] R. Sandstrom, L. Ke, A. Martin, Z. Wang, M. Kianinia, Ben Green, B.b Gao, I. Aharonovich, *Optical properties of implanted Xe color centers in diamond*, *Optics Communications* 411 (2018) 182–186
- [8] R. John, J. Lehnert, M. Mensing, D. Spemann, S. Pezzagna J. Meijer, *Bright optical centre in diamond with narrow, highly polarised and nearly phonon-free fluorescence at room temperature*, *New J. Phys.* 19 (2017) 053008. doi: 10.1088/1367-2630/aa6d3f.
- [9] T. Gaebel, I Popa, A Gruber, M Domhan, F Jelezko, J Wrachtrup, *Stable single-photon source in the near infrared*, *New Journal of Physics* 6 (2004) 98. doi:10.1088/1367-2630/6/1/098.
- [10] I. Aharonovich, S. Castelletto, D. A. Simpson, A. Stacey, J. McCallum, A. D. Greentree, S. Praver, *Two-Level Ultrabright Single Photon Emission from Diamond Nanocrystals*, *Nano Letters* 9 (2009) 3191. doi: 10.1021/nl9014167
- [11] D Gatto Monticone, P Traina, E Moreva, J Forneris, P Olivero, I P Degiovanni, F Taccetti, L Giuntini, G Brida, G Amato, M Genovese, *Native NIR-emitting single colour centres in CVD diamond*, *New Journal of Physics* 16 (2014) 053005. doi: 10.1088/1367-2630/16/5/053005.
- [12] M.W. Doherty, N.B. Manson, P. Delaney, F. Jelezko, Jörg Wrachtrup, and L.C.L. Hollenberg, *The nitrogen-vacancy colour centre in diamond*, *Physics Reports* 528, 1 (2013).
- [13] J. R. Maze, P.L. Stanwix, J.S. Hodges, S. Hong, J.M. Taylor, P. Cappellaro, L. Jiang, M.V.G. Dutt, E. Togan, A.S. Zibrov, A. Yacoby, R.L. Walsworth, M.D. Lukin, *Nanoscale magnetic sensing with an individual electronic spin in diamond*, *Nature* 455, 644 (2008).
- [14] T. Müller, I. Aharonovich, L. Lombez, Y. Alaverdyan, A. N. Vamivakas, S. Castelletto, F. Jelezko, J. Wrachtrup, S. Praver, M. Atatüre, *Wide-range electrical tunability of single-photon emission from chromium-based colour centres in diamond*, *New J. Phys.* 13 (2011) 075001.
- [15] J. Storteboom, P. Dolan, S. Castelletto, X. Li, and M. Gu, *Lifetime investigation of single nitrogen vacancy centres in nanodiamonds*, *Optics Express* 23, 11327 (2015).
- [16] A.M. Zaitsev, *Optical properties of Diamond* (Springer, New York, 2001).
- [17] C. Wang, C. Kurtsiefer, H. Weinfurter, B. Burchard, *Single photon emission from SiV centres in diamond produced by ion implantation*, 2006 *J. Phys. B: At. Mol. Opt.* 39 37.
- [18] K. Li, Y. Zhou, A. Rasmata, I. Aharonovich, W. B. Gao, *Nonblinking Emitters with Nearly Lifetime-Limited Linewidths in CVD Nanodiamonds*, *Phys. Rev. Applied* 6 (2016) 024010.
- [19] L. J. Rogers, K.D. Jahnke, T. Teraji, L. Marseglia, C. Müller, B. Naydenov, H. Schaffert, C. Kranz, J. Isoya, L.P. McGuinness, F. Jelezko, *Multiple intrinsically identical single-photon emitters in the solid state*, *Nat. Commun.* 5 (2014) 4739.
- [20] A. Sipahigil, K. D. Jahnke, L. J. Rogers, T. Teraji, J. Isoya, A. S. Zibrov, F. Jelezko, M. D. Lukin, *Indistinguishable Photons from Separated Silicon-Vacancy Centers in Diamond*, *Phys. Rev. Lett.* 113, 113602 (2014)
- [21] L. J. Rogers, K. D. Jahnke, M. H. Metsch, A. Sipahigil, J. M. Binder, T. Teraji, H. Sumiya, J. Isoya, M. D. Lukin, P. Hemmer,

F. Jelezko, *All-Optical Initialization, Readout, and Coherent Preparation of Single Silicon-Vacancy Spins in Diamond*, Phys. Rev. Lett. 113, 263602 (2014).

[22] T. Müller, C. Hepp, B. Pingault, E. Neu, S. Gsell, M. Schreck, H. Sternschulte, D. Steinmüller-Nethl, C. Becher, M. Atatüre, *Optical signatures of silicon-vacancy spins in diamond*, Nat. Commun. 5 (2014) 3328.

[23] J. N. Becker, J. Görlitz, C. Arend, M. Markham, C. Becher, *Ultrafast all-optical coherent control of single silicon vacancy colour centres in diamond*, Nat. Commun. 7 (2016) 13512.

[24] Y. Zhou, A. Rasmita, K. Li, O. Xiong, I. Aharonovich, W.-b-Gao, *Coherent control of a strongly driven silicon vacancy optical transition in diamond*, Nat. Commun. 8 (2017) 14451.

[25] J. Riedrich-Möller, C. Arend, C. Pauly, F. Mücklich, M. Fischer, S. Gsell, M. Schreck, C. Becher, *Deterministic, Coupling of a Single Silicon-Vacancy Color Center to a Photonic Crystal Cavity in Diamond*, Nano Lett., 14(9) (2014) 5281.

[26] T. Schröder, M. E. Trusheim, M. Walsh, L. Li, J. Zheng, M. Schukraft, A. Sipahigil, R. E. Evans, D. D. Sukachev, C. T. Nguyen, J. L. Pacheco, R. M. Camacho, E. S. Bielejec, M. D. Lukin, D. Englund, *Scalable focused ion beam creation of nearly lifetime-limited single quantum emitters in diamond nanostructures*, Nat. Commun. 8, 15376 (2017).

[27] L. Marseglia, K. Saha, A. Ajoy, T. Schröder, D. Englund, F. Jelezko, R. Walsworth, L. Pacheco, D. L. Perry, E. S. Bielejec, P. Cappellaro, *Bright nanowire single photon source based on SiV centers in diamond*, Optics Express 26 (2018) 81.

[28] S. Lagomarsino, A. M. Flatae, S. Sciortino, F. Gorelli, M. Santoro, F. Tantussi, F. De Angelis, N. Gelli, F. Taccetti, L. Giuntini, M. Agio, *Optical properties of silicon-vacancy color centers in diamond created by ion implantation and post-annealing*, Diam. Relat. Mater. 84 (2018) 196.

[29] T. Iwasaki, F. Ishibashi, M. Miyamoto, Y. Doi, S. Kobayashi, T. Miyazaki, K. Tahara, K. D. Jahnke, L. J. Rogers, B. Naydenov, F. Jelezko, S. Yamasaki, S. Nagamachi, T. Inubushi, N. Mizuochi, M. Hatano, *Germanium-Vacancy Single Color Centers in Diamond*, Sci. Rep. 5 (2016) 12882.

[30] Y. N. Palyanov, I. N. Kupriyanov, Y. M. Borzdov, N. V. Surovtsev, *Germanium: a new catalyst for diamond synthesis and a new optically active impurity in diamond*, Sci. Rep. 5 (2015) 14789.

[31] P. Siyushev, M. H. Metsch, A. Ijaz, J. M. Binder, M. K. Bhaskar, D. D. Sukachev, A. Sipahigil, R. E. Evans, C. T. Nguyen, M. D. Lukin, P. R. Hemmer, Y. N. Palyanov, I. N. Kupriyanov, Y. M. Borzdov, L. J. Rogers, F. Jelezko, *Optical and microwave control of germanium-vacancy center spins in diamond*, Phys. Rev. B 96, 081201 (2017).

[32] S. Ditalia Tchernij, T. Herzog, J. Forneris, J. Meijer, P. Olivero, *Single-Photon-Emitting Optical Centers in Diamond Fabricated upon Sn Implantation*, ACS Photonics 2017, 4, 2580.

[33] T. Iwasaki, Y. Miyamoto, T. Taniguchi, P. Siyushev, M. H. Metsch, F. Jelezko, M. Hatano, *Tin-Vacancy Quantum Emitters in Diamond*, Phys. Rev. Lett. 119, 253601 (2017).

[34] M. E. Trusheim, N. H. Wan, K. C. Chen, C. J. Ciccarino, R. Sundararaman, G. Malladi, E. Bersin, M. Walsh, B. Lienhard, H. Bakhru, P. Narang, D. Englund, *Lead-Related Quantum Emitters in Diamond*, arXiv:1805.12202 (2018).

[35] R. Middleton, "A negative ion cookbook." *University of Pennsylvania* (1989).

[36] A. Lohrmann, S. Pezzagna, I. Dobrinets, P. Spinicelli, V. Jacques, J.-F. Roch, J. Meijer, A.M. Zaitsev, *Diamond based light-emitting diode for visible single-photon emission at room temperature*, Appl. Phys. Lett. 99 (2011) 251106.

[37] M. W. Doherty, V. M. Acosta, A. Jarmola, M. S. J. Barson, N. B. Manson, D. Budker, and L. C. L. Hollenberg, *Temperature shifts of the resonances of the NV center in diamond*, Phys. Rev. B 90, 041201 (2014).

[38] A. M. Zaitsev, *High energy ion implantation into diamond and cubic boron nitride*, Nucl. Instr. Meth. B 62 (1991) 81.

[39] R. Brout, W. Visscher, *Suggested Experiment on Approximate Localized Modes in Crystals*, Phys. Rev. Lett. 9 (1962) 54.

[40] C. D. Clark, H. Kanda, I. Kiflawi, G. Sittas, *Silicon defects in diamond*, Phys. Rev. B 51, 16681 (1995).

Formatted: English (U.S.)

Formatted: English (U.S.)

Formatted: English (U.S.)

Formatted: English (U.S.)

Formatted: Portuguese (Portugal)

Formatted: English (U.S.)

Formatted: English (U.S.)