

Citation: Lastname, F.;
Lastname, F.; Lastname, F. Title.
Heritage 2021, 4, Firstpage–
Lastpage.
<https://doi.org/10.3390/xxxxx>

Academic Editor: Firstname
Lastname

Received: date
Accepted: date
Published: date

Publisher's Note: MDPI stays
neutral with regard to
jurisdictional claims in published
maps and institutional
affiliations.



Copyright: © 2021 by the authors.
Submitted for possible open
access publication under the
terms and conditions of the
Creative Commons Attribution
(CC BY) license
(<https://creativecommons.org/licenses/by/4.0/>).

Article

A multi-analytical study of an ancient Egyptian limestone stela for knowledge and conservation purposes: recovering hieroglyphs and figurative details by image analysis

Tiziana Cavaleri ^{1, 2}, Stefano Legnaioli ^{3, *}, Francesca Lozar ⁴, Cesare Comina ⁴, Federico Poole ⁵, Claudia Pelosi ², Alessia Spoladore ⁶, Daniele Castelli ⁴, and Vincenzo Palleschi ³

¹ Fondazione Centro Conservazione e Restauro dei beni culturali La Venaria Reale Venaria Reale, Turin, Italy; tiziana.cavaleri@centrorestaurovenaria.it

² Università degli Studi della Tuscia, Viterbo, Italy; tiziana.cavaleri@unitus.it; pelosi@unitus.it

³ ICCOM-CNR, Pisa, Italy, stefano.legnaioli@cnr.it; vincenzo.palleschi@cnr.it

⁴ Università degli Studi di Torino, Dipartimento di Scienze della Terra, Turin, Italy, francesca.lozar@unito.it; cesare.comina@unito.it; daniele.castelli@unito.it

⁵ Museo Egizio, Dipartimento collezione e ricerca, Turin, Italy, federico.poole@museoegizio.it

⁶ Freelance Conservator, Turin, Italy, alessia.spoladore@gmail.com

* Correspondence: stefano.legnaioli@cnr.it; Tel.: (+39 050 315222)

Abstract: A multi-analytical study was carried out on an ancient Egyptian limestone stela with red figures and hieroglyphs (S. 6145) coming from the village of Deir el-Medina and belonging to the collection of the Museo Egizio (Turin, Italy). With the support of a multidisciplinary team, a project for the preservation and conservation of this stela provided an opportunity to carry out a very detailed study of the object. Petrographic and mineralogical analysis led to the characterization and dating of the limestone, and ultrasound-based techniques were of great help in shedding light on the state of preservation of the stela, as a preliminary to planning conservation treatment. The chemical nature of the red pigment was investigated by noninvasive spectroscopic analyses. Multispectral imaging and statistical image processing improved the readability of the hieroglyphs, whose preservation ranged from heavily compromised to almost completely invisible, revealing some signs that had previously not been visible.

Keywords: Multispectral Imaging (MSI); statistical image processing; hieroglyphs recovering; noninvasive spectroscopy; petrographical, mineralogical, and micropaleontological analyses; ultrasonic measurements; limestone; Ancient Egypt; commemorative stela; conservation.

1. Introduction

The Museo Egizio in Turin, Italy, houses one of the most important collections of ancient Egyptian antiquities in the world. Its two main sources are the Drovetti collection, purchased in 1824, and artifacts from a number of excavations conducted in Egypt by the director of the museum, Ernesto Schiaparelli, between 1903 and 1920, and by his successor, Giulio Farina, in the 1930s. Interdisciplinary investigations of this collection relying on collaborations with research and conservation institutions are at the forefront of the Museo Egizio's current engagements.

The museum holds a limestone stela (S. 6145, Figure 1) of which only the upper part is preserved. It comes from the village of Deir el-Medina. This site is located in Upper

Egypt in a valley behind the hill of Qurnet Murrain, on the left bank of the Nile, south-west of Sheikh-abd el-Qurna, facing the city of Thebes.

The village of Deir el-Medina was active throughout the New Kingdom (from the Eighteenth to the Twentieth Dynasty, 1539-1076 BC). It housed the workers employed to build the tombs of the Valley of the Kings and the Valley of the Queens. The stele was discovered during the 1905 campaign of the Italian Mission led by Ernesto Schiaparelli at Deir el-Medina, and brought to the Museo Egizio in Turin in the framework of the sharing system (*"partage"*) regulating foreign excavations in Egypt at the time. Its provenance has been repeatedly stated to be chapel D in the sanctuary of Meretseger, south of the village along the path between Deir el-Medina and the Valley of the Queens [1-3]. However, the stele's "high" inventory number suggests that it does not belong to the lot of objects excavated here by the Italian Mission, which only encompass nos. S. 5987-6067 [4]. A provenance from the excavations conducted north of the village, in the area of the Ptolemaic temple, seems more likely [5].

Given its place of discovery and presumed function, the stele S. 6145 is considered to be a commemorative stele. Steles are most often found in tombs, where they evoked the main rite that ensured the connection of the deceased and the world of the living, namely, the bringing by the latter of the offerings that would allow the deceased's survival in the afterlife. Other steles, like this one, were instead made for votive purposes, to honour the gods. Their typological features are not different from those of funeral steles, but their location and function are different: they are found inside temples or shrines, rather than in tombs, and dedicated to the main deities of these places of worship.

As for the representation, the numerous traces of red hieroglyphs and figures present respectively in the upper and underlying register of the stele appear to be faded and almost illegible. Due to its state of preservation, the documentary value of the stele, already partially compromised by the difficulty of reading especially the upper register, was exposed to further risk by a horizontal crack, which threatened to cause the detachment of a large fragment decorated with hieroglyphs. Similar loss of material had already affected much of the upper arched profile in the past.

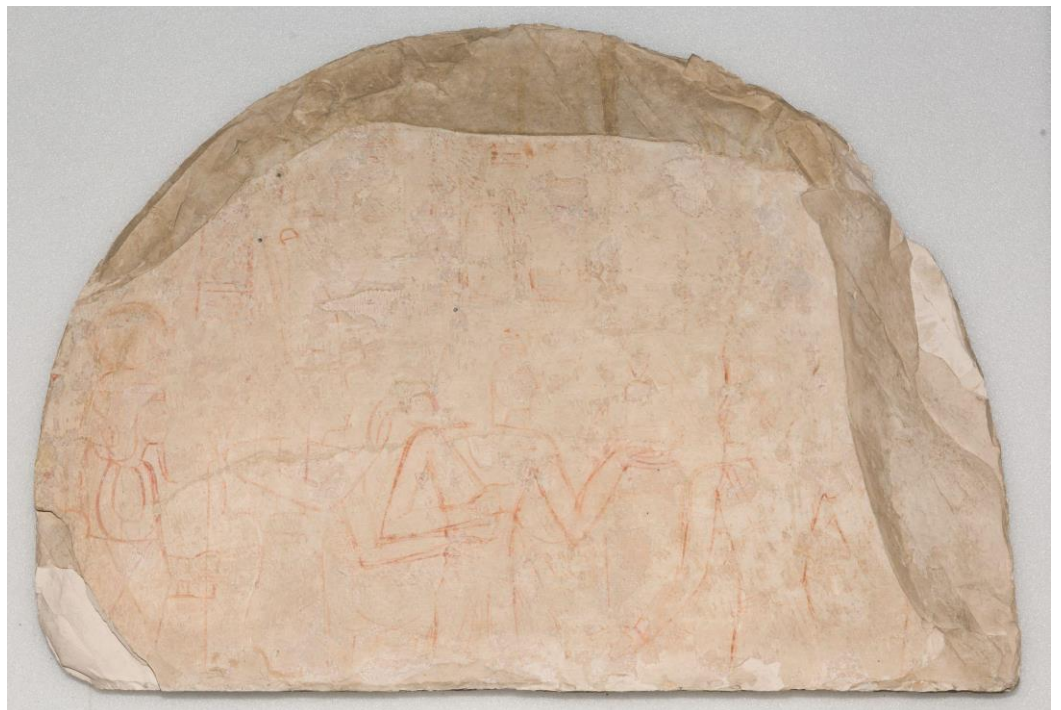


Figure 1. Stele from the village of Deir el-Medina. Turin, Museo Egizio, S. 6145. Photograph taken after the conservation treatment.

This article starts from the multi-analytical study - material, technical, and Egyptological - conducted with the aim of preserving and investigating this object by a multidisciplinary team from the University of Turin (UNITO), the Museo Egizio in Turin, and the Fondazione Centro per la Conservazione e il Restauro dei Beni Culturali La Venaria Reale (CCR), with the collaboration of the Institute of Chemistry of Organometallic Compounds of the Italian National Research Council (ICCOM-CNR) in Pisa [6]. In this study, a conservation treatment aimed at guaranteeing the transmission to others of the contents of a cultural document called for appropriate diagnostic investigations to guide the consolidation treatment and allow the handling and cleaning of the artifact.

Specifically, we needed to investigate the constituent material to verify its intrinsic characteristics and assess the level of risk that cracking posed to the physical integrity of the artifact. Close observation to reveal the execution technique of the stela, the signs of working of the stone, and the original grouts, served as a guide for the following microscope investigations on micro-samples of stone and grouting that underwent petrographical, mineralogical, and micropaleontological analyses [6].

The study of the crack required the stele to be analyzed with ultrasonic-based techniques. When working on cultural heritage, tests and analyses of the integrity of a medium must be carried out with non-destructive techniques. Ultrasonic investigations are therefore among the most frequently adopted to evaluate deterioration and detect areas of structural weakness [7, 8]. The method is based on the analysis of the apparent propagation velocity of an ultrasonic impulse within the medium. This velocity is obtained from the ratio between the distance of the travel path (the straight distance between the transmitting and the receiving probes) and the travel time measured by the instrumentation. The presence of altered material along the travel path results in a decrease in the apparent propagation velocity of the ultrasonic impulses. Analyzing the ultrasonic propagation on a dense pattern of paths can therefore highlight the distribution of the velocities and consequently detect altered portions within the body, in this case fundamental for knowing the state of preservation of the stele.

Furthermore, we carried out a detailed surface study to spot traces of drawings no longer visible to the naked eye, but possibly by other means, in order to prevent the risk of removing them during cleaning. This required the use of spectroscopic analysis for investigating the nature of the red pigment, and of multiband imaging and statistical image processing for improving the readability of the hieroglyphs.

2. Materials and Methods

2.1. Materials

The object of this study and analysis is the limestone stele S. 6145 (see Figure 1), a large fragment of wall decoration measuring approximately 100 x 100 x 15 cm and belonging to the Museo Egizio collections. Only the upper portion of this arched-top stela is preserved. It shows numerous traces of red figures and hieroglyphs which appear to be faded and almost illegible, a preparatory drawing for carving in relief. At close observation the lower side of the artifact appeared to be crossed horizontally by a long crack, following the sedimentary stratification of the stone. This crack intersected the figures and threatened their preservation.

In addition, 4 samples were studied and analyzed. Two of them (samples 1 and 3) were not taken from the stele, being previously detached fragments received with the object. One of them (sample 2) was taken from the reverse of the stele, whereas one (sample 4) comes from an original grouting on the front of the stele.

2.2 Experimental study and methods

One step of the experimental study investigated the nature and state of preservation of the support and the related aspects of technique of execution (signs of working, original groutings). This step was carried out with a multi-technical approach in particular with Scanning Electron Microscopy-Energy Dispersive X-ray Spectroscopy (SEM-EDS) and X-Ray Diffraction (XRD) analyses on samples and with noninvasive ultrasonic measurements on the stele, the latest aimed at better specifying the extent and entity of the fractured zone and verify the presence of further discontinuities nonvisible to the naked eye.

Specifically, samples 1, 2, and 3 were investigated with petrographical, mineralogical, and micropaleontological analyses at the Department of Earth Sciences of the University of Turin. For SEM-EDS tests, the samples were mounted on stubs and analyzed with a JEOL JSM IT300LV (High Vacuum - Low Vacuum 10/650 Pa - 0.3-30kV) Scanning Electron Microscope equipped with an EDS Oxford INCA Energy 200 microanalysis and an INCA X-act SDD thin window detector. For a micropaleontological investigation of the calcareous nannofossil content, smear slides were prepared with the standard technique [9] and observed at 1250X in transmitted light with a B50X Olympus polarized microscope.

Sample 4 was analyzed by XRD. The analysis was carried out with a Rigaku Miniflex II with a high frequency X-ray tube with a copper anode, powered by a 30 kV and 15 mA fixed current. The vertical goniometer has a radius of 150 mm and a 2theta measuring range between -3° and 145° . The detector is a NaI (Ti) scintillator counter, 23 mm in diameter. The spectra acquisition were made with the MDI Jade 9.0 software.

Ultrasonic measurements were executed on the stele with a dense grid of measuring points. To perform the ultrasonic analysis, an ultrasonic pulse generation instrument (Pundit-Proceq) with exponential transmitting and receiving probes, having a nominal frequency of 50 kHz, was employed. The instrument was connected to a notebook computer with appropriate software for storing and analysing the measured data. The measurements were executed on the surface of the stele along a grid of 147 measuring points approximately spaced 5 cm apart. The grid was laid out by superimposing a sheet of melinex onto the stele (red dots in Figure 2). Measurements were conducted both in the horizontal and vertical directions among each couple of measuring points for a total of 268 measurements. Both the transmitting and receiving probes were placed in contact with the melinex paper at an angle of about 45° to the surface of the stele, to allow penetration of the ultrasonic pulse within the material. The ultrasonic pulse travel times were obtained for each measurement by manual picking of first arrivals on the received traces. All the acquired velocity values were then merged and interpolated in the Surfer software to allow for the reconstruction of the velocity field of the stele.



Figure 2. The image shows the dot pattern employed to carry out the ultrasonic test.

Another step of the study was aimed at recovering the legibility of the hieroglyphs and red figures. For this step, a totally non-invasive multi-analytical approach was adopted, which was followed by the Egyptological analysis also intended as validation of the technique.

Preliminary investigation was first conducted through close observation and multiband imaging techniques commonly applied to cultural heritage, specifically, visible Fluorescence induced by UV radiation (UVF) and IR photography. The UVF images were acquired with a Nikon D810 full-frame reflex camera mounting a PECA 916 filter, irradiating the artifact with UV Labino® lamps (365 nm-emission peak). The IR photographs were acquired with a Nikon D810 IRUV full-frame reflex camera mounting a B+W 093 filter, illuminating with Ianiro Varibeam Halogen 800 W lamps. The acquisition required the use of a 24-colour XRITE Classic ColorChecker® and a 99% reflective white ceramic tab as references. The images were colour-corrected and white-balanced in post-production in Adobe Lightroom.

As for the spectroscopic analyses to confirm the chemical nature of the red colour, already hypothesized on the basis of the literature and multiband imaging outcomes, some points of the drawings on the stele were examined by X-Ray Fluorescence (XRF) and Fiber Optics Reflectance Spectroscopy (FORS). The XRF analyses were carried out with a Bruker Tracer III-SD handheld XRF spectrometer that has an X-ray tube with a Radium (Rh) anode. The measurements were made at 40 kV, 10 μ A, and 60 seconds acquisition time. FORS spectra were acquired in the 350-1000 nm range with spectral resolution of about 0.5 nm by using an Ocean Optics HR2000+ES spectrophotometer, an Ocean Optics HL2000 halogen lamp, optical fibres of 400 μ m in diameter, and a Spectralon © 99% white reference. The analyses were carried out in a $2 \times 45^\circ / 0^\circ$ geometry following the CIE standard illuminating/viewing geometry [10] on measuring area of fixed dimensions (approximately 3 mm in diameter).

To improve the readability of the hieroglyphs, the MultiSpectral Imaging technique (MSI) was applied to the stele. For the MSI analysis, we used a system equipped with a high-resolution Moravian G2-8300 camera (CCD detector KAF-8300, imaging area 18.1×13.7 mm, pixel size 5.4×5.4 μ m) with a high dynamic range (16 bits). The sensor is cooled to reduce the electronic noise during the acquisition. The spectral resolution is obtained

through the use of interferential (± 25 nm band pass around the central wavelengths) at 400, 450, 500, 550, 600, 650, in the visible range and 850, 950, 1050 nm in the near infrared. Two sets of 9 acquisitions were carried out for the different available bands (Table 1), one of them using visible light as an illuminator and the second one with UV leds (10 V). In the first case, the integration time was set to 1s for acquisitions from 550 to 950 nm and increased up to 10 s for those from 400 to 500 nm and to 15 s for the 1050 nm band, maintaining the same lighting condition for the visible and infrared image sequence.

Table 1. Experimental parameters of the MSI acquisition.

Spectral band (nm)	Vis acquisition time (s)	UV acquisition time (s)	Aperture
400	10	15	11
450	10	15	11
500	10	30	11
550	1	30	11
600	1	45	11
650	1	90	11
850	1	90	11
950	1	120	11
1050	15	400	11

After the images have been acquired, they must be registered to compensate the unavoidable shifts and distortions introduced by the different filters interposed between the objective and the sensor of the CCD camera. To this purpose, a specialized software made by the Institute of Science and Technologies of Information of the CNR was used [11], which guarantees sub-pixel accuracy in images recording. The colour image was reconstructed through the superposition of three images acquired sequentially in the fundamental RGB spectral bands (450 – 550 – 650), and similarly for the false IR colour (550 - 650 – 1050). Then statistical separation was applied to the whole set of 18 multispectral images.

3. Results

3.1. Characterization, provenance and stratigraphical age of the limestone support

The stele S. 6145 is made out of a clayey limestone (sedimentary rock), pale beige in colour. It has a very fine-grained, homeo-granular, massive structure, without evident stratification. The fracture is typically conchoidal. Small bodies, with a subspherical to ovoid shape, dark grey in color, occur on the surface of the stele (Figure 3). Two are located on the front and two on the reverse of the stele, and are characterized by a blackish border. They vary from a few mm to 2-3 cm in size. Their fine grain size is not distinguishable to the naked eye, and the exposed surfaces show a typical conchoidal fracture. All these characteristics are typical of chert nodules, which are common features of calcareous sedimentary rocks.

On the reverse of the stele, well-closed microfracture systems can be identified (Figure 4). These are clearly visible on the surface, less visible transversely. Their spacing is pluricentimetric, their lateral extension up to decimetric, extending over much of the stele. These fractures could be either syn-sedimentary or tectonic in origin.

During the processing of the reverse, these systems influenced the development and extension of fracture surfaces in a typically conchoidal pattern.

The limestone support, studied in smear slides under the optical microscope, shows abundant micrite together with minor micrometric dolomite crystals, probably diagenetic

in origin, as is also suggested by the moderate to poor preservation of the microfossil remains. No traces of pyrite or glauconite were found, although they have been reported in some Egyptian lithotypes.



Figure 3. Chert nodules, millimetric in size, on the front of the stele (a, b). Chert nodules, centimetric in size, on the reverse of the stele (c, d); the second contains two smaller nodules (d).



Figure 4. Closed, subparallel microfracture systems, with centimetric spacing, visible on the reverse of the stele.

SEM-EDS investigations on samples allowed to better detail the petrographic and micropaleontological features of the limestone. Sample 1 (not taken from the stele, but a previously detached fragment) confirms the carbonatic nature of the rock, its fine grain size (a few microns; Figure 5a) and the presence of micrometric crystals of dolomite; the micropaleontological content, consisting of coccoliths, is also clearly visible. These observations confirm that the rock formed from the lithification of a carbonate sediment deposited in a marine environment, possibly at depths greater than the photic zone. Sample 2 (taken from the reverse of the stele) shows areas where the original surface of the rock (micrite) can be observed, and areas where a mixed coating is observed, also composed of quartz grains (Figure 5b).

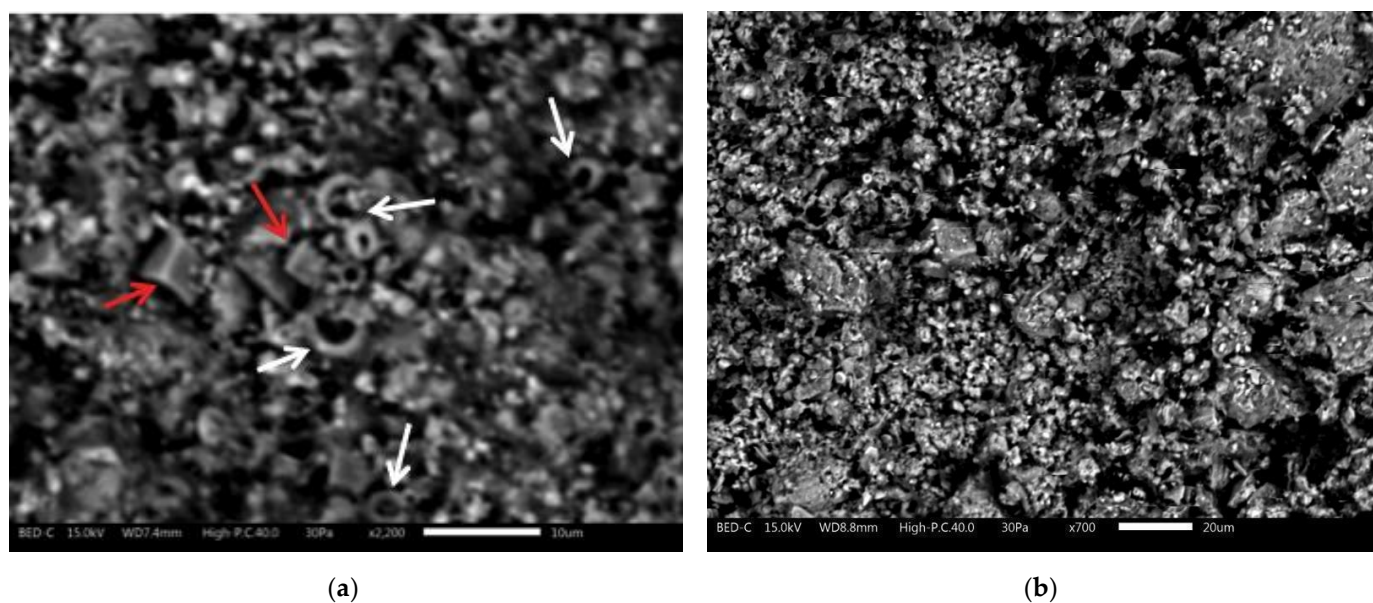


Figure 5. Electron microscope image (SEM backscattered electrons) of: (a) sample 1, the fine grain size of the micrite crystals is clearly visible; white arrows: micropaleontological content (coccoliths); red arrows: dolomite crystals; (b) sample 2, microscopic aspect: micritic crystals and euhedral crystals.

The calcareous nannofossil assemblage is well diversified and dominated by *Ericsonia formosa*, *Chiasmolithus nitidus*, *Toweius pertusus*, *Coccolithus pelagicus*, *C. crassus*; small *Toweius* specimen are also present, not identifiable at the species level. Rare *Sphenolithus moriformis*, *S. radians*, *Biantholithus flosculosus*, *Cyclicargolithus luminis*, and *C. pauxillus* complete the synsedimentary assemblage. The sample also contains rare *Neocrepidolithus fossus*, *Ericsonia aliquanta*, *Fasciculithus tympaniformis*, likely re-worked from older sediments (Paleocene in age).

On the basis of this assemblage, and of the absence of *Tribrachiathus orthostylus*, a species that characterizes the homonymous biozone [12], and of *Discoaster sublodoensis* (marker of the CNE6 biozone), it is possible to assign the sample to the CNE5 biozone, with a Ypresian age (lower Eocene). This is also supported by the presence of *C. crassus*, which appears at the top of the CNE4 biozone [12]. As for the standard biozones, still in use by many authors, the sample belongs respectively to the biozones CP11 [13] and NP13 [14], thus confirming a Ypresian age. This age assignment and its lithological characteristics allow us to attribute the sample to the Thebes Fm. Limestones with dolomite (and pyrite, but absent in the sample) also occur at the base of the Esna Fm. According to some authors [15] the Esna Fm. dates from the Paleocene, according to others to the Eocene age [16]; thus in both cases it would be older than the studied sample. The stratigraphy of the Eocene limestones from central Egypt, cropping out around the area of Thebes and Luxor - where the GSSP of the Eocene (Global Stratigraphic Standard

Section and Point; [17]) is located - and the stratigraphy of the necropolis of the pharaohs [16, 18] suggest possible interpretations based on the data collected.

The presence of dolomite is known throughout the Thebes Fm. [18], in particular in lithological units B4 and D1. However, the assemblage characterized by the absence of *T. orthostylus* is similar to that reported by King et al. (2017) in part of the section of Jebel Gurnah, starting from Units H and I. Up to unit E, the limestone contains planktonic foraminifera with a decreasing upward abundance, indicating a shallowing upward trend, which culminates with the overlying shallow water nummulitic limestones, devoid of planktonic foraminifera. The authors also report that the limestones of Units B4 and D1 may contain nummulites. All other limestones of the lithological units of the Thebes Fm. are bioclastic and/or nodular, or marly-clayey, and therefore cannot be correlated with the stratigraphic level of origin of the stele.

It seems thus reasonable to attribute the sample, which belongs to the Biozone CNE5 (= CP11 and CN13), to a level that can be correlated with Unit H of the Thebes Fm. of the section of Jebel Gurnah, in agreement with the findings of King et al. (2017).

Finally, sample 3 (not taken from the stele, but a previously detached fragment) shows a completely different appearance, consisting of an aggregate of elongated acicular crystals of plurimicrometric size (often larger than 10 microns), and rare larger tabular crystals. The EDS analyses have shown that these are gypsum crystals; the sample could therefore come from the original grouting of the stele, as confirmed by the XRD analyses (see after).

3.2 Technique of execution and state of preservation of the support

Stele S. 6145 has three different levels of processing. The back is roughly hewn to make it approximately flat. The sides are more finely cut but not finished. The front, being meant to accommodate the decoration, has a flat surface, smoothed and locally grouted, probably to remedy constitutive imperfections, or accidental ones produced during the manufacturing process. The pale beige surface of the stele shows several such grouts of whitish colour. They appear compact and can be traced back to the original Egyptian manufacture of the object, since the preparatory drawing intersects them. Thanks to the UVF imaging, all the grouts present on the stele were observed, including some not visible to the naked eye (Figure 6). XRD analysis allowed us to identify their composition, detecting the presence of anhydrite, calcite, quartz, dolomite, and gypsum (sample 4, taken from the stele in correspondence to an original grout).

In addition to the closed microfractures described above, the stone material constituting the stele has a crack extending across the entire width of the stele. Its development and direction were influenced by the sedimentary structure of the limestone. By observing the object from the side, one can indeed see that the fracture is substantially parallel to sub-parallel to the barely visible stratification of the limestone (Figure 7).

The ultrasonic test yielded medium-high velocity values (approximately around 22000 m/s) for most of the stele, but also evidenced localized reduction of the velocity (to about 1000 m/s). The velocity distribution along the stele evidenced a very good correspondence of the low-velocity area (blue-purple area in Figure 8) with the known location of the main visible fractures on the surface of the stele (see Figure 2). No other specific low-velocity zones were observed. The relevance of this low-velocity area and its particularly low-velocity range allowed us to establish a significant persistence of the fractured zone, which can be regarded as a warning of the existence of a threat to the integrity of the stele, particularly during handling.

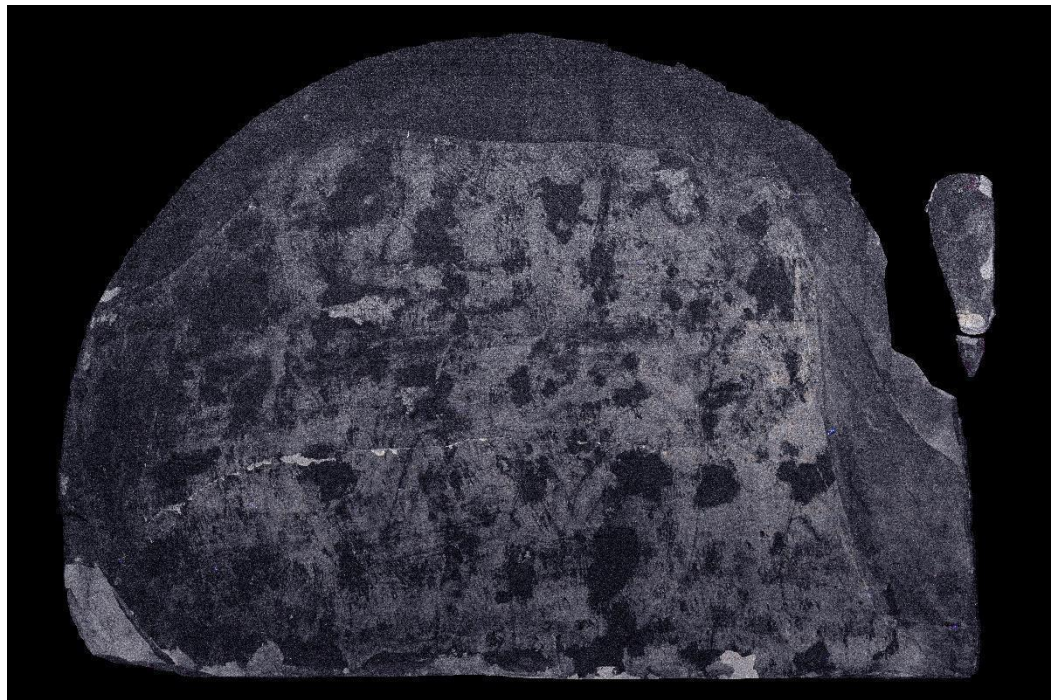


Figure 6. UV fluorescence image of the stele (UVF).



Figure 7. Lateral picture of the stele, showing (in blue) the direction of the crack, which is subparallel to the sedimentation.

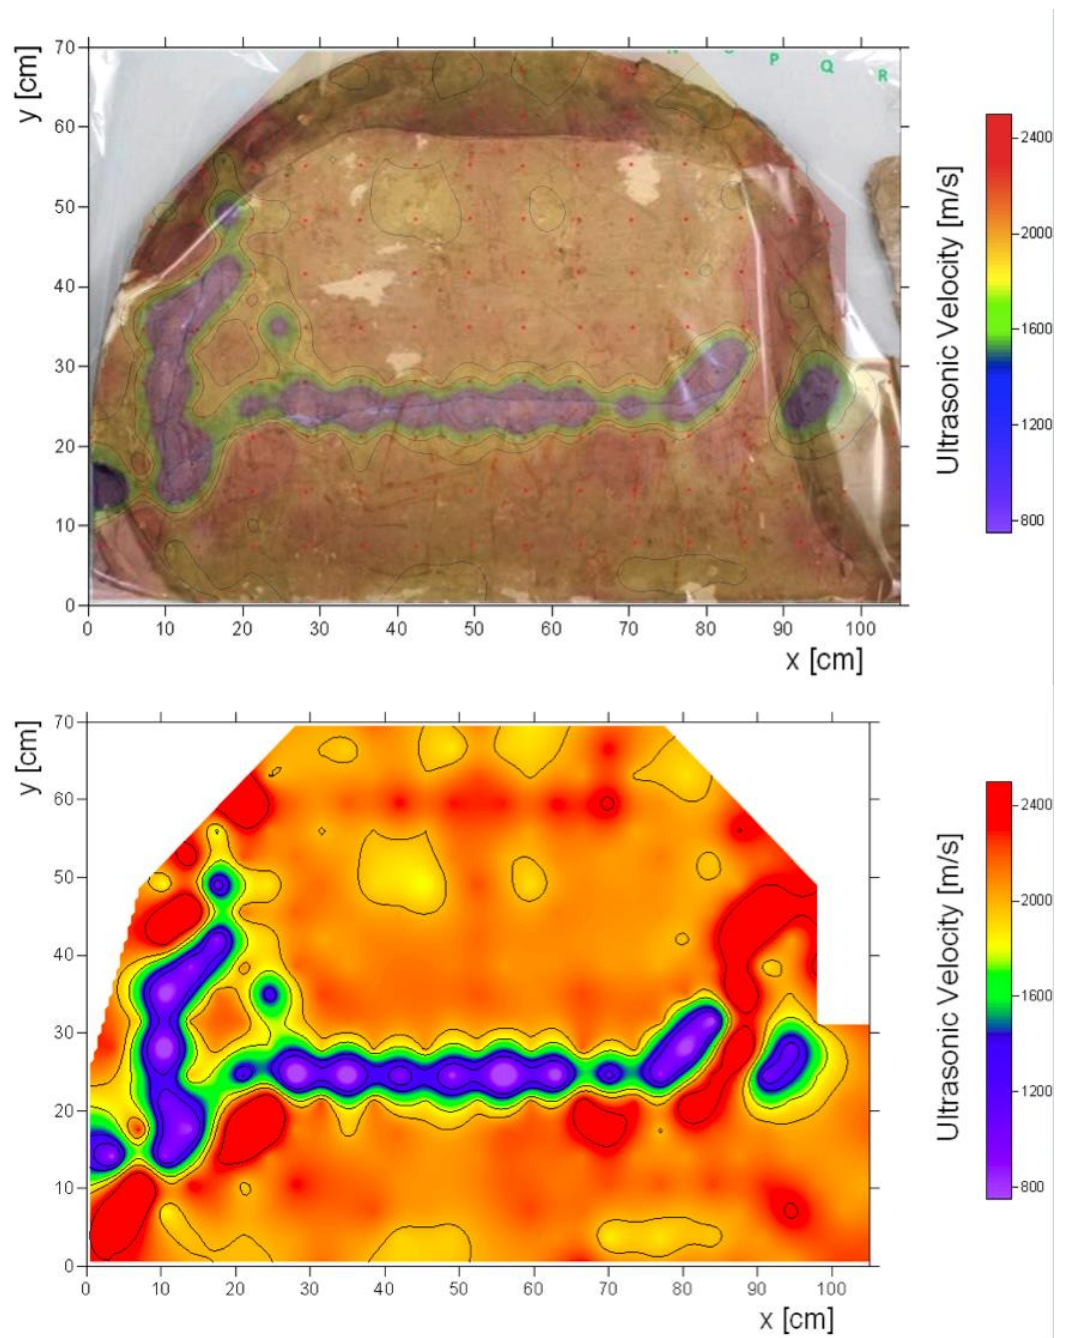


Figure 8. The images show the velocity trends of the ultrasounds in the limestone.

3.3 The decoration: recovering the figures and their accompanying hieroglyphic inscriptions

The decoration of the stele consists of a preparatory drawing for the carving of a figured scene with hieroglyphic captions in its upper part (the lunette). Based on the literature and the analyses, the figures and inscriptions are presumably drawn in red ochre. In ancient times, the red earth was extracted from deposits in Upper Egypt in the Abu Simbel area, along the coastal strip of the Red Sea and in the Sinai Peninsula. Vitruvius and Dioscorides mention that Egypt yielded the best red ochres. The XRF analysis detected indeed the presence of iron, with lower signals of silicon and titanium, as well as calcium, strontium, and a feeble sulfur signal attributable to the support. The red colour, applied directly on the limestone, presumably had a gum arabic binder, as widely reported in the literature [19].

As expected, neither the UVF nor the IR photographs have been of great use for improving the readability of the hieroglyphs, since red ochre in a gum arabic binder does not have a strong absorption in the photographic infrared region, nor a particularly intense fluorescence when illuminated with 365 nm UV radiation.

Figure 9 shows the three RGB acquisitions and the most significant channel in the near infrared at 1050 nm of the upper part of the stele.

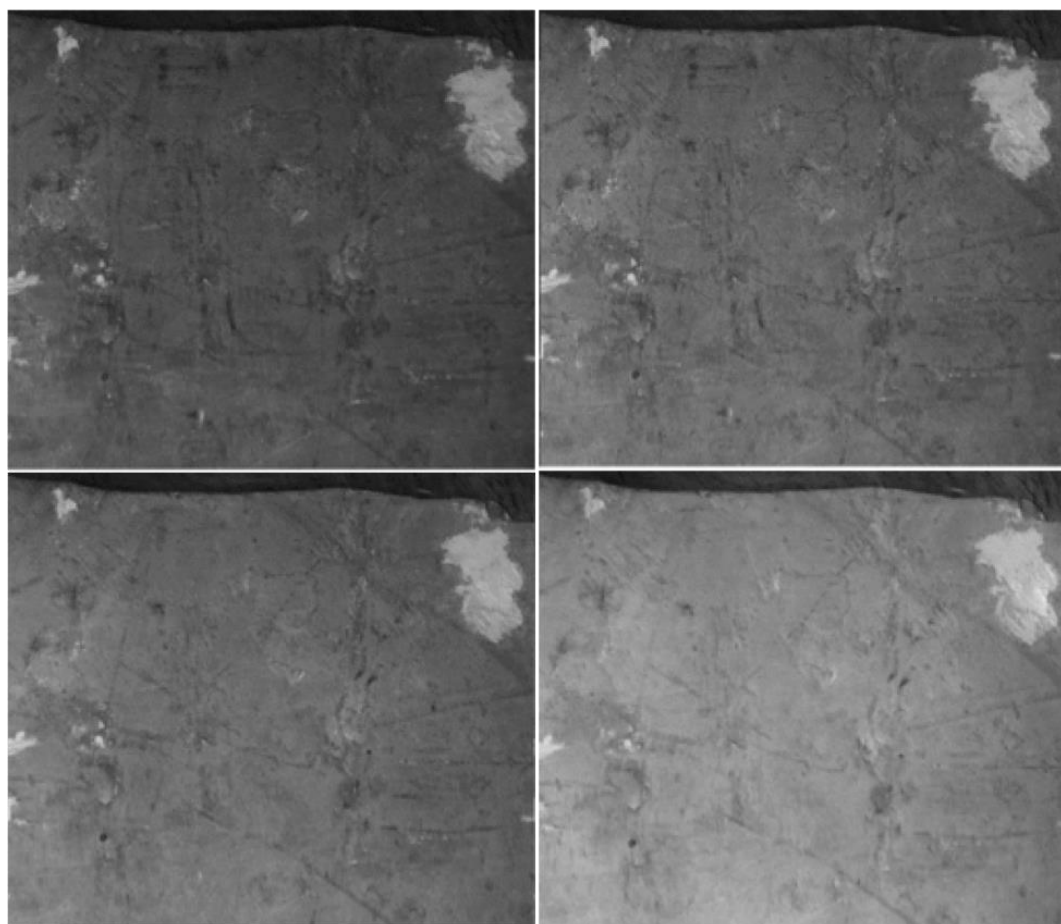


Figure 9. MSI of a detail of the stele: images taken at 450 nm, 550 nm, 650 nm, and 1050 nm.

While the raw images acquired with the MSI did not improve readability, the BSS algorithm greatly improved it. Figure 10 reports the most significant BSS result: it is worth noting that the picture is the composition of different images that were acquired to cover the whole upper surface of the stele.



Figure 10. Output of the BSS algorithm used for enhancing the readability of the hieroglyphic text in the stele S. 6145.

As described below, a different images processing based on the Chromatic Derivative Imaging (ChromaDI) method allowed recovering the readability of the stele (Figure 11). This method, developed by Pisa groups [20, 21], exploits the subtraction of consecutive couples of 4 consecutive spectral images, namely, G-B, R-G, and IR-R.

At the top of the stele the lower coil of two cobras (uraei) can be made out, what is left of the usual motif of the sun disk with uraei topping the lunette of such steles. On either side, the hieroglyphs for “the great god, the Behdetite” can be made out. The text between the uraei appears to read “beloved of Amun”. The main scene shows the pharaoh Seti II (1202-1198 BCE), in the middle, his left hand held up to receive the symbol of the royal jubilee, the *heb sed*, which hangs from a palm shoot (the hieroglyph for “year”) the god Amun holds forth with his left hand. Seti is bearded and clad in a kilt, and holds the *heka* scepter in his right hand. On his head he wears the royal headcloth (nemes) topped by the cobra (uraeus). Amun, also kilted, wears his usual two-feathered crown and holds the *uas* scepter in his right hand. A profile line descending obliquely behind the figure of Amun may belong to a figure of another deity, identified as Ptah in the literature [1], [3] (pp. 125-126). Behind the king are the two other members of the Theban divine triad, with their usual attributes: the goddess Mut, wearing a dress and the Double Crown, and the child-god Khonsu, mummiform and bearded, wearing the sidelock of childhood, the lunar disk on his head, and a necklace, and holding the was scepter. Most of the signs in the inscription above Amun appear to be faded beyond recognition, even in the processed images: we can make out the cobra at the very beginning of the inscription (arranged in columns, going from left to right), which is the first sign of the group *djed medu* (“Saying the words”), and the sign for *.k*, “you” (in what could be the expression *di.en.i ene.k*, “I have given you...”, referring to the god’s granting of the jubilee to the king), as well as the throne glyph in “[lord of the] thrones [of the Two Lands]”. Above the king are his two royal names (prenomen, nomen), which are entirely readable in the multispectral images: “The lord of the Two Lands [Weser]-khepru-Re-mery-Amun, the lord of apparitions Setymery-en-Ptah”. Above Mut we read, from right to left: “Saying the words by Mut, mistress of the sky: ‘I am your mother...’”. Above Khonsu is what looks like a basket (a *neb-* or *k-* sign) followed by “Khonsu in Thebes”.

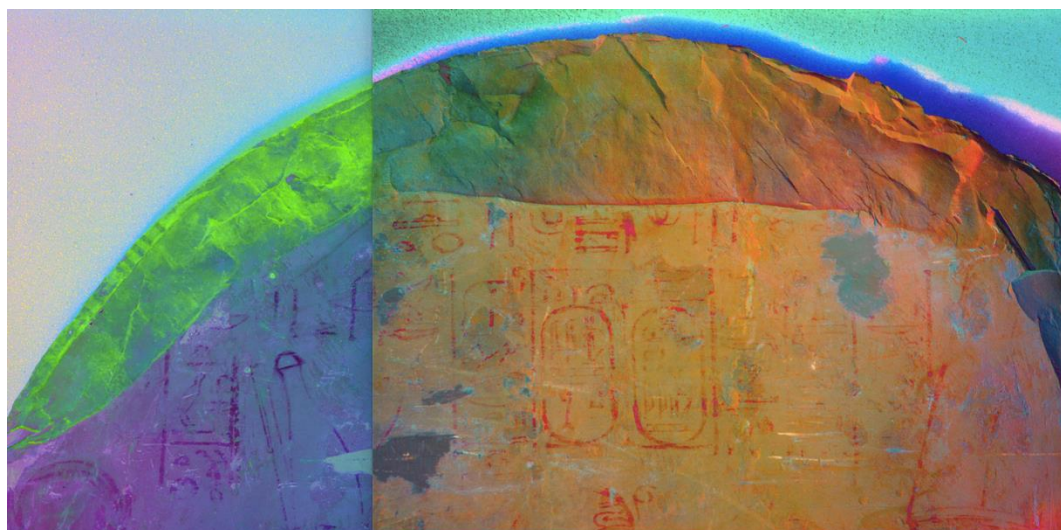


Figure 11. ChromaD images corresponding to the four multispectral series considered. The picture is the composition of different images that were acquired to cover the whole upper surface of the stele.

The stele was published about fifty years ago in the volume of the Museo Egizio’s general catalogue devoted to the steles of Deir el-Medina [3] (pp. 125-126, 301, with further

literature). The images were correctly identified and what was visible of their captions read. MSI imaging, however, has enabled us to improve on these scholars' naked-eye readings, revealing signs that were not visible to them, notably:

- The *weser* (head and neck of canine animal) and *kheper* (scarab) sign in the prenominal of the king, Weser-khepru-Re (correctly reconstructed by Tosi and Roccati, but not actually seen);
- The independent pronoun *inek* ("I (am)": a jar above a shallow basket with a handle, read as *k*) beginning the goddess Mut's utterance;
- The cobra sign (*dj*) at the beginning of the text above Amun;
- The *.k* pronoun (the shallow basket with a handle) in the text above Amun.

The MSI imaging also allowed the details of the figures of the king and the gods to be distinguished more clearly.

At last, Figure 12 shows the picture realized overlapping the RGB image with the pattern obtained with the most significant BSS output. This method enables a sort of "virtual restoration" of the original heritage object, useful for its study and for making it more fully understandable to scholars and the general public..

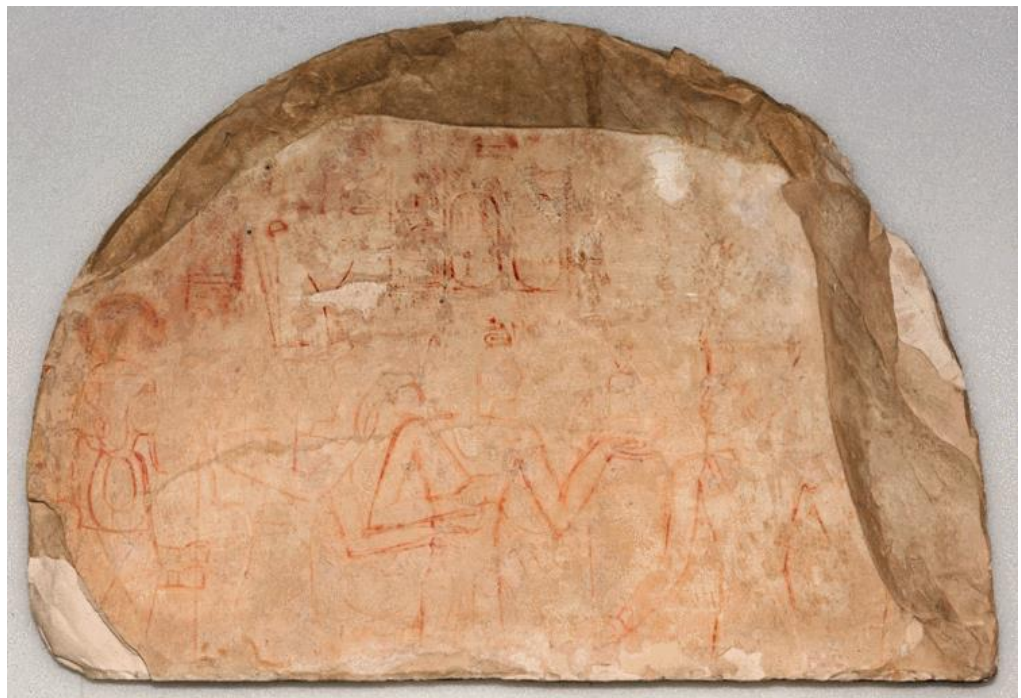


Figure 12. RGB image overlapped with the pattern obtained with the most significant BSS output (virtual restoration).

4. Discussion

The material, technical, and Egyptological study conducted on the stele S. 6145 led to a deep knowledge of the object that allowed us to plan the preservation and conservation treatment. The micropaleontological, mineralogical and petrographical analyses confirmed that the lithic support of the stele consists of micritic limestone with minor dolomite crystals and chert, containing calcareous nannofossils (but devoid of planktonic foraminifera), allowing an assignment to the CNE5 biozone (Ypresian age; lower Eocene). The lithological and micropaleontological characteristics confirm the stele's provenance from the Thebes Fm.

As for the long crack crossing horizontally the limestone support, the identification of the internal discontinuity through ultrasonic analyses has inevitably imposed a

reflection on possible conservation choices and on the present and future precautions to be adopted in handling the artifact. For example, it was turned over on its back only after being placed inside its crate. These analyses were crucial in anticipation of the transportation of the stele and its possible future museum exhibition.

Close observation revealed the execution technique of the stela, first of all recognizing the signs of working of the stone and the original grouts, whose composition has been analysed by combining XRD and SEM-EDS as complementary techniques. Noninvasive spectroscopic analyses allowed confirming the executive technique and chemical nature of the red pigment. It deals with a preparatory drawing for carving in relief: in fact, the red ochre is spread directly on the support, without any preparation layer.

We demonstrated the advantages of using MSI and BSS algorithms to enhance hidden patterns in archaeological steles, using an approach so far limited to paintings and ancient manuscripts. The multispectral investigation made it possible to see and read several hieroglyphs that had not been distinguished by previous scholars. Furthermore, the resulting published images offer much more detail to readers than a natural-light photograph would. Depending on the spectral response of the materials and their conservation state, sometimes satisfactory results can be obtained even limiting the analysis only to one of the infrared bands; more often, however, more sophisticated tests are called for, like those reported upon in this paper.

Author contributions: Conceptualization, Tiziana Cavaleri and Stefano Legnaioli; Data curation, Tiziana Cavaleri, Stefano Legnaioli, Francesca Lozar, Cesare Comina, Daniele Castelli and Vincenzo Palleschi; Formal analysis, Tiziana Cavaleri, Stefano Legnaioli, Federico Poole and Daniele Castelli; Investigation, Tiziana Cavaleri, Stefano Legnaioli, Francesca Lozar, Cesare Comina, Federico Poole, Daniele Castelli and Vincenzo Palleschi; Methodology, Tiziana Cavaleri, Stefano Legnaioli, Francesca Lozar and Vincenzo Palleschi; Project administration, Tiziana Cavaleri; Resources, Federico Poole and Alessia Spoladore; Supervision, Tiziana Cavaleri, Claudia Pelosi and Vincenzo Palleschi; Validation, Federico Poole; Visualization, Francesca Lozar, Cesare Comina, Alessia Spoladore and Daniele Castelli; Writing – original draft, Tiziana Cavaleri, Stefano Legnaioli, Francesca Lozar, Federico Poole and Alessia Spoladore; Writing – review & editing, Tiziana Cavaleri, Stefano Legnaioli, Francesca Lozar, Cesare Comina, Federico Poole, Claudia Pelosi and Daniele Castelli.

Acknowledgments: We warmly thank the Museo Egizio, Turin, and the Soprintendenza Archeologica, Belle Arti e Paesaggio per la Città Metropolitana di Torino for making this study possible. We would also like to thank Dr. Francesco Brigadeci, University of Turin, who acted as conservator tutor in Alessia Spoladore's thesis, and Prof. Paolo Gallo, University of Turin, for being part of the teacher team of the same thesis. The stele S. 6145 was in fact the subject of a thesis of the Master's Degree course in Conservazione e Restauro dei Beni Culturali, a training course with qualification in accordance with Leg. Dec. No. 42/2004 offered by the University of Turin through the Centro Conservazione e Restauro "La Venaria Reale". We thank also the Laboratorio Analisi Scientifiche of the Soprintendenza Regione Autonoma Valle d'Aosta for the XRD and XRF analyses. Finally, our gratitude goes to Paolo Del Vesco, Museo Egizio Turin, and Ikram Ghabriel for archaeological insight.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Bruyère, B. Mert Seger à Deir el Médineh. In *Mémoire publiées par les membres de l'Institut français d'archéologie orientale du Caire*, 1st ed.; IFAO: Le Caire, Egypt, 1929; Volume 1.
2. Bruyère, B. Mert Seger à Deir el Médineh. In *Mémoire publiées par les membres de l'Institut français d'archéologie orientale du Caire*, 1st ed.; IFAO: Le Caire, Egypt, 1930; Volume 2.
3. Tosi, M.; Roccati, A. Stele e altre epigrafi di Deir el Medina. N. 50001-50262. In *Catalogo del Museo Egizio di Torino*, Serie seconda, Collezioni 1; Edizioni d'arte fratelli Pozzo: Torino, Italy; 1972.
4. Del Vesco, P.; F. Poole. Deir el-Medina in the Egyptian Museum of Turin. An Overview, and the Way Forward. In *Outside the Box: Selected papers from the conference "Deir el-Medina and the Theban Necropolis in Contact"*, Liège, 27–29 October 2014, Liège, Dorn, A., Polis, S., Eds.; 2018.

5. Ghabriel, I. The So-Called Oratory of Ptah and Mertseger Re-Examined, in Proceedings of Deir el-Medina Through the Kaleidoscope – 2018 Turin International Workshop, Modena and Torino, Italy, 2018; Del Vesco, P., Poole, F., and Töpfer, S., Eds.; forthcoming.
6. Spoladore, A., The stele S.06145 from the village of Deir El-Medina and conserved in the Egyptian Museum of Turin: handling, reading and conservation problems; Master Degree Thesis; University of Turin, Venaria Reale, 25 November 2019.
7. Sambuelli, L.; Böhm, G.; Capizzi, P.; Cardarelli, E., and Cosentino P. Comparison between GPR measurements and ultrasonic tomography with different inversion algorithms: an application to the base of an ancient Egyptian sculpture. *J. Geophys. Eng.*, 8, S106-S116; 2011.
8. Capizzi, P.; Cosentino, P.L.; Schiavone, S. Some tests of 3D ultrasonic traveltime tomography on the Eleonora d’Aragona statue (F. Laurana, 1468). *J. Appl. Geophys.*, 91, 14-20; 2013.
9. Bown, P.R.; Young, J. R. Techniques. In *Calcareous Nannofossil Biostratigraphy. British Micropalaeontological Society Series*, Bown P.R. Ed., Chapman and Hall, London: 1-15; 1998.
10. Oleari, C. Misurare il colore; Hoepli, Florence, Italy, pp. 53–60; 2008.
11. Salerno, E.; Tonazzini, A.; Grifoni, E.; Lorenzetti, G.; Legnaioli, S.; Lezzerini, M. et al.; Analysis of multispectral images in cultural heritage and archaeology, *J Appl Laser Spectrosc*, 1, pp. 22-27; 2014.
12. Agnini, C.; Monechi, S; Raffi, I. Calcareous nannofossil biostratigraphy: historical background and application in Cenozoic chronostratigraphy. *Lethaia*, 50/3, 447-463; 2017. <https://doi.org/10.1111/let.12218>
13. Okada, H.; Bukry, D. Supplementary modification and introduction of code numbers to the low-latitude coccolith biostratigraphic zonation (Bukry, 1973; 1975). *Marine Micropaleontology*, 5, 321–325; 1980.
14. Martini, E. Standard Tertiary and Quaternary calcareous nannoplankton zonation. In Proceedings of the Second Planktonic Conference Roma 1970, 2, 739-785, Farinacci, A. Eds.; Edizioni Tecnoscienza: Rome; 1971.
15. Abu-Ali R.; El-Kammar, A.; Zakaria, A.; El-Shafeiy, M.; Kuss, J. Paleo-environmental reconstructions of the Upper Cretaceous-Paleogene successions, Safaga, Egypt; *Journal of African Earth Sciences*, Volume 149, pp. 170-193; 2019.
16. Aubry, M.P.; Berggren, W.A.; Dupuis, C.; Ghaly, H.; Ward, D.; King, C.; Knox, R.; Ouda, K.; Youssef, M.; Fathi Galal W. Pharaonic necrostratigraphy: a review of geological and archaeological studies in the Theban Necropolis, Luxor, West Bank, Egypt; *Terra Nova*, 21, 237–256; 2009.
17. Aubry, M.-P., Ouda, K., Dupuis, C., Berggren, W.A., Van Couvering, J.A. and The Members of the Working Group on the Paleocene/Eocene Boundary. The Global Standard Stratotype-section and Point (GSSP) for the Eocene Series in the Dababiya section (Egypt). *Episodes*, 30, 271–286; 2007.
18. King, C.; Dupuis, C.; Aubry, MP.; Berggren, W.A.; O’B.Knox, R.; Galal, W-F.; Baele J-M. Anatomy of a mountain: the Thebes limestone formation (lower Eocene) at Gebel Gurnah, Luxor, Nile valley, upper Egypt. *Journal of African Earth Sciences* 136, pp. 61-108; 2017.
19. Newman, R.; Serpico M. Adhesive and Binders in *Ancient Egyptian Materials and Technology*, Nicholson, P. T., Shaw, I., Eds., Cambridge University Press, pp. 475-493; 2000.
20. Legnaioli, S.; Grifoni, E.; Lorenzetti, G.; Marras, L.; Pardini, L.; Palleschi, V. et al. Enhancement of hidden patterns in paintings using statistical analysis, *J Cult Herit*, 14 (3) pp. S66-S70; 2013.
21. Legnaioli, S.; Lorenzetti, G.; Cavalcanti, G.H.; Grifoni, E.; Marras, L.; Tonazzini, A. et al. Recovery of archaeological wall paintings using novel multispectral imaging approaches. *Herit Sci*, 1; 2013.